

Article

Not peer-reviewed version

Digital Image Analysis and Multivariate Data Analysis as Tools for the Identification of Microplastics in Surface Waters: The Case of the Vistula River (Central Europe)

[Ewa Dacewicz](#)^{*}, Ewa Łobos-Moysa, [Krzysztof Chmielowski](#)

Posted Date: 27 June 2024

doi: 10.20944/preprints202406.1977.v1

Keywords: characteristics of microplastics; digital image analysis; shape descriptors; PCA.



Preprints.org is a free multidiscipline platform providing preprint service that is dedicated to making early versions of research outputs permanently available and citable. Preprints posted at Preprints.org appear in Web of Science, Crossref, Google Scholar, Scilit, Europe PMC.

Copyright: This is an open access article distributed under the Creative Commons Attribution License which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Article

Digital image analysis and multivariate data analysis as tools for the identification of microplastics in surface waters: The case of the Vistula River (Central Europe)

Ewa Dacewicz ^{1,*}, Ewa Łobos-Moysa ² and Krzysztof Chmielowski ³

¹ Department of Sanitary Engineering and Water Management, Faculty of Environmental Engineering and Land Surveying, University of Agriculture in Kraków, Adam Mickiewicz Ave. 24/28, 30-059 Kraków, Poland

² Department of Water and Wastewater Engineering, Faculty of Power and Environmental Engineering, Silesian University of Technology, Akademicka 2A Str., 44-100 Gliwice, Poland; ewa.lobos-moysa@polsl.pl

³ Department of Natural Gas Engineering, Faculty of Drilling, AGH University of Science and Technology, Oil and Gas, Adam Mickiewicz Ave. 30, 30-059 Kraków, Poland; krzysztof.chmielowski@agh.edu.pl

* Correspondence: ewa.wasik@urk.edu.pl; Tel.: +48-12-662-4127

Abstract: The primary objective of this study was to demonstrate the potential of digital image analysis as a tool to identify microplastic (MP) particles in surface waters and to facilitate their characterisation in terms of 2D and 3D morphology. Digital image analysis preceded by microscopic analysis was used for an exhaustive quantitative and qualitative evaluation of MPs isolated from the Vistula river. Using image processing procedures, 2D and 3D shape descriptors were determined. The Principal Components Analysis (PCA) was used to interpret the relationships between the parameters studied, characterising MP particle geometry, type and colour. This multivariate analysis of the data allowed 3 or 4 main factors to be extracted, explaining approximately 90% of the variation in the data characterising MP morphology. It was found that the first principal component for granules, flakes and films was largely represented by strongly correlated with 2D shape descriptors (area, perimeter, equivalent area diameter) and 3D shape descriptors (CSF, Compactness, Dimensionality). Considering the scraps, PC1 was represented by only five of the above descriptors, and the Compactness variable had the largest contribution to PC2. In addition, for granules, flakes and films, a relationship between 2D shape and the colour of their particles could be observed. For the most numerous MP group identified of multicoloured scraps, no such association was found. The results of our study can be used for further multivariate analysis regarding the presence of microplastic floating on the river surface, with a particular focus on particles of secondary origin. This is of key importance for optimising future efforts in conducting small-scale and multidimensional monitoring of and reducing plastics in the aquatic environment.

Keywords: characteristics of microplastics; digital image analysis; shape descriptors; PCA

1. Introduction

The Microplastic (MP) is a pollutant that, due to its properties, can easily spread in surface waters such as rivers, lakes, seas and oceans, and then accumulate in bottom sediments. It is estimated that the percentage of MP in aquatic environments, such as seas and oceans, is: 15% in water and as much as 70% in marine sediments [1]. In studies on the MP content in the Baltic Sea sediments in Poland (Central Europe), the occurrence of this pollutant was found in the amount of 76–295 its/kg_{dw}, and in terms of the type of MP, fiber and plastic fragments predominated [2]. During other studies in a larger area of the Baltic Sea, it was found that only fibres occur in amounts as high as 55–9226

its/kg_{dw} [3]. As regards polymer types, polypropylene (PP), polyethylene (PE) and polystyrene (PS) were the most common polymers identified in coastal waters or on Baltic Sea beaches [2,3]. PE, PP, PS and expanded polystyrene (EPS), unlike other plastics (PET, PVC), are lighter than water and float on or near the surface. Their positive buoyancy makes them easily transported in water, collected on shorelines and, consequently, washed ashore even on remote beaches [4]. According to Chubarenko et al. [5] under idealised external conditions, an EPS particle needs only one day to traverse the Baltic Sea, while spherical particles can persist on its surface for 10-15 years.

Procedures (still not standardised) for determination of MPs in surface waters play an important role in their identification. The GESAMP recommendations [6], which relate to the marine environment, are commonly used and refer to counting plastic particles by origin, shape and colour. Primary microplastics are most commonly described as beads and pellets manufactured in sizes smaller than 5 mm. Secondary MPs are formed by fragmentation and degradation of larger plastic components. The most inaccuracies are caused by the determination of the shape of the MP. Shape factors that characterise natural sediments can be used to describe its particles or methods can be used to determine the main dimensions of non-spherical particles [7]. In the case of natural sediments, shape descriptions are mainly based on geometrical figures, i.e. ellipsoid, flattened spheroid, cylinder, square or disk-shaped plates [8,9]. The Corey Shape Factor (CSF) used for natural particles can be used as a representative parameter to describe the dimensionality of MP. The value of CSF varies from close to 0 (2D plate/disc) to 1 (perfectly rounded 3D sphere), while a CSF of 0.7 is characteristic of naturally worn sediment [10].

The shape categories of microplastics are commonly used in their analysis, but the actual shape of the particles can vary considerably. After all, plastics are susceptible to the processes of wave-induced fragmentation and UV-induced photodegradation [11,12]. MP transformations, which include changes in density and crystallinity due to photodegradation and weathering (known as plastic ageing), can alter the transport and increase the settling rate of the particles [13,14]. Alimi et al. [15] showed that UV-induced degradation led to increased vertical transport of MP in a lake in Quebec. The weathering of 4.5 mm and 0.22 mm disc-sized MP reduced the settling time of the particles from 3 to 2 hours and 18 to 8 days, respectively. Waldschläger and Schüttrumpf [7], on the other hand, while evaluating the effect of shape, size and density on sinking characteristics of MPs, determined an 80x higher settling velocity for EPS pellets compared to polyamide fibres.

Biofouling strongly affects the behaviour of MP in the aquatic environment. The plastic particles can aggregate with particles of biological origin, i.e. phytoplankton or live or dead microorganisms which form zooplankton. The phenomenon of biofilm formation on the MP surface results in an increase in specific gravity and, consequently, faster settling in the water column and accumulation in the bottom sediments of lakes and rivers. Hidalgo-Ruz et al. [16] noted that the settling velocity of polystyrene fragments was higher compared to acrylic fibres and polypropylene pellets with increasing biofilm colonisation. Karkanorachaki et al. [17] showed that the phenomenon of microparticle biofouling in the form of films or pellets also leads to an increase in their settling velocity.

Many authors have conducted studies on the effect of the shape, size and density of plastic microparticles on their settling velocity [7,18,19]. Nguyen [19] analysed the free-fall velocity in the standing water column of polystyrene particles with irregular shapes. He found that the irregularity of EPS could slow down the sinking of large particles, but for too high a level of irregularity, the positive correlation between settling velocity and EPS size became insignificant. The fragmentation and photodegradation processes of expanded polystyrene is an important issue addressed by the researchers. This is because it is one of the most widely used plastics and one of the predominant waste polymers found in the natural environment. Sarkar et al. [12] found that polystyrene particles with an average size of approx. 90–100 µm under optimised atmospheric conditions were broken down into millions of 1–3 µm particles in less than 16 hours. According to these authors, the optimised laboratory conditions corresponded to approximately 10 months of MP weathering in the natural environment. Song et al. [11] showed that, as a result of UV exposure and mechanical fragmentation, the number of fragmented EPS, PE and PP particles increased with decreasing particle

size. These authors noted that approximately 80% of the EPS granules fragmented into nanoparticles as a result of abrasion alone. Yao et al. [20] report that the colour of EPS particles changes during the accelerated UV-induced ageing process. This is because colour groups are formed on the EPS molecular chain, which cause yellowing of the plastic surface. Following photo-oxidative degradation, the stability of the molecular structure is destroyed, resulting in a change in the crystallinity and specific surface area of the polystyrene particles. Therefore, EPS particles become potential carriers of toxic chemicals, e.g. heavy metals [21,22], or PAHs [23]. Ho et al. [24] explained the effect of weathering on the sorption behaviour of polystyrene in a system composed of multiple organic solutes. In order to understand their sorption mechanisms and the formation of toxic chemicals, EPS particles were modified by abiotic weathering (photodegradation) and/or biotic weathering (microbial degradation). These authors observed inhibition of microalgae growth in the presence of chemically contaminated polystyrene particles. There are many reports that polystyrene deposition on microalgae results in a decrease in chlorophyll concentration and, consequently, in their photosynthetic activity [25–27]. Contaminated with toxic substances, MPs also have negative effects on animals. Plastic particles similar in shape and size to natural particles can indeed be mistakenly ingested by animals, e.g. by water birds [28]. Numerous studies have shown that polystyrene micro- and nanoparticles are ingested by marine organisms, causing adverse effects, i.e. reduced foraging activity [29], inhibition of growth and development [30], or oxidative stress [31].

In order to increase the comparability of studies dealing with the identification of MPs in the aquatic environment, appropriate procedures should be developed with a clear distinction of particle shapes. Current forms of MP determination in fresh surface waters are based on the GESAMP recommendations [6]. Water samples are usually concentrated by filtering large volumes of water through plankton nets. This method, called the reduced-volume method, is most suitable for sampling MPs (PP, PE, PS, EPS) floating on the water surface. These plastics are usually separated from organic contaminants by oxidation with hydrogen peroxide (purification). After filtering the sample, flotation is carried out by adding a saturated high density solution (NaCl, CaCl₂, ZnCl₂) [32]. The method of microplastic extraction as a result of sorting and flotation allows the determination of MPs from 5 to 0.3 mm in size by direct observation with a stereoscopic or digital microscope. Manual classification plays a very important role in this stage of MP determination. This is the phase of visual identification of plastic particles, which are sorted according to their size, shape and colour. However, the manual sorting stage is subject to the so called own error of the marking person. To prevent the loss of information, many scientists use software to process images captured by a stereo microscope equipped with a camera. Image processing using ImageJ or ShapeR software is becoming an increasingly common tool for morphological assessment (size, colour, shape) and quantitative evaluation of MP particles [33,34].

In this article, analysis of images obtained with a digital microscope is proposed for the identification of MP particles. Digital image processing using ImageJ software (available online) was used to determine the number of microparticles and their basic morphological parameters, describing size, shape and colour. Implemented image processing procedures allowed the extraction and calculation of 2D and 3D shape descriptors. Multidimensional data analysis using the Principal Component Analysis (PCA) method was used to find relationships between shape and colour MPs.

2. Materials and Methods

2.1. Analysed samples

A stagnant area of the Vistula river in the north-eastern district of Kraków, below the area exposed to anthropogenic pollution, i.e. urban run-off, was selected for the study. The stagnant area is located on the outskirts of the city, behind the industrial zone, at the marina of Yacht Klub Polski Kraków in the Nowa Huta district (50°03'04"N 20°03'29"E). The selection of the sampling site was guided by the location upstream of the treated sewage discharge point and the accessibility of the coastal zone. Additionally, the presence of protected waterbird species was taken into account. Many

years of observations by the authors [35] confirm that a marina with peers is a place where mute swans and mallard ducks frequent.

2.2. Sampling and preliminary sample preparation

Due to the absence of standardised methods for collection and separation of microplastics from riverbank sites, the procedures were based on literature reports [36–38]. In order to obtain a more representative view of microplastic contamination of the Vistula river, samples were collected for 6 months in the period from March to August 2022.

Water was collected using a reduced-volume method, with a 250 μm mesh size plankton net. On site, 15 dm^3 of water was passed through the mesh. Samples with microplastics were transported to the laboratory in sealed glass containers.

The analysis of the samples was each time preceded by a pre-treatment to remove mineral and organic contaminants. The material retained on the filter was quantitatively transferred to a laboratory beaker, where natural organic matter was removed. The separated material was rinsed with distilled water and subjected to chemical oxidation using 30% H_2O_2 , which was repeated if necessary. A density difference method with a 10% NaCl solution was used to separate MP particles [37]. The mixture was allowed to stand for 24 h to allow separation of the plastic particles, and the supernatant liquid was filtered through a GF/A filter (diameter 47 mm, pore size 1.6 μm , Whatman).

2.3. Digital microscopy

Despite the chemical oxidation treatment, organic contaminants, i.e. undegraded plant parts or zooplankton, remained in the samples along with MP. This type of material, which was clearly distinguishable from microplastic particles, was removed during initial sorting under a G1200 digital microscope (*Shenzhen Ltd.* China) at 10x magnification.

For the actual image microscopy, a digital microscope was used at 10x to 100x magnification. When visual observations were made, particles with a specific shape (ideally spherical) or characterised by irregular sharp edges were considered as plastic particles [16]. Unnatural colour or multicolour also indicated MP particles. A total of 1603 plastic particles were photographed and subjected to further image processing.

2.4. Image processing and analysis

For each MP particle, images were taken showing their size, shape and colour. The images were then appropriately transformed using the open-source ImageJ software (type 1.53a). An example of a binary MP image is presented in Figure 1.

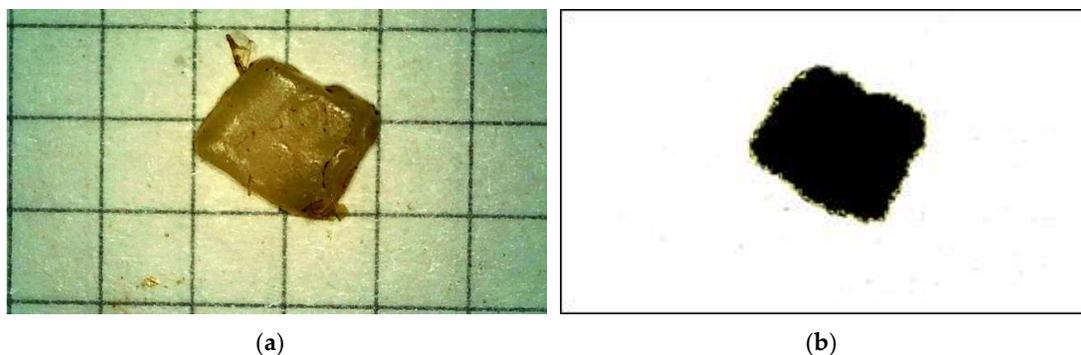


Figure 1. Original photograph of the MP particle (a) and its binary image in ImageJ (b); grid 2.5 x 2.5 mm.

The binary images of MP particles obtained in this way first allowed the determination of two shape descriptors in the 2D plane: surface area (A) and perimeter (P). These parameters were calculated in pixels, which were then converted into units, mm^2 and mm, respectively.

Based on A and P, a third 2D shape descriptor was determined for each particle image. For the evaluation of pellets, granules, fragments and foils, the area-equivalent diameter (DA) was used. This is calculated by converting the captured image into a circle of equivalent area [39]. For fibres, the ratio of major axis length (L length) to minor axis length (W width) was determined.

2.5. Microplastic characteristics / morphology

The isolated microplastic samples were analysed to determine the type of particles by origin, shape and colour. Considering the origin, the plastic particles were divided into primary or secondary. Primary MP comes mostly from domestic and agricultural products (textile fibres, cosmetic additives or fertilisers in the form of pellets). Secondary MP results from the fragmentation of larger pieces of plastic.

Based on the GESAMP recommendations [6], all plastic particles were counted according to the shape category. A distinction was also made between regular (pellets) and irregular particles (granules, fragments, films, fibres). Spherical or almost perfectly spherical particles, which were deformed using the hot needle method, were considered as pellets [6,40]. Considering irregular spherical or near spherical particles that can be partially elastic, they were classified as granules. Fragments were defined as irregularly shaped polymer particles in the form of scraps or flakes derived from fragmentation of larger objects. They looked as if broken off from a larger piece of hard, more convex pieces (scraps) or flat particles with smooth or angular edges (flakes). Films were identified as flexible flat particles with smooth or angular edges. Fibres were defined as a non-tapered long material with a length much greater than the width.

To obtain as complete a view as possible of the MP shape, parameters defining the particle dimensions were used. Area-equivalent diameter (DA) was used to assess the size of pellets, granules, fragments, flakes and foils [41]. The area-equivalent diameter of a particle is the diameter of the circle which has the same area as that of the particle and was calculated as follows [42]:

$$DA = \sqrt{4 \times A_p / \pi} \quad (1)$$

Where:

A_p – the area of a circle with the same perimeter.

The maximum DA at 5 mm and the area size at a maximum of 19.63 mm² with an acceptable error of < 0.5% were defined. In the case of fibres, length L was used to assess their size, which was determined to be equal to or less than 15 mm.

The length (L) was estimated from the maximum Feret diameter. This is the largest distance between two parallel lines that do not intersect the image:

$$L = F_{\max} \quad (2)$$

Where F_{\max} – maximum Feret diameter.

The width (W) was determined from a rectangle of length L, which has the same area A as the image [43]. According to the current procedure for fibre determination, the ratio of L to W should not be greater than 3 [41].

The overall shape of the particles is described by parameters such as convexity, circularity and elongation, regardless of whether the perimeter is smooth or intricate. A visual determination was made as to whether a determined MP has a shape that indicates that it is a spatial (3D) or a planar (2D) particle. Following the guidelines of Rosal [44], pellets, granules and scraps were considered as 3D particles, while 2D particles included flakes and films. Fibres were considered as 1D particles.

In addition to using the usual shape categories for all MPs, an additional subdivision was carried out on the basis of their geometric shape in 2D, i.e. the two-dimensional projection. It was determined how many particles of a given MP type were labelled with a 2D Shape approximating to: circle, ellipse, polygon, square, rectangle or triangle.

A more detailed description of the morphological properties of plastic materials can be obtained by combining their size and different shape descriptors in the 3D plane. Three factors were used to

describe MP particles: Corey Shape Factor (circularity descriptor), compactness (form descriptor) and dimensionality (shape descriptor). Corey Shape Factor (CSF) was defined as [10]:

$$CSF = c / (\sqrt{ab}) \quad (3)$$

Where:

a – longest axis of particle,

b – intermediate axis of particle,

c – shortest axis of particle.

CSF takes values below 0.5 for particles shaped like flakes or discs (2D particles) or fragments (1D particles). Values close to 1 characterise pellet-, granule- and sphere-shaped circular particles (3D particles).

Compactness (C) was defined as [42,45]:

$$C = A / A_P \quad (4)$$

A compactness value of 0 and 1 defines the particles as 1D and ideally 3D, respectively.

Dimensionality (D) was defined as [46]:

$$D = \sum L_i / \max L_i \quad (5)$$

Where:

L_i – the orthogonal length of the particle, i.e. its length in the i -th orthogonal axis.

D takes values from 1 to 3. Particles with dimensionality values close to 1, 2 or 3 can be characterised as 1D, 2D or 3D particles, respectively.

The labelled MP particles were also counted by colour divided into white, grey, black, red, blue, green, yellow, and other (transparent, orange, pink and purple).

The estimated number of MP particles was expressed in units per m^3 of water.

2.6. Statistical analysis

For all shape descriptors in the two-dimensional and three-dimensional planes, basic descriptive statistics were calculated, i.e. mean, median, min, max and SE.

Due to the variability of MP particles, Principal Component Analysis was used to determine the relationships between their geometric shape in 2D (Shape 2D variable), the parameters describing its size and shape (six 2D and 3D shape descriptors) and colour. By reducing the number of primary variables and replacing them with components that significantly explain their variation, PCA analysis allows the processes and phenomena occurring to be described with the maximum amount of information [47]. The Keiser criterion was used to determine the number of principal components. The final step was a graphical representation of the dataset, where each variable was represented by a vector, and its position and length determined the extent to which the individual variables influenced the principal components. Strong correlation occurred when variables whose vectors had similar lengths were located close together in the same part of the factor area. Arrangement of variables far apart or in different parts of the factor area indicated a lack of correlation.

Statistical analysis was performed using Statistica 13.0.

3. Results and Discussion

In terms of the origin of the MP particles, 8,933 pcs· m^{-3} of water were classified as primary. The amount of MPs identified as particles of secondary origin was 97,933 pcs· m^{-3} , representing 91.6% of all plastic particles. This shows that the main source of MPs in the environment is waste from plastic products. The primary sources of MP were mainly household products (microbeads from cosmetics, toy parts in pellet form). The presence of plastic production pellets (so-called nurdles) has also been demonstrated. These are the primary material for the manufacture of most commercial plastics.

Secondary MP resulted from the fragmentation of larger pieces of plastic. Figure 2 shows the types of primary and secondary MP retrieved from the Vistula river during the 6-month observation period.

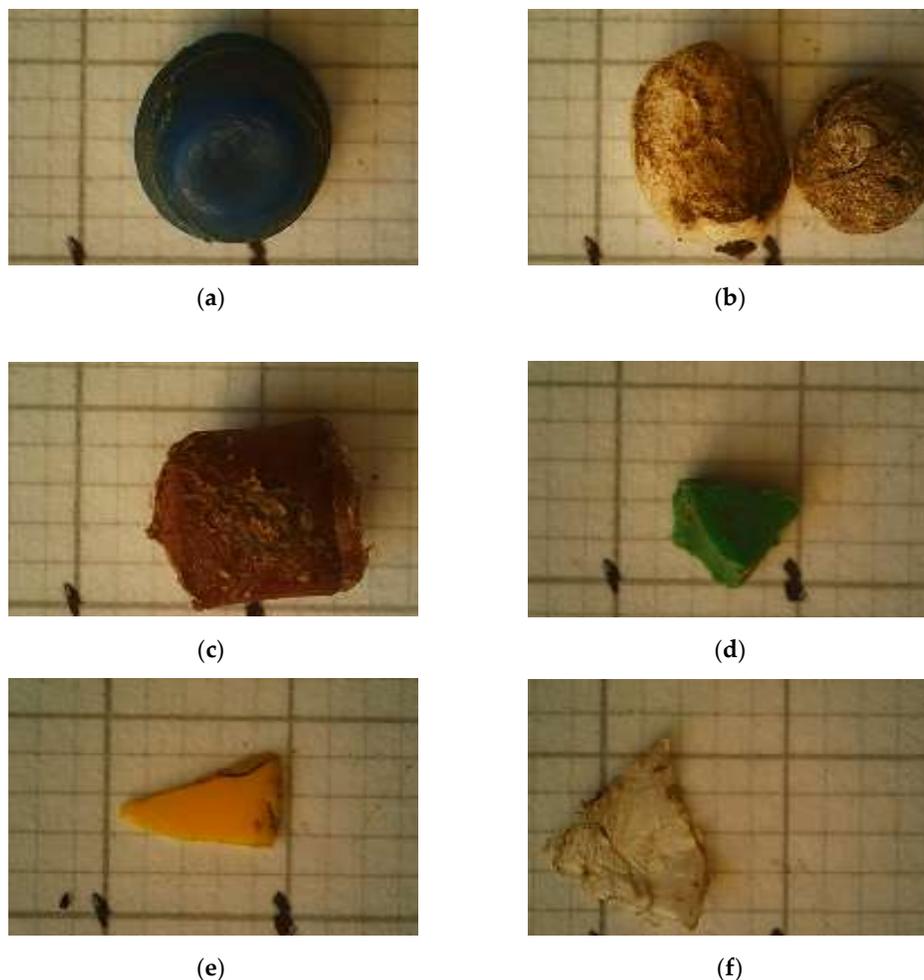


Figure 2. Images of forms of MPs present in the Vistula river: (a) disc; (b) granules; (c) and (d) scraps; (e) flake; (f) foil by digital microscope; grid 1 × 1 mm.

Based on geometric shape, seven groups of particles were distinguished, divided into 3D particles (regular and irregular) and irregular 2D and 1D particles. Taking 3D particles into account, pellets accounted for 6.2% (6,067 items), while granules and trimmings made up 19.0% (18,600 items) and 72.4% (70,933 items) of the designated MP, respectively (Figure 3). Among the regular 3D particles, there was an additional distinction of nurdle, or MP in the form of a flattened ellipsoid (so-called disc), whose content was determined at 2.4% (2,333 items). In the case of 2D particles, the content of flakes and films was 67.9% (6,067 items) and 26.1% (2,333 items), respectively. The content of 1D particles in the form of fibres was the lowest at only 0.5% of all microplastics (533 items).

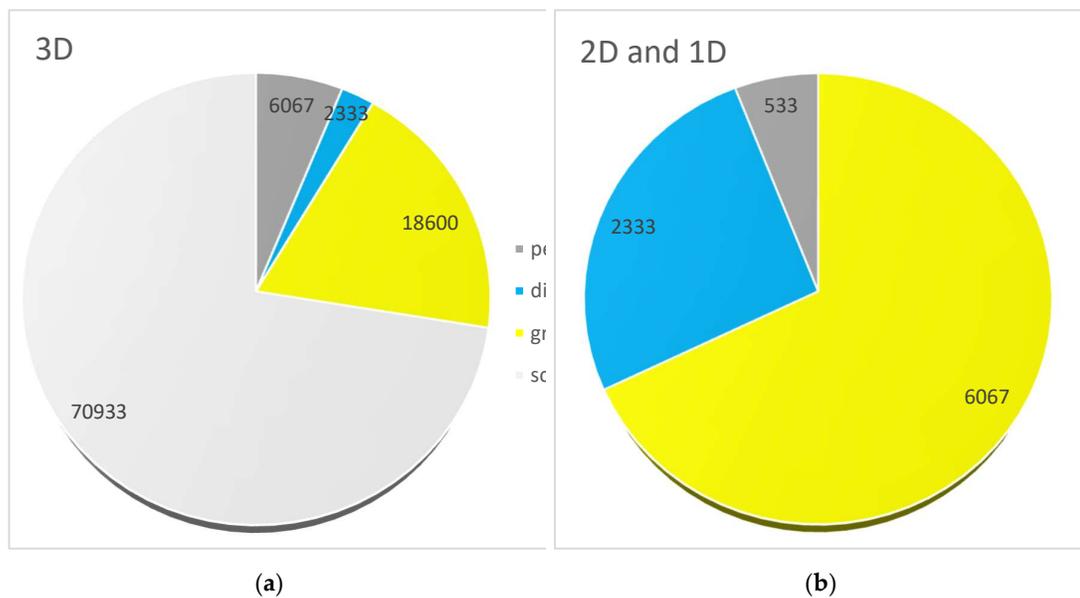


Figure 3. Number of microplastics (items/m³) isolated from the Vistula river by shape: (a) particles in solid form (3D); (b) particles in flat form (2D and 1D).

Tables 1 and 2 show the morphological characteristics of MP particles, divided into 3D, 2D and 1D particles.

Table 1. Morphological characteristics of 3D particles.

Type of MP	3D regular particles						3D irregular particles					
	Pellets			Discs			Granules			Scraps		
Parameters describing size/dimension												
Descriptive statistics	A	P	DA	A	P	DA	A	P	DA	A	P	DA
Mean	0.19	1.49	0.46	15.38	13.93	4.43	7.33	9.59	3.05	3.11	6.68	2.01
Mediane	0.14	1.40	0.43	16.35	14.37	4.57	8.00	10.06	3.20	2.79	6.06	1.88
Min	0.03	0.62	0.20	8.76	10.49	3.34	0.22	1.66	0.53	0.02	0.52	0.16
Max	0.97	3.52	1.11	19.55	15.66	4.99	19.71	15.78	5.01	19.75	16.02	5.02
SE	0.04	0.59	0.18	2.31	1.52	0.47	1.51	5.11	1.33	1.08	2.37	1.08
Parameters describing shape												
Descriptive statistics	CSF	C	D	CSF	C	D	CSF	C	D	CSF	C	D
Mean	0.98	0.94	2.93	0.84	0.99	2.21	0.83	0.83	2.67	0.21	0.71	2.25
Mediane	0.98	0.96	2.95	0.89	0.99	2.21	0.85	0.87	2.70	0.22	0.73	2.21
Min	0.88	0.68	2.69	0.69	0.92	2.14	0.52	0.21	2.04	0.02	0.19	1.60
Max	1.01	1.01	3.01	0.94	1.04	2.31	0.94	1.14	2.90	0.26	1.04	4.12
SE	0.02	0.08	0.07	0.08	0.03	0.04	0.06	0.16	0.13	0.02	0.15	0.29

A – Area; P – Perimeter; DA – Area-equivalent Diameter; CSF – Corey Shape Factor; C – Compactness; D – Dimensionality.

Of the regular 3D particles, pellets had the smallest surface area, circumference and diameter. They were characterised by a diameter of 0.46 ± 0.18 mm. Pellet diameters between 0.2 and 0.3 mm indicated the origin of the particles as a cosmetic additive [48]. Larger diameters indicated the origin of the pellets as, for example, toy parts. The mean surface area and circumference of the pellets were 0.19 mm² and 1.49 mm, respectively. The CSF roundness descriptor of 0.98 ± 0.02 indicated that, among the 3D particles, the form was almost perfectly spherical for all pellets. The compactness and dimensionality values described the form and shape of the pellets as almost perfectly 3D (C~1 and D~3). The low SE values of all shape coefficients indicate the regularity of the pellets. Using the CSF factor, Francalanci et al. [18] and Metz et al. [49] also identified plastic pellets or beads as particles with three dominant dimensions. This confirms that labelled pellets are the primary source of MP in the environment.

The microplastic discs were much larger in size. Compared to pellets, they were characterised by 80x larger surface area, 10x larger circumference and diameter. Their average values were 15.38 mm, 13.93 mm² and 4.43 mm, respectively. The size of the flattened PP pellets studied by Šunta et al. [50] was 4.7 ± 0.1 mm, while Bond et al. [51] reports nurdle dimensions ranging from 2.4 mm to 4.6 mm (weathered pellets) and 3.3 mm to 4.0 mm (pristine pellets). The CSF calculated by these authors for the weathered pellets ranged from 0.31 to 0.97 and for all types of pristine pellets from 0.40 to 0.82 . These values are similar to the results obtained for the discussed particles. MP in the form of a nurdle was characterised by a circularity descriptor CSF at an average level of 0.84 . Based on a CSF close to 1, the discs can be described as 3D particles [10]. However, the values of the other two descriptors C~1 and D~2 indicated that the shape of the nurdles was close to that of 2D particles. Francalanci et al. [18] assigned a 2D shape to the discs. In the present study, the geometric shape of these particles was defined as a flat disk and they were identified as regular 3D particles.

Considering the granules, their diameter was 3.05 mm \pm 1.33 mm, while the average area and perimeter were 7.33 mm² and 9.59 mm, respectively (Table 1). Due to the size and elastic nature of the plastic, these particles were probably formed by fragmentation of polystyrene. Kim et al. [52] determined the size of the polystyrene granules to be 3.5 mm \pm 0.2 mm, or 15% larger. For the granules in question, the mean CSF value was at 0.83 . According to Dietrich, a CSF of approximately 0.7 is characteristic for naturally worn sediment [10]. In our study, the CSF values of the granule varied between 0.52 and 0.94 , indicating flattened or perfectly spherical particles, respectively. Also, the other two shape form descriptors represented the variable dimensionality of this MP. The values of compactness and dimensionality, ranging from 0.21 to 1.14 and 2.04 to 2.90 , respectively, indicated that the granules assumed a 2D or 3D shape. Metz et al. [49] used the term cylindrical granule for particles with 3D dimensions. In the present study, the geometric shape of the granules was defined as irregular 3D particles. This indicates that granules are a secondary source of MP in the environment.

The mean area and perimeter of the scraps were 3.11 mm² and 6.68 mm, respectively. The equivalent surface diameter of these irregular particles was determined to be 2.01 mm \pm 1.08 mm. Strady et al. [53] analysing fragments in freshwater in Vietnam estimated the median of their surface area to be 0.13 mm², about 20 times smaller than in our study.

Values of CSF (about 0.2), C (about 0.7), D (about 2.2) indicated that the geometrical shape of the scraps is close to 2D particles. According to Dietrich, natural particles for which the CSF has a value close to zero are 2D particles that occur in plate form [10]. Francalanci et al. [18] assigned a 1D shape to the fragments, while Metz et al. [49] – a 3D shape. In this study, due to the values of all three coefficients defining roundness, form and shape of the fragments, it was concluded that they should, however, be classified as 2D particles. Their variable geometrical shape confirms the fact that the trimmings are formed by MP fragmentation and are a secondary source in the environment.

Table 2. Morphological characteristics of 2D and 1D particles.

Type of MP	2D irregular particles						1D particles		
	Flakes			Films			Fibres		
Parameters describing size/dimensions									
Descriptive statistics	A	P	DA	A	P	DA	A	P	L
Mean	5.46	8.25	2.40	8.36	12.3 8	3.21	2.94	12.30	6.15
Mediane	3.36	7.38	2.07	8.46	12.9 3	3.28	3.05	8.99	4.49
Min	0.08	1.05	0.32	1.75	4.87	1.50	0.54	2.71	1.36
Max	19.61	15.7 6	4.99	19.72	16.0 1	5.01	4.55	29.01	14.5 0
SE	3.76	4.41	1.09	4.79	4.23	0.93	1.38	9.09	4.55
Parameters describing the shape									
Descriptive statistics	CSF	C	D	CSF	C	D	CSF	C	D
Mean	0.11	0.69	2.11	0.10	0.59	2.01	0.02	0.48	1.01
Mediane	0.11	0.70	2.10	0.09	0.63	2.05	0.02	0.55	1.00
Min	0.06	0.19	1.57	0.06	0.25	1.65	0.01	0.07	1.00
Max	0.12	0.95	2.72	0.12	0.87	2.22	0.05	0.93	1.02
SE	0.01	0.14	0.15	0.01	0.14	0.14	0.01	0.34	0.01

A – Area; P – Perimeter; DA – Area-equivalent Diameter; CSF – Corey Shape Factor; C – Compactness; D – Dimensionality.

Analysing the morphological characteristics of the 2D irregular particles, the mean surface area, perimeter and equivalent surface diameter for the films were found to be larger than for the other irregular particles (Table 2). These were $8.36 \text{ mm}^2 \pm 4.79 \text{ mm}^2$, $12.38 \text{ mm} \pm 4.23 \text{ mm}$ and $3.21 \text{ mm} \pm 0.93 \text{ mm}$, respectively. For the flakes, the area and perimeter were determined to be $5.46 \text{ mm}^2 \pm 3.76 \text{ mm}^2$ and $8.25 \text{ mm} \pm 4.41 \text{ mm}$. Their equivalent diameter was $2.40 \text{ mm} \pm 1.09 \text{ mm}$. Descriptors defining the geometric shape of the flakes and films (CSF about 0.1, C within 0.6-0.7, D about 2) confirmed their identification as 2D particles. Holjeoć et al. [46] in their study for square plate-shaped MP particles determined D values ranging from 2.17 to 2.33, which confirmed their assumption of classification as 2D particles. According to Metz et al. [49], the term film should refer to particles with two dominant dimensions (2D). A study by Strady et al. [53] showed that the largest fragment area (of the order of 0.3 mm^2) and its elevated medians were recorded in the waters of Cua Luc Bay.

Of the MPs analysed, fibres had the greatest average length at $6.15 \text{ mm} \pm 4.55 \text{ mm}$. Their surface area and circumference were $2.94 \text{ mm}^2 \pm 1.38 \text{ mm}^2$ and $12.30 \text{ mm} \pm 9.09 \text{ mm}$, respectively. As proposed by Francalanci et al. [18] and Metz et al. [49] fibres, i.e. particles with only one dominant dimension, were assigned a 1D shape, as indicated by CSF=0 and D=1.

Eight groups of particles were distinguished by colour (Figure 4). 3D particles, i.e. in the form of a solid, were mostly characterised by grey (22,333 items – 22.8%), white (21,133 items – 21.6%), blue (15,200 items – 15.5%) and yellow (14,200 items – 14.5%) colours. Black, red, green and other colours accounted for 5.8% (5,667 items), 6.9% (6,733 items), 7.3% (7,133 items) and 5.7% (5,533 items) of 3D geometric MPs, respectively. 2D particles were mostly characterised by yellow (3,600 items – 40.3%) and white (2,067 items – 23.1%). Grey, black, blue and other colours accounted for 11.2% (1,000 items), 5.2% (467 items), 8.2% (733 items) and 11.2% (1,000 items) of 2D geometric shape MPs, respectively. Green particles were in negligible quantity (67 items) and red particles were not found. In the case of 1D particles, i.e. fibres, their colour was only grey and black. The fibres determined by Uurasjärvi et

al. [54] were characterised by several colours: white, blue, red, brown, black and green. In the case of fibers, it is particularly important to prepare samples for microscopic analysis, because the fibers may be confused with natural plant tissues [55].

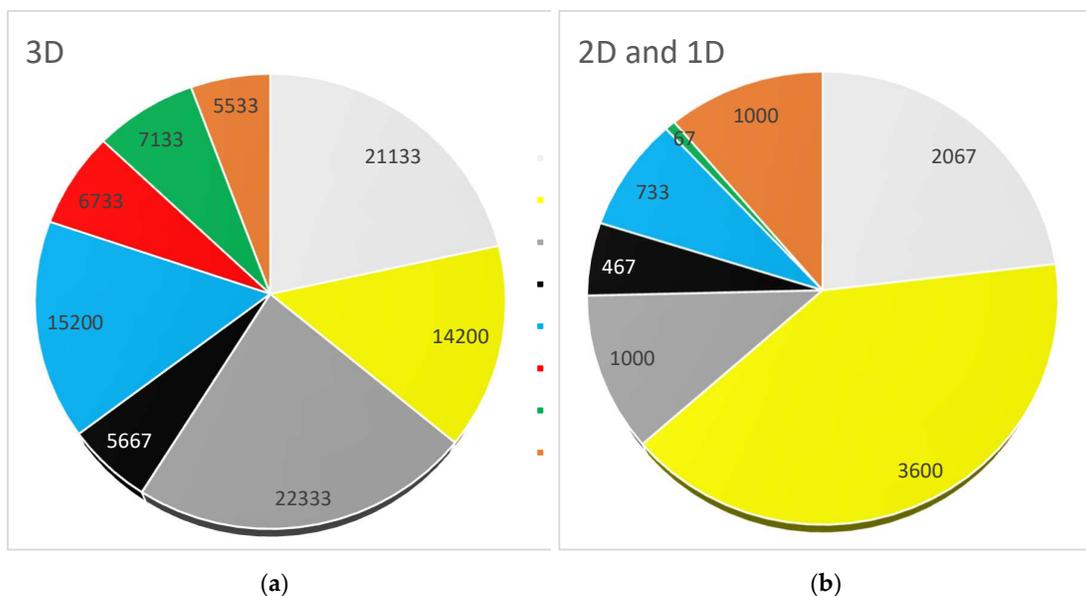


Figure 4. Number of microplastics (items/m³) isolated from the Vistula river by colour: (a) particles in solid form (3D); (b) particles in flat form (2D and 1D).

The observed different colour of MP particles, among which grey, white and blue were the most frequently observed, are consistent with reports by other authors [56]. de Calvarho et al. [57] observed similar colours when studying the impact of urbanisation on MP in the Garonne River. White and blue MP represented 32.4% and 14.3% of particles, respectively. In turn, in the lake waters, white MP constituted as much as 80% and blue MP only 8%. The remaining colors: red, black/grey, orange and green accounted for less than 4% [58]. Also in marine sediments from the Black Sea, transparent and white MP was found in the largest amounts [59]. White and blue colours are commonly used in many plastic products, i.e. food packaging, bottle caps, films. The transparent colour is associated with commonly used packaging materials i.e. bottles and disposable bags. Similar conclusions were reached by Erdoğan [60] when conducting a study on the presence of MP in a pond located in the recreational area of Yozgat Pine Grove National Park in Turkey. Yellow particles were a large group in our study. Their quantity was influenced by the yellowing of EPS granules due to ageing.

Given the varying morphological characteristics and colour of the 3D and 2D particles, a particle-by-particle PCA analysis was performed. Due to the negligible content of fibres, they were not included in the analysis.

PCA for granules, flakes and films identified three main factors PC 1, PC 2 and PC 3, which explained about 90% of the variation in the raw data (Table 3). For trimmings, four main factors were determined for which the% cumulative variance was at the highest level of more than 90%. For pellets, the first, second and third principal components explained 48.79%, 76.64% and 90.00% of the total variance of the primary variables, respectively. For the trimmings, PC 1, PC 2, PC 3 and PC 4 explained 51.25%, 68.74%, 81.18% and 93.42% of the total variance. For the flakes, PC 1, PC 2, PC 3 were 44.67%, 73.96% and 87.13% of the total variance of the primary variables, respectively. For films, the first, second and third principal components explained 47.85%, 76.20% and 88.70% of the total variance, respectively.

Table 3. Eigenvalues of the correlation matrix (3D and 2D particles by type).

Type of MP	3D unregular						2D unregular						
	Granules			Scraps			Flakes			Films			
Principal Component	PC 1	PC 2	PC 3	PC 1	PC 2	PC 3	PC 4	PC 1	PC 2	PC 3	PC 1	PC 2	PC 3
Eigenvalue	3.90	2.23	1.07	4.10	1.40	0.99	0.98	3.57	2.34	1.05	3.83	2.27	1.00
% variance	48.79	27.85	13.36	51.2	17.4	12.4	12.2	44.6	29.2	13.1	47.8	28.3	12.50
% cumulative variance	48.79	76.64	90.00	51.2	68.7	81.1	93.4	44.6	73.9	87.1	47.8	76.2	88.70

The PCA analysis performed for the granule showed that the first principal component of PC1 was almost entirely represented by 6 highly correlated descriptors: 2D shape (A, P, DA) and 3D shape (CSF, C, D) (Table 4).

Table 4. The principal components and factor coordinates of variables (3D and 2D particles by type).

Type of MP	3D unregular						2D unregular						
	Granules			Scraps			Flakes			Films			
Variables	PC 1	PC 2	PC 3	PC 1	PC 2	PC 3	PC 4	PC 1	PC 2	PC 3	PC 1	PC 2	PC 3
Colour	0.08	-0.05	0.90	0.15	-0.04	0.46	0.88	0.06	0.08	-0.74	0.13	-0.29	-0.75
2D shape descriptors													
Shape 2D	0.07	0.50	0.50	-0.14	0.18	0.87	0.43	0.06	-0.12	-0.71	0.17	0.31	-0.65
A	-0.82	0.53	-0.04	0.81	-0.55	0.03	-0.02	-0.68	-0.71	-0.02	0.58	0.80	0.02
P	-0.70	0.70	-0.04	0.94	0.27	-0.02	0.03	-0.87	-0.49	-0.01	0.92	0.36	0.07
DA	-0.83	0.55	-0.04	0.90	0.42	0.03	0.00	-0.73	-0.67	0.00	0.61	0.77	0.02
3D shape descriptors													
CSF	-0.83	-0.54	0.08	0.83	-0.31	-0.06	0.00	0.73	-0.67	0.04	-0.85	0.51	-0.05
C	-0.83	-0.55	0.07	0.55	0.66	0.18	0.15	0.75	-0.65	0.04	-0.85	0.51	-0.04
D	-0.83	-0.54	0.08	0.84	-0.52	0.03	0.07	0.85	-0.50	0.01	-0.88	0.46	-0.05

A – Area; P – Perimeter; DA – Area-equivalent Diameter; CSF – Corey Shape Factor; C – Compactness; D – Dimensionality.

For scraps, 5 of the above descriptors contributed to PC1, as variable C represented the second principal component. The first component for flakes was shown to be correlated at a high level with 6 of the shape descriptors, except that variable A made a similarly strong contribution to both PC1 and PC2. Gabrijelčič Tomc and Hladnik [61], in a PCA analysis of the use of 2D shape descriptors in computer simulation of fabrics, found similar relationships. The first principal component was largely represented by the following mutually strongly correlated 2D shape descriptors: area, perimeter and area-equivalent diameter. In the present study, the PCA analysis performed for the films showed that only one 2D shape descriptor (P) and 3 3D shape descriptors (CSF, C, D) contributed to the first principal component.

Considering the second principal component of the granule, it was found to be correlated with the Shape 2D and Perimeter variables. For PC2 scraps, it was represented by the form descriptor (C). It was observed that, compared to the other MP particles, this may have been influenced by the more intricate contour of the scraps, affecting the size of their perimeter. As mentioned above for the flakes, PC2 was represented by a variable area. The PC2 of the films was shown to be correlated at a high level with two 2D shape-determining descriptors (A, DA).

It was found that for granules, flakes and films, the variables Colour and Shape 2D were high contributors to the third principal component. These two variables in the case of the scraps decomposed into separate principal components PC 4 and PC 3 respectively.

The correlations between the principal components (PC1, PC2, PC3) and the 8 primary variables, i.e. colour, as well as the 4 2D shape descriptors (Shape 2D, Area, Perimeter and Area-equivalent diameter) and the 3 3D shape descriptors (CSF, Compactness, Dimensionality) are graphically presented on Figure 5 as a projection of variables on the factor area (1 x 2 x 3).

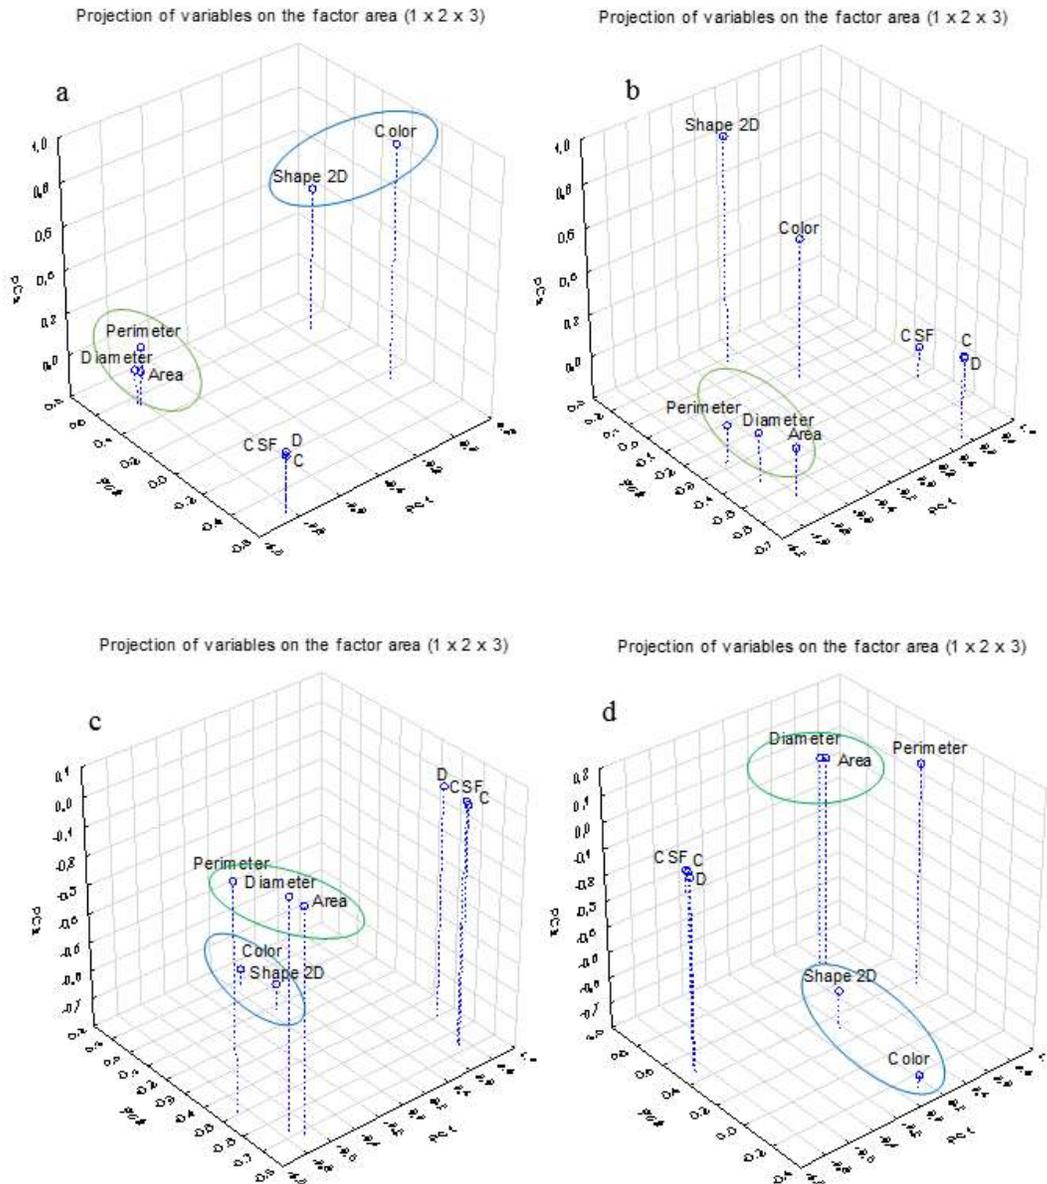


Figure 5. Projection of variables on the principal components area (1 x 2 x 3) for: (a) granules; (b) scraps; (c) flakes and (d) films.

In Figures 5a, 5c and 5d, it can be observed that, for granules, flakes and films, the Shape 2D and Colour variables are correlated (marked with a blue ellipse). Such a correlation was not detected for the scraps, as the Shape 2D and Colour variables are located in different parts of the factor area (Figure 5b). The scraps were also found to be distinguished by the different positioning of all the 3D shape descriptors compared to the rest of the MP particles. Two of them, i.e. the circularity descriptor (CSF) and the shape descriptor (D), are located close to each other, while the form descriptor (C) is situated in a different part of the factor area. This may be due to the ambiguous designation of the scraps as 2D or 3D particles due to their variable roundness and form. Li and Iskander [62] analysing the relationship of 9 shape descriptors and 6 size descriptors for different types of sand found no correlation between them. Following this, they suggested dividing the descriptors into four independent groups, which included descriptors characterising the overall shape of the particle, perimeter smoothness descriptors; roundness descriptor and convexity descriptor.

Considering the granules, scraps and flakes in question, a correlation can be seen between the three 2D shape descriptors describing their size – the variables Area, Perimeter and Diameter marked with a green ellipse (Figure 5 a-c). In the case of the films, a correlation can only be seen between the Area and Diameter variables. This could be due to the intricate contour of these particles, affecting the size of their perimeter. Panunzi et al. [63], in a study on the diversity of MP types consumed by fish, observed differences probably due to different feeding habits. The characterisation of MPs using 2D and 3D shape descriptors allowed a preliminary elucidation of the mechanisms of selection of these particles by marine animals. Using PCA analysis, these authors showed that the ingestion of plastic particles by fish is influenced by their size, circularity and compactness.

Figure 6 shows the number of individual MPs (granules, scraps, flakes and foils), broken down into the 8 differentiated colour groups: white, grey, black, red, blue, green, yellow and other (transparent, orange, pink, purple).

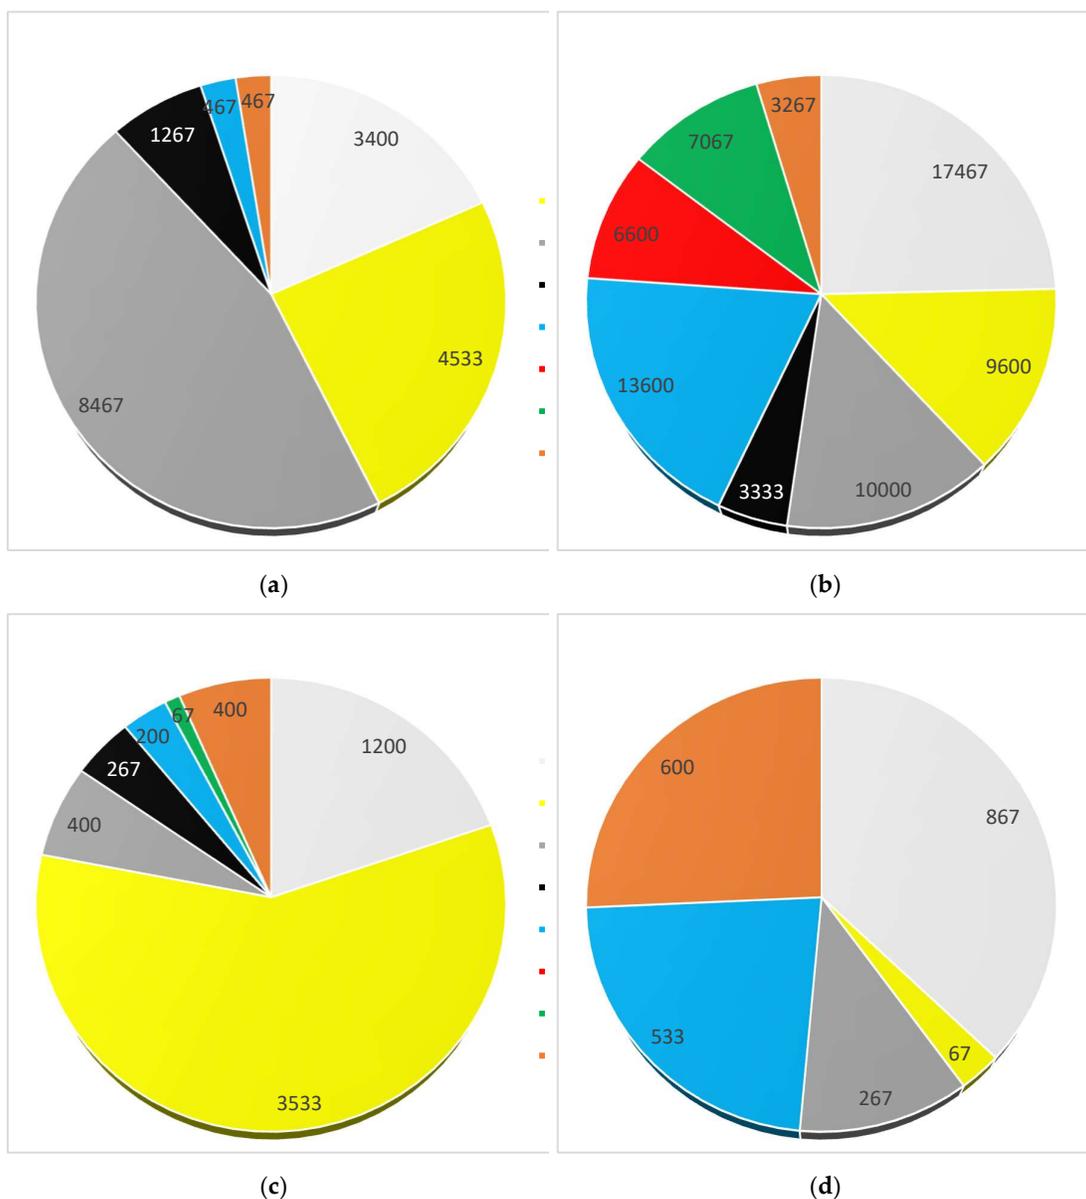


Figure 6. Number of microplastics (items/m³) isolated from the Vistula river by colour: (a) granules; (b) scraps; (c) flakes; (d) films.

In terms of colour, most granules were identified in grey (8,467 items – 45.5%), yellow (4,533 items – 24.4%) and white (3,400 items – 18.3%). 6.8% were black granules (1,267 items), while the remaining granules were blue (467 items – 2.5%) and other i.e. pink (467 items – 2.5%) (Figure 4a). No granules were observed in red and green.


Scraps were most often characterised by white (17,467 items – 24.6%), blue (13,600 items – 19.2%), grey (10,000 items – 14.1%) and yellow (9,600 items – 13.5%). Green, red, black and other colours accounted for 10.0% (7,067 items), 9.3% (6,600 items), 4.7% (3,333 items) and 4.6% (3,267 items) of the total scraps, respectively (Figure 4b). Of the colour different, orange, pink and purple were identified. Uurasjärvi et al. [54] determining microplastic in the surface waters of a northern European lake found that most of the floating fragments found were in white, blue, green and red colours.

For flakes, 58.2% occurred in yellow (3,533 items) and 19.8% in white (1,200 items). The colours grey, black, blue and green accounted for 6.6% (400 items), 4.4% (267 items), 3.3% (200 items) and 1.1% (67 items) of all flakes, respectively (Figure 4c). The colour other, which was only translucent, highlighted 6.6% of the particles in question (400 items). No red-coloured flakes were identified.


Most foil was identified in white (867 items – 37.1%), blue (533 items – 22.9%) and other – mostly transparent (600 items – 25.7%). 11.4% (267 items) was grey foil and 2.9% (67 items) of the foil was yellow (Figure 4d). No film was observed in black, red or green.

The total amount of blue scraps, flakes and film at 14,800 items (13.8% of all MPs) is a concern, as studies report that fish can selectively digest plastic particles coloured blue [64,65]. Lin et al. in their review showed that fibers and fragments were the most frequently determined forms of MP in fish, 75% and 18%, respectively. The dominant colors were blue (35%) and black (31%), followed by transparent (19%) and white (13%) [66].


The PCA analysis showed that, for granules, flakes and films, the Shape 2D and Colour variables are correlated. It is important to remember that plastics change their colour and shape due to, among other things, degradation processes and a reduction in the molecular weight of the polymer. This results in a polymer that is more brittle and thus more susceptible to mechanical and/or biological degradation [67]. Zhu et al. [68] showed that photochemical changes in the properties of plastics occurred as a result of MP irradiation with simulated UV light. These consisted of the white EPS turning yellow and the transparent PP and PE particles turning opaque. After 54 days under simulated sunlight, the EPS, PP and PE particle was reduced in plastic mass. As reported by Chalmers and Meier [69], the white EPS granules under UV light turn yellow after 3 months. Also their shape changes - initially spherical with a regular surface becoming ellipsoidal at first and then increasingly irregular. However, MP located deep in water or soil is less subject to physicochemical erosion and more to biodegradation processes [70]. Kim et al. [52] conducting a study on the shape and morphology of polystyrene MPs, found a lower content of spherical shape particles in the effluent compared to prolate spheroid (P-spheroid) shape. The aged/weathered EPS particles are characterised by a rough, oxidised surface and heterogeneous morphology, with colour through grey to black. In the study in question, image analysis revealed that 70.6% (13,133 items) of the polystyrene particles were circular in shape with an average CSF of 0.89 (Figure 7a). White, grey and yellow granules accounted for 22.3% (2,933 items), 40.1% (5,267 items) and 24.9% (3,267 items) of the round particles, respectively. The least number of round granules was identified in black (6.1% – 800 items), blue (3.0% – 400 items) and other i.e. pink (3.6% – 467 items).

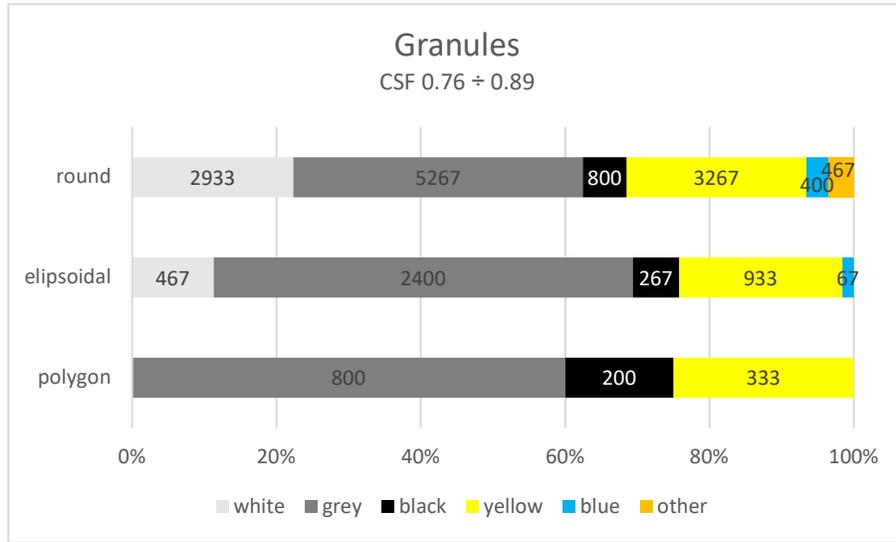

(a)

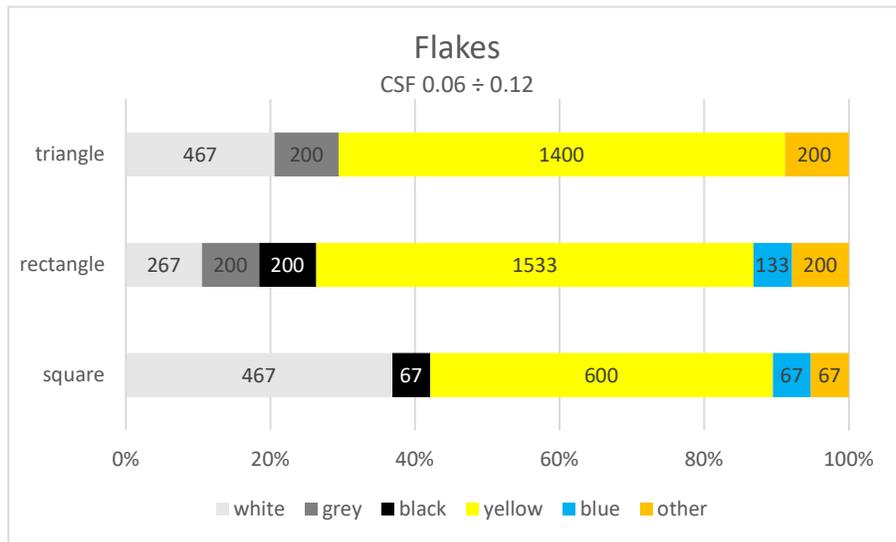

(b)

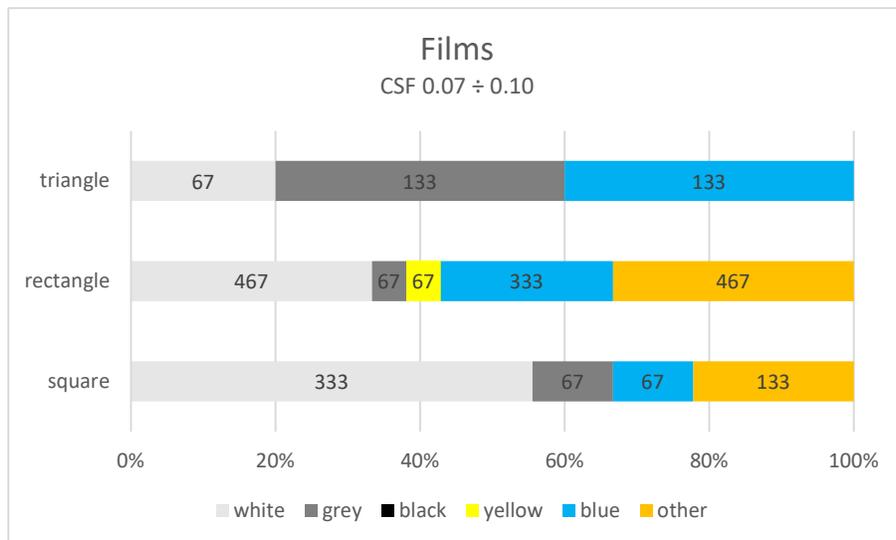

(c)

Figure 7. Number of microplastics (items/m³) isolated from the Vistula river by Shape 2D: (a) granules; (b) flakes; (c) films.

The ellipsoid-shaped particles of 4,133 items, which represented 22.6% of the analysed granules, had a CSF at an average level of approximately 0.80. Among the ellipsoidal granules, the grey colour marked 58.1% (2,400 items) of the polystyrene particles. Yellow and white colour accounted for 22.6% (933 items) and 11.3% (467 items), respectively. This may indicate the progressive ageing of the polystyrene granules under UV light and their gradual degradation. Black-coloured ellipsoidal particles accounted for 6.5% (267 items) and the fewest particles were identified in blue (1.6% – 67 items).

The remaining EPS were considered as irregular particles. Their 2D shape was determined to be polygonal, and the average CSF value was found to be the lowest at 0.76. Grey, yellow and black granules accounted for 60.0% (800 items), 25.0% (333 items) and 15.0% (200 items), respectively. No polygonal white granules were observed, indicating that their ageing state was mature due to the degradation processes of the polystyrene particles taking place.

As shown in Figure 7b, the number of rectangular, triangular and square flakes in yellow was highest at 1,533, 1,400 and 600 items respectively. Grey rectangular and triangular and black rectangular and square flakes were recorded at 200, 200, 200 and 67 items respectively. This indicates the identification of 69.2% of flakes (4200 items) that may have been fragmented and aged by UV radiation. The white square, triangular and rectangular flakes were 467, 467 and 267 items, respectively. Considering the shape of the flakes, the total content of rectangular, triangular and square particles was 41.8% 37.4% and 20.9%, respectively. Sorasan et al. [71] highlighted the ageing of PP and PE fragments and EPS granules in the marine environment. Their study showed that the formation of polymeric nanoparticles resulted first from photochemical reactions and then from their mechanical degradation. As was evident from the MP surface texture image, the PP fragments could be split into rectangular, triangular or square particles as a result of UV radiation.

Analysing the different colours of the films, it was found that 60.0% (600 items) of the particles were rectangular in shape, while 25.7% (1,400 items) and 14.3% (333 items) were square and triangular in shape, respectively (Figure 7c). White rectangular, square and triangular foils were identified with 467, 333 and 67 items respectively. Blue rectangular, triangular and square particles were recorded at 333, 133 and 67 items, respectively. Rectangular and square films in a different colour – transparent – occurred in quantities of 467 and 133 items, respectively. This type of microplastic in grey and yellow was the smallest (267 and 67 items, respectively), and black was not identified. This may be due to other processes occurring during film ageing. Indeed, the morphological changes of flat plastic particles, due to abiotic effects of the environment, are different for flexible particles such as films compared to hard flakes. Julienne et al. [72], analysing the ageing of LDPE films, found that, due to plasticisation of the polymer, water probably accelerates MP cracking. This occurs in a direction normal to the extrusion direction of the film which causes these flexible plastics to elongate and break with a near rectangular shape.

4. Possible future prospects associated with the use of multidimensional analysis of microplastics

Multidimensional image analysis using 2D and 3D shape descriptors is a simple and low-cost way to convert categorical data into quantitative variables, avoiding loss of information. A more detailed description of MPs could expand our knowledge of its diversity and distribution in the environment. For this reason, further research will focus on the analysis of black and grey MPs and organic particles. For this purpose, a thermal imaging camera operating in the 400–1000 nm VNIR band will be tested.

5. Summary and Conclusions

The study confirms the problem of pollution of surface waters by microplastics, in particular polystyrene. In the analysed stagnant Vistula river, located below an area subjected to strong anthropopression, the amount of plastic particles recovered from the river during the 6 months of the study amounted to 106,800 pieces from 1 m³ of water. Scraps and flakes accounted for 66.4% and 5.7%, respectively, of the particles extracted from the Vistula river. Their shape and unnatural colour indicated that degraded packaging and bottles were the main source. Granules, which originated from the fragmentation of polystyrene foam, were also a numerous group at 17%. It should be remembered that polystyrene, or expanded polystyrene, has one of the highest production rates among plastics. Digital image analysis proved to be an effective tool for the identification of microplastics from the surface waters of central Europe. The publicly available ImageJ programme has enabled accurate morphological characterisation of both spherical and irregularly shaped particles. The three-dimensional properties of MP, which can be described by 2D and 3D shape descriptors, can largely suggest the starting material of the microplastic. Some shapes may be derived from specific products – pellets are likely to be microbeads used in cosmetics, film is mainly derived from plastic bags and packaging materials, and granules are derived from polystyrene damage [56].

This article shows that multivariate data analysis using the PCA method, provided an opportunity to replace the input set of correlated parameters by three uncorrelated principal factor components, representing linear combinations of variables. It was found that for granules, flakes and films, the third principal component was most related to the variation in 2D shape and colour of the plastic particles. Such a relationship was not found for the most numerous MP group, i.e. the trimmings, which were described by four principal components. On the one hand, this is related to changes in the colour and shape of the plastic particles due to their degradation processes and progressive fragmentation. On the other hand, the number of colours for granules, flakes and films was not as varied as in the case of trimmings. Indeed, the latter were identified in 10 different colours – as white, yellow, grey, black, blue, red, green, orange, pink, violet. Considering the granules, it was concluded that the white particles came from damaged polystyrene food storage containers, beverage cups and insulation materials. The relationships between the shape and colour of the EPS granules indicate their susceptibility to photodegradation processes. The proposed method can be used to track MP transformations in the natural environment and assess the negative impact on aquatic organisms.

In order to reduce the amount, and therefore the volume, of MP in surface waters, there should be awareness-raising campaigns by local authorities about this risk. It is of great importance to publicise this problem, as plastic packaging – especially those used to store food – is very common and its use exposes the environment to years of harmful microplastic particles and is risky to health [73]. It is also important to introduce another stage of municipal sewage treatment, which will limit the release of MP along with the treated sewage.

Author Contributions: Conceptualization, E.D.; methodology, E.D. and E.Ł.-M.; software, E.D.; validation, E.D. and E.Ł.-M.; formal analysis, E.D. and K.Ch.; investigation, E.D.; data curation, E.D.; writing—original draft preparation, E.D. and E.Ł.-M.; writing—review and editing, E.D.; visualization, E.D. and E.Ł.-M.; supervision, E.D.; project administration, E.D.; funding acquisition, E.D. and K.Ch. All authors have read and agreed to the published version of the manuscript.

Funding: This research was financed by the Ministry of Science and Higher Education of the Republic of Poland.

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: The data presented in this study are available on request from the corresponding author.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Freeman, S.; Booth, A.M.; Sabbah, I.; Tiller, R.; Dierking, J.; Klun, K.; Rotter, A.; Ben-David, E.; Javidpour, J.; Angel, D.L. Between source and sea: The role of wastewater treatment in reducing marine microplastics. *J. Environ. Manag.* **2020**, *226* 110642.
2. Urban-Malinga, B.; Zalewski, M.; Jakubowska, A.; Wodzinowski, T.; Malinga, M.; Palys, B.; Dąbrowska, A. Microplastics on sandy beaches of the southern Baltic Sea. *Mar. Pollut. Bull.* **2020**, *155*, 111170.
3. Esiukova, E. Plastic pollution on the Baltic beaches of Kaliningrad region, Russia. *Mar. Pollut. Bull.* **2017**, *114* 1072–1080.
4. Merlino, S.; Locritani, M.; Bernardi, G.; Como, C.; Legnaioli, S.; Palleschi, V.; Abbate, M. Spatial and temporal distribution of chemically characterized microplastics within the protected area of pelagos sanctuary (Nw mediterranean sea): Focus on natural and urban beaches. *Water* **2020**, *12*(12), 3389.
5. Chubarenko, I.; Bagaev, A.; Zobkov, M.; Esiukova, E. On some physical and dynamical properties of microplastic particles in marine environment. *Mar. Pollut. Bull.* **2016**, *108*(1-2), 105–112.
6. GESAMP, G. Guidelines for the monitoring and assessment of plastic litter in the ocean. *GESAMP Reports Stud.* **2019**, *99*, 130.
7. Waldschläger, K.; Schüttrumpf, H. Effects of particle properties on the settling and rise velocities of microplastics in freshwater under laboratory conditions. *Environ. Sci. Technol.* **2019**, *53*(4), 1958–1966.
8. Ismayilova, I., Zeyer, T., and Timpf, S.: Identification of Microplastics in Soils Using 2D Geometric Shape Descriptors, *AGILE GIScience Ser.* **2021**, *2*, 32, <https://doi.org/10.5194/agile-giss-2-32-2021>
9. Waldschläger, K.; Brückner, M.Z.; Almroth, B.C.; Hackney, C.R.; Adyel, T.M.; Alimi, O.S.; ... Wu, N. Learning from natural sediments to tackle microplastics challenges: a multidisciplinary perspective. *Earth-Sci. Reviews* **2022**, *228*, 104021.
10. Dietrich, W.E. Settling velocity of natural particles. *Water Res. research* **1982**, *18*(6), 1615–1626.
11. Song, Y. K.; Hong, S.H.; Jang, M.; Han, G.M.; Jung, S.W.; Shim, W.J. Combined effects of UV exposure duration and mechanical abrasion on microplastic fragmentation by polymer type. *Environ. Sci. Technol.* **2017**, *51*(8), 4368–4376.
12. Sarkar, A.K.; Rubin, A.E.; Zucker, I. Engineered polystyrene-based microplastics of high environmental relevance. *Environ. Sci. Technol.* **2021**, *55*(15), 10491–10501.
13. Waldschläger, K.; Born, M.; Cowger, W.; Gray, A.; Schüttrumpf, H. Settling and rising velocities of environmentally weathered micro-and macroplastic particles. *Environ. Res.* **2020**, *191*, 110192.
14. Shi, Y.; Shi, L.; Huang, H.; Ye, K.; Yang, L.; Wang, Z.; ... Gao, S. Analysis of aged microplastics: a review. *Environ. Chemistry Lett.* **2024**, 1–28.
15. Alimi, O.S., Claveau-Mallet, D.; Lapointe, M.; Biu, T.; Liu, L.; Hernandez, L.M.; ... Tufenkji, N. Effects of Weathering on the Properties and Fate of Secondary Microplastics from a Polystyrene Single-Use Cup. *J. Hazard. Mater.* **2023**, 131855.
16. Hidalgo-Ruz, V.; Gutow, L.; Thompson, R.C.; Thiel, M. Microplastics in the marine environment: a review of the methods used for identification and quantification. *Environ. Sci. Technol.* **2012**, *46*(6), 3060–3075.
17. Karkanorachaki, K.; Syranidou, E.; Kalogerakis, N. Sinking characteristics of microplastics in the marine environment. *Sci. Total Environ.* **2021**, *793*, 148526.
18. Francalanci, S.; Paris, E.; Solari, L. On the prediction of settling velocity for plastic particles of different shapes. *Environ. Pollut.* **2021**, *290*, 118068.
19. Nguyen, T.H. Settling behaviour of irregular-shaped polystyrene microplastics. *VNUHCM J. Eng. Technol.* **2021**, *4*(4), 1229–1238.
20. Yao, P.; Li, C.; Xiao, S. Effect of ultraviolet aging on properties and structure of polystyrene. *Huagong Xuebao/CIESC J.* **2014**, *65*. 4620–4626. 10.3969/j.issn.0438-1157.2014.11.058.
21. Barus, B.S.; Chen, K.; Cai, M.; Li, R.; Chen, H.; Li, C.; ... Cheng, S.Y. Heavy metal adsorption and release on polystyrene particles at various salinities. *Front. Mar. Sci.* **2021**, *8*, 671802.
22. Khalid, N.; Aqeel, M.; Noman, A.; Khan, S.M.; Akhter, N. Interactions and effects of microplastics with heavy metals in aquatic and terrestrial environments. *Environ. Pollut.* **2021**, *290*, 118104.
23. Paul-Pont, I.; Lacroix, C.; González Fernández, C.; Hégaret, H.; Lambert, C.; Le Goïc, N.; Frère, L.; Cassone, A.-L.; Sussarellu, R.; Fabioux, C.; Guyomarch, J.; Albertosa, M.; Huvet, A.; Soudant, P. Exposure of marine mussels *Mytilus* spp. to polystyrene microplastics: Toxicity and influence on fluoranthene bioaccumulation. *Environ. Pollut.* **2016**, *216*, 724–737. doi: 10.1016/j.envpol.2016.06.039

24. Ho, W.K.; Law, J.C.F.; Zhang, T.; Leung, K.S.Y. Effects of weathering on the sorption behavior and toxicity of polystyrene microplastics in multi-solute systems. *Water Res.* **2020**, *187*, 116419.
25. Sjollem, S.B.; Redondo-Hasselerharm, P.; Leslie, H.A.; Kraak, M.H.; Vethaak, A.D. Do plastic particles affect microalgal photosynthesis and growth?. *Aquat. Toxicol.* **2016**, *170*, 259–261.
26. Mao, Y., Ai, H., Chen, Y., Zhang, Z., Zeng, P., Kang, L., ... & Li, H. (2018). Phytoplankton response to polystyrene microplastics: perspective from an entire growth period. *Chemosphere*, *208*, 59–68.
27. Jalaudin Basha, N.N.; Adzuan Hafiz, N.B.; Osman, M.S.; Abu Bakar, N.F. Unveiling the noxious effect of polystyrene microplastics in aquatic ecosystems and their toxicological behavior on fishes and microalgae. *Front. Toxicol.* **2023**, *5*, 1135081 doi: 10.3389/ftox.2023.1135081
28. Reynolds, C.; Ryan, P.G. Micro-plastic ingestion by waterbirds from contaminated wetlands in South Africa. *Mar. Pollut. Bull.* **2018**, *126*, 330–333.
29. Hämer, J.; Gutow, L.; Köhler, A.; Saborowski, R. Fate of microplastics in the marine isopod *Idotea emarginata*. *Envir. Sci. Technol.* **2014**, *48*(22), 13451–13458.
30. Besseling, E.; Wang, B.; Lurling, M.; Koelmans, A.A. Nanoplastic affects growth of *S. obliquus* and reproduction of *D. magna*. *Envir. Sci. Technol.* **2014**, *48*(20), 12336–12343.
31. Usman, S.; Abdull Razis, A.F.; Shaari, K.; Amal, M.N.A.; Saad, M.Z.; Mat Isa, N.; Nazarudin, M.F. Polystyrene microplastics exposure: an insight into multiple organ histological alterations, oxidative stress and neurotoxicity in Javanese medaka fish (*Oryzias javanicus* Bleeker, 1854). *Intern. J. Environ. Res. Public Health* **2021**, *18*(18), 9449.
32. Masura, J.; Baker, J.E.; Foster, G.D.; Arthur, C.; Herring, C. Laboratory methods for the analysis of microplastics in the marine environment: recommendations for quantifying synthetic particles in waters and sediments. NOAA Technical Memorandum NOS-OR&R-48, **2015**
33. Zhang, S.; Yang, X.; Gertsen, H.; Peters, P.; Salánki, T.; Geissen, V. A simple method for the extraction and identification of light density microplastics from soil. *Sci. Total Environ.* **2018**, *616*, 1056–1065.
34. Valente, T.; Ventura, D.; Matiddi, M.; Sbrana, A.; Silvestri, C.; Piermarini, R.; Jacomini C.; Costantini, M.L. Image processing tools in the study of environmental contamination by microplastics: reliability and perspectives. *Envir. Sci. Pollut. Res.* **2023**, *30*(1), 298–309.
35. Dacewicz, E.; Bergel, T.; Łobos-Moysa, E.; Moraczewska-Majkut, K.; Nocoń, W. Microplastic and mesoplastic in stagnation of the vistula water in highly urbanized areas of the Krakow poviat-preliminary research. *Acta Scientiarum Polonorum - Formatio Circumiectus* **2021**, *20*(3/4), 5–17.
36. Horton, A.A.; Svendsen, C.; Williams, R.J.; Spurgeon, D.J.; Lahive, E. Large microplastic particles in sediments of tributaries of the River Thames, UK—Abundance, sources and methods for effective quantification. *Mar. Pollut. Bull.* **2017**, *114*(1), 218–226.
37. Nel, H.A.; Dalu, T.; Wasserman, R.J.; Hean, J.W. Colour and size influences plastic microbead underestimation, regardless of sediment grain size. *Sci. Total Environ.* **2019**, *655*, 567–570.
38. Wendt-Potthoff, K.; Avellán, T.; van Emmerik, T.; Hamester, M.; Kirschke, S.; Kitover, D.; Schmidt, C. *Monitoring plastics in rivers and lakes: Guidelines for the harmonization of methodologies*. United Nations Environment Programme, **2020**, 1–108.
39. Shanthi, C.; Porpatham, R.K.; Pappa, N. Image analysis for particle size distribution. *Intern. J. Eng. Technol.* **2014**, *6*(3), 1340–1345.
40. Mintenig, S.M.; Int-Veen, I.; Löder, M.G.; Primpke, S., Gerds, G. Identification of microplastic in effluents of waste water treatment plants using focal plane array-based micro-Fourier-transform infrared imaging. *Water Res.* **2017**, *108*, 365–372.
41. ANNEX...2024. Annex to the Commission Delegated Decision supplementing Directive (EU) 2020/2184 of the European Parliament and of the Council by laying down a methodology to measure microplastics in water intended for human consumption, 11 March **2024**.
42. ISO 13322-1:2014 Particle size analysis — Image analysis methods — Part 1: Static image analysis methods, **2014**.
43. Li, M.; Wilkinson, D.; Patchigolla, K. Comparison of particle size distributions measured using different techniques. *Particulate Sci. Technol.* **2005** *23*(3), 265–284.
44. Rosal, R. Morphological description of microplastic particles for environmental fate studies. *Mar. Pollut. Bull.* **2021**, *171*, 112716. doi: 10.1016/j.marpollbul.2021.112716
45. Schnepf, U.; von Moers-Meßmer, M.A.L.; Brümmer, F. A practical primer for image-based particle measurements in microplastic research. *Microplastics and Nanoplastics* **2023**, *3*(1), 16.

46. Holjević, T.; Družeta, S.; Grbčić, L.; Alvir, M. Empirical Shape-Based Estimation of Settling Microplastic Particles Drag Coefficient. *J. Mar. Sci. Eng.* **2023**, *11*, 2166.
47. Jolliffe, I.T. Principal Component Analysis. *Technometrics* **2003**, *45*(3), 276.
48. Hussain, S.; Sial, N.; Nawaz, Z.; Naeem, M.; Habib, R.Z.; Thiemann, T. Presence of microplastic in personal care and cosmetic products from markets in Punjab, Pakistan. **2023**
49. Metz, T.; Koch, M.; Lenz, P. Quantification of microplastics: Which parameters are essential for a reliable inter-study comparison? *Mar. Pollut. Bull.* **2020**, *157*, 111330.
50. Šunta, U.; Trebše, P.; Kralj, M.B. Simply applicable method for microplastics determination in environmental samples. *Molecules* **2021**, *26*(7), 1.
51. Bond, T.; Morton, J.; Al-Rekabi, Z.; Cant, D.; Davidson, S.; Pei, Y. Surface properties and rising velocities of pristine and weathered plastic pellets. *Environ. Sci.: Processes & Impacts* **2022**, *24*(5), 794–804.
52. Kim, S.; Hyeon, Y.; Park, C. Microplastics' Shape and Morphology Analysis in the Presence of Natural Organic Matter Using Flow Imaging Microscopy. *Molecules* **2023**, *28*(19), 6913.
53. Strady, E.; Dang, T.H.; Dao, T.D.; Dinh, H.N.; Do, T.T.D.; Duong, T.N.; ... Chu, V.H. Baseline assessment of microplastic concentrations in marine and freshwater environments of a developing Southeast Asian country, Viet Nam. *Mar. Pollut. Bull.* **2021**, *162*, 111870.
54. Uurasjärvi, E.; Hartikainen, S.; Setälä, O.; Lehtiniemi, M.; Koistinen, A. Microplastic concentrations, size distribution, and polymer types in the surface waters of a northern European lake. *Water Environ. Res.* **2020**, *92*(1), 149–156.
55. Finnegan, A.; Süsserott, R.C.; Koh, L.H.; Teo, W.B. Gouramanis C. A Simple Sample Preparation Method to Significantly Improve Fourier Transform Infrared (FT-IR) Spectra of Microplastics. *Appl Spectrosc* **2022**, *76*(7), 783-792. DOI: 10.1177/00037028221075065.
56. Yang, L.; Zhang, Y.; Kang, S.; Wang, Z.; Wu, C. Microplastics in freshwater sediment: a review on methods, occurrence, and sources. *Sci. Total Environ.* **2021**, *754*, 141948.
57. de Carvalho, A.R.; Garcia, F.; Riem-Galliano, L.; Tudesque, L.; Albignac, M.; Ter Halle, A.; Cucherousset, J. Urbanization and hydrological conditions drive the spatial and temporal variability of microplastic pollution in the Garonne River. *Sci. Total Environ.* **2021**, *769*, 144479.
58. Henny, C.; Rohaningsih, D.; Suryono, T.; Santoso, A.; Waluyo, A. Microplastic pollution in the surface water of Lake Singkarak, Indonesia. *IOP Conference Series: Earth and Environmental Science* **2022**, 1118. 012050. 10.1088/1755-1315/1118/1/012050.
59. D'Hont, A.; Gittenberger, A.; Leuven, R.S.E.W.; Hendriks, J. Dropping the microbead: Source and sink related microplastic distribution in the Black Sea and Caspian Sea basins. *Marine Pollution Bulletin* **2021**, *173*. 10.1016/j.marpolbul.2021.112982.
60. Erdoğan, Ş. Microplastic pollution in freshwater ecosystems: A case study from Turkey. *Ege J. Fisheries and Aquat. Sci.* **2020**, *37*(2), 213–221. DOI: 10.12714/egejfas.37.3.02
61. Gabrijelčić Tomc, H.; Hladnik, A. 1D and 2D Shape Descriptors Applied in Fabric Drape Computer Simulation. *Fibres & Textiles in Eastern Europe* **2015**, *6*(114), 92–101.
62. Li, L.; Iskander, M. Evaluation of roundness parameters in use for sand. *J. Geotech. Geoenviron. Eng.* **2021**, *147*(9), 04021081.
63. Panunzi, G.; Valente, T.; Matiddi, M.; Lasinio G.J. A preliminary study on shape descriptors for the characterization of microplastics ingested by fish. In *Book of the Short Papers*, **2023**
64. Güven, O.; Gökdağ, K.; Jovanović, B.; Kideys, A.E. Microplastic litter composition of the Turkish territorial waters of the Mediterranean Sea, and its occurrence in the gastrointestinal tract of fish. *Environ. Pollut.* **2017**, *223*, 286–294.
65. Karlsson, T.M.; Vethaak, A.D.; Almroth, B.C.; Ariese, F.; van Velzen, M.; Hassellöv, M.; Leslie, H.A. Screening for microplastics in sediment, water, marine invertebrates and fish: Method development and microplastic accumulation. *Mar. Pollut. Bull.* **2017**, *122*, 403–408.
66. Lin X.; Gowen, A.A.; Pu H.; Xu J-L. Microplastic contamination in fish: Critical review and assessment of data quality, *Food Control* **2023**, *153*, 109939, <https://doi.org/10.1016/j.foodcont.2023.109939>
67. Arpia, A.A.; Chen, W.H.; Ubando, A.T.; Naqvi, S.R.; Culaba, A.B. Microplastic degradation as a sustainable concurrent approach for producing biofuel and obliterating hazardous environmental effects: a state-of-the-art review. *J. Hazard. Mater.* **2021**, *418*, 126381.
68. Zhu, L.; Zhao, S.; Bittar, T.B.; Stubbins, A.; Li, D. Photochemical dissolution of buoyant microplastics to dissolved organic carbon: rates and microbial impacts. *J. Hazard. Mater.* **2020**, *383*, 121065.

69. Lin, Z.; Jin, T.; Zou, T.; Xu, Li.; Xi, Bi.; Xu, D.; He, J.; Xiong, L.; Tang, C.; Peng, J.; Zhou, Y.; Fei, J. Current progress on plastic/microplastic degradation: Fact influences and mechanism, *Environmental Pollution* **2022**, *304*, 119159, <https://doi.org/10.1016/j.envpol.2022.119159>.
70. Chalmers, J.M.; Meier, R.J. Polymer Degradation and Oxidation: An Introduction. In *Molecular Characterization and Analysis of Polymers*; Chalmers, J.M., Meier, R.J., Eds.; Elsevier: Amsterdam, The Netherlands, **2008**; Volume 53, pp. 387–450.
71. Sorasan, C.; Edo, C.; González-Pleiter, M.; Fernández-Piñas, F.; Leganés, F.; Rodríguez, A.; Rosal, R. Ageing and fragmentation of marine microplastics. *Sci. Total Environ.* **2022**, *827*, 154438.
72. Julienne, F.; Delorme, N.; Lagarde, F. From macroplastics to microplastics: Role of water in the fragmentation of polyethylene. *Chemosphere* **2019**, *236*, 124409.
73. Kadac-Czapska, K.; Knez, E.; Gierszewska, M.; Olewnik-Kruszkowska, E.; Grembecka, M. Microplastics Derived from Food Packaging Waste—Their Origin and Health Risks. *Materials* **2023**, *16*, 674. <https://doi.org/10.3390/ma16020674>

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.