
A Green and Sustainable Organic Catalyst Based on Dimethylaminopyridinium Iodide for the Efficient Utilization of Atmospheric Carbon Dioxide Through the Nucleophilic Activation of Carbon Dioxide

[Hae-Jo Kim](#)^{*}, [Jae-Hyuk Do](#), Won Joo Lee

Posted Date: 1 April 2025

doi: 10.20944/preprints202504.0064.v1

Keywords: Carbon dioxide; Eco-friendly reaction; Organic catalyst



Preprints.org is a free multidisciplinary platform providing preprint service that is dedicated to making early versions of research outputs permanently available and citable. Preprints posted at Preprints.org appear in Web of Science, Crossref, Google Scholar, Scilit, Europe PMC.

Copyright: This open access article is published under a Creative Commons CC BY 4.0 license, which permit the free download, distribution, and reuse, provided that the author and preprint are cited in any reuse.

Article

A Green and Sustainable Organic Catalyst Based on Dimethylaminopyridinium Iodide for the Efficient Utilization of Atmospheric Carbon Dioxide Through the Nucleophilic Activation of Carbon Dioxide

Jae-Hyuk Do, Won Joo Lee and Hae-Jo Kim *

Department of Chemistry, Hankuk University of Foreign Studies, Yongin 17035, Korea

* Correspondence: haejkiml@hufs.ac.kr; Tel.: (82)-31-330-4703

Abstract: A series of *p*-substituted pyridinium catalysts were investigated as sustainable organic catalysts for carbon dioxide utilization under ambient conditions. Dimethylaminopyridine hydroiodide (DMAP·HI) was found to be a superior catalyst for cyclic carbonate synthesis from epoxide and CO₂ without solvents or additives. Mechanistic studies indicated that DMAP played a pivotal role as a nucleophile toward carbon dioxide during the cyclic carbonate formation. The organic catalyst could be recycled without any significant loss of catalytic activity, and was successfully applied for the multigram-scale synthesis of cyclic carbonate at mild temperature under atmospheric carbon dioxide.

Keywords: Carbon dioxide; Eco-friendly reaction; Organic catalyst


1. Introduction

Carbon dioxide is an important electrophilic C₁ resource widely used in organic syntheses. However, it is produced as inevitable wastes during the combustion of fossil fuels and respiration of living organisms, and is thus believed to significantly contribute to the global warming. Therefore, intensive research is currently devoted to carbon dioxide capture and utilization (CCU) in order to protect the earth's environment. [1,2] While capture or storage of carbon dioxide has been attempted using various metal organic frameworks [3–5] and amine functionalized organic polymers, [6–8] the low capacity and poor stability of captured carbon dioxide have often caused problems because carbon dioxide is released, even at a slightly elevated temperature. Thus, the complete and irreversible covalent bond formation between carbon dioxide and anionic carbon was directed as an alternative strategy of CCU, using organometallic reagents (PhMgBr, PhLi). Despite the rapid capture of carbon dioxide, these organometallic reagents are too sensitive to survive in environmental moisture. To overcome their vulnerability, soft organic metal-based reagents have been developed in conjunction with acetylide substrates. [9,10] However, these reagents still require a high temperature to make a covalent bond with CO₂, thus hampering their practical application.

As a current alternative in the research of CCU, metal-salen complex-based Lewis acid catalysts are emerging. [11] Although the metal-salen complexes show high efficiency in CCU, [12–14] most of them suffer severe limitation due to the competitive coordination or hydrolysis by the environmental moisture, and their catalytic activities are eventually lost. Therefore, the use of chemically stable and moisture-insensitive organocatalysts is attracting increasing interest as a sustainable method for CCU.

Numerous amine-based organic catalysts have recently been developed for the production of carbonates from epoxides and carbon dioxide (Scheme 1). Among them, the most effective catalysts working under mild conditions are derived from triethylammonium iodide and imidazolium bromide. Shirakawa's group utilized simple triethylamine hydroiodide as a bifunctional catalyst for

cyclic carbonate formation. [15] Triethylammonium hydrogen activates an epoxide group via H-bonding and produces a cyclic carbonate at mild temperature (40 °C) with turnover frequency (TOF) = 0.4 h⁻¹. More recently, Han's group constructed a novel organocatalyst based on ionic liquids, by combining methylimidazolium carboxylic acid with guanidine. [16] While the organic catalyst showed better efficiency with alkyl epoxides, its reaction was somewhat slower with aryl epoxide (TOF 0.13 h⁻¹), thus requiring a high reaction temperature (60 °C) as well as a significant amount of catalyst loading (25 mol %). Interestingly, Zhang's group introduced dimethylaminopyridine hydrobromide (DMAP·HBr) as a sustainable catalyst for cyclic carbonate formation and achieved an efficient catalytic transformation of styrene oxide into cyclic carbonate at high temperature (120 °C) with TOF = 24 h⁻¹. [17] The authors proposed an elegant reaction mechanism from the delocalized resonance structure of DMAP, they did not perform further experiments such as a counteranion effect or an electronic effect for the given pyridine derivatives. In addition, the reaction was performed at 120 °C, significantly greater than ambient conditions. Inspired by the well-known property of pyridine as a nucleophilic catalyst to carbonyl groups [18] and the recent work by Zhang's group, we started our research on carbon dioxide utilization using a series of pyridinium hydrohalides and found that dimethylaminopyridinium hydroiodide (DMAP·HI) is a superior catalyst for the formation of cyclic carbonates.

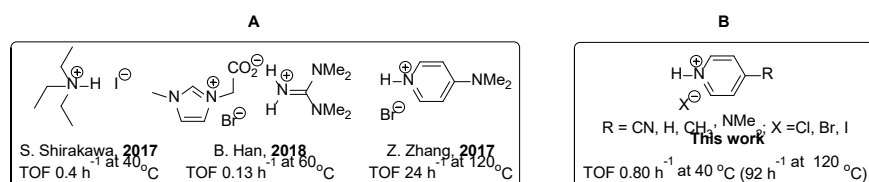

Scheme 1. Organic catalysts for cyclic carbonate synthesis. (A) Previously reported organic catalysts and their reaction efficiencies of styrene oxide with 1 atm CO₂, where TOF stands for turnover frequency. (B) *p*-Substituted pyridine·HX derivatives investigated in this work.

2. Results and Discussion

2.1. Model Reaction

A preliminary and model experiment was carried out for cyclic carbonate synthesis by employing styrene oxide as a model compound under a CO₂ balloon. The resulting cyclic carbonate formation was monitored using ¹H nuclear magnetic resonance (NMR) spectroscopy in the presence of DMAP·HI salt. Styrene oxide was slowly transformed into cyclic carbonate in the presence of 2 mol % of DMAP·HI. The methine proton of styrene oxide (*H*^a) at 3.90 ppm clearly shifted into a downfield region to afford a proton peak (*H*^c) at 5.88 ppm. In addition, the methylene protons (*H*^b) as well as the aromatic peaks of the initial epoxide also shifted downfield into a set of peaks of cyclic carbonate, indicating that an electron-withdrawing functional group was introduced to afford a cyclic carbonate from the epoxide. The product was purified by column chromatography and identified as a cyclic carbonate (Figure 1). This experiment demonstrates that styrene oxide underwent a clean reaction to cyclic carbonate with a catalytic amount of DMAP·HI under 1 atm CO₂.

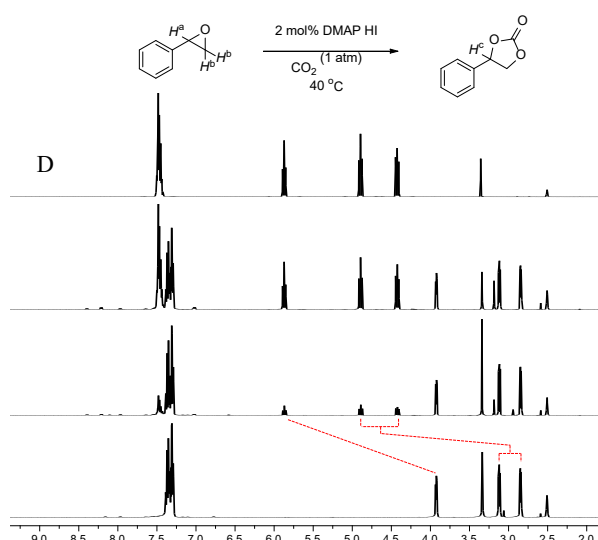


Figure 1. Time-dependent ^1H NMR spectra of styrene oxide in the presence of 2 mol% of catalyst **4** under 1 atm CO_2 at 40 °C. (A) Styrene oxide after 0 h, (B) 2 h, (C) 6 h, (D) cyclic carbonate. All the spectra were taken in $\text{DMSO}-d_6$.

2.2. Counterion Effect

Encouraged by the model reaction, the counterion effect of the pyridinium salts was investigated by adding an equimolar ratio of strong acid (HCl, HBr, or HI) to DMAP. The resulting catalysts (10 mol% each), DMAP·HCl, DMAP·HBr, and DMAP·HI, were incubated with styrene oxide (5.0 mmol) and the amounts of cyclic carbonate relative to styrene oxide were measured 12 h after incubation at 40 °C under 1 atm CO_2 . Catalyst DMAP·HI provided a cyclic carbonate with excellent yield (96%) compared to two the other congeners: DMAP·HCl (20%) and DMAP·HBr (37%). This result indicates that the most efficient reaction was achieved by the iodide counterion, owing to its plausible dual activity as a nucleophile and a leaving group, as observed in previous studies. [19,20] It is also noticeable that DMAP·HBr, the Zhang's catalyst, had a lower TOF value at a mild reaction temperature (0.30 h^{-1} at 40 °C).


2.3. Analysis of the Catalyst System (DMAP·HI)

As a control experiment, we monitored the cyclic carbonate formation reaction of styrene oxide (5.0 mmol) without any pyridinium salts and found that no products were formed (< 1%) at 40 °C under 1 atm CO_2 (Table 1, entry 1). Moreover, the reaction of styrene oxide in the presence of DMAP (10 mol%) and absence of HI did not proceed, indicating that DMAP alone cannot open a neutral epoxide (Table 1, entry 2). Interestingly, the reaction proceeded to the cyclic carbonate in the sole presence of HI, allowing a small amount of carbonate (9.9%) together with 8.3% of 2-iodo-2-phenylethan-1-ol (**Int**), a typical epoxide opening product under an acidic condition (Table 1, entry 3). This abnormal phenomenon can be explained as follows: Carbonate formation will stop with the formation of intermediate **Int**, since HI is irreversibly consumed as a reagent of the epoxide ring opening reaction. In the presence of DMAP·HI, the cyclic carbonate formation continued until completion (Table 1, entry 7). These experiments indicated that both HI and DMAP are essential components for the success of the catalyst in cyclic carbonate formation from epoxide as represented in Figure 2A. The optimal reaction time was also determined from a time-dependent reaction profile of the cyclic carbonate formation, and it was found that the reaction was complete within 12 h (Figure 2B).

Table 1. Cyclic carbonate formation from styrene oxide in the various reaction conditions. ^a.

| Entry | Catalyst (mol%) | Yield (%) | TOF (h ⁻¹) |
|-------|--------------------------------------|------------------------|------------------------|
| 1 | – | 0 | – |
| 2 | DMAP (10) | 0 | – |
| 3 | HI (10) | 9.9 (8.3) ^b | 0.08 |
| 4 | <i>p</i> -CNPy·HI (10) | 46 | 0.38 |
| 5 | Py (10)·HI | 66 | 0.55 |
| 6 | <i>p</i> -CH ₃ Py·HI (10) | 89 | 0.74 |
| 7 | DMAP·HI (10) | 96 | 0.80 |
| 8 | DMAP·HI (4) | 57 | 1.2 |
| 9 | DMAP·HI (2) | 32 | 1.3 |
| 10 | DMAP·HI (1) | 17 | 1.4 |
| 11 | DMAP·HI (10) | 61 ^c | 0.51 |
| 12 | DMAP·HI (10) | 46 ^d | 0.38 |


^a All the reactions were performed in neat styrene oxide (5.0 mmol) under 1 atm CO₂ at 40°C unless otherwise stated. Yields were determined by ¹H NMR spectral analysis after 12 h. The catalysts of *p*-CNPy, Py, and *p*-CH₃Py stand for 4-cyanopyridine, pyridine, and 4-methylpyridine, respectively. ^b A by-product of acidic epoxide ring opening reaction was also observed in 8.3% yields and identified as 2-iodo-2-phenylethan-1-ol (**Int**). ^c Reaction at 30 °C. ^d Reaction at 25 °C.

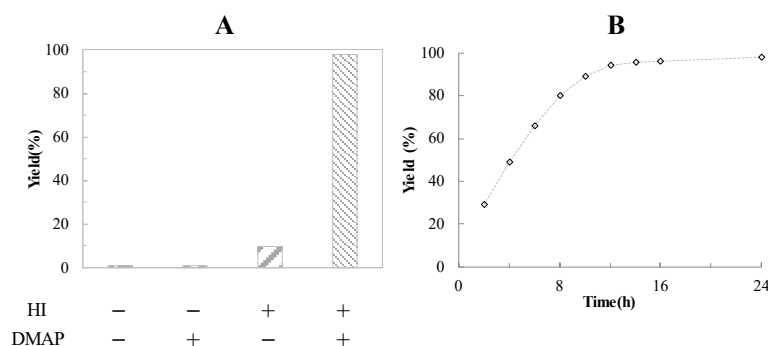**Figure 2.** (A) Optimization of catalyst components and (B) reaction time.

2.4. Structure and Activity Relationship of Catalyst: Electronic Effect

Organic catalysts of the epoxide-to-carbonate transformation usually consist of three components: H-bond donor, halide, and base. H-bond donors are commonly regarded as crucial activators of epoxide, while halides are considered to play a dual role not only as a nucleophile for the activated epoxide but also as a leaving group. However, the role of bases is not well understood and sometimes neglected with organic catalysts for cyclic carbonate. If the electrophilic activation of epoxide via H-bonding and the subsequent nucleophilic attack of halide were critical rate-determining steps during the cyclic carbonate formation, we could expect significant rate acceleration with acidic pyridinium iodide derivatives. Thus, we attempted to assess the acidity effect of pyridinium iodide salts by modulating the electronic property of *p*-substituted pyridines (Scheme 2). A parallel reaction of styrene oxide (5.0 mmol) was investigated at 40 °C under 1 atm CO₂ using a series of *p*-substituted pyridinium iodide salts (0.50 mmol) from the electron-withdrawing cyano group to the electron-donating dimethylamino group with a broad range of pK_a's in water (1.90 ~ 9.66). [21] Unexpectedly, the reaction of the most acidic *p*-cyanopyridinium iodide (*p*-CNPy·HI) was far slower than that of the other congeners. While catalyst *p*-CNPy·HI (pK_a 1.9) gave a 46% yield, the more basic pyridine derivatives exhibited higher yields for cyclic carbonates: Py·HI (pK_a 5.2) in 66%, *p*-CH₃Py·HI (pK_a 6.0) in 89%, and DMAP·HI (pK_a 9.7) in 96% yields (Table 1, entries 4–7). This unusual result suggests that the epoxide activation via H-bonding is not an exclusive factor for determining

the overall reaction rates, and other factors will be involved in the epoxide-to-cyclic carbonate transformation reaction.

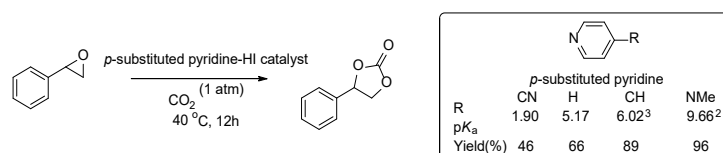


Scheme 2. Reaction of styrene oxide (5 mmol) with 1 atm CO₂ in the presence of various *p*-substituted pyridinium iodide derivatives.

We determined the optimal amounts of catalysts. When reducing the amount of catalyst loading from 10 mol% to 1 mol%, the chemical yields dramatically decreased from 96% to 17%, although the catalyst efficiency (TOF) increased by 1.8 times (Table 1, entries 7-10). We chose 10 mol % catalyst DMAP·HI as a practical condition for the carbonate formation. In addition, we investigated the effect of temperature on the yields by varying the reaction temperature from 40 °C to 25 °C and found the reaction occurred in a high yield at 40 °C (Table 1, entries 7 and 11-12). For comparison with Zhang's catalyst (DMAP·HBr, TOF 24 h⁻¹), we heated the reaction mixture upto 120 °C and found that catalyst DMAP·HI was sustainable at the high temperature and the TOF value was as high as 92 h⁻¹. This experiment demonstrated that DMAP·HI is 3.8 times more efficient than DMAP·HBr.

2.5. Proposed Mechanism

The experimental evidence above indicated that an intermediate (**Int**) formed rapidly and irreversibly (Scheme 3). Further transformation into the cyclic carbonate took place readily. However, we observed that the overall reaction was very slow and took 12 h to completion. These results imply that DMAP·CO₂ complex formation is a critical step in the epoxide-to-carbonate transformation reaction. First, the cyclic carbonate formation reaction of styrene oxide is believed to proceed via an intermediate **Int** and to releases free DMAP. The resulting DMAP can attack CO₂ as an active nucleophile to form a short-lived pyridinium carboxylate (DMAP·CO₂, **II**). [23] This dianionic carboxylate is assumed to be highly basic and nucleophilic, and can thus be readily accessed by the alcohol group of **Int** via H-bonding. The H-bond system is supposed to undergo a substitution reaction and to form an activated ester (**III**), which finally delivers a tetrahedral intermediate by intramolecular nucleophilic acyl attack from the neighboring alcohol group and the subsequent collapse of tetrahedral oxyanion intermediate leads to cyclic carbonate, regenerating the catalyst.

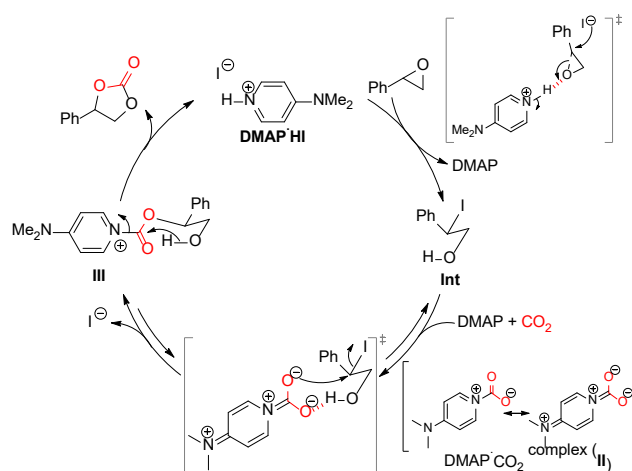

Scheme 3. A proposed catalytic mechanism of DMAP·HI through the nucleophilic CO₂ activation of DMAP.

DFT calculation of the intermediates was carried out using the B3LYP, 6-31G* basis set (Figure 4). An interesting hydrogen bond between **II** and **Int** was clearly observed, where the oxyanion of **II** possibly can reinforce the hydrogen bonding interaction with alcohol (1.545 Å of H-bond distance and 171° of O...H-O bond angle). The resulting H-bond caused a proximal distance between the carboxylate anion and the iodoalkyl group (2.998 Å of O...CHI distance) to favor an S_N2 reaction. Finally, the ester intermediate **III** disposed of an alcohol group within a reaction sphere with the activated carbonyl groups and immediately underwent the cyclic carbonate formation reaction via a favorable 5-exo-trig approach according to the Baldwin rule. [24]

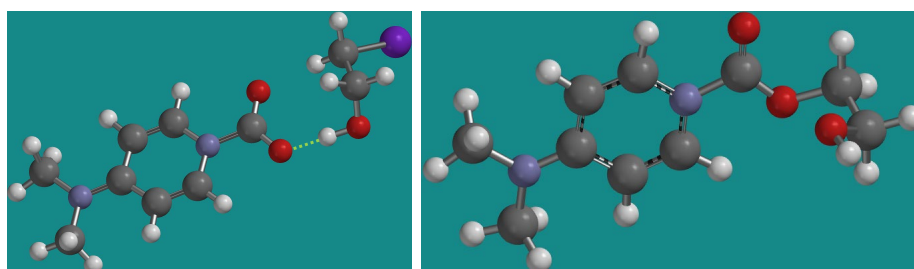


Figure 4. Energy-minimized DFT calculation structures: Left (**II** and iodoethanol complex) and right (**III**). A dashed line shows an explicit H-bond between alcohol and carboxylate functional group of **II**.

2.6. Practical Applicability

Interestingly, the catalytic efficiency of DMAP·HI was hardly affected by the environmental moisture and it was still active with 10 mol % water addition and did not show any significant loss of the catalytic activity (Figure 5A). Therefore, the organic catalyst system is promising for practical application even in the presence of ambient moisture existing as a common pollutant in waste CO₂. We also tested the reusability of the organic catalyst, since DMAP·HI is a very stable chemical species. After the first cycle, the ionic catalyst was extracted from the reaction mixture by adding water and dried over by evaporation of the aqueous layer. The resulting solid was reused directly for the next run. The catalytic activity of DMAP·HI did not change notably and gave a yield of more than 90% even after recycling five times, showing the robust stability of the DMAP·HI system (Figure 5B).

Moreover, the catalyst was applied in a scale-up reaction. A multigram scale of neat styrene oxide (5.7 mL, 6.0 g) was incubated in the presence of 10 mol% DMAP-HI at 40 °C under 1 atm CO₂ to afford 8.0 g of the cyclic carbonate (98% yield) by selective removal of DMAP-HI through extraction. Further column chromatographic purification yielded 7.7g (94%) of cyclic carbonate in an analytically pure form (Figure 5C).

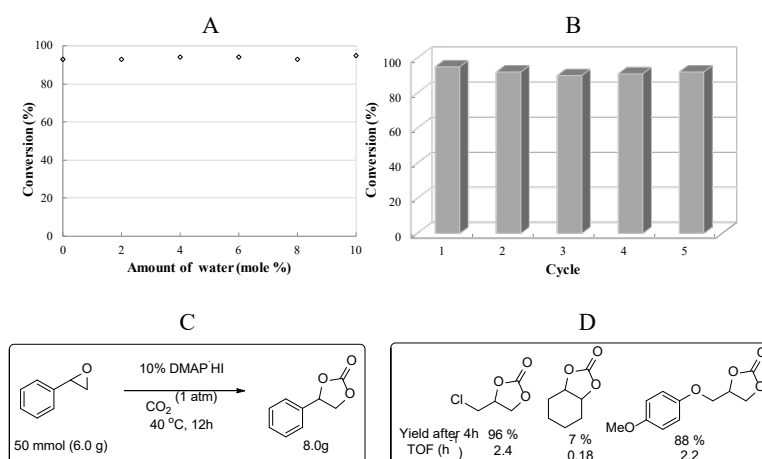


Figure 5. Cyclic carbonate formation of styrene oxide in the presence of DMAP·HI (10 mol %) under 1 atm CO₂ at 40 °C. (A) Effect of water on catalytic activity, (B) reusability of the catalyst, (C) scale-up and (D) substrate scope.

For the substrate scope, several alkyl substituted epoxides were investigated for the carbonate formation reaction under the similar conditions (Figure 5D). In general, the terminal alkyl epoxides underwent faster reactions with better efficiency than styrene oxide, probably due to the anchimeric effect of neighboring heteroatoms. Cyclic carbonates from epichlorohydrin and allyloxypropylene oxide efficiently formed in 96% and 88% yields, respectively. However, as an internal epoxide, cyclohexane oxide did not proceed effectively due to the steric and 1,3-diaxial repulsion. [25]

3. Materials and Methods

Typical reaction condition of epoxide with CO₂: DMAP (0.061 g, 0.50 mmol), and HI (0.112 g, 57%, 0.50 mmol) were dissolved in 5 mL vial to afford DMAP·HI as an ionic liquid catalyst. After epoxide (5.0 mmol) was added, the reaction mixture was stirred under 1 atm CO₂ pressurized reactor for accurate and closed reaction. After 12 h at 40 °C, the sample was analyzed by ¹H NMR spectroscopy to determine the yield.

4. Conclusions

A series of pyridinium iodide-based catalysts were investigated as green and sustainable organic catalysts for carbon dioxide utilization under ambient conditions. DMAP·HI was found to be a superior catalyst for cyclic carbonate formation, with an excellent yield and high efficiency (96%, TOF 0.80 h⁻¹) at a mild temperature without any solvents or additives. Elaborative mechanistic studies indicated that DMAP played a pivotal role as a nucleophile toward carbon dioxide during the cyclic carbonate formation. The organic catalyst could be recycled five times without any significant loss of catalytic activity, and was successfully applied for the multi-gram scale of cyclic carbonate synthesis under ambient conditions even in the presence of moisture.

Author Contributions: “Conceptualization and methodology, H.-J.K.; formal analysis and investigation, J.-H.D. and W.L.; writing—original draft preparation, J.-H.D. and W.L.; writing—review and editing, H.-J.K.; funding acquisition, H.-J.K. All authors have read and agreed to the published version of the manuscript.” Please turn to the [CRediT taxonomy](#) for the term explanation. Authorship must be limited to those who have contributed substantially to the work reported.

Funding: “This research was funded by the National Research Foundation of Korea, grant number 2017R1A2B4006706”.

Conflicts of Interest: The authors declare no conflicts of interest.

Abbreviations

The following abbreviations are used in this manuscript:

| | |
|------|--|
| CCU | Carbon dioxide capture and utilization |
| DMAP | Dimethylaminopyridine |
| NMR | Nuclear magnetic resonance |

References

1. IPCC Fourth Assessment Report: Climate Change 2007, Cambridge University Press, Cambridge, 2007.
2. Karl, T. R.; Trenberth, K. E. Modern Global Change. *Science*, **2003**, *302*, 1719–1723.
3. Lu, A. H.; Dai, S. (Eds.), *Porous Materials for Carbon Dioxide Capture*, Springer-Verlag, Berlin, 2014.
4. Sumida, K.; Rogow, D. L.; Mason, J. A.; McDonald, T. M.; Bloch, E. D.; Herm, Z. R.; Bae, T.-H.; Long, J. R. Carbon dioxide capture in metal-organic frameworks. *Chem. Rev.*, **2012**, *112*, 724–781.

5. Walton, K. S.; Millward, A. R.; Dubbeldam, D.; Frost, H.; Low, J. J.; Yaghi, O. M.; Snurr, R. Q. Understanding inflections and steps in carbon dioxide adsorption isotherms in metal-organic frameworks. *J. Am. Chem. Soc.*, **2008**, *130*, 406–407.
6. Choi, W.; Min, K.; Kim, C.; Ko, Y. S.; Jeon, J. W.; Seo, H.; Park, Y.-K.; Choi, M. Epoxide-functionalization of polyethyleneimine for synthesis of stable carbon dioxide adsorbent in temperature swing adsorption. *Nat. Commun.*, **2016**, *7*, 12640.
7. McDonald, T. M.; Long, J. R. et al. Cooperative insertion of CO₂ in diamine-appended metal-organic frameworks. *Nature*, **2015**, *519*, 303–308.
8. Goeppert, A.; Czaun, M.; May, R. B.; Prakash, G. K. S.; Olah, G. A.; Narayanan, S. R. Carbon dioxide capture from the air using a polyamine based regenerable solid adsorbent. *J. Am. Chem. Soc.*, **2011**, *133*, 20164–20167.
9. Kim, S. H.; Kim, K. H.; Hong, S. H. Carbon Dioxide Capture and Use: Organic Synthesis Using Carbon Dioxide from Exhaust Gas. *Angew. Chem. Int. Ed.*, **2014**, *53*, 771–774.
10. Bruneau, C.; Dixneuf, P. H. Catalytic incorporation of CO₂ into organic substrates: Synthesis of unsaturated carbamates, carbonates and ureas. *J. Mol. Catal.*, **1992**, *74*, 97–107.
11. Liu, Q.; Wa, L.; Jackstell, R.; Beller, M. Using carbon dioxide as a building block in organic synthesis. *Nat. Commun.*, **2015**, *6*, 5953.
12. Sujith, S.; Min, J. K.; Seong, J. E.; Na, S. J.; Lee, B. Y. A highly active and recyclable catalytic system for CO₂/propylene oxide copolymerization. *Angew. Chem. Int. Ed.*, **2008**, *47*, 7306–7309.
13. North, M.; Pasquale, R. Mechanism of cyclic carbonate synthesis from epoxides and CO₂. *Angew. Chem. Int. Ed.*, **2009**, *48*, 2946–2948.
14. Decortes, A.; Kleij, A. W. Ambient Fixation of Carbon Dioxide using a Zn(II)-salphen Catalyst. *ChemCatChem*, **2011**, *3*, 831–834.
15. Kumatabara, Y.; Okada, M.; Shirakawa, S. Triethylamine Hydroiodide as a Simple Yet Effective Bifunctional Catalyst for CO₂ Fixation Reactions with Epoxides under Mild Conditions. *ACS Sustainable Chem. Eng.*, **2017**, *5*, 7295–7301.
16. Hu, J.; Ma, J.; Liu, H.; Qian, Q.; Xie, C.; Han, B. Dual-ionic liquid system: an efficient catalyst for chemical fixation of CO₂ to cyclic carbonates under mild conditions. *Green Chem.*, **2018**, *20*, 2990–2994.
17. Zhang, Z.; Fan, F.; Xing, H.; Yang, Q.; Bao, Z.; Ren, Q. Efficient Synthesis of Cyclic Carbonates from Atmospheric CO₂ Using a Positive Charge Delocalized Ionic Liquid Catalyst. *ACS Sustainable Chem. Eng.*, **2017**, *5*, 2841–2846.
18. Clayden, J.; Greeves, N.; Warren, S. *Organic Chemistry*, 2nd ed.; Oxford: New York, USA, 2012; pp. 198–200.
19. Cheng, W.; Su, Q.; Wang, J.; Sun, J.; Ng, F.T.T. Ionic Liquids: The Synergistic Catalytic Effect in the Synthesis of Cyclic Carbonates. *Catalysts*, **2013**, *3*, 878–901.
20. Ma, J.; Song, J. L.; Liu, H. Z.; Liu, J. L.; Zhang, Z. F.; Jiang, T.; Fan, H. L.; Han, B. X. One-pot conversion of CO₂ and glycerol to value-added products using propylene oxide as the coupling agent. *Green Chem.*, **2012**, *14*, 1743–1748.
21. Jencks W. P.; Regenstein, J. *Handbook of Biochemistry and Molecular Biology*, 4th Ed. 2010.
22. Bordwell, F. G. Equilibrium acidities in dimethyl sulfoxide solution. *Acc. Chem. Res.*, **1988**, *21*, 456–463.
23. The role of pyridine as a base was excluded because we observed the reaction rate of 2,5-dimethylpyridien (lutidine, pK_a 6.77) was much slower than those of 2-methyl (2-picoline, pK_a 5.97) or 4-methylpyrdine (4-picoline, pK_a 6.02). Lutidine (3.5%), 2-picoline (35%), and 4-picoline (89%).
24. Clayden, J.; Greeves, N.; Warren, S. *Organic Chemistry*, 2nd ed.; Oxford: New York, USA, 2012; pp. 810–814.
25. Clayden, J.; Greeves, N.; Warren, S. *Organic Chemistry*, 2nd ed.; Oxford: New York, USA, 2012; pp. 869–870.

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.