

Article

Not peer-reviewed version

Kinetic Insights into the Antioxidant Effect of Isatin-Thiosemicarbazone in Biodiesel Blends

[Nalan Turkoz Karakullukcu](#)*, [Halit Muglu](#), [Hasan Yakan](#), [Volkan Murat Yilmaz](#), Sarmad Marah, [Ikbai Agah Ince](#)

Posted Date: 27 June 2024

doi: 10.20944/preprints202406.0056.v2

Keywords: thiosemicarbazones; biodiesel; oxidative stability; kinetic study; energy



Preprints.org is a free multidiscipline platform providing preprint service that is dedicated to making early versions of research outputs permanently available and citable. Preprints posted at Preprints.org appear in Web of Science, Crossref, Google Scholar, Scilit, Europe PMC.

Copyright: This is an open access article distributed under the Creative Commons Attribution License which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Article

Kinetic Insights into the Antioxidant Effect of Isatin-Thiosemicarbazone in Biodiesel Blends

Nalan Türköz Karakullukçu ^{1,*}, Halit Muğlu ², Hasan Yakan ³, Volkan Murat Yılmaz ⁴, Sarmad Marah ⁵ and İkbâl Agah İnce ⁶

¹ Karadeniz Advanced Technology Research and Application Center, Ondokuz Mayıs University, 55200, Atakum, Samsun, Türkiye

² Department of Chemistry, Faculty Science, Kastamonu University, 37150, Kastamonu, Türkiye

³ Department of Chemistry Education, Faculty of Education, Ondokuz Mayıs University, 55200, Atakum, Samsun, Türkiye

⁴ Central Research Laboratory, Bartın University, 74100, Bartın, Türkiye

⁵ Department of Chemistry, Faculty of Science, Ondokuz Mayıs University, 55200, Atakum, Samsun, Türkiye

⁶ Department of Medical Microbiology, School of Medicine, Acibadem Mehmet, Ali Aydınlar University, 34752 Atasehir, Istanbul, Türkiye

* Correspondence: nturkoz@omu.edu.tr; Tel.: +90-535-7928967

Abstract: Biodiesel has several drawbacks, such as being prone to oxidation, having reduced stability, and having limited storage time. Antioxidants compatible with biodiesel are being used to address its drawbacks. Utilizing antioxidants effectively improves the quality of biodiesel. Enhancing the quality of biodiesel for use as a clean energy source benefits both the global economy and ecology. Therefore, we believe that our work will contribute to the advancement of the worldwide industry. The study used blends consisting of 20% biodiesel and 80% diesel fuel. Isatin-thiosemicarbazones were tested as additives in blends at a concentration of 3000 parts per million (ppm) using an oxifast device. Comparing them to the chemical antioxidant Trolox. FT-IR, DSC, and TGA were used to characterize these samples. DSC measured sample crystallization temperatures (T_c). Samples with antioxidants showed decreased values compared to the non-antioxidant diesel sample D100. Several DSC tests were conducted to determine the antioxidant strengths of various samples. The results showed that the FT-IR spectrum's antioxidant effect regions grow clearer with antioxidants. The extra antioxidant is effective. Biodiesel's oxidative stability improves with isatin-thiosemicarbazones at varying concentrations. The kinetics of thermal decomposition of isatin-thiosemicarbazones under non-isothermal conditions have been determined using the Kissinger, Ozawa, and Boswell techniques. The activation energies of compounds **1** and **2** were calculated 137–147 kJ mol⁻¹ and 173–183 kJ mol⁻¹, respectively.

Keywords: thiosemicarbazones; biodiesel; oxidative stability; kinetic study; energy

1. Introduction

Antioxidants are a group of molecules that effectively halt the process of oxidation. In order to effectively manage the oxidation of biodiesel, one method employed is the inhibition of free radical formation or the scavenging of existing radicals [1]. Antioxidants are commonly composed of phenolic functional groups within their chemical structure [2]. In recent studies, it has been discovered that the addition of both natural and synthetic antioxidants to biodiesel is crucial for improving and maximizing its oxidative stability. The significance of reducing the amount of free radicals in biodiesel and delaying oxidation is highlighted by the use of antioxidants [3]. The auto-oxidation mechanism involves the interruption of the peroxide radical (ROO·) progression by the antioxidant (AH), which inhibits the creation of an additional radical. The oxidation stability of

biodiesel can be improved by incorporating antioxidants in specific proportions. This addition serves to prevent the occurrence of oxidative reactions with antioxidant radicals [4]. The addition of antioxidants to biodiesel has been found to significantly improve its overall quality, extend its storage time, and enhance its durability [5].


The prediction indicates that there will be an increase in the utilization of fossil fuels to meet the growing energy demands. In recent years, there has been a growing body of research dedicated to exploring alternative fuel sources as a response to the detrimental effects of fossil resource consumption on environmental contamination [6]. The utilization of biodiesel offers a wide range of advantages. The non-toxic nature of this specific characteristic provides both safety and cost-effectiveness, making it a significant advantage [7]. The production of biodiesel is a complex process that involves several chemical reactions. These reactions lead to the formation of free radicals, which are highly reactive molecules that can easily undergo oxidation when exposed to the surrounding atmosphere [8]. In a study conducted, it was shown that the oxidation process has a negative impact on both fuel efficiency and engine performance [9]. The storage stability of biodiesel is crucial in assessing its overall quality. The significance of standards and fuel quality cannot be overstated [10]. The study of heterocyclic Schiff bases and their metallic complexes is of significant interest in the fields of chemistry, biology, and pharmacology [11,12]. These compounds are formed through the primary amino groups of ketones or the condensation reaction of aldehydes [11,13]. They exhibit various biological functions, including antioxidant [14], antifungal [14], antitumor [15], anticancer [16], antiviral [17], antimicrobial [18], and antimalarial properties [19]. Phenolic Schiff bases (SB-OH) exhibit antioxidant activity that is directly linked to their capacity to release hydrogen atoms [20]. Schiff bases have the potential to enhance the quality of biodiesel-diesel blends through two distinct mechanisms. Firstly, they can form complexes with metal ions, effectively deactivating them. Secondly, they can trap radicals present in biodiesel-diesel blends, thereby interrupting the chain reaction of radical reactions. Schiff bases are prone to undergo reactions due to the presence of a nitrogen atom in the azomethine group. The nitrogen atom is in the sp^2 hybrid orbital and possesses a lone electron pair [21]. Schiff bases have gained considerable prominence in the academic world due to their exceptional chelating powers. Trace amounts of some metals in diesel fuel have been seen to act as catalysts, accelerating the reactions related to fuel instability. Metal deactivators work by forming chelates with metals, which efficiently deactivate their catalytic activity [22,23].

Furthermore, the presence of Schiff bases in biodiesel can efficiently regulate the oxidation process by either preventing the generation of free radicals or scavenging existing radicals, even in low concentrations. Antioxidants often contain phenolic functional groups in their chemical composition. There has been a notable decrease in the breakdown of biodiesel. The use of antioxidants highlights the significance of reducing the presence of free radicals in biodiesel and extending the oxidation process. Phenolic antioxidants (AH) are commonly used as scavengers of free radicals because of their beneficial characteristics [24,25].


Phenolic compounds commonly exhibit the ability to scavenge free radicals. The antioxidative activity of phenolic Schiff bases (SB-OH) is strongly linked to their ability to release hydrogen atoms. Several techniques can be employed to eliminate free radicals, such as hydrogen atom transfer (HAT), single electron transfer followed by proton transfer (SET-PT), and sequential proton loss electron transfer (SPLET). Each of these procedures yields the identical result, namely the production of the suitable phenoxy radical. The hydrogen atom transfer (HAT) process is defined by a solitary step in which a hydrogen atom undergoes conversion into a free radical. As given in Reaction 1.



The SET-PT and SPLET mechanisms consist of a two-step procedure. The SET-PT process starts with the electron loss, leading to the formation of a radical cation. Afterwards, in the second stage, the radical cation experiences deprotonation, resulting in the creation of the matching radical. As given in Reaction 2.

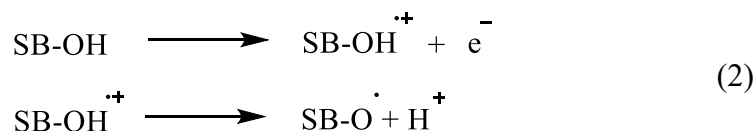

The first stage in the SPLET process involves the removal of a proton from the parent molecule. In the second step, the anion experiences electron loss, leading to the creation of a corresponding radical. As given in Reaction 3 [20–22].

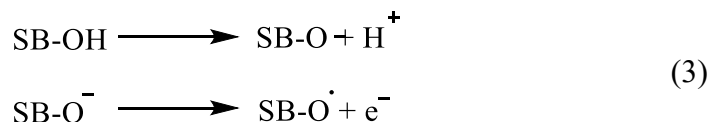

Thiosemicarbazones are a notable category of synthetic chemicals that exhibit a diverse range of pharmacological and biological activities [26]. A diverse range of actions have been disclosed, including anti-HIV [27], anticancer [28], antimalarial [29], anticonvulsant [30], anti-inflammatory [31], antioxidant [32], anti-viral [33], enzymatic inhibition [34], antifungal [35], and antibacterial [36] properties. Isatin derivatives have demonstrated a wide range of biological activities, including antioxidant [37], antiviral [38], antifungal [39], antibacterial [40], antimicrobial [41], anti-HIV [27], antitubercular [42], and anticonvulsant [43] properties. In this study, two previously synthesized isatin-thiosemicarbazones were used, whose chemical structures were elucidated by spectroscopic methods. Schiff bases have potent antioxidant and metal-chelating effects. Schiff base-based isatin-thiosemicarbazone derivatives have been preferred as substitutes for organic and synthetic antioxidants due to their ability to counteract radical reactions in biodiesel-diesel fuel mixes [21]. Using a comparative analysis with Trolox, the antioxidant capacity of the compounds employed was confirmed [44]. Trolox facilitates high-throughput screening for putative antioxidant capacity [45]. These approaches are employed to evaluate the antioxidant capacity of biological samples such as plasma, individual chemicals, dietary components, or food extracts [40,41]. But it is believed that this synthetic antioxidant variant possesses hazardous and carcinogenic properties. Isatin-thiosemicarbazone derivatives were added, and a concentration of 3000 parts per million (ppm) was added to the mixtures. Several characterization techniques, including thermogravimetric analysis (TGA), differential scanning calorimetry (DSC), fourier-transform infrared spectroscopy (FT-IR), and the 1,1-diphenyl-2-picryl hydrazyl (DPPH) assay, were used to evaluate the antioxidant activity of isatin-thiosemicarbazone derivatives. Also, the investigation of the breakdown kinetics of isatin-thiosemicarbazone derivatives was conducted using TGA. Non-isothermal experiments are more appropriate than isothermal kinetic studies for avoiding a rapid increase in temperature in the sample at the start. Conventional techniques that include fitting experimental data to the reaction model are not effective in providing accurate kinetic information for non-isothermal research. This is because these approaches fail to properly differentiate between the reaction model, $f(\alpha)$, and the temperature dependency, $k(T)$. To address this drawback of model fitting, one might employ model-free isoconversional approaches. These approaches enable the determination of the activation energy based on conversion or temperature without making any assumptions about the reaction model [46].

2. Materials and Methods

2.1. Materials

Compounds from recognized suppliers such as Merck, Sigma, or Aldrich Chemical Company were used without further purification in their as-received form. Methods used to characterize the obtained Schiff bases: The solvent used was of spectroscopic quality. An elemental analysis was conducted using a CHNS-932 (LECO) instrument. The Bruker Alpha FT-IR spectrometer was used to record infrared spectra. The JEOL ECX-400 (400 MHz) spectrophotometer was used to obtain ^1H NMR and ^{13}C NMR spectra in $\text{DMSO}-d_6$. The melting points were determined with a Gallenkamp

melting point equipment. Thermal investigations of isatin-thiosemicarbazone compounds were carried out utilizing a Hitachi STA 7300 Thermogravimetric Analyzer (TGA).

Methods used to measure the ability of the resulting mixtures to exhibit antioxidant activity:

The thermogravimetric analysis (TGA) was performed using SDTQ 600, while the differential scanning calorimetry (DSC) was conducted using DSCQ 2000. Fourier-transform infrared spectroscopy (FT-IR) was carried out using ATR-FTIR (Perkin Elmer, Spectrum-Two, USA).

Diesel fuel (D100) was given to OPET in Samsun, Turkiye, while biodiesel (B100), made totally of waste sunflower and corn oil, was given to Aves Energy Oil and Food Industry in Mersin, Turkiye.

2.2. Methods

2.2.1. Schiff Based Isatin-Thiosemicarbazones Synthesis

The configuration of the substituents in the thiocarbohydrazone is vital in defining its antioxidant activity, much to the role of the substituents in the carbohydrazone structure [47]. A previous work done by Kiran et al. [48] found that the presence of halogen-bonded aromatic structures in novel bis-isatin carbohydrazone derivatives was responsible for the antioxidant activity. The isatin-thiosemicarbazones chosen for study were produced by reacting 5-methoxyisatin with thiosemicarbazides in a mixture of aqueous ethanol and one drop of hydrochloric acid. The reaction was carried out at reflux for a duration of three hours (Figure 1). The synthesis and characterization of the compounds have been performed previously by Muglu [49]. IR, ¹H NMR, and ¹³C NMR data as well as elemental analysis were utilized to confirm the chemical structures of products. Physical data, melting points, and yields of the compounds are summarized in Table 1.

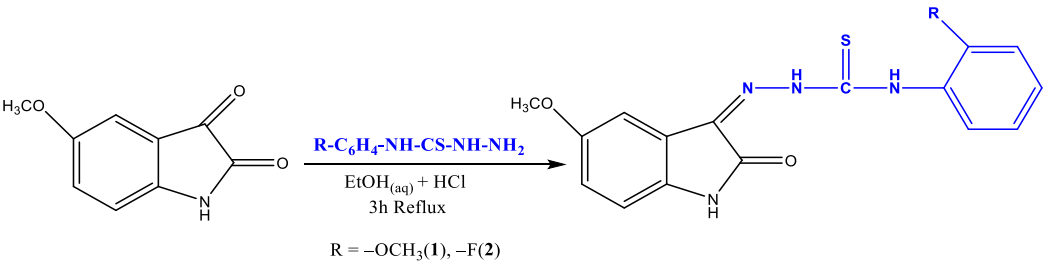


Figure 1. Synthetic route for Schiff bases based on isatin-thiosemicarbazones (1-2).

Table 1. Physical data of the synthesized compounds (1-2).

Compound code	R	Molecular formula	Molecular weight	Melting point (°C)	Yield %
1	2-OCH ₃	C ₁₇ H ₁₆ N ₄ O ₃ S	356.41	218–220	87
2	2-F	C ₁₆ H ₁₃ FN ₄ O ₂ S	344.37	234–235	82

N⁴-2-methoxyphenyl-5-methoxyisatin-β-thiosemicarbazone (**1**) Yield: 87%, m.p.: 218–220 °C, IR (KBr, cm⁻¹): ν(-NH ist) 3207, ν(-C=N-NH and -NH-Ar carbazide) 3137, 3092, ν(Ar C-H) 3043–2995, ν(C=O) 1687, ν(C=N) 1544, ν(C=S) 1487, ν(C-N) 1182; ¹H NMR (400 MHz, DMSO-d₆) δ/ppm: 12.71 (s, NH ist), 11.01 (s, NH), 10.39 (s, NH), 7.67–7.65 (d, 1H, J = 7.9 Hz), 7.28–7.23 (m, 2H, ArH), 7.10–7.08 (d, 1H, J = 7.9 Hz), 6.98–6.94 (t, 1H, J = 7.6 Hz), 6.92–6.89 (dd, 1H, J = 8.5, 2.4 Hz, ArH), 6.83–6.81 (d, 1H, J = 8.5 Hz, ArH), 3.79 (s, 3H, OCH₃), 3.71 (s, 3H, OCH₃); ¹³C NMR (100 MHz, DMSO-d₆) δ/ppm: 177.07 (C=S), 163.24 (C=O), 155.84 (C-O), 153.90 (C-O), 136.79 (C=N), 132.97, 128.35, 127.55, 127.51, 121.13, 120.65, 118.15, 112.47, 112.34, 106.65, 56.28 (OCH₃), 56.08 (OCH₃); Elemental Analysis Calcd: C, 57.29; H, 4.53; N, 15.72. Found: C, 56.84; H, 4.61; N, 15.34.

N⁴-2-fluorophenyl-5-methoxyisatin-β-thiosemicarbazone (**2**) Yield: 82%, m.p.: 234–235 °C, IR (KBr, cm⁻¹): ν(-NH ist) 3309, ν(-C=N-NH and -NH-Ar carbazide) 3147, 3096, ν(Ar C-H) 3040–3005,

$\nu(\text{C=O})$ 1686, $\nu(\text{C=N})$ 1536, $\nu(\text{C=S})$, 1479, $\nu(\text{C-N})$ 1193, $\nu(\text{C-F})$ 906; ^1H NMR (400 MHz, DMSO- d_6) δ/ppm : 12.81 (s, NH ist), 11.02 (s, NH), 10.64 (s, NH), 7.47–7.43 (t, 1H, $J = 7.3$ Hz), 7.39–7.34 (m, 1H, ArH), 7.32–7.30 (d, 2H, $J = 7.9$ Hz), 7.27–7.21 (m, 1H, $J = 7.7$ Hz, ArH), 6.92–6.89 (dd, 1H, $J = 8.5, 2.4$ Hz, ArH), 6.83–6.81 (d, 1H, $J = 8.5$ Hz, ArH), 3.71 (s, 3H, OCH_3); ^{13}C NMR (100 MHz, DMSO- d_6) δ/ppm : 178.54, 163.29, 159.11, 156.64, 155.86, 136.82, 133.51, 130.80, 129.74, 129.66, 126.98, 126.86, 124.99, 124.96, 121.27, 121.16, 118.23, 116.65, 116.45, 112.47, 106.91, 56.11; Elemental Analysis Calcd: C, 55.81; H, 3.81; N, 16.27. Found: C, 55.44; H, 3.79; N, 16.05.

2.2.2. Preparations of Biodiesel-Diesel Blends

In diesel and biodiesel blends, the ratio of biodiesel to diesel typically ranges from 20% to 80%. The formula B20D80 represents the mixture under blend [43]. A recent study carefully blended the additives, Trolox, **2**, and **1**, involved in biodiesel, at a concentration of 3000 ppm. This concentration was chosen to ensure optimal effectiveness and maximize the potential benefits of the combined extracts. It is aimed at investigating the potential synergistic effects that could arise from this combination, as each plant extract may possess unique bioactive compounds [44]. To fully understand the implications and potential applications of Table 2, further research is necessary. Various sample codes and content were presented.

The ratio of biodiesel to diesel in diesel and biodiesel blends typically ranges from 20% to 80%. The mixture being blended is represented by the formula B20D80 [50]. A recent study carefully blended the additives, Trolox, **2**, and **1**, involved in biodiesel, at a concentration of 3000 ppm. . This concentration was chosen to ensure optimal effectiveness and maximize the potential benefits of the combined additives. [51]. Further research is needed to fully understand the implications and potential applications of Table 2. Various sample codes and content were presented.

Table 2. Exploring the contents and codes of blends containing biodiesel, diesel, antioxidants, and isatin-thiosemicarbazones.

Sample	Biodiesel (%)	Diesel (%)
D100	-	100
B20D80	20	80
B20D80TROLOX	20	80
B20D80_2	20	80
B20D80_1	20	80

2.2.3. Differential Scanning Calorimetry (DSC)

DSC approaches can be used to characterize, quantify, and infer the precise moment when crystallization begins in fuel samples. After taking all these factors into account, it can be concluded that the chemical exhibits traits like quick oxidation, early crystallization, and heightened susceptibility to oxidation. This decline results in a decrease in the stability of the characteristics. The primary objective of this study was to investigate the temperatures at which crystallization begins (measured in degrees Celsius) for the materials D100, B30D70, B30D70BHT, B30D70_2, and B30D70_1. The experiment was carried out with a TA Q-2000 type calorimeter equipped with an RCS90 and a cooling system. Aluminum pans were utilized for the purpose of conducting analysis. In the course of this experimental process, a sample with a weight of 5 ± 0.5 mg was carefully positioned within the pan. The cooling rate throughout the temperature range of 25°C to -90°C was determined to be 10°C per minute, while a nitrogen flow rate of 50 mL per minute was maintained [52].

2.2.4. Thermogravimetric Analysis (TGA)

TGA is commonly employed to investigate the correlation between changes in mass and temperature variations, either rising or constant, within controlled air circumstances. This analytical methodology is utilized to quantify vapors, analyze combustion reactions, examine degradation processes, and ascertain residual components in products. The TGA technique has been employed to observe the decomposition characteristics of various organic compounds and the potential improvement of their constituents. TGA was performed using a SDT Q-600 instrument manufactured by TA Instruments-Waters, located in the United States. The collection of samples was achieved by subjecting five powder samples, each weighing 5 ± 0.5 mg, to a heating process at a rate of 10°C per minute. This heating process took place in an alumina pan, and an oxygen gas flow of 50 mL per minute was maintained during the process. The temperature was increased until it reached 400°C , as documented in reference [53]. The DSC and TGA graphics were generated using the Advantage/Universal Analysis (UA) Software provided by TA Instruments-Waters.

Thermal studies of isatin-thiosemicarbazone compounds were conducted using a Hitachi STA 7300. TGA, DTG, and DTA curves were obtained by measuring the thermal behavior of 3 mg samples at a heating rate of $10^\circ\text{K min}^{-1}$. The experiment was conducted within a temperature range of $25\text{--}900^\circ\text{C}$ in a nitrogen environment with a flow rate of 100 mL min^{-1} . A crucible made of Al_2O_3 is utilized for conducting measurements [54].

2.2.5. Fourier Transform Infrared Spectroscopy (FT-IR)

FT-IR (Perkin Elmer, Spectrum-Two, USA) was used to analyze the chemical functional groups in isatin-thiosemicarbazone derivatives. The spectral region ranging from 650 to 4000 cm^{-1} was utilized for the purpose of scanning the surface of the sample. The ATR FT-IR spectra were obtained using an isothermal method at room temperature. At the beginning of our work, the background removal techniques, baseline correction, and data tune-up correction were implemented according to the procedure [55].

2.2.6. DPPH Method for Antioxidant Activity

The DPPH radical scavenging activity test was used to find out how effective the produced chemicals were as antioxidants. The free radical scavenging ability was assessed using the method of Brand-Williams et al. [56], with minor modifications. To assess antioxidant activity, the compounds were prepared in DMSO at a concentration of $250\text{ }\mu\text{M}$. The compounds were dissolved in DMSO and then diluted to five different concentrations. The concentration of DPPH in ethanol was $50\text{ }\mu\text{M}$. Different concentrations of compound solutions ($5\text{ }\mu\text{M}$, $10\text{ }\mu\text{M}$, $20\text{ }\mu\text{M}$, $50\text{ }\mu\text{M}$, and $100\text{ }\mu\text{M}$) were added to a previously prepared 5 mL DPPH solution, along with enough ethanol to make a total volume of 6 mL . The mixture was measured at 517 nm against a blank after being left for 30 minutes at room temperature in a dark room [57].

2.2.7. Kinetics of Isatin-Thiosemicarbazone Derivatives

The values of the kinetic parameters reveal certain relationships that contribute to enhanced antioxidant properties. This is attributed to the low activation energy and the appropriate conversion dependence [58]. The degradation of solids may be analyzed using a non-isothermal kinetic approach known as the model-free method. This method involves examining the temperature values associated with the reaction rate (α) in thermal analysis graphs obtained at various heating rates. Activation energies can also be calculated using this approach [59]. The thermal decomposition of isatin-thiosemicarbazone derivatives is a process that occurs in the solid state. The kinetics of this reaction may be broadly characterized by equation 4:

$$\frac{d(a)}{d(t)} = k(T) \cdot f(a) \quad (4)$$

The variables in the equation are as follows: t represents the reaction time in minutes, T represents the temperature in Kelvin, α represents the degree of conversion or reaction rates, $k(T)$ represents the rate constant that depends on temperature, and $f(\alpha)$ represents the unique reaction model. The expression for $k(T)$ can be represented using the Arrhenius equation 5:

$$k(T) = A \cdot \exp\left(\frac{-E}{RT}\right) \quad (5)$$

Where A represents the exponential factor with units of min^{-1} , R represents the gas constant with units of $8.314 \text{ J mol}^{-1} \text{ }^{\circ}\text{K}^{-1}$, and E represents the activation energy with units of J mol^{-1} . The kinetic triples, consisting of the E , A , and $f(\alpha)$ values, are used to forecast the conversion degree of a chemical given the temperature [60].

$$\ln\left(\frac{\beta}{T^2}\right) = \ln\left[\frac{E \cdot A}{R \cdot g(a)}\right] - \left(\frac{E}{R \cdot T}\right) \quad (6)$$

$$g(a) = \int_0^a f(a)^{-1} da \quad (7)$$

The activation energies for various α values may be determined by calculating the slope of the graph $\ln(\beta/T^2) - (1000/T)$ [61], using Equations (6) and (7).

$$\ln\left(\frac{\beta}{T^2}\right) = k_1 - \left(\frac{E}{R \cdot T}\right) \quad (8)$$

$$\ln\left(\frac{\beta}{T}\right) = k_2 - \left(\frac{E}{R \cdot T}\right) \quad (9)$$

$$\ln \beta = k_3 - 1,051 \frac{E}{R \cdot T} \quad (10)$$

Where k_1 , k_2 , and k_3 are fixed values. The activation energy was determined from the thermogravimetric curves using the Kissenger (Equation 8), Boswell (Equation 9), and Ozawa (Equation 10) techniques [46]. The thermogravimetric analysis tests were conducted using a Hitachi STA 7300 instrument at various heating rates ($\beta = 5, 10, 15, 20 \text{ }^{\circ}\text{K min}^{-1}$) in a N_2 environment with a flow rate of 100 mL min^{-1} . The temperature range for the studies was from ambient temperature to $1173 \text{ }^{\circ}\text{K}$.

2.2.8. Analytical Statistics

The SPSS 22.0 (Statistical Packages for the Social Sciences) package application was used to present the DPPH test findings. The Tukey HSDa, b test was used to produce a one-way ANOVA to compare the differences between the compounds. The findings were expressed as mean $\pm$ standard deviation, and $p < 0.05$ indicated statistical significance.

3. Results and Discussion

3.1. Differential Scanning Calorimetry (DSC)

DSC measurements were conducted on a blend of fuel containing isatin-thiosemicarbazone derivatives and unbleached fuel in a nitrogen gas atmosphere. The resulting data is graphically shown in Figure 2.

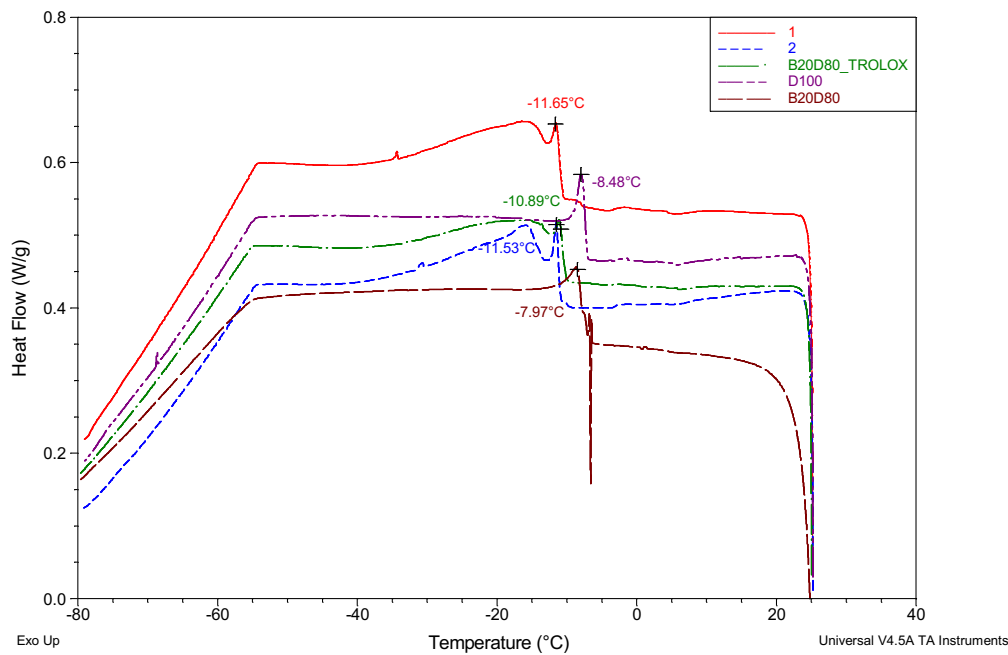


Figure 2. DSC thermograms of D100, B20D80, B20D80TROLOX, B20D80_2, and B20D80_1 under N₂ atmosphere.

The purpose of this research was to examine the effects of adding isatin-thiosemicarbazone derivatives to biodiesel-diesel blends on their crystallization temperatures. As a result, the study demonstrated that the extract derived from isatin-thiosemicarbazone derivatives had an increase in the crystallization point. This inquiry pertains to the initiation temperatures of crystallization for four distinct alloys, namely D100, B20D80, B20D80TROLOX, B20D80_2, and B20D80_1. After conducting experiments, the starting temperatures for crystallization were found to be -7.97 °C, -8.48 °C, -10.89 °C, -11.53 °C, and -11.65 °C for the samples marked D100, B20D80, B20D80TROLOX, B20D80_2, and B20D80_1, respectively. The mean onset temperature for crystallization is $x_{mean} = 10.10$. A value of 1.75 has been determined for the standard deviation, which is a common way to measure the variability of experimental measurements according to Equation (11). As shown in Table 3.

$$s^2 = \frac{\sum_{i=1}^N (xi - x_{mean})^2}{N - 1} \tag{11}$$

Table 3. Crystallization onset temperatures (°C) of D100, B20D80, B20D80TROLOX, B20D80_2, and B20D80_1 determined using DSC in a N₂ atmosphere*.

Sample	Crystallizations onset temperature (xi)(°C)	(xi - x _{mean}) ²
D100	7.97	4.55
B20D80	8.48	2.64
B20D80TROLOX	10.89	0.62
B20D80_2	11.53	2.03
B20D80_1	11.65	2.39

*Values are expressed as means (n = 2).

3.2. Thermogravimetric Analysis (TGA)

TGA is a method used to analyze the thermal and oxidative stability of a substance or combination by observing alterations in its physicochemical properties. The properties were described by how the weight changed as the temperature increased. Oxidative stability is an important quality indicator for esters. Thermogravimetric curves (TGA) display the changes in

weight as temperature varies, along with the corresponding derivative curves that indicate the rate of weight loss [62]. The compound of TGA-DTG graphs of several combinations were compared. It is observed that there is only one degree of degradation concerning temperature. The temperature at which degradation begins, known as the onset temperature, offers valuable information regarding thermal stability and the first boiling point. A positive association has been seen between the stability of the samples and the Tonset values, suggesting that an increase in sample stability is associated with a corresponding rise in Tonset values [53]. Figure 3 displays the graphical representations of the thermogravimetric analysis (TGA) and derivative thermogravimetric analysis (DrTGA) curves. Upon closer inspection, the curves are pretty like one another. At these temperatures, sample mass is lost between 98.56 and 99.36%. The values taken from the thermometers and recorded on the thermograms are listed in Table 4.

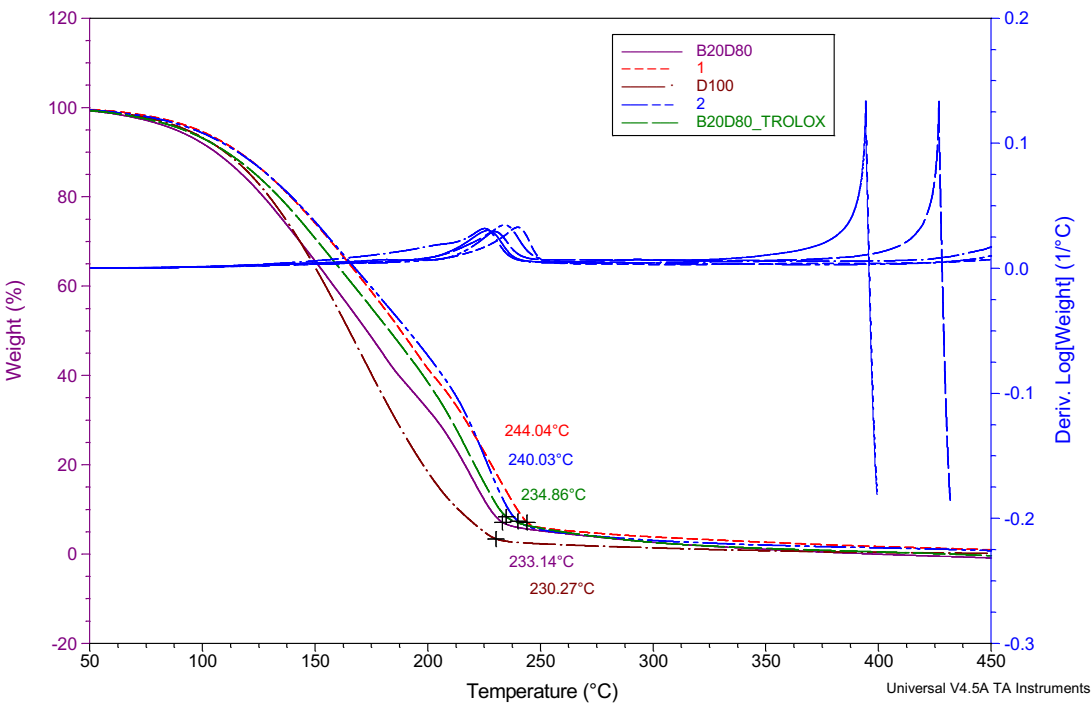


Figure 3. TGA and DrTGA curves of D100, B20D80, B20D80TROLOX, B20D80_2, and B20D80_1 under O₂ atmosphere.

The mean degradation temperature (Tonset) is $y_{mean} = 99.11$ with a standard deviation of $s = 0.32$. The mean mass loss is $z_{mean} = 9.22$ with a standard deviation of $s = 1.65$, as calculated using Equation (8). As shown in Table 4.

Table 4. Thermogravimetric analysis (TGA) of samples.

Sample name	Temperature range (°C)	Max, degradation temperature (yi) (°C) (Tonset)	$(yi - y_{mean})^2$	Mass loss (zi) (%)	$(zi - z_{mean})^2$
D100	25-250	99.36	0.06	11.52	5.29
B20D80	25-250	99.12	1.10 ⁻⁴	7.72	2.25
B20D80TROLOX	25-250	99.27	0.03	7.71	2.28
B20D80_2	25-250	99.24	0.02	8.94	0.08
B20D80_1	25-250	98.56	0.30	10.20	0.86

3.3. Fourier Transform Infrared Spectroscopy (FT-IR)

The FT-IR spectra of the biodiesel-diesel blends are depicted in Figure 4 (a–f). The impact of incorporating antioxidants at a concentration of 3000 ppm into biodiesel samples is displayed in Table 5. The valence-stretching vibration frequency range of an unbounded hydroxyl group, $\nu(\text{O-H})$, is approximately $3661\text{--}3687\text{ cm}^{-1}$. Spectral peaks in the range of $2925\text{--}3000\text{ cm}^{-1}$ are often associated with the vibration of $\nu(\text{C-H})$ bonds, indicating oxidation. Aldehyde and ketone compounds in biodiesel samples contain these bonds, which are also found in antioxidants. The spectral range of $2925\text{--}2990\text{ cm}^{-1}$ is often linked to the $\nu(\text{C-H})$ bending vibration, which is known to be involved in oxidation processes. Peaks in the 1079 cm^{-1} wavenumber indicate stretching of the $\nu(\text{C-O})$ bond. The spectrum shows strong absorption bands, indicating the presence of the ester carbonyl functional group (C=O). The absorption is observed in the spectral range of 1746 cm^{-1} . The lack of a nearby band could suggest that carboxylic acids are not present. The bending vibrations of $\nu(\text{N-H})$ are attributed to the observed vibrational modes at 1458 cm^{-1} . In isatin-thiocarbohydrazones, the bending vibrations of $\nu(\text{C-N})$ occur within the range of $1199\text{--}1173\text{ cm}^{-1}$. The long-term stability of biodiesel samples is linked to low oxidation levels [54]. Antioxidants, particularly phenolic chemicals, have been found to enhance peak intensity, according to studies.

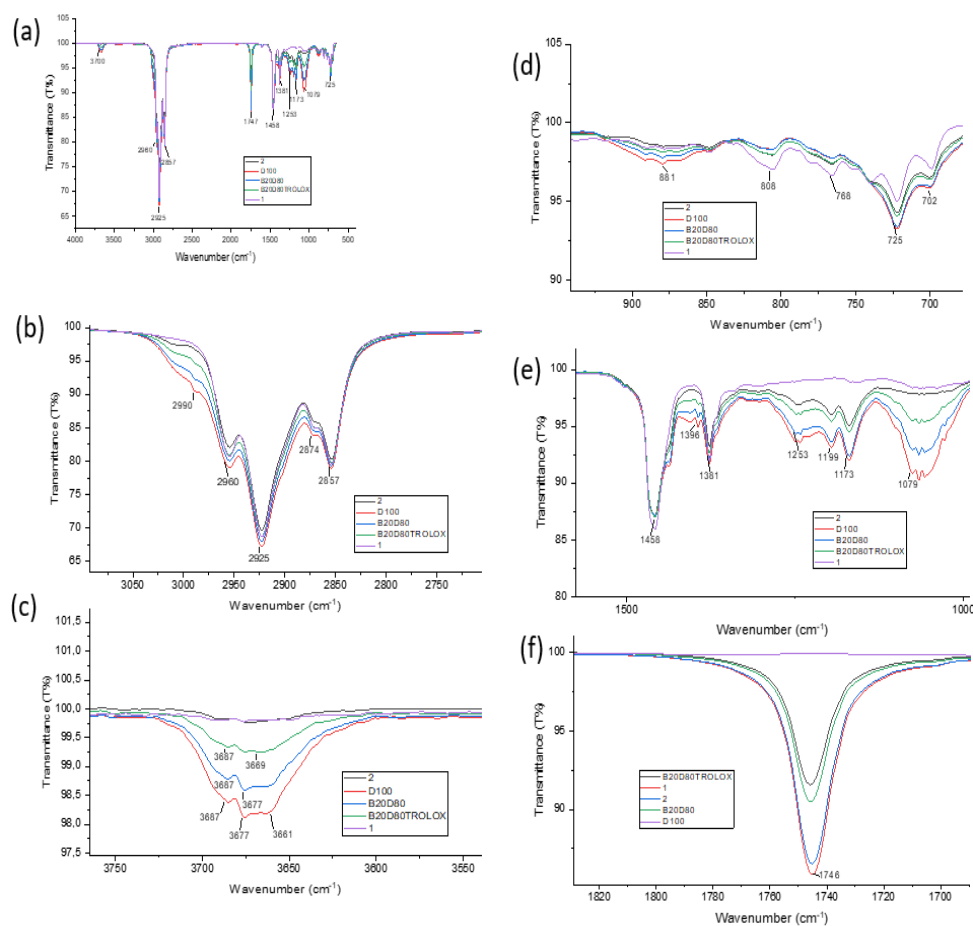


Figure 4. (a) FT-IR spectra of D100, B20D80, B20D80TROLOX, B20D80_2, and B20D80_1 at $4000\text{--}500\text{ cm}^{-1}$. (b) Antioxidant effects of D100, B20D80, B20D80TROLOX, B20D80_2, and B20D80_1 samples between wavenumbers $2750\text{ and }3050\text{ cm}^{-1}$. (c) Antioxidant effects of D100, B20D80, B20D80TROLOX, B20D80_2, and B20D80_1 samples between wavenumbers $3550\text{ and }3750\text{ cm}^{-1}$. (d) Antioxidant effects of D100, B20D80, B20D80TROLOX, B20D80_2, and B20D80_1 samples between wavenumbers $700\text{ and }900\text{ cm}^{-1}$. (e) Antioxidant effects of D100, B20D80, B20D80TROLOX, B20D80_2, and B20D80_1 samples between wavenumbers $1000\text{ and }1500\text{ cm}^{-1}$. (f) Antioxidant effects of D100, B20D80, B20D80TROLOX, B20D80_2, and B20D80_1 samples between wavenumbers $1700\text{ and }1820\text{ cm}^{-1}$.

Table 5. Experimental FT-IR values of the compounds (cm⁻¹).

Compound	ν(O–H)	ν(C–H)	ν(C–H)	ν(C=O)	ν(N–H)	ν(C–N)	ν(C–O)
		Aromatic	Aliphatic				
B20D80_2	–	2925	2874	1746	1458	1199	1079
B20D80_1	–	2925	2874	1746	1458	1173	1079
B20D80 TROLOX	3687	2925	2857	1746	–	–	1079
B20D80	3687	2925	2857	1746	–	–	1079
D100	3687	2925	2857	1746	–	–	1079

3.4. DPPH Free Radical Scavenger Effect for Isatin-Thiosemicarbazones

The study assessed the samples' capacity to eliminate free radicals. Compound **1** had more activity with a value of 66.178 ± 0.11 μM, whereas compound **2** showed lesser activity with a value of 79.927 ± 0.13 μM. The arrangement of substituents in isatin-thiocarbohydrazones plays a vital role in determining their antioxidant activity, which is comparable to that of carbohydrazones [63]. The antioxidant activity of isatin-thiosemicarbazone derivatives can be attributed to the presence of substituted groups/atoms attached to the aromatic ring in Table 6.

Table 6. Free Radical Scavenger Effect of the compounds (μM)*.

Compound	IC ₅₀ values μM
1	66.178±0.11 ^b
2	79.927±0.13 ^c
Trolox	8.757±0.07 ^a

*Values are expressed as means (n = 3).

3.5. Thermal Characterization of Isatin-Thiosemicarbazones.

Compound **1** is represented by the TGA, DTG, and DTA curves in Figure 5. The thermogravimetric (TGA) curve revealed that the thermal decomposition of compound **1** commenced at a temperature of 201 °C and exhibited two distinct stages of weight loss. The first and subsequent stages of weight loss account for 33.3% and 23.3%, respectively. The weight loss experienced from room temperature to 900 °C is precisely 69.8%. The differential thermogravimetric (DTG) curve of compound **1** exhibited two distinct peaks that corresponded to the thermogravimetric (TGA) curve. The initial stage was characterized by an exothermic peak at 213.3 °C observed in the DTA graph, indicating the melting point of the sample. The second stage was detected at a temperature of 265 °C on the DTA graph, and it manifested as an exothermic peak, indicating the thermal decomposition of compound **1**.

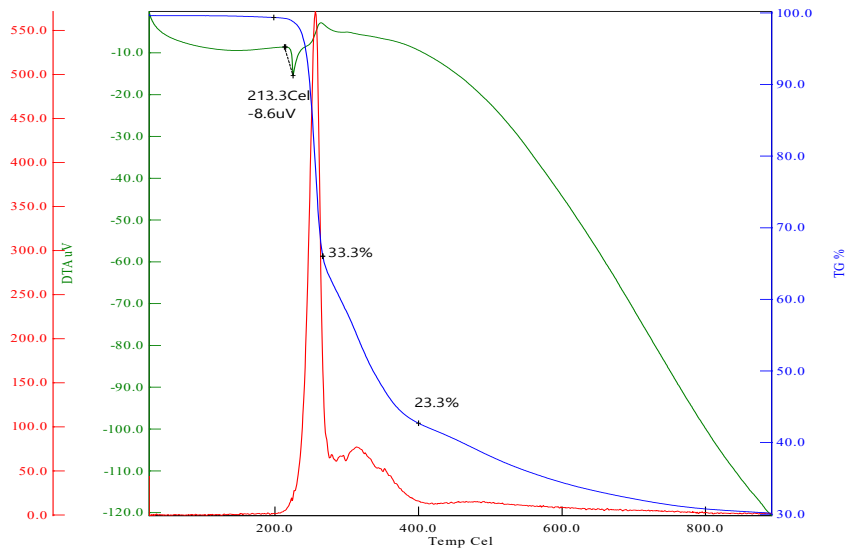


Figure 5. Studying the thermal properties of compound **1**.

Figure 6 displays the TGA, DTG, and DTA curves for compound 2. The thermogravimetric (TGA) curve indicates that the decomposition begins around 218 °C and follows a two-step process. The initial stage of weight reduction accounts for 37.3%, whereas the subsequent stage accounts for 18.5%. The weight loss experienced from a temperature of 25 °C to 900 °C amounts to 69.9%. The DTG curve of compound 2 exhibited two peaks that corresponded to the TGA curve. The initial stage is associated with the determination of the melting point, as evidenced by the presence of an endothermic peak at 243.3 °C recorded on the DTA curve. The second stage is linked to thermal deterioration, as evidenced by the exothermic peak at 267 °C observed on the DTA curve [64].

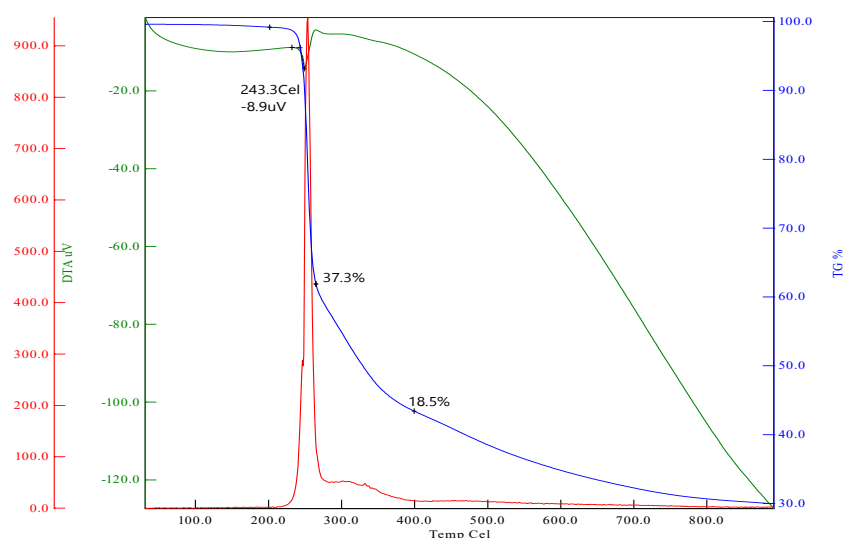


Figure 6. Studying the thermal properties of compound 2.

3.6. Investigating the Kinetics of Isatin-Thiosemicarbazones

The TGA curves of compound 1 are displayed in Figure 7, depicting four continuous heating rates: 5, 10, 15, and 20 °C min⁻¹. As the heating rate increases from 5 to 20 °C, the TGA curves exhibit a rightward shift. Additionally, the peak temperature also changes towards a higher value with an increasing heating rate. Substantial reductions in weight were seen across all measures within the temperature range of 200–400 °C. Thermal decomposition occurs within the temperature range of 200 to 400 °C. Given that this phase has also been detected in the sample and its decomposition happens within the temperature range under investigation, it unavoidably impacts the kinetic curves [60].

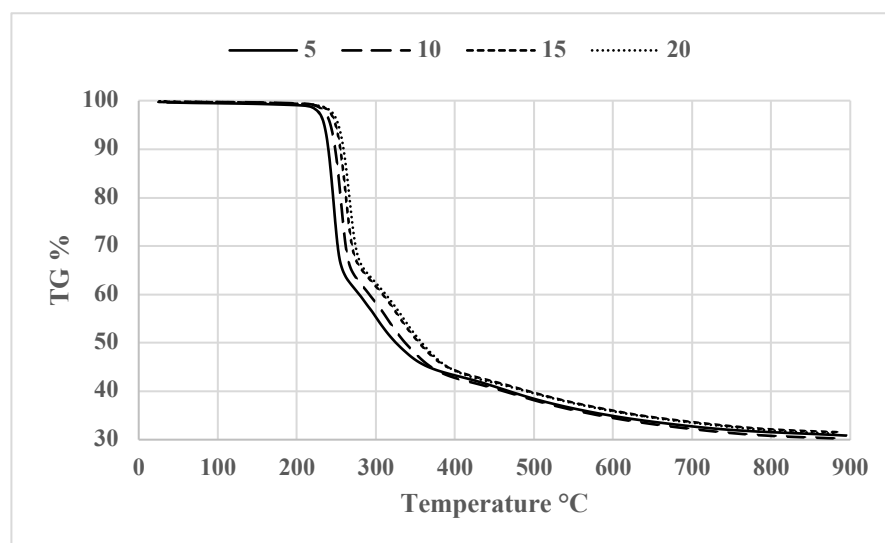


Figure 7. TGA curves of compound 1 at different heating rates.

Figure 8a depicts the temperature-response rate relationship for compound 1, as represented by the curves. Figures 8b, 8c, and 8d display the diagrams used to calculate active tion energy using the Kissinger, Ozawa, and Boswell approaches, respectively. The activation energies obtained from the three approaches exhibit a high degree of similarity. The standard deviations (s) for each individual approach, as well as for the Kissinger, Ozawa, and Boswell methods, are presented in Table 7. The activation energy values for the thermal decomposition process were determined using three different methods: the Kissinger approach yielded a value of 137.60 kJ mol⁻¹, the Ozawa method yielded a value of 146.58 kJ mol⁻¹, and the Boswell technique yielded a value of 142.09 kJ mol⁻¹. These calculations were performed under non-isothermal circumstances. Based on these results, it can be concluded that the activation energy needed for the decomposition of compound 1 falls within the range of 137–147 kJ mol⁻¹.

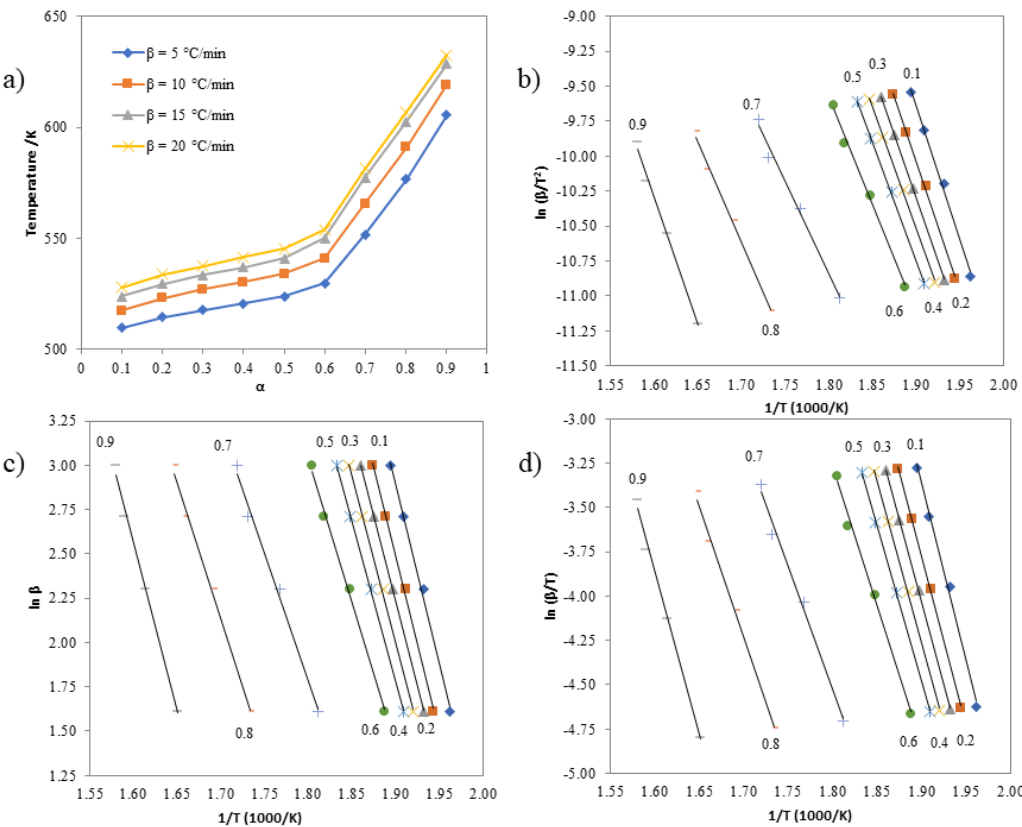


Figure 8. (a) Relationship between α and thermal decomposition temperature of the compound 1 at different heating rates, and Arrhenius plots for (b) Kissinger (c) Ozawa (d) Boswell methods.

Table 7. Calculating the relationship between activation energy values and $-\alpha$ using three methods for compound 1*.

α	Activation Energies (kJ mol ⁻¹)			The standard deviation (s) for the Kissinger, Ozawa, and Boswell methods
	Kissinger	Ozawa	Boswell	
0.1	163.05	171.68	167.37	4.31
0.2	155.18	163.89	159.53	4.35
0.3	152.00	160.77	156.38	4.38
0.4	146.72	155.54	151.13	4.41
0.5	143.70	152.59	148.15	4.44

0.6	130.64	139.65	135.14	4.50
0.7	114.96	124.38	119.67	4.71
0.8	123.40	133.24	128.32	4.92
0.9	153.22	163.51	158.36	5.14
Standart	16.09	15.88	15.98	
Deviation (s) for Separate for each method				

*Values are expressed as means (n = 2).

Figure 9 displays the thermogravimetric (TGA) curves of compound 2 obtained under several heating rates. Figure 9 demonstrates that the TGA curves changed towards higher temperatures as the heating rates increased. The temperature- α curves for compound 2 are shown in Figure 10a. The graphs illustrating the calculation of activation energy using the Kissinger, Ozawa, and Boswell approaches are displayed in Figures 10b, 10c, and 10d, respectively. The activation energy was determined using the same methodologies for all three procedures. Table 8 displays the results and standard deviations (s) for each specific methodology, as well as for the Kissinger, Ozawa, and Boswell methodologies. The activation energies for the thermal decomposition of compound 2, as determined by the Kissinger, Ozawa, and Boswell techniques, were 173.61, 182.48, and 178.04 kJ mol⁻¹, respectively. Based on these figures, the amount of energy needed to decomposition compound 2 is between 173 and 183 kJ mol⁻¹.

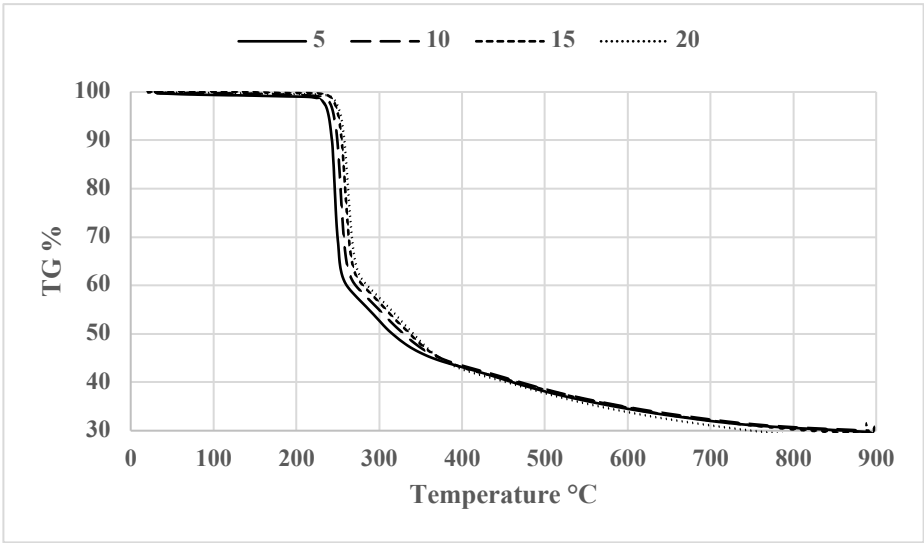


Figure 9. TGA curves of compound 2 at different heating rates.

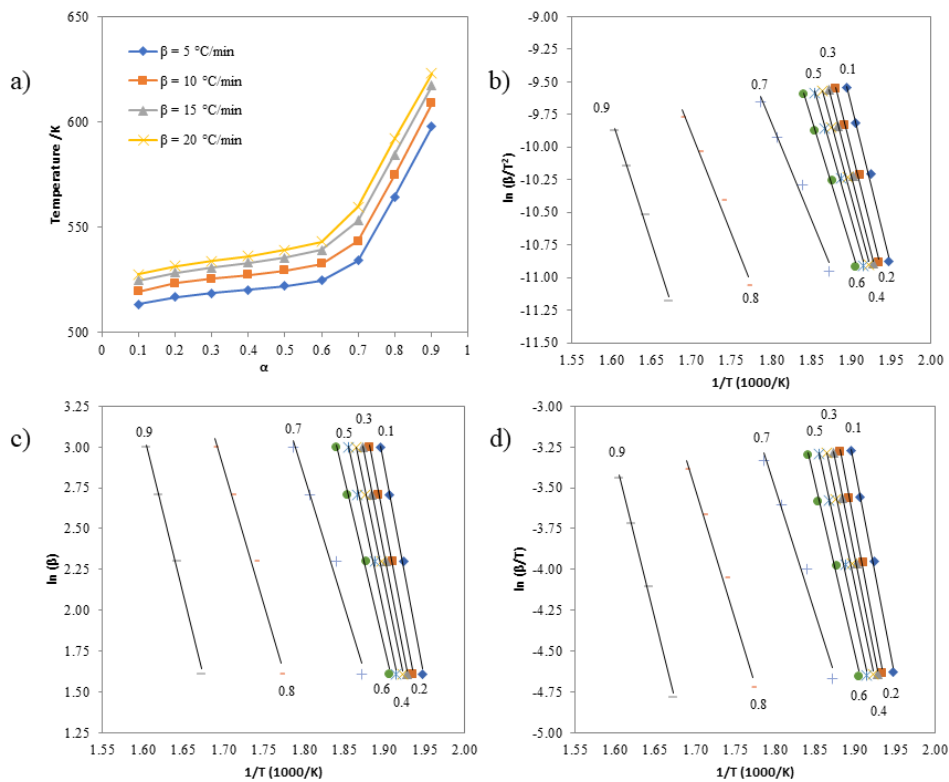


Figure 10. (a) Relationship between α and thermal decomposition temperature of the compound **2** at various heating rates, and Arrhenius plots for (b) Kissinger (c) Ozawa (d) Boswell methods.

Table 8. Calculating the relationship between activation energy values and $-\alpha$ using three methods for compound **2***.

α	Activation Energies (kJ mol ⁻¹)			The standard deviation (s) for the Kissinger, Ozawa, and Boswell methods
	Kissinger	Ozawa	Boswell	
0.1	211.74	220.40	216.07	4.33
0.2	206.48	215.19	210.83	4.35
0.3	199.63	208.38	204.01	4.37
0.4	190.60	199.38	194.99	4.39
0.5	182.53	191.35	186.94	4.41
0.6	169.41	178.29	173.85	4.44
0.7	125.89	134.98	130.44	4.54
0.8	129.56	139.17	134.36	4.80
0.9	160.42	170.57	165.49	5.07
Standart Deviation (s) for Separate for each method	31.56	31.24	31.39	

Values are expressed as means (n = 2).

The non-isothermal kinetic investigations of isatin-thiosemicarbazone derivatives revealed that the activation energy needed for the thermal decomposition of compound **1** is lower than that of

compound 2. The thermal stability of compounds is directly proportional to their activation energy; a more extensive activation energy value indicates more excellent thermal stability [57]. Based on the findings of non-isothermal decomposition kinetics, compound 2 exhibits more incredible activation energy than compound 1. Compound 2 has superior heat stability. Additionally, it is recognized that the molecule with a lower activation energy exhibits superior antioxidant capabilities [58]. Therefore, it has been verified that compound 1, which shows a greater yield, possesses superior antioxidant characteristics.

5. Conclusions

Bi-fuel is cheaper and greener than diesel. Biodiesel's instability was studied because to its significant oxidation risk. Our study results are below:

The DSC found: Natural and synthetic antioxidants heat crystallization. Many samples crystallized at -11.76–13.97 °C. Analysis at lower temperatures purifies material. Crystallization origin was dictated by temperature. A research examined samples and temps. D100 and B30D70 measured temp. B30D70 was somewhat lower than D100 at -11.76 °C at -11.87. B30D70TROLOX -12.03, B30D70_2 -12.73. The coldest sample was B30D70_1 (-13.97 °C). Results show study samples' temperatures. B30D70TROLOX, B30D70_2, and B30D70_1 crystallize below D100. Antioxidants slow oxidation. Fast oxidation, early crystallization, and high oxidation susceptibility define the material. Sequential feature stability rises. Schiff bases_1 and 2 crystallized gasoline blends 87.78% and 72.16%, respectively.

D100, B30D70, B30D70TROLOX, B30D70_2, and B30D70_1 oxidized at 25–275 °C, according to TGA. First was deterioration. Thermal dynamics causes mass loss at certain temps. Recent investigations show 98.09% to 99.44% in samples. Biodiesel-diesel samples had small Tonset discrepancies that fit curves.

Sample functional groups were identified using FT-IR. B30D70_2 and B30D70_1 contain fewer functional groups than B30D70TROLOX. This reduction was caused by 3000 ppm Schiff bases. Schiff bases increase composite oxidative stability, researchers discovered.

An DPPH free radical activity assay tested the compounds' antioxidant capabilities. The studies included spectrophotometry and scavenging. Isatin-thiosemicarbazones have free radical scavenging activity, with IC₅₀ values of 66.178 ± 0.11 µM for DPPH and 79.927 ± 0.13 µM. Compound 1 is the most antioxidant but less than Trolox. Chemical structure and behavior were explored. Study examined substituents. Isatin-thiosemicarbazones antioxidantly enhanced biodiesel, a higher-efficiency diesel. The activation energies of isatin-thiosemicarbazone derivative thermal breakdown were also assessed. We examined non-isothermal thermogravimetric (TGA) curves at 5, 10, 15, 20 °K min⁻¹. The Kissinger, Ozawa, and Boswell methods produced compounds 1 and 2 activation energies of 137–147 and 173–183 kJ mol⁻¹. Low-activation energy molecules were more antioxidant.

Author Contributions: Nalan Turkoz Karakullukcu; Formal analysis, funding acquisition, validation, writing – review & editing, investigation, resources, supervision, project administration. Halit Muğlu; Formal analysis, investigation, writing – original draft, resources, data curation. Hasan Yakan; Formal analysis, investigation, supervision, writing – original draft, data curation. Volkan Murat Yilmaz; Conceptualization, formal analysis, writing – original draft, investigation, software. Sarmad Marah; Formal analysis, data curation, writing. Ikbale Agah Ince; Formal analysis, supervision, writing – review & editing, visualization, software.

Funding: This research received no external funding.

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: Data are contained within the article.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Fang, H.L.; McCormick, R.L. Spectroscopic Study of Biodiesel Degradation Pathways. *SAE Technical Papers* **2006**, 776–790, doi:10.4271/2006-01-3300.
2. Abbas, M.; Saeed, F.; Anjum, F.M.; Afzaal, M.; Tufail, T.; Bashir, M.S.; Ishtiaq, A.; Hussain, S.; Suleria, H.A.R. Natural Polyphenols: An Overview. *International Journal of Food Properties* **2017**, *20*, 1689–1699, doi:10.1080/10942912.2016.1220393.
3. Rizwanul Fattah, I.M.; Masjuki, H.H.; Kalam, M.A.; Hazrat, M.A.; Masum, B.M.; Imtenan, S.; Ashraful, A.M. Effect of Antioxidants on Oxidation Stability of Biodiesel Derived from Vegetable and Animal Based Feedstocks. *Renewable and Sustainable Energy Reviews* **2014**, *30*, 356–370, doi:10.1016/j.rser.2013.10.026.
4. Pullen, J.; Saeed, K. An Overview of Biodiesel Oxidation Stability. *Renewable and Sustainable Energy Reviews* **2012**, *16*, 5924–5950, doi:10.1016/j.rser.2012.06.024.
5. Rashedul, H.K.; Masjuki, H.H.; Kalam, M.A.; Teoh, Y.H.; How, H.G.; Rizwanul Fattah, I.M. Effect of Antioxidant on the Oxidation Stability and Combustion-Performance-Emission Characteristics of a Diesel Engine Fueled with Diesel-Biodiesel Blend. *Energy Conversion and Management* **2015**, *106*, 849–858, doi:10.1016/j.enconman.2015.10.024.
6. Atabani, A.E.; Silitonga, A.S.; Badruddin, I.A.; Mahlia, T.M.I.; Masjuki, H.H.; Mekhilef, S. A Comprehensive Review on Biodiesel as an Alternative Energy Resource and Its Characteristics. *Renewable and Sustainable Energy Reviews* **2012**, *16*, 2070–2093, doi:10.1016/j.rser.2012.01.003.
7. Srivastava, A.; Prasad, R. Triglycerides-Based Diesel Fuels. *Renewable & sustainable energy reviews* **2000**, *4*, 111–133, doi:10.1016/S1364-0321(99)00013-1.
8. Hosseinzadeh-bandbafha, H.; Kumar, D.; Singh, B.; Shahbeig, H. Biodiesel Antioxidants and Their Impact on the Behavior of Diesel Engines : A Comprehensive Review. *Fuel Processing Technology* **2022**, *232*, 107264, doi:10.1016/j.fuproc.2022.107264.
9. Ravi Krishna, E.; Muralidhar Reddy, P.; Sarangapani, M.; Hanmanthu, G.; Geeta, B.; Shoba Rani, K.; Ravinder, V. Synthesis of N4 Donor Macrocyclic Schiff Base Ligands and Their Ru (II), Pd (II), Pt (II) Metal Complexes for Biological Studies and Catalytic Oxidation of Didanosine in Pharmaceuticals. *Spectrochimica Acta - Part A: Molecular and Biomolecular Spectroscopy* **2012**, *97*, 189–196, doi:10.1016/j.saa.2012.05.073.
10. Kumar, R.; Kumar, V.; Sham, R. Stability of Biodiesel – A Review. *Renewable and Sustainable Energy Reviews* **2016**, *62*, 866–881, doi:10.1016/j.rser.2016.05.001.
11. Uddin, M.N.; Ahmed, S.S.; Alam, S.M.R. REVIEW: Biomedical Applications of Schiff Base Metal Complexes. *Journal of Coordination Chemistry* **2020**, *73*, 3109–3149, doi:10.1080/00958972.2020.1854745.
12. Koteswara Rao, N.S.R.R.M.M.; Ram Reddy, M.G. Studies on the Synthesis, Characterisation and Antimicrobial Activity of New Co(II), Ni(II) and Zn(II) Complexes of Schiff Base Derived from Ninhydrin and Glycine. *Biology of Metals* **1990**, *3*, 19–23, doi:10.1007/BF01141172.
13. Kalem, E.; Açar, E. Schiff Bazlarınin Biyolojik Aktivitesi Biological Activity of Schiff Bases Öz : Abstract : **2021**, *8*, 57–76.
14. Chen, Y.; Mi, Y.; Li, Q.; Dong, F.; Guo, Z. Synthesis of Schiff Bases Modified Inulin Derivatives for Potential Antifungal and Antioxidant Applications. *International Journal of Biological Macromolecules* **2020**, *143*, 714–723, doi:10.1016/j.ijbiomac.2019.09.127.
15. Ren, S.; Wang, R.; Komatsu, K.; Bonaz-Krause, P.; Zyrianov, Y.; McKenna, C.E.; Csipke, C.; Tokes, Z.A.; Lien, E.J. Synthesis, Biological Evaluation, and Quantitative Structure -Activity Relationship Analysis of New Schiff Bases of Hydroxysemicarbazide as Potential Antitumor Agents. *Journal of Medicinal Chemistry* **2002**, *45*, 410–419, doi:10.1021/jm010252q.

16. Duff, B.; Reddy Thangella, V.; Creaven, B.S.; Walsh, M.; Egan, D.A. Anti-Cancer Activity and Mutagenic Potential of Novel Copper(II) Quinolinone Schiff Base Complexes in Hepatocarcinoma Cells. *European Journal of Pharmacology* **2012**, *689*, 45–55, doi:10.1016/j.ejphar.2012.06.004.
17. Jarrahpour, A.; Sheikh, J.; Mounsi, I. El; Juneja, H.; Hadda, T. Ben Computational Evaluation and Experimental in Vitro Antibacterial, Antifungal and Antiviral Activity of Bis-Schiff Bases of Isatin and Its Derivatives. *Medicinal Chemistry Research* **2013**, *22*, 1203–1211, doi:10.1007/s00044-012-0127-6.
18. Singh, K.; Raparia, S.; Surain, P. Co(II), Ni(II), Cu(II) and Zn(II) Complexes of 4-(4-Cyanobenzylideneamino)-3-Mercapto-5-Oxo-1,2,4-Triazine: Synthesis, Characterization and Biological Studies. *Medicinal Chemistry Research* **2015**, *24*, 2336–2346, doi:10.1007/s00044-014-1298-0.
19. Tople, M.S.; Patel, N.B.; Patel, P.P.; Purohit, A.C.; Ahmad, I.; Patel, H. An in Silico-in Vitro Antimalarial and Antimicrobial Investigation of Newer 7-Chloroquinoline Based Schiff-Bases. *Journal of Molecular Structure* **2023**, *1271*, 134016, doi:10.1016/j.molstruc.2022.134016.
20. Petrović, Z.D.; Orović, J.; Simijonović, D.; Petrović, V.P.; Marković, Z. Experimental and Theoretical Study of Antioxidative Properties of Some Salicylaldehyde and Vanillic Schiff Bases. *RSC Advances* **2015**, *5*, 24094–24100, doi:10.1039/c5ra02134k.
21. Marković, Z.; Đorović, J.; Petrović, Z.D.; Petrović, V.P.; Simijonović, D. Investigation of the Antioxidant and Radical Scavenging Activities of Some Phenolic Schiff Bases with Different Free Radicals. *Journal of Molecular Modeling* **2015**, *21*, doi:10.1007/s00894-015-2840-9.
22. Amić, A.; Marković, Z.; Marković, J.M.D.; Jeremić, S.; Lučić, B.; Amić, D. Free Radical Scavenging and COX-2 Inhibition by Simple Colon Metabolites of Polyphenols: A Theoretical Approach. *Computational Biology and Chemistry* **2016**, *65*, 45–53, doi:10.1016/j.compbiolchem.2016.09.013.
23. Marković, Z. Study of the Mechanisms of Antioxidative Action of Different Antioxidants. *Journal of the Serbian Society for Computational Mechanics* **2016**, *10*, 135–150, doi:10.5937/jsscm1601135M.
24. Agarwal, S.; Singhal, S.; Singh, M.; Arora, S.; Tanwer, M. Role of Antioxidants in Enhancing Oxidation Stability of Biodiesels. **2018**, doi:10.1021/acssuschemeng.8b02523.
25. Rice-Evans, C. Plant Polyphenols: Free Radical Scavengers or Chain-Breaking Antioxidants? *Biochemical Society symposium* **1995**, *61*, 103–116, doi:10.1042/bss0610103.
26. Bharti, S.K.; Nath, G.; Tilak, R.; Singh, S.K. Synthesis, Anti-Bacterial and Anti-Fungal Activities of Some Novel Schiff Bases Containing 2,4-Disubstituted Thiazole Ring. *European Journal of Medicinal Chemistry* **2010**, *45*, 651–660, doi:10.1016/j.ejmech.2009.11.008.
27. Bal, T.R.; Anand, B.; Yogeewari, P.; Sriram, D. Synthesis and Evaluation of Anti-HIV Activity of Isatin β -Thiosemicarbazone Derivatives. *Bioorganic and Medicinal Chemistry Letters* **2005**, *15*, 4451–4455, doi:10.1016/j.bmcl.2005.07.046.
28. Cvijetić, I.N.; Herlah, B.; Marinković, A.; Perdih, A.; Bjelogrić, S.K. Phenotypic Discovery of Thiosemicarbazone with Anticancer Properties and Catalytic Inhibition of Human DNA Topoisomerase II α . *Pharmaceuticals* **2023**, *16*, 341, doi:10.3390/ph16030341.
29. de Oliveira, R.B.; de Souza-Fagundes, E.M.; Soares, R.P.P.; Andrade, A.A.; Krettli, A.U.; Zani, C.L. Synthesis and Antimalarial Activity of Semicarbazone and Thiosemicarbazone Derivatives. *European Journal of Medicinal Chemistry* **2008**, *43*, 1983–1988, doi:10.1016/j.ejmech.2007.11.012.
30. Fayed, E.A.; Ragab, A.; Ezz Eldin, R.R.; Bayoumi, A.H.; Ammar, Y.A. In Vivo Screening and Toxicity Studies of Indolinone Incorporated Thiosemicarbazone, Thiazole and Piperidinosulfonyl Moieties as Anticonvulsant Agents. *Bioorganic Chemistry* **2021**, *116*, 105300, doi:10.1016/j.bioorg.2021.105300.

31. Jacob, Í.T.T.; Gomes, F.O.S.; de Miranda, M.D.S.; de Almeida, S.M.V.; da Cruz-Filho, I.J.; Peixoto, C.A.; da Silva, T.G.; Moreira, D.R.M.; de Melo, C.M.L.; de Oliveira, J.F.; et al. Anti-Inflammatory Activity of Novel Thiosemicarbazone Compounds Indole-Based as COX Inhibitors. *Pharmacological Reports* **2021**, *73*, 907–925, doi:10.1007/s43440-021-00221-7.
32. Yakan, H. Preparation, Structure Elucidation, and Antioxidant Activity of New Bis(Thiosemicarbazone) Derivatives. *Turkish Journal of Chemistry* **2020**, *44*, 1085–1099, doi:10.3906/KIM-2002-76.
33. Pelosi, G.; Bisceglie, F.; Bignami, F.; Ronzi, P.; Schiavone, P.; Re, M.C.; Casoli, C.; Pilotti, E. Antiretroviral Activity of Thiosemicarbazone Metal Complexes. *Journal of Medicinal Chemistry* **2010**, *53*, 8765–8769, doi:10.1021/jm1007616.
34. Yakan, H.; Muğlu, H.; Türkeş, C.; Demir, Y.; Erdoğan, M.; Çavuş, M.S.; Beydemir, Ş. A Novel Series of Thiosemicarbazone Hybrid Scaffolds: Design, Synthesis, DFT Studies, Metabolic Enzyme Inhibition Properties, and Molecular Docking Calculations. *Journal of Molecular Structure* **2023**, *1280*, doi:10.1016/j.molstruc.2023.135077.
35. Qin, Y.; Xing, R.; Liu, S.; Li, K.; Meng, X.; Li, R.; Cui, J.; Li, B.; Li, P. Novel Thiosemicarbazone Chitosan Derivatives: Preparation, Characterization, and Antifungal Activity. *Carbohydrate Polymers* **2012**, *87*, 2664–2670, doi:10.1016/j.carbpol.2011.11.048.
36. Khan, S.A.; Kumar, P.; Joshi, R.; Iqbal, P.F.; Saleem, K. Synthesis and in Vitro Antibacterial Activity of New Steroidal Thiosemicarbazone Derivatives. *European Journal of Medicinal Chemistry* **2008**, *43*, 2029–2034, doi:10.1016/j.ejmech.2007.12.004.
37. Andreani, A.; Burnelli, S.; Granaola, M.; Leoni, A.; Locatelli, A.; Morigi, R.; Rambaldi, M.; Varoli, L.; Cremonini, M.A.; Placucci, G.; et al. New Isatin Derivatives with Antioxidant Activity. *European Journal of Medicinal Chemistry* **2010**, *45*, 1374–1378, doi:10.1016/j.ejmech.2009.12.035.
38. Elsaman, T.; Mohamed, M.S.; Eltayib, E.M.; Abdel-aziz, H.A.; Abdalla, A.E.; Munir, M.U.; Mohamed, M.A. Isatin Derivatives as Broad-Spectrum Antiviral Agents: The Current Landscape. *Medicinal Chemistry Research* **2022**, *31*, 244–273, doi:10.1007/s00044-021-02832-4.
39. Chohan, Z.H.; Pervez, H.; Rauf, A.; Khan, K.M.; Supuran, C.T. Isatin-Derived Antibacterial and Antifungal Compounds and Their Transition Metal Complexes. *Journal of Enzyme Inhibition and Medicinal Chemistry* **2004**, *19*, 417–423, doi:10.1080/14756360410001710383.
40. Guo, H. Isatin Derivatives and Their Anti-Bacterial Activities. *European Journal of Medicinal Chemistry* **2019**, *164*, 678–688, doi:10.1016/j.ejmech.2018.12.017.
41. Tangadanchu, V.K.R.; Sui, Y.F.; Zhou, C.H. Isatin-Derived Azoles as New Potential Antimicrobial Agents: Design, Synthesis and Biological Evaluation. *Bioorganic and Medicinal Chemistry Letters* **2021**, *41*, 128030, doi:10.1016/j.bmcl.2021.128030.
42. Jiang, D.; Wang, G.Q.; Liu, X.; Zhang, Z.; Feng, L.S.; Liu, M.L. Isatin Derivatives with Potential Antitubercular Activities. *Journal of Heterocyclic Chemistry* **2018**, *55*, 1263–1279, doi:10.1002/jhet.3189.
43. Nain, S. Recent Advancement in Synthesis of Isatin as Anticonvulsant Agents: A Review. *Medicinal Chemistry* **2014**, *4*, doi:10.4172/2161-0444.1000173.
44. Van Den Berg, R.; Haenen, G.R.M.M.; Van Den Berg, H.; Bast, A. Applicability of an Improved Trolox Equivalent Antioxidant Capacity (TEAC) Assay for Evaluation of Antioxidant Capacity Measurements of Mixtures. *Food Chemistry* **1999**, *66*, 511–517, doi:10.1016/S0308-8146(99)00089-8.
45. Lúcio, M.; Nunes, C.; Gaspar, D.; Ferreira, H.; Lima, J.L.F.C.; Reis, S. Antioxidant Activity of Vitamin E and Trolox: Understanding of the Factors That Govern Lipid Peroxidation Studies in Vitro. *Food Biophysics* **2009**, *4*, 312–320, doi:10.1007/s11483-009-9129-4.

46. Volkan, Y.M. Investigation of The Evaluation of Diasporic Bauxite from Islahiye Region in Alumina Production, Sakarya University, 2022.
47. Božić, A.R.; Filipović, N.R.; Novaković, I.T. Synthesis , Antioxidant and Antimicrobial Activity of Carbohydrazones. **2017**, *82*, 495–508.
48. Gangarapu, K.; Manda, S.; Jallapally, A.; Thota, S.; Karki, S.S.; Balzarini, J.; De Clercq, E.; Tokuda, H. Synthesis of Thiocarbohydrazide and Carbohydrazide Derivatives as Possible Biologically Active Agents. *Medicinal Chemistry Research* **2014**, *23*, 1046–1056, doi:10.1007/s00044-013-0684-3.
49. Muğlu, H. Synthesis, Characterization, and Antioxidant Activity of Some New N 4-Arylsubstituted-5-Methoxyisatin- β -Thiosemicarbazone Derivatives. *Research on Chemical Intermediates* **2020**, *46*, 2083–2098, doi:10.1007/s11164-020-04079-x.
50. Wang, X.; Dai, M.; Xie, Y.; Han, J.; Ma, Y.; Chen, C. Experimental Investigation of Evaporation Characteristics of Biodiesel-Diesel Blend Droplets with Carbon Nanotubes and Nanoceria as Nanoadditives. *Applied Surface Science* **2020**, *505*, 144186, doi:10.1016/j.apsusc.2019.144186.
51. Dunn, R.O. Effect of Antioxidants on the Oxidative Stability of Methyl Soyate (Biodiesel) B. **2005**, *86*, 1071–1085, doi:10.1016/j.fuproc.2004.11.003.
52. Maru, M.M.; Lucchese, M.M.; Legnani, C.; Quirino, W.G.; Balbo, A.; Aranha, I.B.; Costa, L.T.; Vilani, C.; de Sena, L.Á.; Damasceno, J.C.; et al. Biodiesel Compatibility with Carbon Steel and HDPE Parts. *Fuel Processing Technology* **2009**, *90*, 1175–1182, doi:10.1016/j.fuproc.2009.05.014.
53. Soykan, C. Synthesis , Characterization , and Biological Activity of N - (4- Acetylphenyl) Maleimide and Its Oxime , Carbazone , Thiosemicarbazone Derivatives and Their Polymers. **2003**, 1942–1951.
54. Aniza, R.; Chen, W.H.; Kwon, E.E.; Bach, Q.V.; Hoang, A.T. Lignocellulosic Biofuel Properties and Reactivity Analyzed by Thermogravimetric Analysis (TGA) toward Zero Carbon Scheme: A Critical Review. *Energy Conversion and Management: X* **2024**, *22*, 100538, doi:10.1016/j.ecmx.2024.100538.
55. Kutuk, H.; Turkoz, N. Microwave-Assisted Synthesis of Disulfides. *Phosphorus, Sulfur and Silicon and the Related Elements* **2011**, *186*, 1515–1522, doi:10.1080/10426507.2010.520174.
56. Brand-Williams, W.; Cuvelier, M.E.; Berset, C. Use of a Free Radical Method to Evaluate Antioxidant Activity. *LWT - Food Science and Technology* **1995**, *28*, 25–30, doi:10.1016/S0023-6438(95)80008-5.
57. Yakan, H.; Cakmak, S.; Kutuk, H.; Yenigun, S.; Ozen, T. Synthesis, Characterization, Antioxidant, and Antibacterial Activities of New 2,3-Dimethoxy and 3-Acetoxy-2-Methyl Benzamides. *Research on Chemical Intermediates* **2020**, *46*, 2767–2787, doi:10.1007/s11164-020-04118-7.
58. Vlase, T.; Doca, N.; Vlase, G.; Bolcu, C.; Borcan, F. Kinetics of Non-Isothermal Decomposition of Three IRGANOX-Type Antioxidants. *Journal of Thermal Analysis and Calorimetry* **2008**, *92*, 15–18, doi:10.1007/s10973-007-8726-z.
59. Haji, I.; Yıldız, K. Decomposition Kinetics of Diasporitic Bauxite from Gaziantep Region. In Proceedings of the 9th International Scientific Research Congress, Ankara.; 2021; pp. 439–447.
60. Angelopoulos, P.; Samouhos, M.; Taxiarchou, M. Thermal Decomposition Kinetics of Greek Diasporic Bauxite. *Proceedings of OPMR 2016- Opportunities in Processing of Metal Resources in South East Europe* **2016**, 191–200.
61. Küçük, F.; Yıldız, K. The Decomposition Kinetics of Mechanically Activated Alunite Ore in Air Atmosphere by Thermogravimetry. *Thermochimica Acta* **2006**, *448*, 107–110, doi:10.1016/j.tca.2006.07.003.
62. Borugadda, V.B.; Goud, V. V Thermochimica Acta Thermal , Oxidative and Low Temperature Properties of Methyl Esters Prepared from Oils of Different Fatty Acids Composition: A Comparative Study. *Thermochimica Acta* **2014**, *577*, 33–40, doi:10.1016/j.tca.2013.12.008.

63. Çavuş, M.S.; Yakan, H.; Muğlu, H.; Bakır, T. Novel Carbohydrazones Including 5-Substituted Isatin: Synthesis, Characterization, and Quantum-Chemical Studies on the Relationship between Electronic and Antioxidant Properties. *Journal of Physics and Chemistry of Solids* **2020**, *140*, doi:10.1016/j.jpcs.2020.109362.
64. Pitucha, M.; Ramos, P.; Wojtunik-Kulesza, K.; Głogowska, A.; Stefańska, J.; Kowalczyk, D.; Monika, D.; Augustynowicz-Kopeć, E. Thermal Analysis, Antimicrobial and Antioxidant Studies of Thiosemicarbazone Derivatives. *Journal of Thermal Analysis and Calorimetry* **2023**, *148*, 4223–4234, doi:10.1007/s10973-023-12029-z.

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.