

Article

Not peer-reviewed version

---

# Predictions of Crack Growth Rates, R-Ratio and Overload Effects Based on Smooth Specimen LCF Data and the Moving Plastic Stress Field Ahead of the Crack Tip

---

[Stephen Williams](#)\*, [Mark Whittaker](#), [Mark Hardy](#)

Posted Date: 21 April 2026

doi: 10.20944/preprints202604.1454.v1

Keywords: crack growth; LCF; strip yield models; plasticity; R-ratio effects; overloads



Preprints.org is a free multidisciplinary platform providing preprint service that is dedicated to making early versions of research outputs permanently available and citable. Preprints posted at Preprints.org appear in Web of Science, Crossref, Google Scholar, Scilit, Europe PMC.

Copyright: This open access article is published under a [Creative Commons CC BY 4.0 license](#), which permit the free download, distribution, and reuse, provided that the author and preprint are cited in any reuse.

Disclaimer/Publisher's Note: The statements, opinions, and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions, or products referred to in the content.

Article

# Predictions of Crack Growth Rates, R-Ratio and Overload Effects Based on Smooth Specimen LCF Data and the Moving Plastic Stress Field Ahead of the Crack Tip

Steve Williams <sup>1,\*</sup>, Mark Whittaker <sup>1</sup> and Mark Hardy <sup>2</sup>

<sup>1</sup> Institute of Structural Materials, Swansea University, Fabian Way, Swansea SA1 8EN, United Kingdom

<sup>2</sup> Rolls-Royce plc, PO Box 31, Moor Lane, Derby DE22 8BJ, United Kingdom

\* Correspondence: 2031771@swansea.ac.uk; Tel.: +44-7795-380230

## Abstract

Previous work has attempted, often within the framework of strip yield-type models, to predict crack growth rates based on the accumulation of fatigue damage ahead of the crack tip as it moves through a structure. This study performs similar calculations using results from plastic 2D plane stress analyses run on a finite element (FE) model containing a sharp semi-circular notch representing an edge crack. Stress-distance profiles ahead of the crack tip (notch root) were extracted at the maximum and minimum points of a range of fatigue cycles with different loading amplitudes. These were used with data from smooth specimen Low Cycle Fatigue (LCF) tests to predict the build-up of fatigue damage at regularly spaced locations ahead of the crack tip and hence crack growth rates. The FE analyses were performed for a wide range of  $K_{max}$  values at loading R-ratios of 0, -1 and 0.5, and the growth rate predictions were compared with test data. The method was then extended to predict overload behaviour. The material studied was the nickel-based superalloy fine grain (FG) RR1000 at 20 °C.

**Keywords:** crack growth; LCF; strip yield models; plasticity; R-ratio effects; overloads

## 1. Introduction

As part of a wider programme to investigate crack growth phenomena such as closure, R-ratio (min/max load) effects, overload retardation and high temperature tunnelling, non-linear FE analyses using the ABAQUS code have been run on a range of 2D and 3D models containing sharp notches representing cracks.

This paper takes the predicted maximum and minimum plastic stress fields from 2D plane stress analyses on geometry representing an edge crack together with data from smooth specimen LCF tests to predict the build-up of fatigue damage at evenly spaced locations ahead of the crack tip (notch root) as it moves towards them. When the fatigue damage at a location reaches unity the material there is considered to have failed and hence the crack has reached that position. Knowing the number of fatigue cycles required to fail the material at successive calculation locations then allows crack growth rates to be calculated.

It is hoped that this fatigue analogy model will provide further insight on a number of aspects of crack growth behaviour that are usually represented empirically, such as the overall shape of the  $da/dN-\Delta K$  curve, R-ratio effects and propagation rates following an overload cycle.

The material studied was the  $\gamma'$  strengthened nickel-based superalloy Fine Grain (FG) RR1000 at 20 °C. RR1000 is used for aero engine high pressure compressor and turbine discs, and different heat treatments are used to produce two variants of the material for specific applications. Fine Grain RR1000 has high tensile strength, allowing certification overspeed regulations to be met with

lightweight disc designs. There is also a Coarse Grain (CG) version which is optimised for high temperature crack growth resistance.

Many of the analytical methods for understanding crack tip stress fields and phenomena such as closure and overload behaviour are based on the strip yield model originally developed by Newman [1]. This represents the crack and the plastic zone ahead of the crack tip by a series of elements that support a 1D stress field in the loading direction and have finite widths. The material's deformation is usually assumed to be solely due to plasticity i.e., its behaviour is rigid-perfectly plastic. Creep deformation can also be included in high temperature analyses.

Predictions of crack closure behaviour from strip yield models have been shown to line up well with experimental data in papers by many authors including Wang and Blom [2], Vidler, Kotousov and Ng [3], Rose and Wang [4] and Beretta and Carboni [5]. Measured plane stress closure loads on steel and aluminium sheet test pieces from these programmes are often high, around 40% of the maximum applied load. Work by Paluskiewicz et al. [6] on In718 alloy, however, which is a similar type of material to FG RR1000, showed no closure at a loading R-ratio (min/max load) of 0.1.

The end point of strip yield modelling work and similar studies using FE models of the crack tip region is usually to determine the effective stress intensity factor range  $\Delta K_{eff}$ , which represents the stress intensity range over which the crack is open. Its relationship with the maximum stress intensity in the loading cycle  $K_{max}$  and the stress intensity at which the crack opens  $K_{op}$  is shown in Equation (1).

$$\Delta K_{eff} = K_{max} - K_{op} \quad (1)$$

If the relationship between  $\Delta K_{eff}$  and experimental crack growth rates is established for one R-ratio, the strip yield models then allow growth rate predictions to be made for other loading conditions.

Studies by Chen, Weiss and Stickler [7], Castro, Meggiolaro and Miranda [8], Vasudevan, Sadananda and Holtz [9] and Fleck [10] have all, however, provided examples where  $\Delta K_{eff}$  has not been able to represent aspects of crack growth behaviour correctly.

As an alternative, therefore, methods that represent crack growth as a fatigue process and use stress and/or strain-related parameters rather than stress intensities as the basis for their predictions of crack growth rate were investigated. Examples of these Critical Damage Models based on a strip yield framework have been published by Noroozi et al. [11] and Ferreira et al. [12].

The basis of Noroozi's model is shown schematically in Figure 1 below. As with the work described in this paper, the crack tip is represented as a sharp semi-circular notch. The notch radius is  $\rho^*$ , and the fatigue damage is assessed using averaged loading conditions in material strips of this width ahead of the notch. The Creager-Paris [13] solution is used to determine the mean tensile elastic stresses in each strip ahead of the crack tip, and the compressive elastic stress fields are determined by treating the crack tip as a circular hole. The Neuber [14] construction and a Ramberg-Osgood [15] stress-strain curve are then used to calculate the plastic Smith-Watson-Topper [16] parameter and hence fatigue damage and crack growth rates. The dimension  $\rho^*$  is used as a fitting parameter to line the predictions up with the material's threshold stress intensity value, which is required as an input to the model.

Ferreira et al. used both the Smith-Watson-Topper and Coffin-Manson [17] equations to calculate fatigue damage, concluding that the latter gave a better match to experimental crack growth rates. They also linked the crack growth threshold to the fatigue endurance limit and the fracture toughness to a critical level of plastic strain.

Reasonable crack growth rate predictions were made for a wide range of loading R-ratios in both papers, but it was considered that using similar crack geometry and plastic finite element analyses rather than strip yield methods to calculate the input stresses could provide additional insights on the material behaviour.

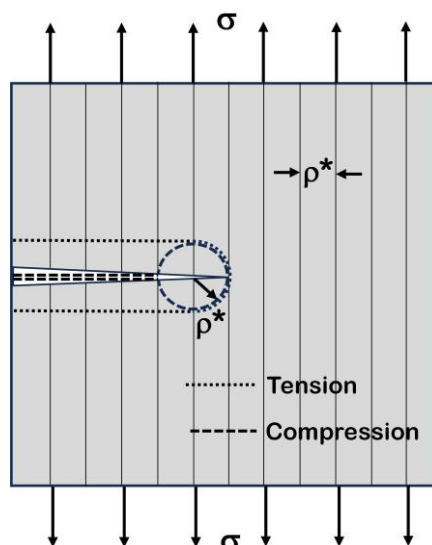


Figure 1. Schematic illustration of the model used by Noroozi et al. to predict crack tip stresses.

## 2. Materials, Methods, Results and Discussion

The modelling work required to predict crack growth rates under different loading regimes based on fatigue damage accumulation ahead of the crack tip was done in four distinct phases, each of which is discussed separately in this section.

Firstly, a finite element modelling framework was established that was shown to calculate geometry correction factors for edge cracks (and hence elastic stress fields) that were consistent with previously published solutions. Plastic FE analyses were then run for a wide range of  $K_{\max}$  values at  $R=0$  to generate maximum and minimum stress-distance profiles that were used as inputs to the fatigue damage calculations.

Next, a spreadsheet-based method was developed to allow the fatigue damage accumulation at a large number of discrete material locations ahead of the crack tip to be calculated as it moves through the structure. The fatigue curve used for the damage calculations was fitted to the results of load and strain controlled LCF tests run on plain specimens at  $R$ -ratios of 0 and -1. The method was then used to predict  $R=0$  crack growth rates at a wide range of  $K_{\max}$  values and hence the overall shape of the  $da/dN-\Delta K$  curve.

After running additional FE analyses, the method was extended to predict crack growth rates at  $R$ -ratios of -1 and 0.5.

Finally, the spreadsheet method was improved to use a finer spatial grid for the calculations and to implement the calculation process as a macro. This allowed crack growth rates following single cycle overloads to be predicted.

In each of the four following sections the calculation method is first described, followed by a comparison of the modelled results with experimental data and a discussion on the findings.


### 2.1. Finite Element Modelling to Generate Edge Crack Geometry Correction Factors and Calculate Plastic Stress-Distance Profiles

The model used for the finite element analyses is shown in Figure 2. A 1.4mm long notch with a  $10\mu\text{m}$  end radius is contained within a rectangular section 7mm wide and 30mm long. The crack length and section geometry were chosen to match an experimental condition in the overall research programme, which used corner crack test pieces with a 7mm wide test section and threaded ends. Advantage was taken of the geometry's symmetry to model only the top half of the crack and surrounding material. 4-noded CPS4 elements were used with linear geometry.

The model also contains a row of fully rigid elements which runs from the crack mouth to just short of the run-out of the notch radius. The tops of these elements contact the crack face in such a way that they separate under tension but can transmit compressive stresses in the loading (y) direction if the crack is predicted to close. All the nodes on the bottom edge of the cracked geometry and contact block are fixed in the y direction, and the nodes at the notch root and the bottom right-hand corner of the contact block are also pinned in the x direction.

A uniform pressure load is applied to the top of the model, and the nodal displacements there in the loading direction are all set to be equal using the ABAQUS \*EQUATION keyword. This is not strictly necessary, but represents the remote boundary conditions for a threaded test piece more appropriately than allowing the nodes there to deform freely.


The geometry was generated using a macro in Microsoft Excel, and a variety of node/element patterns close to the notch root were used in the full programme. The version used for this study contains multiple layers of elements ahead of the crack tip  $0.5\mu\text{m}$  wide that, in other work, were switched off progressively as the load was cycled to simulate crack growth whilst maintaining the original crack tip radius. Finally, five rings of elements around the arc of the notch root were specified by the \*CONTOUR INTEGRAL keyword to allow J-integral values to be calculated from the analyses.

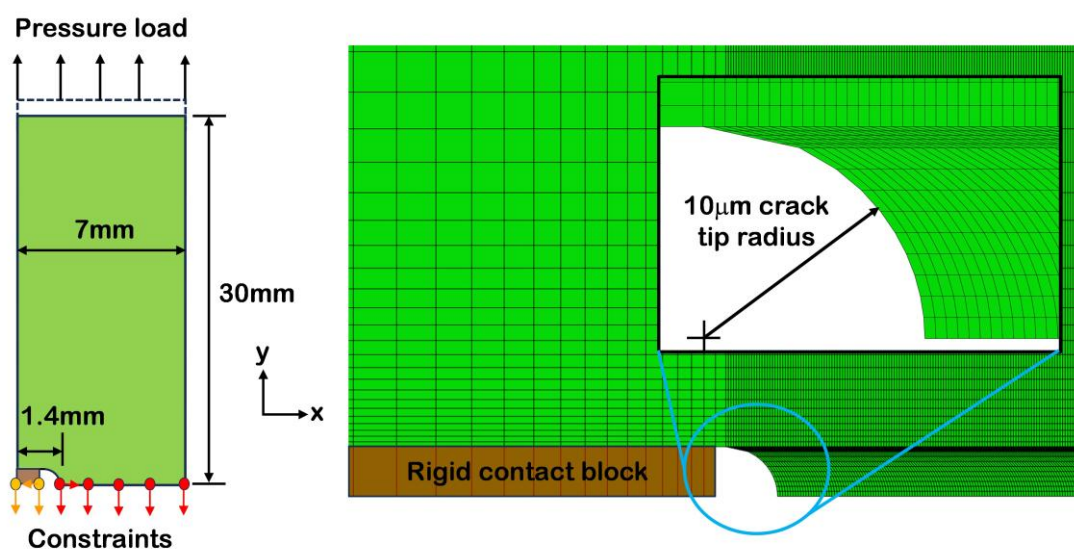


**Figure 2.** Edge crack 2D plane stress finite element model - mesh geometry and loading details.

Example stress contours in the loading direction are shown in Figure 3 from elastic (3a) and plastic (3b) FE analyses. Initial analyses had kinks in the contours around the shallow angled elements at the top of the notch radius which were largely resolved by splitting each of them horizontally into five smaller elements. This detail can be seen in the magnified region of Figure 2.

The suitability of the sharp notch for representing the crack tip stress field was then established. Geometry correction factors  $Y$  for nine different crack lengths were calculated from the ABAQUS J-integral output for models run with no constraints on the top edge. These were compared with the standard solution for edge cracks developed by Brown and Srawley [18] as shown in Figure 4. In the figure, the data points are from the FE analyses and the curves are generated from the geometry correction factor polynomials. The FE results are within 0.5% of the Brown and Srawley values throughout. Also shown in Figure 4 are the effects of constraining the top of the model to remain horizontal as it deforms, which are significant for longer edge cracks. The addition of this boundary condition is equivalent to adding a compressive load to the top of the model above the cracked region, reducing the elastic stresses and hence the  $Y$  and  $K$  values. Figure 4 also shows the polynomial fitted to these geometry correction factor values.

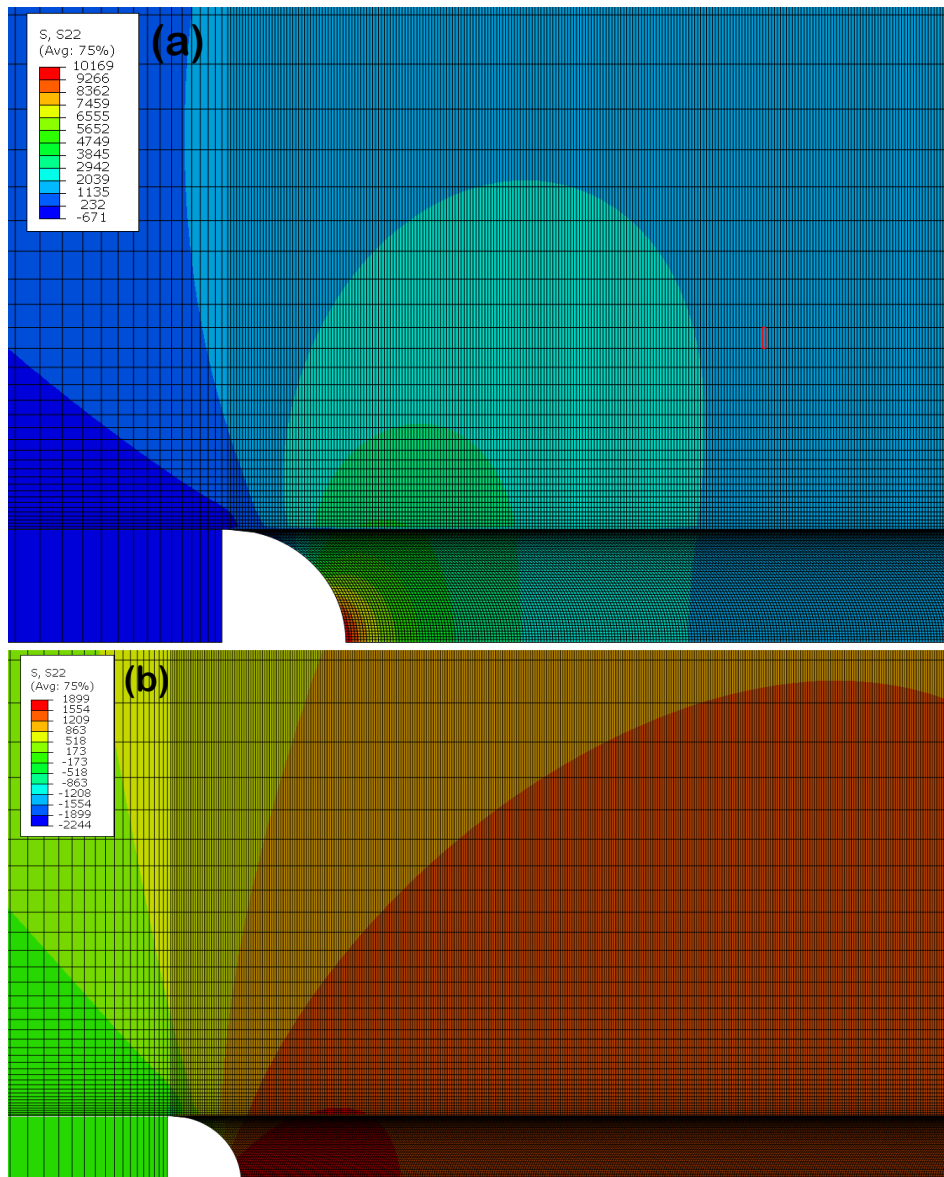


**Figure 3.** Loading direction stress contours from (a) elastic and (b) plastic FE analyses, FG RR1000 at 20 °C,  $K_{max}=25.8\text{MPa}\sqrt{\text{m}}$ .

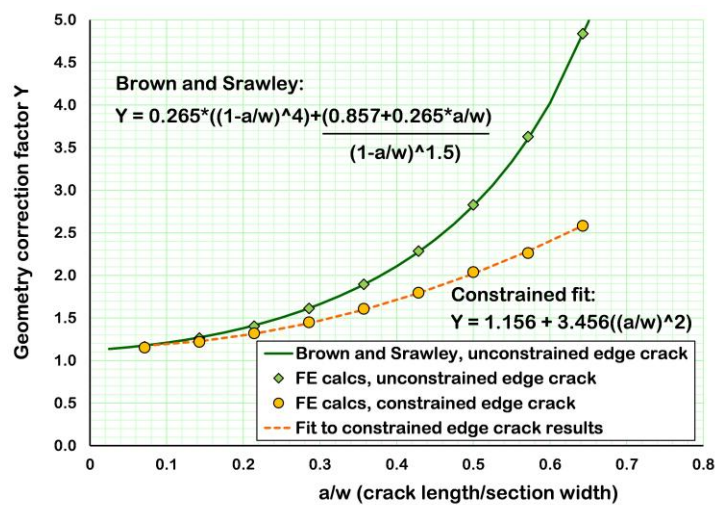

**Figure 4.** Comparison of geometry correction factors from the FE model with those from the Brown and Srawley equation.

The contact arrangement shown in Figure 2 does not currently account for plasticity in the crack wake, which could cause the crack to close at a higher load level at R=0 loading conditions than predicted by the model and affect the calculated crack tip stress and strain ranges. To understand whether this was an issue, measurements of Potential Drop (PD) voltage were taken throughout twenty loading cycles at R-ratios of 0, -0.25 and -0.5 using FG RR1000 corner crack test pieces as shown in Figure 5. The plot indicates negligible closure at R=0, and hence it is not necessary to include crack wake plasticity in the corresponding FE models. The crack closes fully at the other two R-ratios.

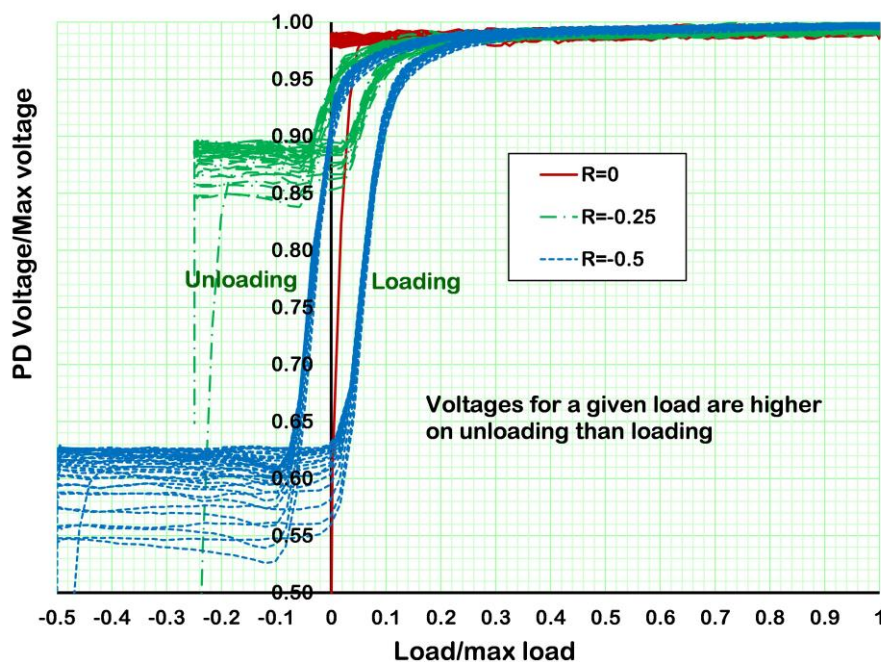

**Figure 5.** Hysteresis loops of PD voltage against applied load for three different loading R-ratios, FG RR1000 material at 20 °C.


Additional sensitivity calculations exploring a 1 $\mu$ m notch radius, non-linear geometry and different values of Young's modulus and Poisson's ratio all gave Y values within 0.7% of the datum FE results. The elastic stress-distance profile close to the notch root in the crack growth direction was also checked to confirm that it captured the expected  $1/\sqrt{r}$  singularity well.

Having determined that the modelling method was appropriate to represent the crack tip stress fields, plastic R=0 FE analyses were run at nineteen different peak loads representing  $K_{max}$  values from 1-86MPa $\sqrt{m}$ . Isotropic plasticity was used with a single cycle zero-max-zero loading history. The plasticity data for FG RR1000 at 20 °C was expressed in true stress-log strain form and was supplied by Rolls-Royce plc. Isotropic rather than kinematically hardened plasticity was used because the material close to the crack tip experiences higher absolute strain levels than it has seen previously with each load reversal and data from complex cycle strain controlled tests has shown that this causes its plastic response to follow an isotropic, rather than kinematically hardened, stress-strain curve.

## 2.2. Calculation of R=0 Crack Growth Rates Based on Fatigue Damage Accumulation Ahead of the Moving Crack Tip Stress Field

Figure 6 shows the general principle behind representing crack growth as progressive material failure due to the accumulation of damage from successive fatigue loading cycles as the crack tip moves towards a point in the crack path. Initially the crack tip is at position A, and the maximum and minimum plastic stress-distance profiles associated with the loading cycle extremes are shown by the darker curves. At a location C some distance ahead of the crack tip the amplitude of the fatigue

loading cycle will be relatively modest. As the crack grows and the tip reaches B, however, the stress range experienced at location C increases, reaching a maximum value when the crack tip approaches that point.

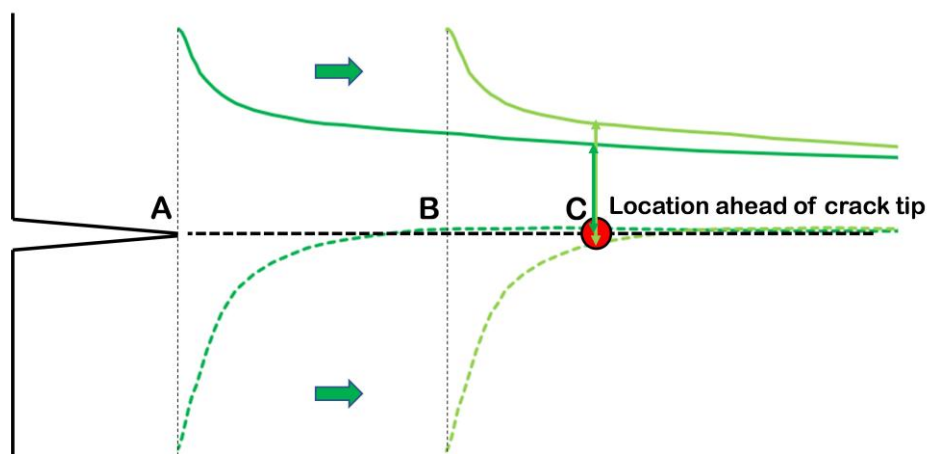

**Figure 6.** Increasing maximum and minimum stress fields experienced at a location as the crack tip moves towards it.

To calculate crack growth rates, the plastic maximum and minimum stress fields for a selected  $K_{max}$  value and R-ratio are moved towards the location where the fatigue damage is calculated in  $1\mu\text{m}$  steps in an Excel spreadsheet, starting with the notch root  $300\mu\text{m}$  away. At each step, the fatigue damage in  $N$  loading cycles (damage= $N/N_f$  where  $N_f$  is the number of cycles to failure) is calculated using a Basquin-style [19] life equation based on the Walker [20] corrected equivalent 0-max stress at the current distance from the crack tip as shown in Equations (2) and (3). A threshold stress  $\sigma_{th}$  below which no damage occurs is also included in the life equation. The fatigue damage values from each step are summed, and a value of  $N$  is calculated such that the total fatigue damage at the calculation location is equal to unity when the crack tip reaches it. The crack growth rate for this geometry and loading condition is then the size of the crack tip movement step ( $1\mu\text{m}$ ) divided by  $N$ .

$$\frac{(\Delta\sigma_{equiv\ 0-max-\sigma_{th}})}{UTS} = \alpha \cdot (N_f)^\beta \quad (2)$$

$$\Delta\sigma_{equiv\ 0-max} = \Delta\sigma(1-R)^{(m-1)} \quad (3)$$


In Equations (2) and (3)  $\sigma_{th}$  is the threshold value of equivalent 0-max stress, UTS is the material's Ultimate Tensile Strength,  $\alpha$  and  $\beta$  are fitting parameters and  $m$  is the Walker exponent.

The S-N (stress-life) curve used to calculate the fatigue damage ahead of the crack tip was fitted to FG RR1000 LCF test results from plain specimens run under strain and load control at two different loading R-ratios. Unfortunately, no results were available at  $20\text{ }^\circ\text{C}$  and therefore data from  $300\text{ }^\circ\text{C}$  tests were used instead. The fatigue lives at this temperature are expected to be similar to but slightly lower than those at  $20\text{ }^\circ\text{C}$  for equivalent loading conditions. The load controlled test lives are to failure, and the strain controlled lives are to a 10% load drop relative to stabilised stress conditions. Two different surface conditions were used for the fatigue tests, polished and shot peened, although the lives were similar and therefore the data were combined.

The strain controlled tests were analysed using a single element FE model through one loading cycle with isotropic plasticity and  $20\text{ }^\circ\text{C}$  material properties to calculate maximum and minimum stresses. This is consistent with the calculation method used to determine the maximum and minimum crack tip stress fields and helps to scale the test results to  $20\text{ }^\circ\text{C}$ , the temperature that will be used for the crack growth rate predictions.

The fitted values of the parameters  $m$ ,  $\sigma_{th}/UTS$ ,  $\alpha$  and  $\beta$  were 0.44, 0.31, 3.60 and -0.17. This gives the curve shown in Figure 7(a), which collapses the test data well for all the different loading conditions. Because the relationship between equivalent 0-max plastic stress and peak elastic stress


is different for the two R-ratios, Equations (2) and (3) generate separate curves on peak elastic stress-life axes as shown in Figure 7(b). The full curve shapes shown in this plot were predicted by running additional single element plastic FE simulations at a wide range of R=0 and R=-1 strain controlled loading conditions.

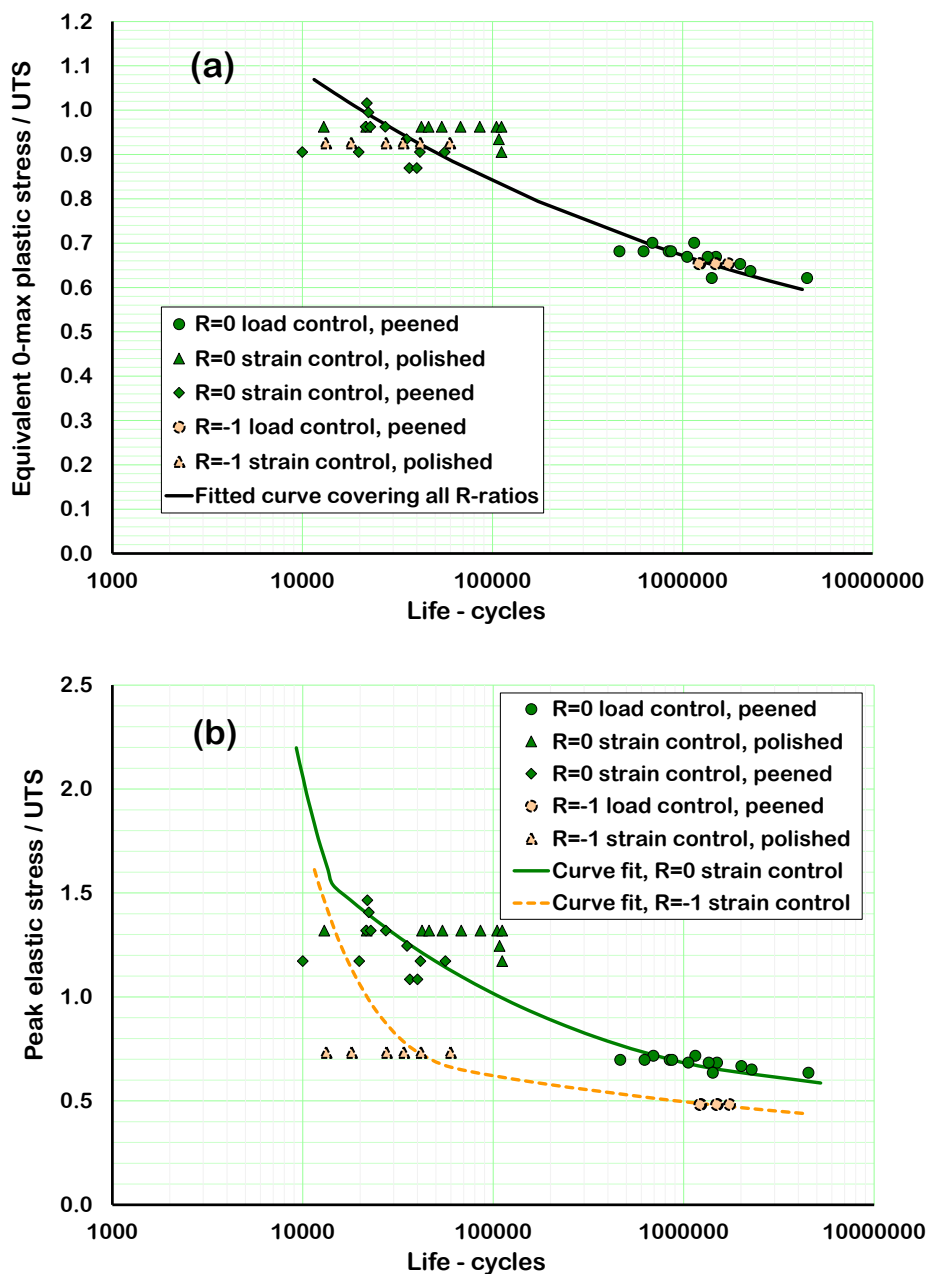

**Figure 7.** Fitted fatigue curves based on plastic stresses as a function of (a) Equivalent 0-max plastic stress/UTS and (b) Peak elastic stress/UTS, fine grain RR1000 material at 300 °C.

The  $da/dN-\Delta K$  curve prediction depends solely on the stress fields ahead of the crack tip from the plastic FE analyses and the fit to the plain test piece LCF data. When the crack tip is close to the calculation position, however, the stresses are very high and the corresponding fatigue damage rate comes from extrapolating the curves in Figure 7 to low lives. It is possible for this extrapolation to be varied slightly without upsetting the fit to the test data, and therefore an improved fitting method was developed that had inputs of both the LCF data and typical crack growth Paris law-based design data for FG RR1000 at 20 °C. The curves shown in Figure 7 use this fitting method.

The resulting predicted crack growth rate curve for  $R=0$  is compared with typical design data and test results from the current research programme in Figure 8. The curve exhibits threshold-like behaviour at low  $K$  values and the slope also increases at high  $K$  values due to the FE model experiencing plastic strain across the whole ligament of material ahead of the crack. In the  $\Delta K$  range of  $15\text{--}40\text{MPa}\sqrt{\text{m}}$ , where most experimental data are usually collected, the growth rate- $\Delta K$  relationship is approximately linear and its slope is very close to the database value. Overall the agreement between the predictions and the test and design data is extremely good, although the predicted threshold  $\Delta K$  value is a little low compared to the typical value from tests of around  $8\text{MPa}\sqrt{\text{m}}$ .

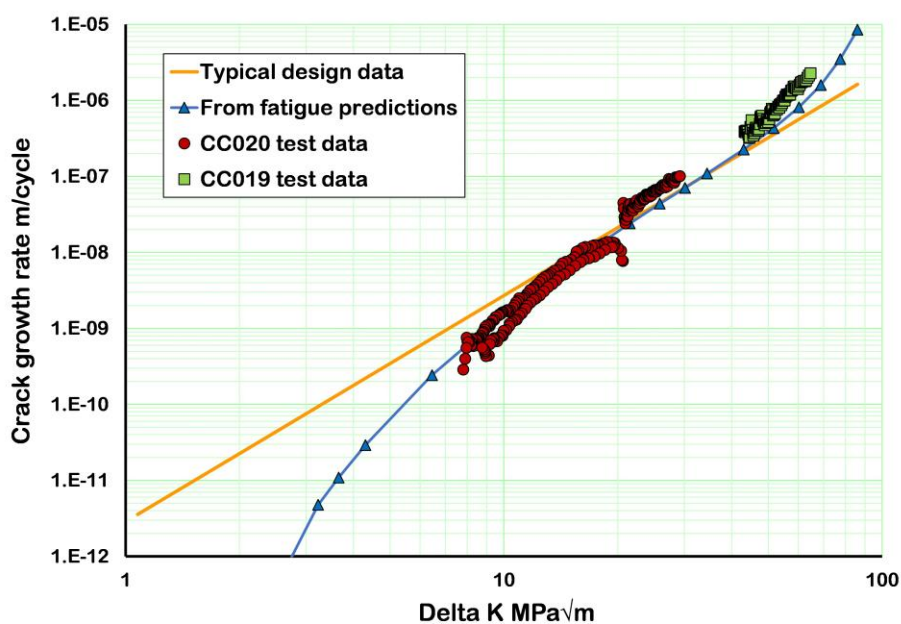


**Figure 8.** Comparison of predicted crack growth rates from the fatigue analogy method with database Paris law values and experimental data, FG RR1000 at  $20\text{ }^{\circ}\text{C}$ .

### 2.3. Growth Rate Predictions for Other $R$ -Ratios


The effects of loading  $R$ -ratio on crack growth rates were then studied by running two further series of 2D plane stress analyses at  $R=-1$  and  $R=0.5$ . As shown in Figure 9(a), close to the crack tip the plastic equivalent  $\sigma$ -max stress-distance profiles for the same peak applied load at  $R=0$  and  $R=-1$  are very similar and therefore the predicted growth rates for  $R=-1$  were only slightly faster despite the applied load range being twice that at  $R=0$  conditions. This trend was consistent across the range of applied loads and lines up extremely closely with the behaviour seen in tests conducted by Rolls-Royce.


The trends are different, however, between  $R=0.5$  and  $R=0$  as shown in Figure 9(b). The  $R=0$  equivalent stress-distance profiles are significantly higher than those for  $R=0.5$  at low  $K_{\text{max}}$  values. As  $K_{\text{max}}$  increases, the profiles then start to coalesce at the crack tip location and the predicted fatigue damages and hence crack growth rates become more similar. This can be seen in Figure 10(a). The interesting thing about this figure is that it clearly shows that whilst the  $da/dN$ - $\Delta K$  curves are parallel for  $R=0$  and  $R=-1$ , the predicted  $R=0.5$  curve is steeper. Data available in the literature (Dinda [21], Zheng [22], Bulloch [23] and Huang [24]) goes against this prediction, however, and often suggests that the  $R=0.5$  crack growth curves are flatter than for  $R=0$ .

A laboratory test was therefore run at  $20\text{ }^{\circ}\text{C}$  at an  $R$ -ratio of  $0.5$  and a comparison was also made between Rolls-Royce  $R=0$  and  $R=0.5$  crack growth data at a range of temperatures. Growth rates from the test are compared in Figure 11 with the  $R=0$  results shown previously. Unfortunately, the natural variability in the test data from different specimens meant that no clear answer could be obtained on whether the slopes of the  $R=0$  and  $0.5$  growth rate curves should be the same or different.

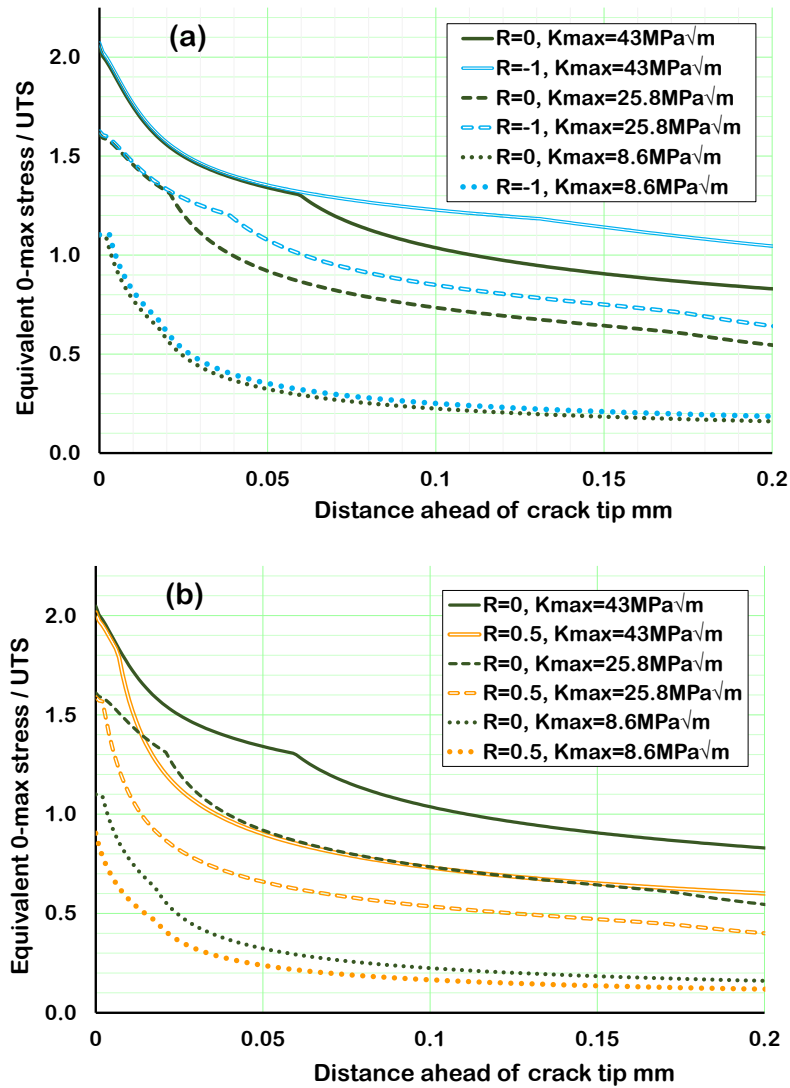


**Figure 9.** Comparison of equivalent 0-max stress-distance profiles ahead of the crack tip from (a) R=0 and R=-1 loading profiles and (b) R=0 and R=0.5 loading profiles at different  $K_{max}$  values.

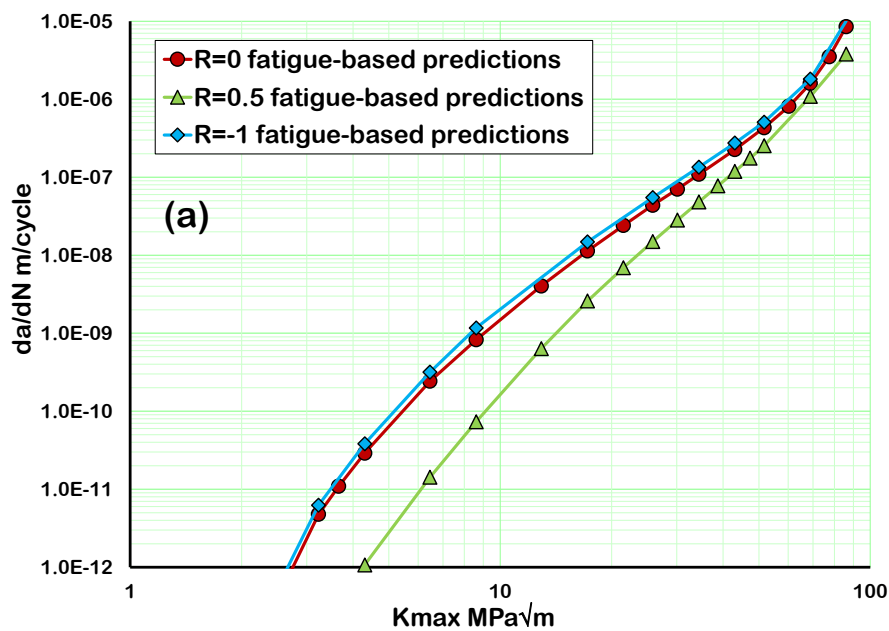

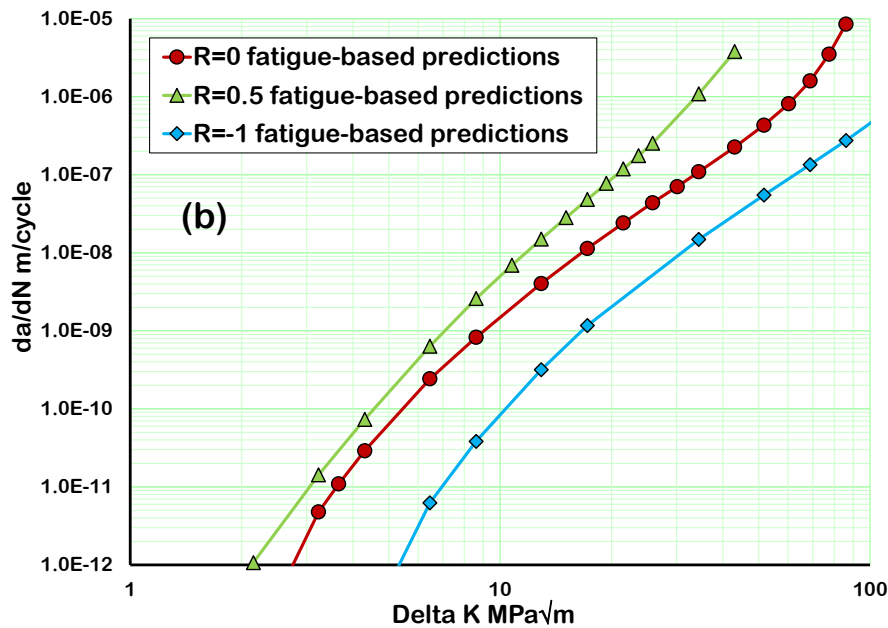

**Figure 10.** Predicted R=0, -1 and 0.5 crack growth curves for FG RR1000 material at 20 °C based on stress-distance profiles from 2D plane stress analyses and plain test piece LCF data as a function of (a)  $K_{max}$  and (b)  $\Delta K$ .

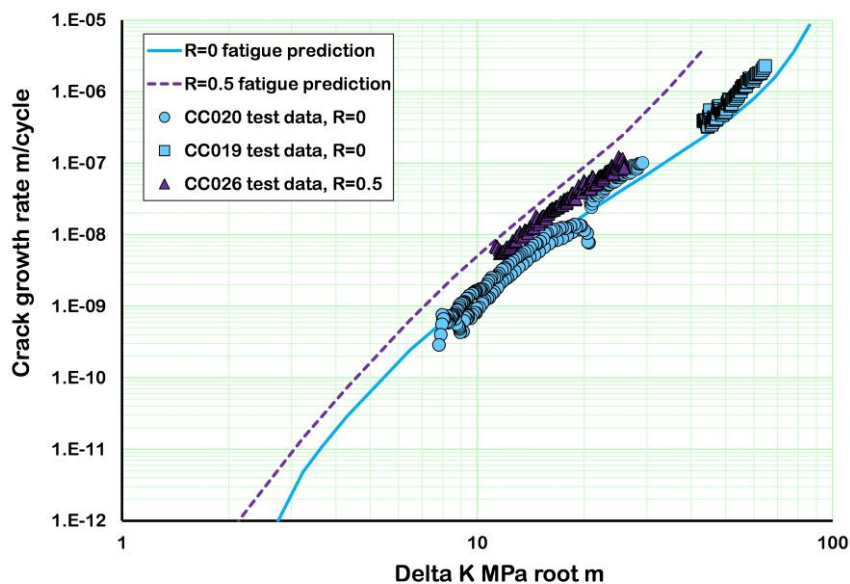


**Figure 11.** Comparison of R=0 and R=0.5 predictions from the fatigue analogy method with test data, FG RR1000 material at 20 °C.

#### 2.4. Overload Behaviour Predictions

Finally, the expected R=0 growth rates following an overload were predicted using the fatigue analogy. This is a much more complex calculation, and was implemented in Excel using a Visual Basic macro rather than formulae in specific worksheet cells. This greatly reduced the physical size of the spreadsheet and allowed a finer spatial resolution of 0.1  $\mu\text{m}$  per calculation step and an overall calculation distance of 1mm to be used. It also allowed the K values and stress fields to be modified as the crack moves and grows. The main inputs to the macro were, as previously, plastic maximum and minimum stress-distance profiles for a wide range of  $K_{max}$  values and in addition the peak applied load as a function of crack length.

The calculation process for the spreadsheet macro is shown in Figure 12. Based on the  $K_{max}$  value calculated for the starting crack length and peak datum cycle load using the edge crack geometry correction factor polynomials for constrained conditions shown in Figure 4, initial plastic stress-distance profiles are determined by interpolation between the closest sets of FE results. Increments of fatigue damage are then calculated at all the locations in the 1mm calculation length. The crack tip position is then moved progressively through the material and the above calculation process is repeated, with the fatigue damage increments at each location ahead of the crack tip being summed, until the change in applied load associated with the overload is found in the input data. At this time, the fatigue damage calculated during all the previous timesteps and at all locations within the material is scaled by the same factor such that the value at the current crack tip position is unity. This allows the  $da/dN-\Delta K$  behaviour to date to be output.

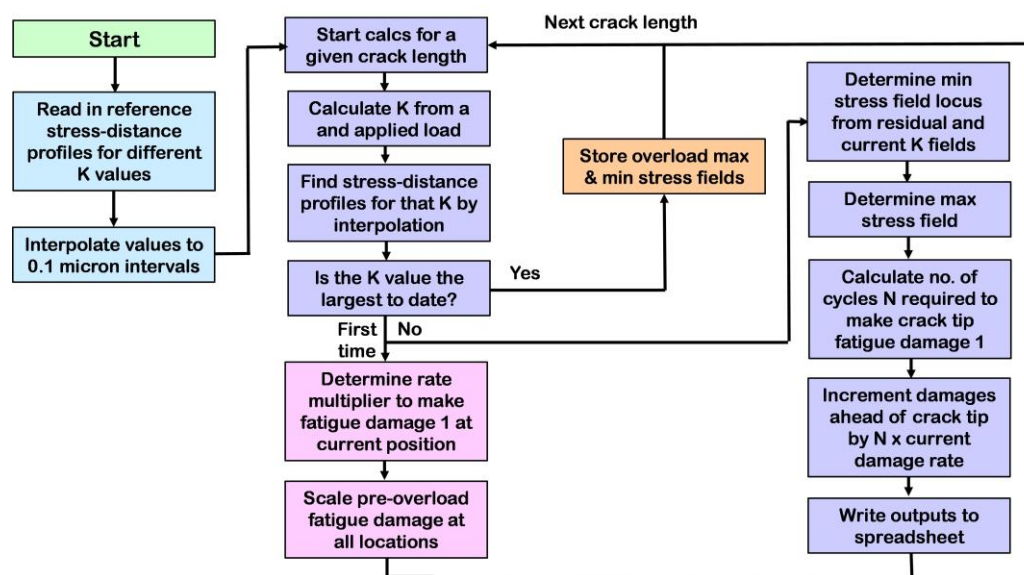

**Figure 12.** Excel macro flowchart for calculating overload behaviour using the fatigue analogy for crack growth.

To describe the subsequent crack growth, a number of assumptions first have to be made about how the minimum (residual) stress field associated with the overload cycle combines with the moving stress fields from the subsequent cycles at the datum load level:

- Because the residual compressive stress field resulting from the overload is generated by a localised inelastic strain distribution it is assumed to remain fixed in space and have the same stress magnitudes as the crack grows
- When the crack tip has moved to a distance  $x$  ahead of the overload position, the peak tensile stress in the cycle at that location is given by the overload residual stress at  $x$  plus the crack tip stress range corresponding to the  $K$  value from the datum loading at the new crack length
- As the crack grows further, it will reach a position where the overload residual stress field at  $x$  is less compressive than the minimum crack tip stress field associated with the  $R=0$  loading at the current  $K$  range. The minimum crack tip stress is then assumed to be that from the  $R=0$  analysis. This is because the maximum and minimum crack tip stress fields are assumed to equilibrate at this level: additional yielding at one extreme of the loading cycle would generate higher stresses in the opposite direction at the other end of the loading cycle which would return the stresses to their starting values
- Ahead of the crack tip, the minimum stress is assumed to be the more compressive of that from the residual stress field and the  $R=0$  analysis at the current  $K$  range
- The maximum stress field is determined by adding the stress range-distance profile for the current  $K$  value to the minimum stress field

The implementation of these assumptions was checked in detail by comparing stress-distance profiles produced by the spreadsheet against the behaviour from an analysis where, after an overload, bands of elements ahead of the crack tip were removed progressively to grow the crack and evolve the stress fields.

As described previously, at the crack length where the overload occurs all of the calculated fatigue damages are scaled by the same factor such that the value at the crack tip is unity. The fatigue damage at the next location ahead of the crack tip will then be close to this value. The crack tip is moved to that point, and using the above assumptions first the minimum and then the maximum stress field are determined by combining the contributions from the residuals and the current loading. The corresponding fatigue damage rates per cycle are then calculated at all the assessment locations. At the new crack tip location, the number of additional cycles required to cause the material to fail is calculated based on the difference between unity and its previous damage. The current damage rate at all the other locations ahead of the crack tip is multiplied by this number of cycles and then added to the previous fatigue damage values.

This calculation process is repeated to grow the crack, with the number of cycles required to fail the current ligament of material always varying because of the changing stress fields and different amounts of prior fatigue damage. Crack growth rates throughout this process are defined as the calculation step length divided by the number of cycles to fail each successive ligament.

The crack growth rate predictions following an overload were then compared with experimental data from a room temperature  $R=0$  corner crack growth test with overloads to twice the normal cycle amplitude at datum  $K_{max}$  values of 17.3 and 25.8 MPa $\sqrt{m}$  run at Swansea University on FG RR1000 material. Each overload was modelled separately in the spreadsheet, starting the calculations at a crack length 0.3mm smaller than that associated with the overload and continuing for a further 0.7mm. Note that because of the different geometry correction factors for corner and edge cracks the modelled crack lengths for the overload cycles do not match those from the test, although the  $K$  values and stress fields are the same.


The experimental data and the model predictions are shown in Figure 13. The dashed black Paris line was fitted to those parts of the experimental data that were unaffected by the overloads.

Following both overloads, the predicted growth rates return to the datum cycle values when the extremes of the plastic zones from the current load and the overload are coincident. This behaviour results from the rules used to generate the stress fields following the load drop and is consistent with the assumptions made in the Wheeler [25] and Willenborg [26] overload retardation models.

For both overloads, the predictions of the reduced crack growth rates immediately after the overload are very good. The general curve shapes also look reasonable and are an improvement over those generated by the Wheeler and Willenborg models, which have a discontinuity in the growth rate where they return to Paris behaviour. The duration of the overload effects is under-predicted, however, which has been seen consistently in similar tests run at Swansea University and is considered to be associated with using corner crack test pieces.

In addition, the calculations show oscillations in the predicted crack growth rates as can be seen in the simulation of the first overload. This is thought to result from using finite width calculation steps and stress fields that sometimes have fluctuations and sub-surface peaks when the residuals from the overload are included. These stress field irregularities can cause the next calculation point to accumulate almost as much fatigue damage as at the current crack tip location. Very few cycles are then required to reach failure there, resulting in a high crack growth rate. The damage one step ahead of the new crack tip position will only have increased by a small amount during this step, however, and it may then require a higher number of additional cycles before it becomes unity. This results in a slow predicted crack growth rate in this increment and the behaviour can persist, resulting in oscillations in the predicted growth rate.

Overall, the method clearly shows promise in modelling post-overload behaviour and merits additional work to eliminate the currently predicted growth rate oscillations.

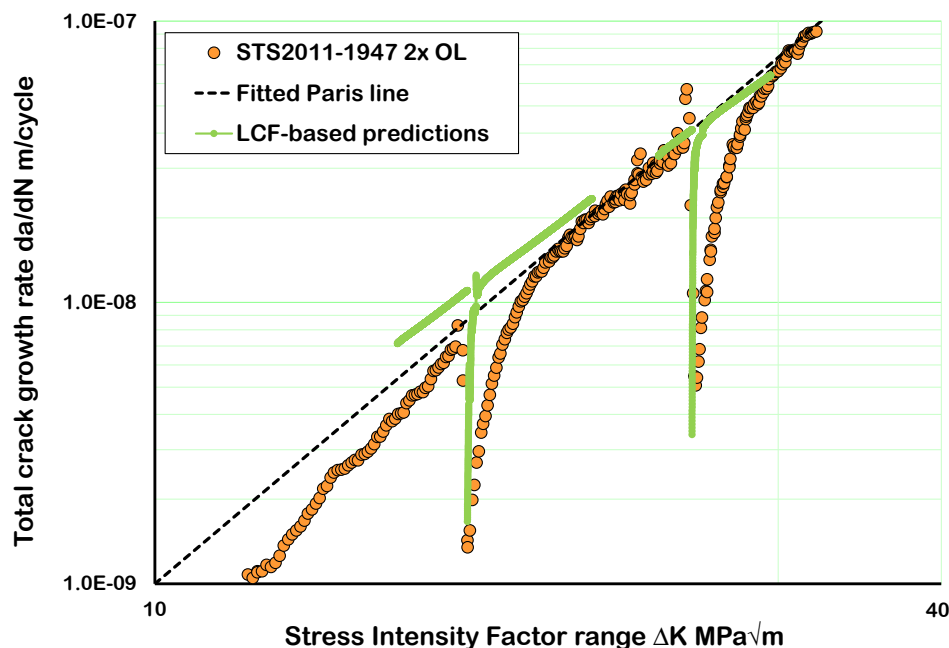

**Figure 13.** Comparison of overload crack growth rate predictions made based on fatigue behaviour with test data: R=0 corner crack growth test with single cycle overloads to twice baseline magnitude at  $K_{max}$  values of 17.3 and 25.8 MPa $\sqrt{m}$ , fine grain RR1000 material at 20 °C.

### 3. Conclusions

The finite element analysis style used has been shown to reproduce established geometry correction factors for edge cracks (and, in other work by Williams [27], for 3D corner cracks) very closely.

It has also been shown that a stress-based curve fit performed to fatigue test results on plain smooth FG RR1000 specimens can be used to generate R=0 low temperature crack growth rates that agree extremely well with database values. The predicted threshold  $\Delta K$  value, however, is slightly lower than that obtained from crack growth tests.

Use of the calculation method to predict crack growth behaviour at other loading R-ratios has provided an analytical basis for the similarity in growth rates observed in R=0 and R=-1 loading cycles at the same peak load. The prediction of a slightly increased  $da/dN$ - $\Delta K$  curve slope at R=0.5 was unexpected. Other test data were examined to try to substantiate these trends but the results were inconclusive.

Good predictions of post-overload behaviour were also made using the fatigue analogy for crack growth. The current calculation method would benefit from improvements, however, to reduce the oscillations that are sometimes seen in the predicted crack growth rates.

Overall, the calculation framework presented in this paper for relating low cycle fatigue and crack growth data has shown significant promise and warrants further development.

**Author Contributions:** Conceptualization, S.W.; methodology, S.W.; software, S.W.; validation, S.W.; formal analysis, S.W.; resources, M.W., M.H.; data curation, M.H.; writing—original draft preparation, S.W.; writing—review and editing, M.W., M.H.; supervision, M.W.; funding acquisition, M.H. All authors have read and agreed to the published version of the manuscript.

**Funding:** The work was carried out as part of an EPSRC-funded iCASE Ph.D. programme under project EP/V519601/1 with top-up funding from Rolls-Royce plc.

**Data Availability Statement:** Data can be requested and accessed from the article author.

**Acknowledgments:** The academic authors are grateful for the financial support provided for this work by Rolls-Royce plc. The work was carried out at the Institute of Structural Materials in Swansea University as part of a Ph.D. project.

**Conflicts of Interest:** The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

## Abbreviations

The following abbreviations are used in this manuscript:

a	Crack length
$\alpha$	Lifing curve parameter related to its intercept
$\beta$	Lifing curve parameter related to its slope
$\Delta K_{\text{eff}}$	Effective stress intensity factor range
K	Stress intensity factor
$K_{\text{max}}$	Maximum stress intensity factor in loading cycle
$K_{\text{op}}$	Stress intensity factor at which the crack is fully open
m	Walker exponent
N	Number of applied fatigue cycles
$N_f$	Number of fatigue cycles to failure
PD	Potential Drop
r	Distance ahead of the crack tip
$\rho^*$	Notch root radius and calculation block size in the Noroozi model
$\sigma_{\text{th}}$	Threshold stress value in fatigue curve equation
Y	Geometry correction factor in stress intensity formula

## References

1. Newman J Jr. A crack-closure model for predicting fatigue crack growth under aircraft spectrum loading. In: Chang JB and Hudson CM (eds) Methods and models for predicting fatigue crack growth under random loading, ASTM STP 748, 1981, pp.53–84.
2. Wang GS and Blom AF. A strip model for fatigue crack growth predictions under general load conditions. *Eng. Fract. Mech.* 1991; Vol. 40, No. 3: 507-533.
3. Vidler J, Kotousov A and Ng C-T. Residual closure of fatigue cracks. *Int. J. Solids Struct.* 2024; 302 112973.
4. Rose LRF and Wang CH. Self-similar analysis of plasticity-induced closure of small fatigue cracks. *J. Mech. Phys. Solids* 2001; 49: 401-429.
5. Beretta S and Carboni M. A Strip-Yield algorithm for the analysis of closure evaluation near the crack tip. *Eng. Fract. Mech.* 2005; 72: 1222–1237.
6. Paluskiewicz S, Narasimhachary SB, Shinde SR et al. Crack closure of Ni-based superalloy 718 at high negative stress ratios. *Int. J. Fatigue* 2022; 160 106822
7. Chen DL, Weiss B and Stickler R. The effective fatigue threshold: significance of the loading cycle below the crack opening load. *Int. J. Fatigue* 1994; 16: 485-491.
8. Castro JTP, Meggiolaro MA and Miranda ACO. Singular and non-singular approaches for predicting fatigue crack growth behavior. *Int. J. Fatigue* 2005; 27: 1366-1388.
9. Vasudevan AK, Sadananda K and Holtz RL. Analysis of vacuum fatigue crack growth results and its implications. *Int. J. Fatigue* 2005; 27: 1519-1529.
10. Fleck NA. Influence of stress state on crack growth retardation. ASTM STP 924, 1988, pp.157-183.
11. Noroozi A, Glinka G and Lambert S. A study of the stress ratio effects on fatigue crack growth using the unified two-parameter fatigue crack growth driving force. *Int. J. Fatigue* 2007; 29: 1616–1633.
12. Ferreira S, Pinho de Castro J and Meggiolaro M. Fatigue crack growth predictions based on damage accumulation ahead of the crack tip calculated by strip-yield procedures. *Int. J. Fatigue* 2017; 103: 557–575.
13. Creager M and Paris P. Elastic field equations for blunt cracks with reference to stress corrosion cracking. *Int. J. Fract. Mech.* 1967; 3: 247–52.

14. Neuber H. Theory of stress concentration for shear-strained prismatical bodies with arbitrary nonlinear stress–strain law. *ASME J. Appl.Mech.* 1961; 28: 544–551.
15. Ramberg W and Osgood W. Description of stress–strain curves by three parameters. Technical Note 902, National Advisory Committee For Aeronautics, Washington DC., 1943.
16. Smith KN, Watson P and Topper TH. A stress-strain function for the fatigue of metals. *J. Materials* 1970; 5: 767–778.
17. Coffin LF. A study of the effect of cyclic thermal stresses on a ductile metal. *Trans. ASME* 1954; 76: 931:950.
18. Brown W and Srawley J. Plane strain crack toughness testing of high strength metallic materials. ASTM STP 410, ASTM, Philadelphia, 1966.
19. Basquin OH. The exponential law of endurance test. *Proc. ASTM* 1910; 10: 625–630.
20. Walker K. Effects of Environment and Complex Load History on Fatigue Life. ASTM International, 1970.
21. Dinda S and Kujawski D. Correlation and prediction of fatigue crack growth for different R-ratios using  $K_{max}$  and  $\sigma K$ . *Eng. Fract. Mech.* 2004; 71: 1779–1790.
22. Zheng J and Powell BE. Effect of stress ratio and test methods on fatigue crack growth rate for nickel based superalloy Udimet720. *Int. J. Fatigue* 1999; 21: 507–513.
23. Bulloch JH. Effect of temperature on the threshold fatigue crack growth behavior of spheroidal graphite cast iron. *Int. J. Press. Vessels Pip.* 1993; 54: 497–522.
24. Huang X and Moan T. Improved modeling of the effect of R-ratio on crack growth rate. *Int. J. Fatigue* 2007; 29: 591–602.
25. Wheeler OE. Spectrum loading and crack growth. *J. Basic Eng.* 1972; 94: 181-186.
26. Willenborg J, Engle R and Wood H. A Crack Growth Retardation Model Using An Effective Stress Concept. Report AFDL-TM-FBR-71-1, 1971.
27. Williams SJ. Geometry correction factor polynomials for corner crack test pieces accounting for constrained boundary conditions. *Finite Elem. Anal. Des.* 2023; 224: 103985.

**Disclaimer/Publisher’s Note:** The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.