

Biodentine Stimulates Calcium-Dependent Osteogenic Differentiation of Mesenchymal Stromal Cells from Periapical Lesions

[Mile Eraković](#) , [Marina Bekić](#) , [Jelena Đokić](#) , [Sergej Tomić](#) , Dragana Vučević , Luka Pavlović , Miloš Duka ,
[Milan Marković](#) , [Dejan Bokonjić](#) , [Miodrag J Čolić](#) *

Posted Date: 13 March 2025

doi: 10.20944/preprints202503.0957.v1

Keywords: Biodentine; Mesenchymal Stromal Cells; Proliferation; Osteogenic Differentiation; Gene Expression



Preprints.org is a free multidisciplinary platform providing preprint service that is dedicated to making early versions of research outputs permanently available and citable. Preprints posted at Preprints.org appear in Web of Science, Crossref, Google Scholar, Scilit, Europe PMC.

Copyright: This open access article is published under a Creative Commons CC BY 4.0 license, which permit the free download, distribution, and reuse, provided that the author and preprint are cited in any reuse.

Article

Biodentine Stimulates Calcium-Dependent Osteogenic Differentiation of Mesenchymal Stromal Cells from Periapical Lesions

Mile Eraković ¹, Marina Bekić ², Jelena Đokić ³, Sergej Tomić ², Dragana Vučević ⁴,
Luka Pavlović ², Miloš Duka ¹, Milan Marković ², Dejan Bokonjić ⁵ and Miodrag Čolić ^{5,6,*}

¹ Clinic for Stomatology, Medical Faculty of the Military Medical Academy, University of Defense, 11154 Belgrade, Serbia

² Institute for the Application of Nuclear Energy, University of Belgrade, 11080 Belgrade, Serbia

³ Institute of Molecular Genetics and Genetic Engineering, University of Belgrade, 11042 Belgrade, Serbia

⁴ University of Defence, Faculty of Medicine of the Military Medical Academy, Center for Medical Scientific Information

⁵ University of East Sarajevo, Medical Faculty Foča, 73300 Foča, Bosnia and Herzegovina

⁶ Serbian Academy of Sciences and Arts, 11000 Belgrade, Serbia

* Correspondence: miodrag.colic@sanu.ac.rs

Abstract: Biodentine, a tricalcium silicate cement, has emerged as a retrograde root-end filling material to promote periapical lesion (PL) healing after apicoectomy. However, its underlying mechanisms remain unclear. This study tested the hypothesis that Biodentine stimulates the osteogenic differentiation of mesenchymal stromal cells (MSCs) derived from PLs. The Biodentine extract (B-Ex) was prepared following ISO 10993-12 by incubating polymerized Biodentine in RPMI medium (0.2 g/mL) for three days at 37 °C. B-Ex, containing both released microparticles and soluble components, was incubated with PL-MSCs cultured in either basal MSC medium or suboptimal osteogenic medium. Osteogenic differentiation was assessed by Alizarin Red staining and the expression of 20 osteoblastogenesis-related genes, including transcription factors, signaling molecules, extracellular matrix proteins, bone hormones, cytokines/cytokine receptors, and bone remodeling factors. Non-cytotoxic concentrations of B-Ex stimulated the proliferation of PL-MSCs and induced their osteogenic differentiation in a dose-dependent manner, with a significantly enhanced effect in suboptimal osteogenic medium. The differentiation process was prolonged relative to optimal osteogenic conditions. The stimulatory effect of B-Ex was primarily calcium-dependent, as it was reduced by 85% when B-Ex was treated with the calcium-chelating agent EGTA. In conclusion, Biodentine promotes the osteogenic differentiation of PL-MSCs in a calcium-dependent manner, supporting its stimulatory role in periapical healing.

Keywords: Biodentine; Mesenchymal Stromal Cells; Proliferation; Osteogenic Differentiation; Gene Expression

1. Introduction

Biodentine belongs to the group of Mineral Trioxide Aggregate (MTA) cements, which have been extensively utilized in various pulp and endodontic procedures. Developed in 2009, Biodentine is composed of tricalcium silicate (80.7%), calcium carbonate (14.25%), and zirconium dioxide (5%) to enhance radiopacity. Compared to other MTA cements, it offers a faster setting time (6–12 minutes) and superior mechanical properties. Its hardening process involves hydration, a silicate gel, and calcium hydroxide formation, with porosity gradually decreasing over time [1,2].

Biodentine forms a crystalline network with hard dental tissues, releasing calcium and hydroxide ions, which stimulate dentin formation and osteoblast activity. It is widely used in

dentistry for dentin replacement, pulp capping, perforation repair, pulpotomy, treatment of resorptions, or apexification. Its key properties include hermetic sealing, reduction of microleakage, and prevention of bacterial infiltration. Contact with dentin promotes hydroxyapatite deposition in dentinal tubules, enhancing chemical bonding and protection against demineralization. Biodentine is stable in moist environments and resistant to disintegration due to polymer additives. Its high pH (~12) provides antimicrobial properties and acts as a disinfectant [1,2].

Numerous studies have shown that Biodentine is a biocompatible material [3,4], although a certain degree of cytotoxicity has been observed when cells are cultured on Biodentine discs for extended periods or when Biodentine powder is used in high concentrations [5,6].

Biodentine's biological activity has been primarily evaluated through experimental models designed for its original indications, such as pulp repair, classifying it as a bioactive endodontic cement. Studies comparing Biodentine and MTA using primary human pulp cells showed that both materials promote cell proliferation, differentiation, migration, and mineralization with no significant differences in biological potential [7,8]. Additionally, studies on osteoblast cell lines and periodontal ligament stem cells showed that Biodentine promotes osteoblast differentiation, increases the expression of genes associated with osteoblast activation or differentiation, and induces hydroxyapatite crystal cluster formation. [9–12].

Due to its ability to stimulate osteoblasts and its effective sealing properties in the root canal, Biodentine has also been used in apical surgery. However, its effectiveness in this area is not sufficiently known. Current evidence is limited to positive findings from one clinical study [13] and several clinical cases demonstrating its effect on the healing of periapical lesions (PLs) after apicoectomy and retrograde root-end filling [14,15].

Our previous studies showed that Biodentine possesses immunomodulatory properties by suppressing pro-inflammatory cytokines and osteolytic mediators while augmenting anti-inflammatory cytokines in cultures of cells infiltrating PLs [16]. We hypothesized that Biodentine additionally stimulates regenerative processes in periapical tissue through the induction of osteoblast differentiation of mesenchymal stromal cells (MSCs). The hypothesis was evaluated in MSC cultures derived from PLs (PL-MSCs), which were cultivated with different concentrations of an extract obtained by incubating Biodentine in a culture medium. In addition, the role of calcium (Ca) in these processes was investigated. We believe this unique study model is suitable for drawing valid conclusions, as leachable components of Biodentine during root-end filling could reach periapical tissues and affect MSC differentiation.

2. Results

2.1. Establishment and Characterization of PL-MSCs

Four MSC lines were successfully established from clinically asymptomatic PLs. Each line was analyzed for its clonogenic potential, growth characteristics in culture, and morphological changes during passaging. Following four passages, the phenotypic profile was assessed, and the cells' ability to differentiate into osteoblasts, chondroblasts, and adipocytes was evaluated. One cell line was used to assess the effect of B-Ex on cytotoxicity and proliferation of PL-MSCs, three cell lines were used to assess their phenotypic properties, and two cell lines were employed to investigate the effect of B-Ex on the osteogenic differentiation of PL-MSCs. One cell line was used to study the role of Ca in osteogenic differentiation

PL-MSCs exhibited a fibroblast-like morphology, characteristic of MSCs derived from other tissues (Figure 1A). They also demonstrated clonogenic potential, as evidenced by their ability to form colony-forming unit-fibroblast (CFU-F) colonies (Figure 1B). All PL-MSCs displayed the capacity to differentiate into osteoblasts, chondroblasts, and adipocytes when cultured in appropriate induction media. However, they exhibited a higher differentiation potential toward osteoblasts and chondroblasts compared to adipocytes. The histochemical analysis of the respective cultures is presented in Figure 1C.

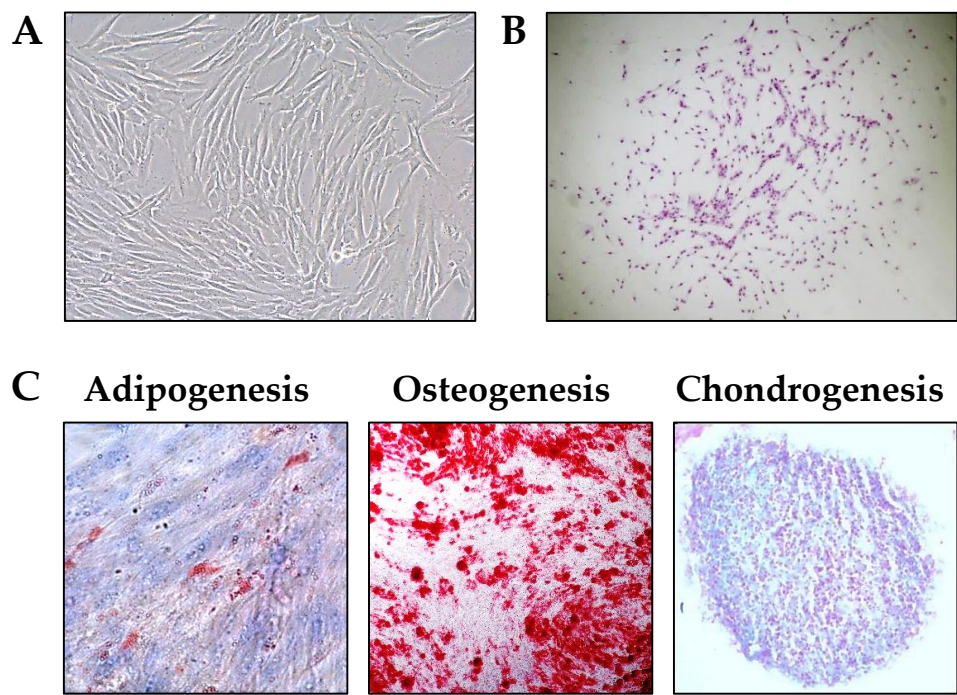


Figure 1. Fibroblastoid morphology (A), clonogenicity (B), and differentiation potential of PL-MSCs into adipocytes, osteoblasts, and chondroblasts (C).

The phenotypic characteristics of PL-MSCs, pooled from three cell lines, are summarized in Table 1, while fluorescence histograms of a representative cell line are shown in Supplementary Figure 1. The results show that all PL-MSCs expressed CD73, CD90, and CD166, while approximately 90% of the cells were positive for CD105 and CD39. A significantly lower percentage of cells expressed CD146 ($28.18 \pm 6.25\%$) and CD56 ($20.04 \pm 4.88\%$). The lowest expression levels were observed for STRO-1 ($8.06 \pm 4.60\%$) and SSEA4 ($12.12 \pm 5.56\%$). As anticipated, PL-MSCs did not express markers associated with hematopoietic stem cells (CD34), total hematopoietic cells (CD45), monocytes (CD14), T lymphocytes (CD3), or B lymphocytes (CD19), as less than 2% of the cells were positive for these markers.

Table 1. Phenotypic analysis of PL-MSC.

Markers	% positive cells
CD73	99.43 $\pm$ 0.34
CD90	99.52 $\pm$ 0.30
CD105	91.23 $\pm$ 3.24
CD166	99.02 $\pm$ 0.28
CD39	90.50 $\pm$ 3.64
CD146	28.18 $\pm$ 6.25
CD56	20.04 $\pm$ 4.88
STRO-1	8.06 $\pm$ 4.60
SSEA4	12.12 $\pm$ 5.56
CD45	1.12 $\pm$ 0.46
CD34	1.24 $\pm$ 0.37
CD14	1.50 $\pm$ 0.24
CD3	0.54 $\pm$ 0.14
CD19	0.48 $\pm$ 0.22

The phenotypic analysis of the PL-MSC cell lines after four passages in culture was performed as described in the *Materials and Methods* section. The results represent the mean percentage of positive cells from three different PL-MSC lines $\pm$ SD.

2.2. Cytotoxicity of the Biodentine Extract

B-Ex was prepared as described in the *Materials and Methods* section. The extract contained microparticles of Biodentine, had a pH value of 11.5, and a total Ca content of 828.33 mg/L (20.68 mM). Before use in subsequent experiments, the pH of B-Ex was adjusted to 7.4. PL-MSCs were treated with different concentrations of B-Ex for 24 and 72 hours, after which the metabolic activity of the cultures was assessed using the MTT assay.

The results presented in Figure 2A show that extract concentrations of 50% and higher significantly decreased cell viability at 72 hours, in a concentration-dependent manner ($p < 0.01$ and $p < 0.001$, respectively). After 24 hours, the concentrations of 75% and 100% B-Ex were cytotoxic. In contrast, lower concentrations (10%, and 30%) increased the metabolic activity of PL-MSCs, particularly after 72 hours, in a concentration-dependent manner ($p < 0.05$ and $p < 0.001$, respectively). The inhibition of MTT activity resulted from cell death, as confirmed by Propidium Iodide (PI) staining (Figure 2B), whereas the increased MTT activity was due to enhanced cell proliferation, as demonstrated by the increased incorporation of [3 H]-thymidine in the presence of 30% B-Ex ($p < 0.05$) (Figure 2C).

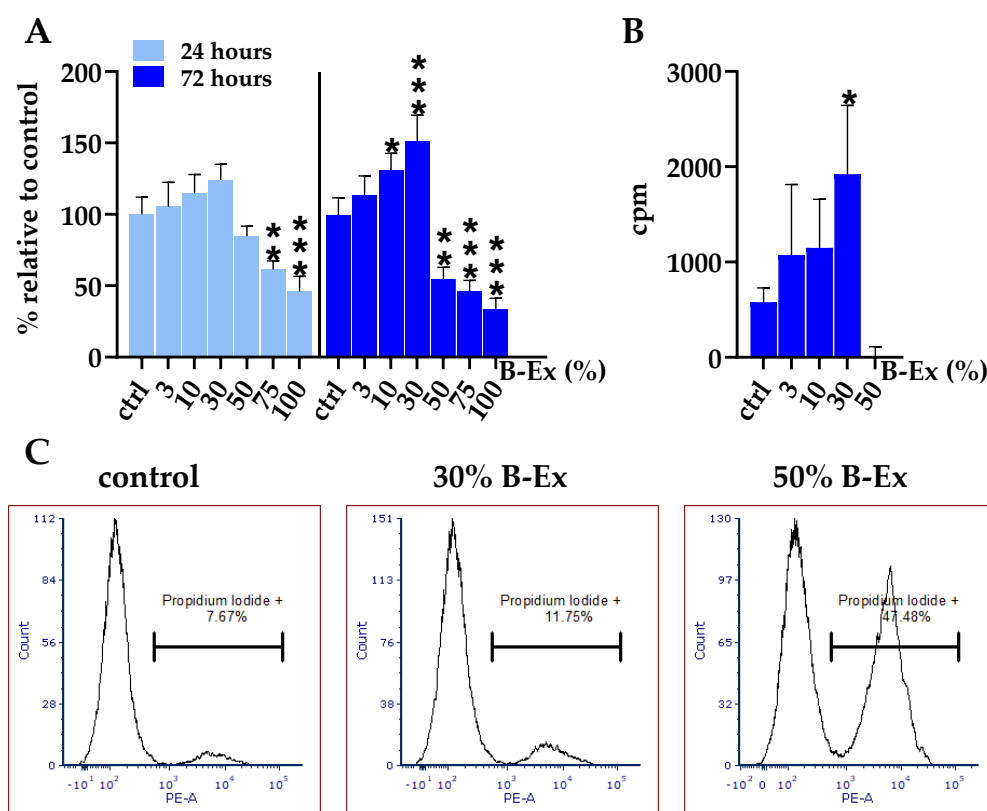


Figure 2. The effect of B-Ex on the metabolic activity (A), proliferation (B), and necrosis (C) of PL-MSCs. PL-MSCs were treated with different concentrations of B-Ex, as described in the *Materials and Methods* section. Metabolic activity was assessed using the MTT assay after 24 and 72 hours, while cell proliferation was evaluated by [3 H]-thymidine incorporation after 72 hours. Cell necrosis was determined by propidium iodide (PI) staining after 72 hours. Data are presented as the mean $\pm$ SD of triplicate cultures (A and B) or as representative histograms (C). * $p < 0.05$; ** $p < 0.01$; *** $p < 0.001$ compared to the corresponding controls (ctrl).

2.3. The Effect of Biodentine Extract on Osteogenic Differentiation of PL-MSCs

Based on the results of the proliferation assay, PL-MSCs were cultured with 10% and 30% B-Ex in the basal medium without any osteogenic stimuli. In addition, these concentrations of the extract were added to PL-MSCs, which were cultured either with the complete osteogenic medium or with basal medium supplemented with 30% osteogenic medium, referred to as the suboptimal osteogenic medium. After 21 days, the cultures were stained with Alizarin Red to visualize mineralized islands characteristic of osteoblasts.

The results presented in Figure 3 show that both concentrations of B-Ex significantly enhanced osteoblastogenesis in the suboptimal osteogenic medium ($p < 0.05$ and $p < 0.001$, respectively), as did the higher concentration of B-Ex in the control basal medium ($p < 0.001$). No significant modulation of osteoblastic differentiation was observed in the optimal osteogenic medium, in which osteogenic differentiation was highest.

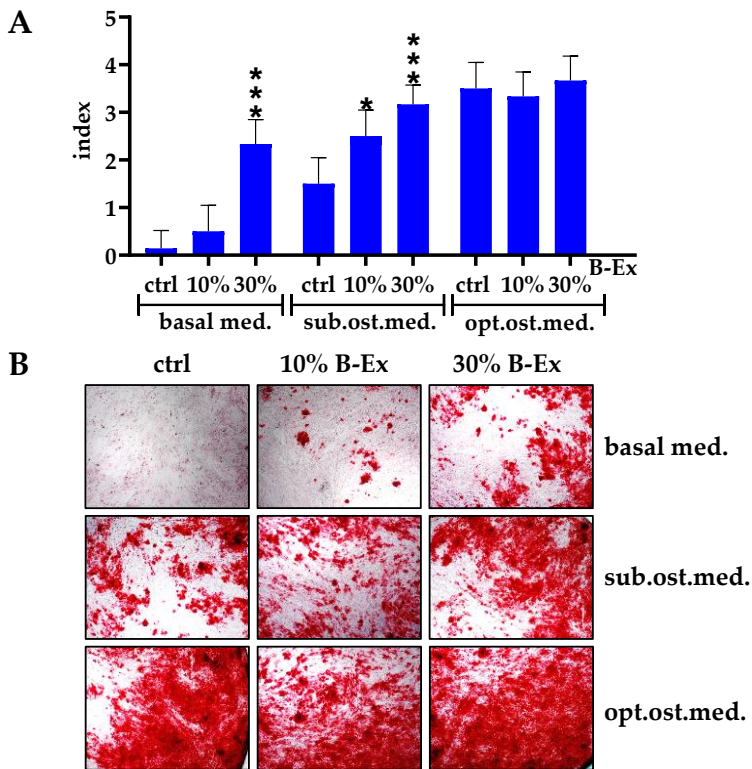


Figure 3. The effect of B-Ex on osteogenic differentiation of PL-MSCs as analyzed by Alizarin Red staining. PL-MSCs were cultivated in basal, suboptimal osteogenic, or optimal osteogenic medium with 10% or 30% B-Ex or without B-Ex (control) as described in the Materials and Methods sections. Results are presented as mineralization indexes (A) or representative images (B). * $p < 0.05$; *** $p < 0.001$ compared to the corresponding controls (ctrl).

2.4. The Biodentine Extract Significantly Modulates the Expression of Osteoblastic Genes

The next phase of the study aimed to evaluate the impact of two concentrations of B-Ex (10% and 30%) on the expression of 20 genes during the differentiation of PL-MSCs into osteoblasts, which were cultured in either basal medium or suboptimal osteogenic medium. Gene expression in PL-MSC cultures grown in the complete osteogenic medium served as a positive control. Since previous experiments indicated that B-Ex had no modulating effect in the complete osteogenic medium, these cultures were not treated with B-Ex. Gene expression was analyzed at day 5 (early phase) and day 16 (late phase) of osteogenic differentiation. All genes were analyzed at both phases of osteoblast differentiation.

2.5. Genes Expressed in Early and Late Phases of Osteogenic Differentiation

The expression of four early osteogenic differentiation genes such as runt-related transcription factor 2 (*RUNX2*), osterix (*SP7*), wingless-type MMTV integration site family member 2 (*WNT2*), and collagen type I alpha 1 chain (*COL1A1*), was evaluated, with the results shown in Figure 4. All genes were significantly upregulated ($p < 0.001$) in the early phase when PL-MSCs were cultured in the complete osteogenic medium (positive control), followed by a notable decline in expression in the late phase. A similar trend was observed in PL-MSCs treated with 30% B-Ex in a suboptimal osteogenic medium ($p < 0.001$). Higher concentrations of B-Ex in the basal medium upregulated *RUNX2*, *SP7*, and *COL1A1*, with a more pronounced effect in the late phase ($p < 0.001$). In contrast, *WNT2* was downregulated during the early phase ($p < 0.01$). Lower B-Ex concentrations had a pronounced upregulating effect on the *WNT2* expression in the suboptimal osteogenic medium, especially in the late phase ($p < 0.001$), and the opposite suppressive effect in the basal medium ($p < 0.01$).

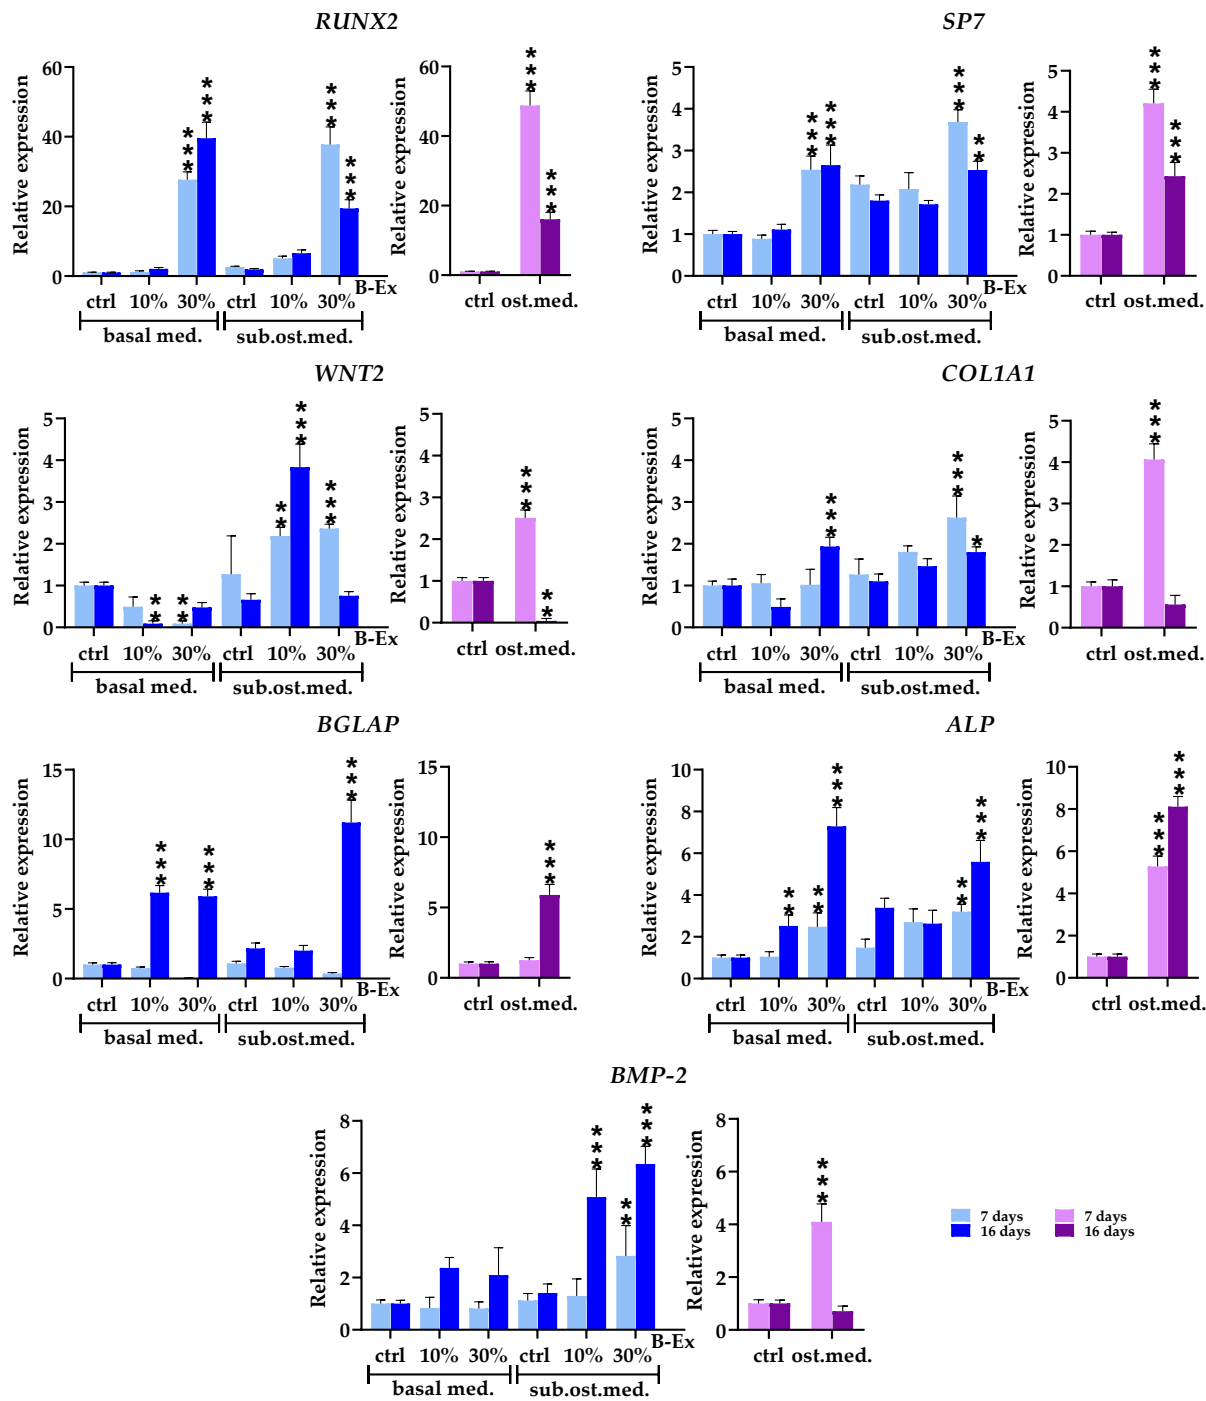


Figure 4. The effect of B-Ex on the expression of key osteoblastic genes in PL-MSCs. The methodology of the experiment is described in the *Materials and Methods* section. Data are presented as mean $\pm$ SD (n = 4) of relative mRNA expression compared to control PL-MSCs, used as index 1. * $p < 0.05$; ** $p < 0.01$; *** $p < 0.001$ compared to the corresponding controls (ctrl).

The expression of three genes predominantly active during the late phase of osteogenic differentiation, bone gamma-carboxyglutamate protein (*BGLAP*), alkaline phosphatase (*ALP*), and bone morphogenetic protein-2 (*BMP-2*) was evaluated. As shown in Figure 4, *BGLAP* and *ALP* exhibited significantly higher expression in the late phase in the complete osteogenic medium ($p < 0.001$) compared to the early phase, whereas *BMP-2* showed the opposite trend. However, in the presence of 30% B-Ex within a suboptimal osteogenic medium, all three genes were upregulated during the late phase ($p < 0.001$). Among them, *BMP-2* was also significantly upregulated at lower B-Ex concentrations ($p < 0.001$). A similar expression pattern was observed for both *BGLAP* ($p < 0.001$) and *ALP* ($p < 0.01$) in the basal medium with both B-Ex concentrations.

2.6. Cytokine/Cytokine Receptor Genes and Hormone Receptor Genes

The expression of three cytokine genes, transforming growth factor beta (TGF- β), fibroblast growth factor 2 (FGF2), and connective tissue growth factor (CTGF), was evaluated (Figure 5). TGF- β and FGF2 were significantly upregulated in the complete osteogenic medium during both phases, with a stronger effect in the late phase ($p < 0.001$). A similar pattern was observed in the 30% B-Ex/suboptimal osteogenic medium ($p < 0.001$ and $p < 0.05$, respectively). Conversely, CTGF showed an opposite pattern of expression (upregulation only in the early phase; $p < 0.001$), with lower concentrations of B-Ex further decreasing its expression in the late phase ($p < 0.05$). However, in the basal medium, neither concentration of B-Ex significantly altered the expression of the three genes.

The expression of interleukin 6 signal transducer (*IL-6ST*) mRNA was significantly upregulated only in the early phase in the complete osteogenic medium ($p < 0.001$) and 30% B-Ex/suboptimal osteogenic medium ($p < 0.05$). In the osteogenic medium, the growth hormone receptor gene (*GHR*) was expressed only in the early phase of osteogenic differentiation ($p < 0.001$). Higher concentrations of B-Ex added to both suboptimal osteogenic and basal medium exerted the same stimulatory effect but only in the late phase ($p < 0.001$), as did the lower concentration of B-Ex in the suboptimal osteogenic medium ($p < 0.05$). Upregulation of the parathyroid hormone receptor gene (*PTHr*) was seen in the late phase of osteogenic differentiation in osteogenic and 30% B-Ex/basal medium ($p < 0.001$). In contrast, an increase in PTHr expression in 30% B-Ex/suboptimal osteogenic medium was noticed in the early phase ($p < 0.05$) (Figure 5).

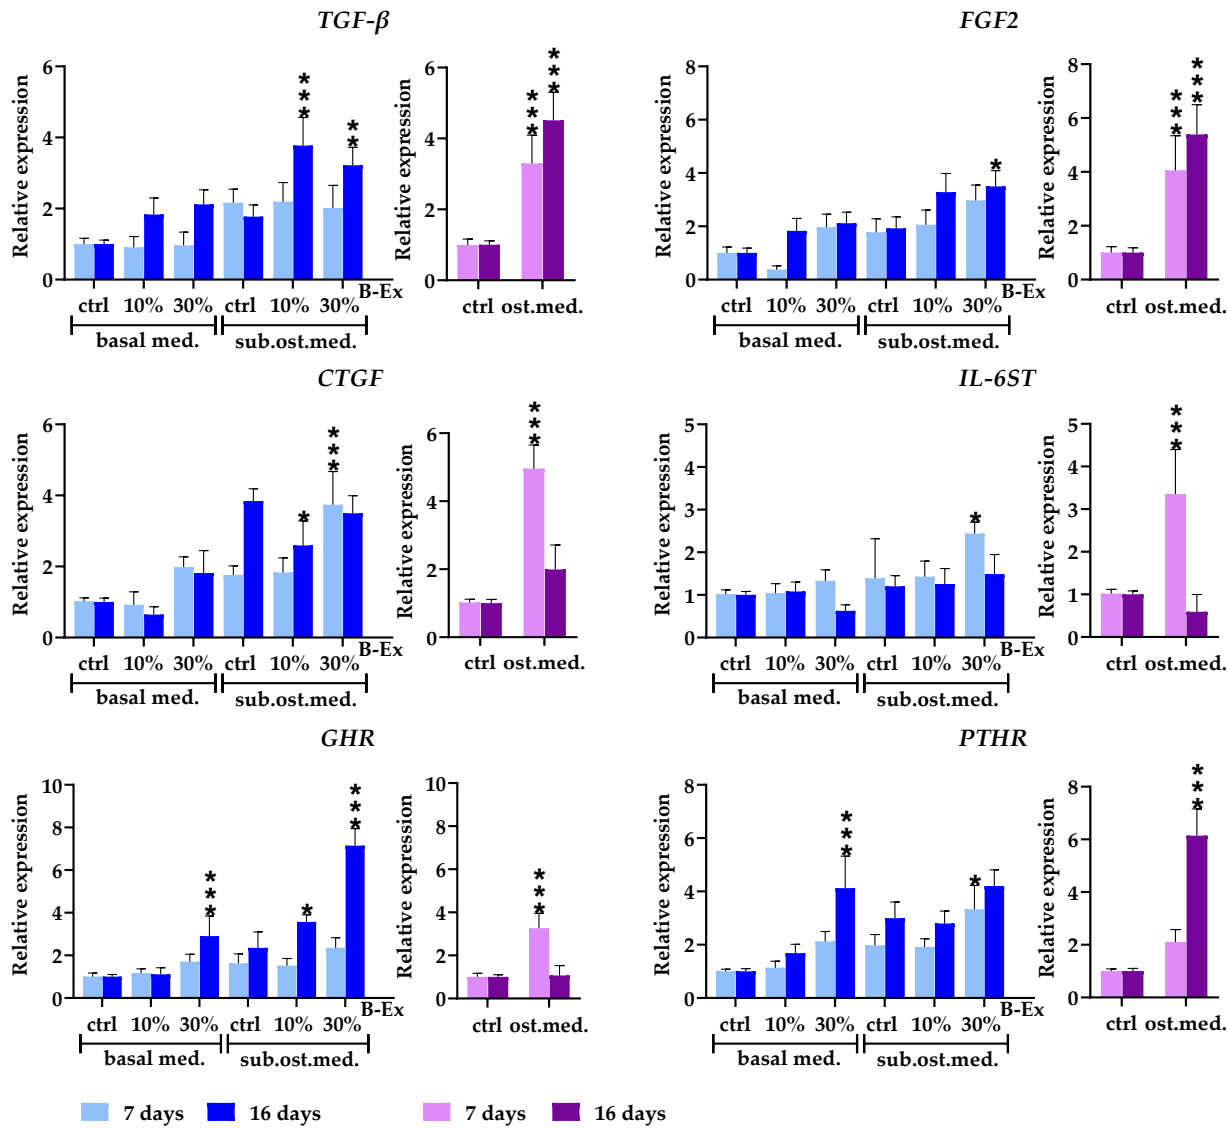


Figure 5. The effect of B-Ex on the expression of cytokines/cytokine receptor and hormone receptor genes in PL-MSCs. The methodology of the experiment is described in the *Materials and Methods* section. Data are presented as mean ± SD (n = 4) of relative mRNA expression compared to control PL-MSCs, used as index 1. *p < 0.05; **p < 0.01; ***p < 0.001 compared to the corresponding controls (ctrl).

2.7. Genes Modeling Bone and Extracellular Matrix

Three genes modeling bone and extracellular matrix, receptor activator of nuclear factor kappa-B ligand (RANKL), cathepsin K (CTSK), and versican (VCAN) were analyzed (Figure 6). In the complete osteogenic medium, all genes were upregulated only in the early phase of osteoblastic differentiation, followed by a decrease to basal levels (RANKL and CTSK) or complete suppression (VCAN) (p < 0.01) in the late phase. Higher concentrations of B-Ex increased the expression of RANKL in the early phase in both control basal medium (p < 0.05) and suboptimal osteogenic medium (p < 0.01). In contrast, neither concentration of B-Ex modulated the expression of CTSK and VCAN, regardless of the medium used.

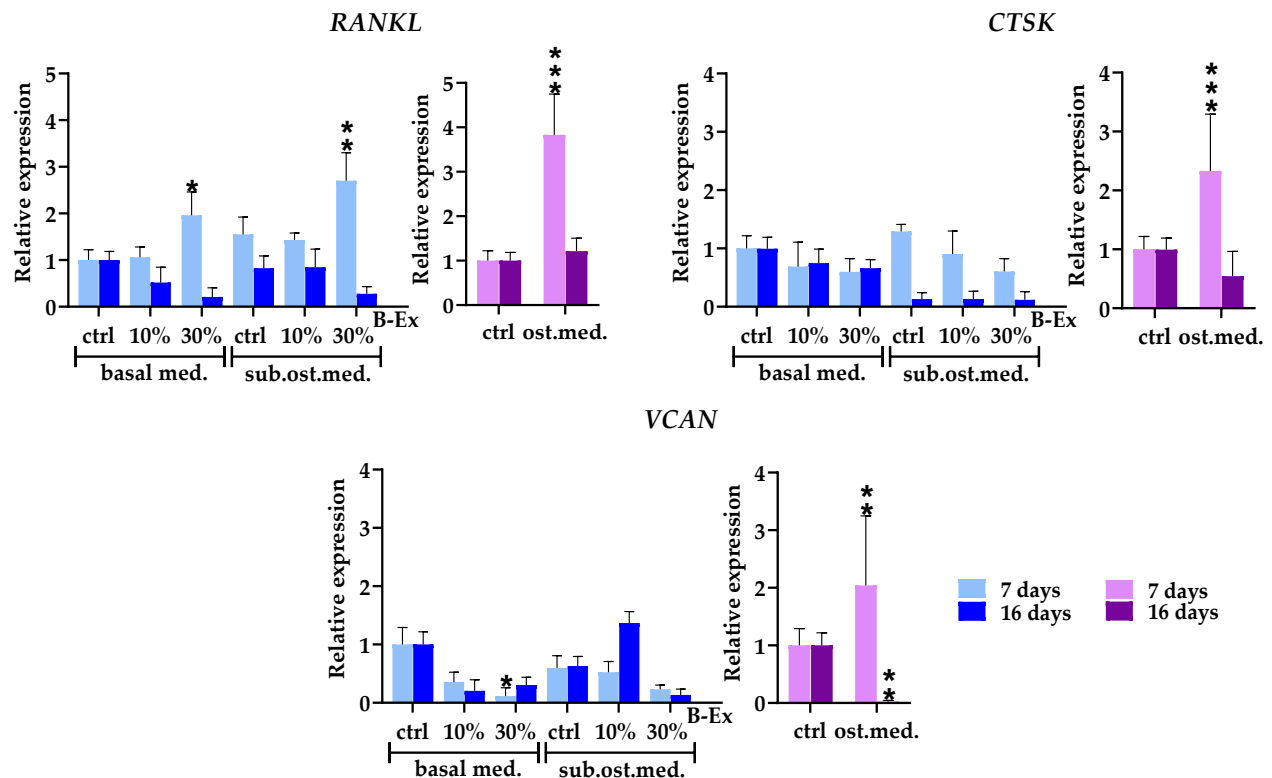


Figure 6. The effect of B-Ex on the expression of genes modeling bone and extracellular matrix in PL-MSCs. The methodology of the experiment is described in the *Materials and Methods* section. Data are presented as mean $\pm$ SD ($n = 4$) of relative mRNA expression compared to control PL-MSCs, used as index 1. * $p < 0.05$; ** $p < 0.01$; *** $p < 0.001$ compared to the corresponding controls (ctrl).

2.8. Genes Modulating Osteoblast Signaling

Four genes involved in osteoblast signaling, FosB proto-oncogene, AP-1 transcription factor subunit (FOSB), FOS like 2, AP-1 transcription factor subunit (FOSL2), discoidin domain receptor tyrosine kinase 1 (DDR1), and discoidin domain receptor tyrosine kinase 2 (DDR2), were evaluated. Results are presented in Figure 7. The expression of FOSB was increased in the complete osteogenic medium and 30% B-Ex/suboptimal osteogenic medium during the late phase of osteoblast differentiation ($p < 0.001$). However, the same concentration of B-Ex had an inhibitory effect in the basal medium. The expression of FOSL2 was downregulated during both investigated phases of osteoblastic differentiation ($p < 0.001$). However, 30% B-Ex had a stimulatory effect in both the suboptimal osteogenic and basal medium ($p < 0.001$) in the late phase. In contrast, FOSL2 expression in PL-MSCs cultured in the basal medium was significantly down-regulated with both concentrations of the extracts at the early phase of osteogenic differentiation ($p < 0.001$).

The expression of DDR1 was significantly upregulated in the complete osteogenic medium ($p < 0.001$) during the early phase of osteoblastic differentiation, followed by a significant decline thereafter. A similar stimulatory effect was observed during the early phase with both concentrations of B-Ex in the basal medium ($p < 0.001$), as well as with 30% B-Ex in the suboptimal osteogenic medium ($p < 0.001$). The expression of DDR2 was lower than that of DDR1, but followed a similar pattern—upregulation in the early phase of PL-MSCs differentiation in the presence of 30% B-Ex (both types of medium) as well as in the complete osteogenic medium ($p < 0.001$).

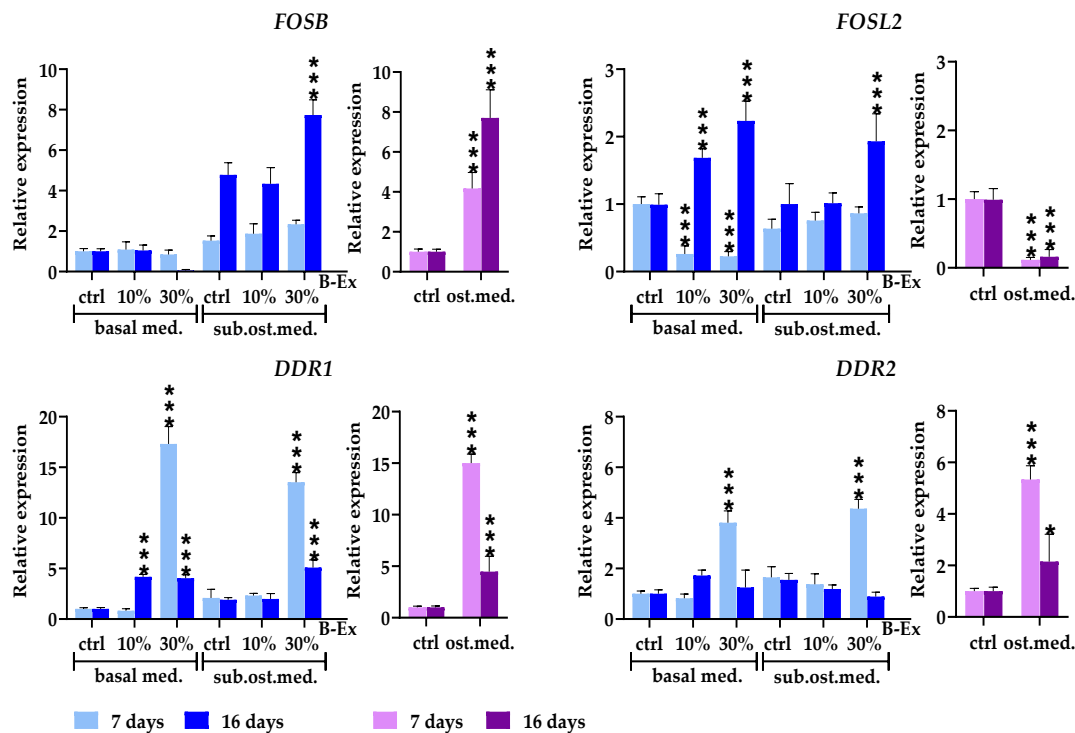


Figure 7. The effect of B-Ex on the expression of genes modulating osteoblast signaling in PL-MSCs. The methodology of the experiment is described in the *Materials and Methods* section. Data are presented as mean $\pm$ SD (n = 4) of relative mRNA expression compared to control PL-MSCs, used as index 1. *p < 0.05; ***p < 0.001 compared to the corresponding controls (ctrl).

2.9. The Role of Calcium in PL-MSC Proliferation and Osteoblastic Differentiation Induced by Biodentine Extract

To investigate the role of Ca ions in PL-MSC proliferation and osteoblastic differentiation induced by B-Ex, we used EGTA, a Ca-chelating agent. PL-MSCs cultivated in the complete basal medium were treated with either 30% B-Ex alone or 30% B-Ex with 2 mM EGTA for 24 hours. After this incubation, the extract and extract/EGTA were washed away, and the cells were further cultured for an additional 48 hours. Cell proliferation and RUNX2 expression were then assessed. A parallel set of cultures was treated with 6.2 mM Ca (matching the concentration determined in 30% B-Ex), with and without EGTA, as a specific control.

The results, presented in Table 2, show that a 24-hour exposure to CaCl₂ was sufficient to trigger both proliferation and RUNX2 expression in PL-MSCs (p < 0.001), and these effects were completely inhibited by EGTA. Proliferation and RUNX2 expression were also increased in PL-MSC cultures treated with 30% B-Ex (p < 0.001) and both parameters were slightly higher compared to Ca-supplemented cultures. However, a statistically significant difference (p < 0.05) was observed only at the level of RUNX2 expression. EGTA completely suppressed B-Ex-induced cell proliferation, while the suppression of RUNX2 expression was approximately 85%.

Table 2. The effect of EGTA pretreatment on proliferation and *RUNX2* expression in PL-MSCs stimulated with Ca or B-Ex.

Culture conditions	Proliferation (cpm)	RUNX2 expression
Negative control	642 ± 88	1.00 ± 0.12
Ca	1864 ± 198***	16.34 ± 1.92***
Ca + EGTA	706 ± 102**	0.92 ± 0.04***
30% B-Ex	2122 ± 170***	22.6 ± 3.90*** #
30% B-Ex + EGTA	734 ± 102***	3.70 ± 0.86*** **

PL-MSCs were pretreated with CaCl₂ (6.2 mM Ca) or 30% B-Ex, with or without 2 mM EGTA, for 24 hours, followed by washing and further culture in the complete basal medium for an additional 48 hours. Results are presented as mean ± SD (n = 3). *p < 0.001 vs. the negative control. **p < 0.01; ***p < 0.001 vs. corresponding controls (without EGTA). #p < 0.05 vs. Ca-supplemented cultures.

3. Discussion

Biodentine has recently been investigated as a root-end filling material in endodontic surgery [13–15]. However, it remains unclear whether its beneficial effects on periapical wound healing are primarily due to improved root obturation or its additional support for osteogenesis. To test this hypothesis, we prepared an extract of this cement (B-ex) and used it to study its effect on the differentiation of PL-MSCs into osteoblasts. This original *in vitro* model mimics the impact of Biodentine’s released compounds on the osteoinductive potential of this population of inflammatory MSCs [13–15], which come into close contact *in vivo* with Biodentine and its components.

We showed that PL-MSCs satisfy all the characteristics of MSCs as defined by Dominici et al. [17], including fibroblastoid morphology, adherence to plastic substrates, clonogenicity, differentiation potential into osteoblasts, chondroblasts, and adipocytes, as well as the expression of characteristic MSC markers. PL-MSCs highly or moderately expressed CD73, CD90, CD105, CD166, CD39, CD146, and CD56, but exhibited low levels of STRO-1+ and SSEA4+ cells, similar to the PL-MSCs we previously established [18]. Some specific characteristics are most probably related to the fact that PL-MSCs, established from an inflamed microenvironment, originate both from residual periodontal ligament cells and pericytes from newly formed vasculature [18] within the granulomatous tissue of PLs.

The initial screening tests aimed to determine non-cytotoxic concentrations of B-Ex for further studies. Although Biodentine has been reported to be non-cytotoxic, as documented in studies on L929 cells [19,20], dental pulp fibroblasts [21], odontoblasts [22], osteoblasts [23], and SHED MSCs [4], the results of our study, performed strictly by ISO 10993-5 [24], showed that concentrations of 50% B-Ex and higher are cytotoxic. These findings align with those of previous studies investigating the effects of a powder prepared from polymerized and hardened Biodentine [5], or a conditioned medium of Biodentine [6], prepared under similar conditions as in our study. The cytotoxic effect may be attributed to increased concentrations of Ca or other ions and/or microparticles released from Biodentine during the extraction procedure [4,5,24]. An increased pH value, as suggested by other authors [5], is not relevant since in our study the pH of the extract was adjusted to physiological values.

The key finding of this study is that B-Ex stimulates PL-MSCs proliferation and osteoblast differentiation in complete α-MEM, further enhancing osteoblastogenesis in the 30% osteoinductive medium. However, these effects were less pronounced compared to the complete osteogenic medium. MSC differentiation into osteoblasts is a complex process involving extracellular and hormonal interactions that activate intracellular signaling pathways and transcription factors [25,26]. *RUNX2* plays a central role by regulating key pathways (FGF, Hedgehog, WNT, Pthlh) and transcription factors (SP7, Dlx5), promoting osteoblast differentiation while inhibiting chondrogenesis [27,28]. Canonical WNT signaling, particularly WNT2, activates *RUNX2* and *SP7* transcription via β-catenin [28,29], providing the rationale for our gene expression analysis.

In the osteoinductive medium, *RUNX2* peaked early (40-fold increase), with moderate *SP7* and *WNT2* expression. In the late phase, *RUNX2* and *SP7* declined, while *WNT2* was suppressed. A similar but weaker pattern appeared under suboptimal osteogenic conditions in the presence of higher concentrations of B-Ex, confirming the primary role of *WNT2* in regulating the other two genes. However, this hypothesis was not supported when B-Ex was used without additional osteogenic stimuli, as the increased expression of *RUNX2* and *SP7* was followed by suppressed *WNT2* expression. Moreover, lower concentrations of B-Ex in a suboptimal osteogenic medium prolonged *WNT2* expression until the late phase without affecting *RUNX2* and *SP7*. Based on these findings, it can be postulated that suboptimal osteogenic stimulation prolongs osteogenic differentiation of PL-MSCs and modifies osteogenic signaling in these cells. However, this presumption requires further verification.

Three key genes involved in matrix mineralization are *BGLAP*, *COL1A1*, and *ALP*. *BGLAP* encodes osteocalcin (OCN), a late osteoblast marker essential for bone mineralization and remodeling [30]. OCN binds calcium and hydroxyapatite, facilitating mineral deposition, while its soluble form acts as a hormone in various physiological processes [30,31]. It enhances bone formation, osteoblast adhesion, and bone healing around hydroxyapatite-based composites, relevant to Biodentine [32,33]. We observed consistently higher *BGLAP* expression in the late differentiation phase across all conditions, with B-Ex further enhancing its levels beyond those in the complete osteogenic medium.

BGLAP expression is regulated by factors such as parathyroid hormone (PTH) [31,34]. We detected increased *PTHrP* expression in the late differentiation phase, coinciding with *BGLAP* upregulation. *PTHrP*, a G-protein-coupled receptor for PTH and PTH-related peptides, activates cAMP-PKA and calcium-PKC pathways. B-Ex-induced *PTHrP* upregulation may contribute to calcium homeostasis and bone remodeling by promoting osteoblast proliferation, reducing apoptosis, counteracting PPAR γ inhibition, and enhancing bone formation [35]. A similar pattern was observed for *GHR*, a receptor mediating growth hormone's anabolic effects on bone via insulin-like growth factor-1 (IGF-1), which stimulates osteoblast activity and matrix deposition [36]. The B-Ex stimulatory effect, particularly in basal medium, suggests that this bioactive cement promotes mineralization by regulating *GHR* and *PTHrP* expression.

COL1A1 expression peaked early in the complete osteoinductive medium before declining, following a similar pattern under suboptimal conditions. B-Ex enhanced its early expression in suboptimal conditions and increased its late-phase expression in the control medium, paralleling *RUNX2*. Type I collagen, regulated by *RUNX2* and *Osterix* (*SP7*) via p38 and ERK signaling, constitutes 90% of bone proteins [37]. While both *BGLAP* and *COL1A1* typically rise as osteoblasts mature, we confirmed this only for *BGLAP*, possibly due to timing differences or PL-MSC-specific traits.

Unlike *COL1A1*, *ALP* followed *BGLAP*'s late-phase increase across all conditions, with B-Ex further stimulating its expression. *ALP* is crucial for calcification and a key marker of dental MSC differentiation and bone regeneration [38]. Though often considered an early osteoblast marker, its higher late-phase expression in our study suggests prolonged differentiation and mineralization, aligning with other gene expression patterns in PL-MSC cultures with B-Ex.

BMP-2, a late marker of osteoblast differentiation, belongs to the BMP cytokine family within the TGF- β superfamily. Originally isolated from the mineralized bone matrix, BMP-2, along with BMP-4, BMP-5, and BMP-7, promotes MSC osteoblast differentiation and bone formation, with BMP-2 exhibiting the highest activity [39]. It binds to membrane receptors, activating the Smad pathway to regulate *RUNX2*, *SP7*, and *ALP* expression [40]. Our results indicate increased BMP-2 expression in the early phase of PL-MSC differentiation in a complete osteogenic medium, followed by inhibition in the late phase. However, in B-Ex cultures, BMP-2 expression was stimulated in the late phase, suggesting again that B-Ex prolongs osteoblastic differentiation under suboptimal conditions.

TGF- β mRNA expression exhibited an inverse pattern, with higher levels in the early phase under suboptimal osteogenic conditions and the late phase under optimal conditions. B-Ex stimulated both cytokines in the late differentiation phase across control and suboptimal cultures.

This suggests that BMP-2 is more crucial in early osteogenesis, while TGF- β dominates later, at least in our model. TGF- β , a multipotent cytokine, regulates proliferation, differentiation, migration, adhesion, and extracellular matrix synthesis [41]. In bone, it is produced by osteoblasts and osteocytes, promoting MSC migration and early osteoblast differentiation while inhibiting late differentiation and enhancing proliferation and mineralization. These effects vary depending on TGF- β concentration, culture conditions, MSC type, and cell density [42].

B-Ex also upregulated FGF2 expression in both culture conditions, with a stronger effect in the late osteoblastic differentiation phase. As a key member of the FGF family, FGF-2 regulates bone formation and osteoblast differentiation [43] while stimulating osteoprogenitor proliferation through MAPK, PI3K/Akt, and ERK pathways. Beyond bone formation, FGF-2 participates in angiogenesis, wound healing, morphogenesis, and metabolism [44]. It promotes the expression of *RUNX2*, *COL1A1*, *ALP*, and *BGLAP*, facilitating extracellular matrix deposition [45]. The observed positive correlation between *FGF2* and *BGLAP*, as well as *AP*, suggests that Biodentine's effect on *FGF2* expression is more relevant for bone mineralization than for other functions.

CTGF is a matricellular protein from the CCN family that regulates osteoblast differentiation by promoting extracellular matrix (ECM) production, osteoblast proliferation, and bone matrix protein expression, such as collagen and osteocalcin. It is involved in key signaling pathways, including TGF- β and Wnt, essential for bone formation and remodeling [46]. Our findings show increased *CTGF* expression in the early phase of osteogenic differentiation, both in standard and suboptimal osteogenic cultures supplemented with 30% B-Ex, suggesting its primary role in ECM stimulation. This aligns with the upregulation of *VCAN*, *CTSK*, and *RANKL*, though this correlation was significant only under optimal conditions.

VCAN encodes a chondroitin sulfate proteoglycan that supports early osteoblast differentiation by facilitating MSC adhesion, ECM organization, and signaling through Wnt/ β -catenin and TGF- β [47]. *CTSK*, a lysosomal cysteine protease, primarily functions in osteoclasts but also contributes to osteoblast matrix turnover and osteoblast-osteoclast communication [48]. Similarly, *RANKL* activates osteoclasts via *RANK* binding but also plays a role in MSC differentiation, particularly in early osteogenesis [49]. In cultures with Biodentine, our results did not support a major role for *VCAN* and *CTSK* under suboptimal osteogenic conditions, except for *RANKL*, suggesting that other genes may be more relevant or that the timing of gene expression analysis was suboptimal.

IL-6ST is a key mediator in the IL-6 signaling pathway, crucial for osteoblast proliferation and differentiation. By activating *IL-6ST*, IL-6 upregulates essential osteogenic genes (*RUNX2*, *WNTs*, *BMPs*), enhancing progenitor cell differentiation and modulating bone formation and resorption [50]. Our findings suggest that while *IL-6ST* is primarily expressed in the early phase of osteogenic differentiation, its activation requires stronger osteogenic stimuli, as Biodentine alone is insufficient.

DDR1 and *DDR2*, collagen-binding receptor tyrosine kinases (RTKs), play essential roles in osteoblast adhesion, migration, and differentiation. *DDR1*, with multiple isoforms, regulates osteogenesis via the p38 MAPK pathway, influencing *RUNX2* expression. Its inhibition reduces *ALP* activity, mineralization, and osteogenic markers (*BMP2*, collagen type I, osteocalcin) [51]. *DDR2*, in contrast, regulates *RUNX2* and *Osterix*, promoting extracellular matrix synthesis [52]. Despite both being collagen-activated, they differ in expression patterns and regulatory mechanisms [53]. Our results show that B-Ex significantly upregulated these receptors, particularly *DDR1*, during early osteogenic differentiation of PL-MSCs, underscoring its role in initiating osteogenic transcription.

FOSB, a key AP-1 transcription factor, regulates osteoblast differentiation by promoting osteogenic genes such as *COL1A1*, *ALP*, and *BGLAP* [54]. Its overexpression in transgenic mice induces osteoblastic bone tumors, highlighting its pivotal role in bone biology. We observed that B-Ex increased *FOSB* expression in the late phase, mirroring its pattern under optimal osteogenic conditions and reinforcing its role in bone mineralization. *FOSL2*, in contrast, plays a distinct role in later osteoblast differentiation and extracellular matrix production, particularly type I collagen synthesis and osteoblast-osteoclast communication [55]. Higher B-Ex concentrations elevated *FOSL2* expression in both basal and suboptimal conditions during the late differentiation phase, aligning

with previous findings. However, its suppression under optimal osteogenic conditions remains unclear, possibly serving to regulate matrix formation and osteoblast maturation once these processes are fully established.

The mechanisms by which Biodentine and other tricalcium silicate cements promote osteoblastic differentiation of MSCs remain under investigation. Current evidence suggests that Ca released from Biodentine plays a key role in cytotoxicity, proliferation, and osteoinductive potential in MSC cultures (5). A relevant comparison can be drawn with chitosan-TiO₂ nanotube scaffolds incorporating Ca²⁺ ions. Lim et al. [56] found that Ca²⁺ concentrations up to 4.5 mM had minimal impact on osteoblast proliferation, whereas 13.5 mM stimulated growth. However, levels above 40 mM were cytotoxic, consistent with findings by Lee et al. [57], who observed optimal MSC proliferation at 6 mM. Similarly, we found that treating PL-MSCs with 6.2 mM Ca (concentration in 30% B-Ex) enhanced proliferation and *RUNX2* expression. Notably, these effects occurred even without additional osteoinductive factors.

To assess whether Ca from B-Ex mediated these effects, we treated B-Ex with EGTA, a calcium chelator. While EGTA in our experimental setup fully suppressed Ca-induced proliferation and *RUNX2* expression, it did not completely inhibit B-Ex-induced *RUNX2* expression. This suggests that other B-Ex components, such as Si ions, phosphates, Biodentine microparticles, or hydroxyapatite, may contribute. Both phosphates and hydroxyapatite activate osteoblastic genes via the Erk1/2 pathway, with phosphates interacting with extracellular phosphate co-transporters and hydroxyapatite additionally engaging FGFR [58]. Several calcium channels facilitate cellular Ca entry, but the calcium-sensing receptor (CaSR) appears to play the most crucial role [59]. Therefore, further studies on this topic present a significant challenge.

In conclusion, our results demonstrate that B-Ex, at non-cytotoxic concentrations, enhances the proliferation and osteoblastic differentiation of PL-MSCs. This effect is further amplified when cells are co-stimulated with a suboptimal osteogenic medium. Notably, the kinetics and levels of osteoblastogenesis-related gene expression in B-Ex-treated cultures differ from those observed in cultures stimulated with the complete osteogenic medium, which served as a positive control. Overall, transcriptional dynamics suggest a prolonged osteoblastic differentiation process in response to B-Ex. Using EGTA, a calcium chelator, we confirmed that PL-MSC proliferation and osteogenic differentiation, at least as indicated by *RUNX2* expression, are predominantly driven by elevated Ca levels in B-Ex. A limitation of this study is that it does not fully elucidate the mechanisms by which Ca and potentially other factors in the extract contribute to osteogenic differentiation. Nevertheless, our findings provide a strong foundation for further research, particularly given the potential of PL-MSCs as a model for studying post-surgical healing of PLs following apicoectomy and root-end filling.

4. Materials and Methods

4.1. Periapical Tissue

Human PLs (n = 4) were obtained from four patients undergoing apicoectomy or tooth extraction at the Clinic for Stomatology, Military Medical Academy (MMA), Belgrade, Serbia. The study was approved by the MMA Ethical Committee (No. 1/2019) and conducted in compliance with the ethical principles outlined in the Declaration of Helsinki. Written informed consent was obtained from all participants. Exclusion criteria encompassed patients with cancer, autoimmune disorders, or diabetes, as well as those undergoing immunosuppressive treatment or having taken antibiotics within the past two weeks. PLs were diagnosed based on standard clinical and radiographic criteria. No distinction was made regarding patients' age, sex, tooth type, lesion size, or clinical presentation of PLs. Two patients presented with two PLs on separate teeth, while the other two had a single lesion on one tooth. After extraction, PLs were immediately placed in RPMI-1640 medium (Sigma, Munich, Germany) supplemented with antibiotics and antimycotics and swiftly transported to the laboratory.

4.2. Preparation of Conditioned Medium from Biodentine

Biodentine (Septodont, Saint-Maur-des-Fossés, France) was aseptically prepared according to the manufacturer's instructions. The polymerized material was pressed into 24-well plate wells, forming circular samples with a diameter of 10 mm and a thickness of 2 mm. These samples were then left under sterile laminar airflow for one hour to dry and complete polymerization. To obtain the eluate, referred to as Biodentine Extract (B-Ex), each Biodentine disc was placed in a plastic tube containing RPMI-1640 medium supplemented with antibiotics and antimycotics. The Biodentine mass-to-medium ratio was maintained at 0.2 g/ml (2.2 cm²/ml), following ISO 10993 standards (ISO 10993:12-2021). The conditioning process lasted for three days, during which microparticles remained suspended in the medium, and the pH increased to 11.5. Before supplementing B-Ex with 10% fetal calf serum (FCS), its pH was adjusted to 7.4 using HCl. The prepared B-Ex was subsequently used to treat PL-MSCs.

4.3. Establishment of PL-MSCs

Cells were isolated from PLs following apicoectomy or tooth extraction. Immediately after extraction, the PLs were transferred to bottles containing α -MEM culture medium (Sigma-Aldrich, Darmstadt, Germany) supplemented with a cocktail of antibiotics and antimycotics (Sigma-Aldrich, Darmstadt, Germany) and promptly transported to the laboratory. The PL tissue was finely minced with scissors and enzymatically digested using collagenase type II (5 μ g/mL) and DNase (40 IU/mL) in serum-free α -MEM for one hour at 37 °C in an incubator with 5% CO₂. Both enzymes were sourced from Sigma-Aldrich, Darmstadt, Germany.

The digested tissue was filtered through a 30 μ m nylon mesh, rinsed with α -MEM, and centrifuged at 1800 rpm for 10 minutes. The resulting cell suspension was seeded into 24-well culture plates (Sarstedt, Nümbrecht, Germany) at a density of 2000 cells per cm² and cultured in a complete medium optimized for MSCs. This medium consisted of α -MEM, 10% fetal calf serum (FCS) (Thermo Fisher Scientific, Grand Island, NY, USA), 100 IU/mL penicillin, 50 μ g/mL streptomycin, 2.5 μ g/mL amphotericin B (Thermo Fisher Scientific, Dreieich, Germany), 1% sodium pyruvate, and 100 μ M L-ascorbate-2-phosphate (Sigma-Aldrich, Darmstadt, Germany).

After three days, non-adherent cells were removed by washing with α -MEM, and the medium was replaced twice weekly. Once the cells reached confluency, they were detached using 0.02% trypsin/0.02% NaEDTA (Sigma-Aldrich, Darmstadt, Germany) in phosphate-buffered saline (PBS) (Sigma-Aldrich, Darmstadt, Germany). The harvested cells were reseeded into 6-well plates at a density of 5000 cells per cm² in the complete α -MEM medium, excluding amphotericin B. These cells, designated as PL-MSCs, were used in experiments after the fourth passage.

The Colony-Forming Unit-Fibroblast (CFU-F) assay was performed as follows: PL-MSCs were plated at a low density (200 cells per well in a 6-well plate) in the complete MSC culture medium. The cells were cultured for 10 days at 37°C with 5% CO₂, with the medium replaced every 2–3 days. At the end of the culture period, the cells were washed with PBS, fixed with 4% paraformaldehyde for 10–15 minutes, stained with hematoxylin-eosin, and rinsed with water. Colonies containing $\geq$ 50 cells were counted under a microscope to assess PL-MSCs proliferation and clonogenic potential.

4.4. Phenotypic Analysis of PL-MSCs

After four passages, PL-MSCs were washed with PBS supplemented with 2% FCS and 0.1% sodium azide and then incubated in PBS/FCS/Na-azide containing primary antibodies conjugated to fluorescein isothiocyanate (FITC) or phycoerythrin (PE). The antibodies were used at the manufacturer-recommended dilution and incubated for 45 minutes at 4°C. The following monoclonal antibodies were obtained commercially: anti-CD146-FITC, anti-CD90-FITC, anti-CD105-FITC, anti-CD166-FITC, and anti-CD56-PE from Serotec, Oxford, UK; anti-CD73-PE from R&D Systems, Minneapolis, USA; and anti-STRO-1-FITC from Millipore/Chemicon, Billerica, MA, USA. Anti-CD39-PE and anti-SSA4-FITC antibodies were from ThermoFisher Scientific, Waltham, Massachusetts,

USA. Additionally, anti-CD45-FITC, anti-CD34-PE, anti-CD14-FITC, anti-CD3-PE, and anti-CD19-FITC were purchased from BioLegend, San Diego, California, USA.

After antibody incubation, the cells were washed with PBS/Na-azide and analyzed using a CellFlow CUBE6 flow cytometer (Sysmex Partec GmbH, Görlitz, Germany). Results are expressed as the percentage of positive cells and mean fluorescence intensity (MFI) based on the analysis of at least 5000 cells per sample. Data were processed using FCS Express 6 RUO Edition software (version 6.00.0053).

4.5. Differentiation of PL-MSCs

The differentiation of PL-MSCs into osteoblasts was induced by culturing the cells in the osteoblast differentiation medium for 21 days in 6-well plates. Initially, the cells were cultured for two days in basal α MEM medium until they reached approximately 70% confluence. The medium was then replaced with a commercial osteoblast differentiation medium (Lonza Group Ltd, Basel, Switzerland), and culture continued for the next 21 days. The medium was refreshed every 4 days. After the incubation period, the cultures were washed and stained with Alizarin Red (Sigma-Aldrich, Darmstadt, Germany) to identify mineralized nodules.

For adipogenic differentiation, PL-MSCs were cultured in the adipogenic medium (Lonza Group Ltd, Basel, Switzerland) following the same procedure as for osteogenic differentiation, except that the culture period lasted 14 days. Adipocytes were identified by staining with Oil Red O (Sigma-Aldrich, Darmstadt, Germany).

For chondrogenic differentiation, the cells were centrifuged in polypropylene tubes, and the supernatant was discarded. A commercial chondrogenic medium (Lonza Group Ltd, Basel, Switzerland) was added to the pellet. The cells were cultured for 4 weeks, with medium changes twice a week. After the differentiation period, the pellet was embedded in a freezing medium (Bio-Optica Milano S.p.A, Milano, Italy) and frozen in liquid nitrogen. For analysis under a light microscope, 7 μ m thick samples were cut on a cryotome (Leica Cryocut 1850, Leica Biosystems, Deer Park, IL, USA) and stained with Alcian Blue solution (Sigma-Aldrich, Darmstadt, Germany), which stains glycosaminoglycans, a component of the extracellular matrix produced by chondroblasts.

4.6. Cytotoxicity Tests

Cytotoxicity was evaluated according to ISO 10993-5:2009, the standard biocompatibility test for medical devices. The measured variables included cell viability and metabolic activity of PL-MSCs. Viability was assessed based on the percentage of necrotic cells stained with propidium iodide (PI) (Sigma-Aldrich, Darmstadt, Germany), while metabolic activity was measured using the MTT assay, which evaluates succinate dehydrogenase activity in viable cells. The intensity of the formazan product was proportional to cell viability.

PL-MSCs were cultured in 96-well plates ($1-2 \times 10^4$ cells/well) in complete α -MEM medium. The next day, the medium was replaced with either fresh medium (control) or medium supplemented with different concentrations of B-Ex. PL-MSC cultures were incubated for 24 or 72 hours. After incubation, the plates were centrifuged, the medium was carefully aspirated and 100 μ L of MTT solution (100 μ g/mL) was added to each well. The plates were incubated for 4 hours at 37°C, after which the formazan crystals were dissolved overnight using 0.1N HCl/10% sodium dodecyl sulfate (SDS) (Sigma-Aldrich, Darmstadt, Germany). Optical density (OD) was measured at 570/650 nm in an ELISA reader (ThermoFisher Scientific, Waltham, Massachusetts, USA), and results were expressed as relative metabolic activity compared to control cultures (100%). Wells without cells served as blank controls.

A parallel set of cultures was used to assess cell viability, calculated based on the percentage of necrotic (PI⁺) cells. After incubation, PL-MSCs were detached using 0.25% trypsin/0.2 mM EDTA (both from Sigma-Aldrich, Darmstadt, Germany), transferred to flow cytometry tubes, washed with PBS, and stained with PI (1 μ g/mL) for 10 minutes in the dark. The cells were analyzed using a

CellFlow CUBE6 flow cytometer (Sysmex Partec GmbH, Görlitz, Germany). Results were expressed as the percentage of PI⁺ cells, with viability calculated as follows: Viability (%) = 100% - % PI⁺ cells.

4.7. Modulatory Effect of Biodentine Extract on Osteoblast Differentiation of PL-MSCs

The effect of non-cytotoxic concentrations of B-Ex (30% and 10%) on the osteoblast differentiation of PL-MSCs was assessed in cultures maintained in basal medium alone, complete osteogenic medium, and basal medium supplemented with 30% osteogenic medium, referred to as suboptimal osteogenic medium. Osteoblast differentiation was evaluated in two ways: Gene expression analysis of osteoblastogenesis-related genes was performed on days 7 and 16; The mineralization index was assessed using Alizarin Red staining after 21 days of cultivation. Cultures were photographed using an Olympus inverted microscope equipped with a digital camera.

Mineralization scoring was performed semiquantitatively at 10x magnification based on the following criteria: Index 0: No visible positivity; Index 1: Mild staining of individual cells and the presence of 1–2 small mineralized nuclei stained pink-red in one of 10 analyzed fields; Index 2: Mild staining of individual cells and the presence of up to 5 small to medium-sized mineralized nuclei stained pink-red in two of 10 analyzed fields; Index 3: Presence of up to 10 mineralized nuclei of different sizes, stained pink-red, in five of 10 analyzed fields; Index 4: Presence of mineralized nuclei of all sizes, some fused, stained pink-red in all 10 analyzed fields.

4.8. Gene Expression Determination by Real-Time PCR

To determine the expression of genes involved in osteoblast differentiation of MSC, the Real-Time PCR method was used. Gene expression was determined in a set of parallel PL-MSC cultures as described above. Cells were collected after 7 days (early phase of osteoblastogenesis) and 16 days (late phase of osteoblastogenesis). Total RNA was isolated from the cell pellets, which were collected by centrifuging the PL-MSCs, using the RNeasy Mini Kit (Qiagen, Hilden, Germany). Complementary DNA (cDNA) was synthesized using a commercial reverse transcription kit following the manufacturer's instructions (High-Capacity cDNA Reverse Transcription Kit; ThermoFisher Scientific, Waltham, Massachusetts, USA). qPCR of cDNA was performed using SYBRTM Green PCR Master Mix (2x, Thermo Fisher Scientific) with primer pairs specific for each of 20 genes of interest, synthesized by Microsynth, Balagach, Switzerland, and listed in Table 3. The entire procedure was carried out on the 7500 real-time PCR system (Applied Biosystems, Waltham, Massachusetts, USA). The qPCR reaction started with an initial denaturation step for 10 minutes at 95°C, followed by a cycle consisting of a DNA strand denaturation step for 15 seconds at 95°C, and a primer binding and strand elongation step for 1 minute at 60°C. The cycle was repeated 40 times. The gene expression level of the gene of interest was standardized against the expression of the control gene, Glyceraldehyde-3-Phosphate Dehydrogenase (*GAPDH*) detected in the same sample and expressed as 2-dCt, where dCt is the difference between the Ct values of the gene of interest and β-actin. The relative expression of the gene of interest was later normalized as the relative increase or decrease (fold change) compared to the gene expression in the corresponding control (set as index 1). Each sample was analyzed in duplicates. Total number of analyses was four (two samples of two cell lines).

Table 3. Sequences of the primer pairs used for the real-time PCR experiments.

Primers	Sequences (5'-3')
WNT2	TTCCAGAGCTAACTCGTGCC
	ACTGGGCTTGAAGGGTGATG
COL1A1	TCGGAGGAGAGTCAGGAAGG
	AACAGAACAGTCTCTCCCGC
SP7	TTCTGCGGCAAGAGGTTCACTC
	GTGTTTGCTCAGGTGGTCGCTT
BMP-2	GGGGTGGGGGAAAGGTAATG

	TCGGGTTATCCAGGTTTGTGCT
<i>RUNX2</i>	GCGGTGCAAACCTTCTCCAG
	TCACTGTGCTGAAGAGGCTG
<i>BGLAP</i>	GACTGTGACGAGTTGGCTGA
	CACATCCATAGGGCTGGGAG
<i>TGF-β1</i>	GGACACCAACTATTGCTTCAGCTCC
	AGGCTCCAAATGTAGGGGCAGGGCC
<i>FGF 2</i>	GGGTGCCAGATTAGCGGAC
	GTTACGGATGGGTGTCTCC
<i>ALP</i>	GGGCATTGTGACTACCACTC
	AGTCAGGTTGTTCCGATTCA
<i>FOSB</i>	TCTGTCTTCGGTGGACTCCTTC
	GTTGCACAAGCCACTGGAGGTC
<i>FOSL2</i>	AAGAGGAGGAGAAGCGTCGCAT
	GCTCAGCAATCTCCTTCTGCAG
<i>DDR1</i>	GCGTCTGTCTGCGGGTAGAG
	ACGGCCTCAGATAAATACATTGTCT
<i>DDR2</i>	TGTTCTGCTGCTGCCTATCTT
	AGGATAGCGGCATATAGCTGGAT
<i>CTGF</i>	GTTTGGCCCAGACCCAACT
	GGAACAGGCGCTCCACTCT
<i>VCAN</i>	TTGGACCTCAGGCGCTTTCTAC
	GGATGACCAATTAACTCAAATCAC
<i>RANKL</i>	GCCTTTCAAGGAGCTGTGCAAAA
	GAGCAAAAGGCTGAGCTTCAAGC
<i>CTSK</i>	GAGGCTTCTCTTGGTGTCCATAC
	TTACTGCGGGAATGAGACAGGG
<i>IL-6ST</i>	CACCCTGTATCACAGACTGGCA
	TTCAGGGCTTCCTGGTCCATCA
<i>PTHr</i>	CATCTTTTGGTCCATCTGTCCATC
	CTGGAGACCCTCGAGACCACA
<i>GHR</i>	TGCTTTTTCTGGAAGTGAGGA
	GGTTCTTTGTACCATGATGAACCT
<i>GAPDH</i>	GTCTCCTCTGACTTCAACAGCG
	ACCACCCTGTTGCTGTAGCCAA

4.9. Proliferation Tests

The proliferation of PL-MSCs under the influence of different concentrations of B-Ex was primarily assessed using the MTT assay, as described in the cytotoxicity section. An additional test was performed based on the incorporation of ³H-thymidine. In this assay, PL-MSCs were cultured in 96-well polystyrene plates in triplicate in the presence of different dilutions of B-Ex for three days. Proliferation was evaluated based on either the metabolic activity of the cultures (via MTT) or the amount of incorporated ³H-thymidine (Amersham, Buks, UK; 1 μCi/ml of culture) compared to the control (cell proliferation in the control medium). Radioactive thymidine was added to the cultures during the final eight hours of incubation, and its incorporation was measured using a standard procedure with a scintillation β-counter (RAGBETA, Turku, Finland). The results were expressed as counts per minute (cpm).

4.10. The Role of Ca in the Proliferation and Osteoblastogenic Activity of Biodentine Extract

To investigate the role of Ca in PL-MSC proliferation and osteoblastic differentiation induced by B-Ex, the Ca-chelating agent EGTA was used. PL-MSCs cultured in the complete basal medium were treated with either 30% B-Ex alone or 30% B-Ex supplemented with 2 mM EGTA (Sigma-Aldrich,

Darmstadt, Germany), for 24 hours. After incubation, both the extract and the extract/EGTA were carefully washed away and the cells were further cultured for an additional 48 hours. Cell proliferation and *RUNX2* expression were then assessed. A parallel set of cultures was treated with 6.2 mM Ca (corresponding to the concentration determined in 30% B-Ex), with and without EGTA, as a specific control.

4.11. Statistics

To assess differences between the parameters of control and experimental cultures one- or two-way ANOVA with Tukey multiple comparison was used. Differences in mRNA expression between groups were analyzed using a ratio-paired *t*-test or Wilcoxon test. Values at $p < 0.05$ or less were considered to be statistically significant. The statistical analysis and graphs were performed in GraphPad Prism version 8.0.0 (GraphPad Software, San Diego, CA, USA).

Author Contributions: Conceptualization: M.Č. and M. E.; Data curation: M.B., J.Đ., L.P.; Formal analysis: M.B., D.V., J.Đ., S.T., and M.M.; Funding acquisition: M.Č. and D.B.; Investigation: M.E., M.D., J.Đ., S.T., M.E., D.V., D.B., and M.Č.; Methodology: M.B., J.Đ., S.T., M.M., L.P. and M.Č.; Project administration: M.E., and M.Č.; Software: S.T., and J.Đ.; Supervision: M.Č.; Writing—original draft preparation: M.Č. and M.E. Writing—review and editing: M.Č. All authors have read and agreed to the published version of the manuscript.

Funding: This study was supported by the University of Defense in Belgrade, Medical Faculty of the Military Medical Academy, Belgrade, Serbia (project MFVMA/03/20-22); University of East Sarajevo, Medical Faculty Foča, Foča, Bosnia and Herzegovina, (project UIS/MFF: I.1.20-22) and Serbian Academy of Sciences and Arts, Belgrade, Serbia (Project F 115).

Institutional Review Board Statement: The study was conducted in accordance with the Declaration of Helsinki, and the protocol was approved by the Ethics Committee of MMA (permission number: 01/2019).

Informed Consent Statement: Informed consent was obtained from all subjects involved in the study.

Data Availability Statement: All data are included in this article.

Acknowledgments: The authors thank Ivana Majstorović, Institute for Medical Research, Military Medical Academy, Belgrade Serbia for help with PL-MSC culture.

Conflicts of Interest: The authors declare no conflict of interest. The funders had no role in the design of the study; in the collection, analyses, or interpretation of data; in the writing of the manuscript, or in the decision to publish the results.

References

1. Mahmoud, S.; El-Negoly, S.; Zaeneldin, A.; El-Zekrid, M.; Grawish, L.; Grawish, H.; Grawish, M. Biodentine versus mineral trioxide aggregate as a direct pulp capping material for human mature permanent teeth – A systematic review. *J. Conserv. Dent.* **2018**, *21*, 466. https://doi.org/10.4103/JCD.JCD_198_18.
2. Ravi, H.; Mahendran, K.; Velusamy, V.; Babu, S. BIODENTINE- A review on its properties and clinical applications. *J. Biomed. Pharm. Res.* **2021**, *10*, 10.32553/jbpr.v10i5.881.
3. Pérard, M.; Le Clerc, J.; Watrin, T.; Meary, F.; Pérez, F.; Tricot-Doleux, S.; Pellen-Mussi, P. Spheroid model study comparing the biocompatibility of Biodentine and MTA. *J. Mater. Sci. Mater. Med.* **2013**, *24*, 1527–1534. <https://doi.org/10.1007/s10856-013-4961-7>.
4. Araújo, L.B.; Cosme-Silva, L.; Fernandes, A.P.; Oliveira, T.M.; Cavalcanti, B.D.N.; Gomes Filho, J.E.; Sakai, V.T. Effects of mineral trioxide aggregate, Biodentine™ and calcium hydroxide on viability, proliferation, migration and differentiation of stem cells from human exfoliated deciduous teeth. *J. Appl. Oral Sci.* **2018**, *26*, e20160629. <https://doi.org/10.1590/1678-7757-2016-0629>.
5. Abuarqoub, D.; Aslam, N.; Jafar, H.; Abu Harfil, Z.; Awidi, A. Biocompatibility of Biodentine™ with periodontal ligament stem cells: In vitro study. *Dent. J. (Basel)* **2020**, *8*, 17. <https://doi.org/10.3390/dj8010017>.
6. Zhou, H.M.; Shen, Y.; Wang, Z.J.; Li, L.; Zheng, Y.F.; Häkkinen, L.; Haapasalo, M. In vitro cytotoxicity evaluation of a novel root repair material. *J. Endod.* **2013**, *39*, 478–483. <https://doi.org/10.1016/j.joen.2012.12.015>.

7. Emara, R.; Elhennawy, K.; Schwendicke, F. Effects of calcium silicate cements on dental pulp cells: A systematic review. *J. Dent.* **2018**, *77*, 18–36. <https://doi.org/10.1016/j.jdent.2018.06.012>.
8. Michel, A.; Erber, R.; Frese, C.; Gehrig, H.; Saure, D.; Mente, J. In vitro evaluation of different dental materials used for the treatment of extensive cervical root defects using human periodontal cells. *Clin. Oral Investig.* **2017**, *21*, 753–761. <https://doi.org/10.1007/s00784-016-1900-x>.
9. Youssef, A.R.; Emara, R.; Taher, M.M.; Al-Allaf, F.A.; Almalki, M.; Almasri, M.A.; Siddiqui, S.S. Effects of mineral trioxide aggregate, calcium hydroxide, biodentine, and Emdogain on osteogenesis, odontogenesis, angiogenesis, and cell viability of dental pulp stem cells. *BMC Oral Health* **2019**, *19*, 133. <https://doi.org/10.1186/s12903-019-0796-z>.
10. da Fonseca, T.S.; Silva, G.F.; Guerreiro-Tanomaru, J.M.; Delfino, M.M.; Sasso-Cerri, E.; Tanomaru-Filho, M.; Cerri, P.S. Biodentine and MTA modulate immunoinflammatory response favoring bone formation in sealing of furcation perforations in rat molars. *Clin. Oral Investig.* **2019**, *23*, 1237–1252. <https://doi.org/10.1007/s00784-018-2611-1>.
11. Wairooy, V.W.; Bagio, D.A.; Margono, A.; Amelia, I. In vitro Analysis of DSPP and BSP Expression: Comparing the Odontogenic Influence of Bio-C Repair and Biodentine in hDPSCs. *Eur. J. Dent.* **2024**. <https://doi.org/10.1055/s-0044-1786984>.
12. Jalan, A.L.; Warhadpande, M.M.; Dakshindas, D.M. A comparison of human dental pulp response to calcium hydroxide and Biodentine as direct pulp-capping agents. *J. Conserv. Dent.* **2017**, *20*, 129–133.
13. Tolibah, Y.A.; Kouchaji, C.; Lazkani, T.; Ahmad, I.A.; Baghdadi, Z.D. Comparison of MTA versus Biodentine in Apexification Procedure for Nonvital Immature First Permanent Molars: A Randomized Clinical Trial. *Children* **2022**, *9*, 410. <https://doi.org/10.3390/children9030410>.
14. Caron, G.; Azérad, J.; Faure, M.-O.; Machtou, P.; Boucher, Y. Use of a new retrograde filling material (Biodentine) for endodontic surgery: two case reports. *Int. J. Oral Sci.* **2014**, *6*, 250–253. <https://doi.org/10.1038/ijos.2014.25>.
15. Pawar, A.M.; Kokate, S.R.; Shah, R.A. Management of a large periapical lesion using Biodentine™ as retrograde restoration with eighteen months evident follow-up. *J. Conserv. Dent.* **2013**, *16*, 573–575. <https://doi.org/10.4103/0972-0707.120934>.
16. Eraković, M.; Duka, M.; Bekić, M.; Tomić, S.; Ismaili, B.; Vučević, D.; Čolić, M. Anti-inflammatory and immunomodulatory effects of Biodentine on human periapical lesion cells in culture. *Int. Endod. J.* **2020**, *53*, 1398–1412. <https://doi.org/10.1111/iej.13351>.
17. Dominici, M.; Le Blanc, K.; Mueller, I.; Slaper-Cortenbach, I.; Marini, F.; Krause, D.; Deans, R.; Keating, A.; Prockop, D.; Horwitz, E. Minimal criteria for defining multipotent mesenchymal stromal cells. *Cytotherapy* **2006**, *8*, 315–317.
18. Đokić, J.; Tomić, S.; Cerović, S.; Todorović, V.; Rudolf, R.; Čolić, M. Characterization and immunosuppressive properties of mesenchymal stem cells from periapical lesions. *J. Clin. Periodontol.* **2012**, *39*, 807–816. <https://doi.org/10.1111/j.1600-051X.2012.01917.x>.
19. Giraud, T.; Jeanneau, C.; Bergmann, M.; Laurent, P.; About, I. Tricalcium silicate capping materials modulate pulp healing and inflammatory activity in vitro. *J. Endod.* **2018**, *44*, 1686–1691.
20. Ranjkesh, B.; Isidor, F.; Kraft, D.C.E.; Løvschall, H. In vitro cytotoxic evaluation of novel fast-setting calcium silicate cement compositions and dental materials using colorimetric methyl-thiazolyl-tetrazolium assay. *J. Oral Sci.* **2018**, *60*, 82–88.
21. Nikfarjam, F.; Beyer, K.; König, A.; Hofmann, M.; Butting, M.; Valesky, E.; Kippenberger, S.; Kaufmann, R.; Heidemann, D.; Bernd, A.; Zöller, N.N. Influence of Biodentine® A Dentine Substitute On Collagen Type I Synthesis in Pulp Fibroblasts In Vitro. *PLoS ONE* **2016**, *11*, e0167633.
22. Poggio, C.; Ceci, M.; Dagna, A.; Beltrami, R.; Colombo, M.; Chiesa, M. In vitro cytotoxicity evaluation of different pulp capping materials: a comparative study. *Arh. Hig. Rada Toksikol.* **2015**, *66*, 181–188.
23. Attik, G.N.; Villat, C.; Hallay, F.; Pradelle-Plasse, N.; Bonnet, H.; Moreau, K.; Colon, P.; Grosogeat, B. In vitro biocompatibility of a dentine substitute cement on human MG63 osteoblasts cells: Biodentine™ versus MTA®. *Int. Endod. J.* **2014**, *47*, 1133–1141.
24. ISO 10993-5:2009. Biological evaluation of medical devices - Part 5: Tests for in vitro cytotoxicity. *International Organization for Standardization*, 2009.

25. Hanna, H.; Mir, L.M.; Andre, F.M. In vitro osteoblastic differentiation of mesenchymal stem cells generates cell layers with distinct properties. *Stem Cell Res. Ther.* **2018**, *9*, 203.
26. Luo, Z.; Shang, X.; Zhang, H.; Wang, G.; Massey, P.A.; Barton, S.R.; Kevil, C.G.; Dong, Y. Notch Signaling in Osteogenesis, Osteoclastogenesis, and Angiogenesis. *Am. J. Pathol.* **2019**, *189*, 1495–1500.
27. Kawane, T.; Qin, X.; Jiang, Q.; Miyazaki, T.; Komori, H.; Yoshida, C.A.; Matsuura-Kawata, V.K.D.S.; Sakane, C.; Matsuo, Y.; Nagai, K.; Maeno, T.; Date, Y.; Nishimura, R.; Komori, T. Runx2 is required for the proliferation of osteoblast progenitors and induces proliferation by regulating Fgfr2 and Fgfr3. *Sci. Rep.* **2018**, *8*, 13551.
28. Chen, Y.; Zhao, X.; Wu, H. Transcriptional Programming in Arteriosclerotic Disease: A Multifaceted Function of the Runx2 (Runt-Related Transcription Factor 2). *Arterioscler. Thromb. Vasc. Biol.* **2021**, *41*, 20–34. doi: 10.1161/ATVBAHA.120.313791.
29. Hu, L.; Chen, W.; Qian, A.; et al. Wnt/ β -catenin signaling components and mechanisms in bone formation, homeostasis, and disease. *Bone Res.* **2024**, *12*, 39. doi: 10.1038/s41413-024-00342-8.
30. Zoch, M.L.; Clemens, T.L.; Riddle, R.C. New insights into the biology of osteocalcin. *Bone* **2016**, *82*, 429.
31. Moser, S.C.; van der Eerden, B.C.J. Osteocalcin: A Versatile Bone-Derived Hormone. *Front. Endocrinol. (Lausanne)* **2019**, *9*, 794.
32. Tavakol, M.; Liu, J.; Hoff, S.E.; Zhu, C.; Heinz, H. Osteocalcin: Promoter or Inhibitor of Hydroxyapatite Growth? *Langmuir* **2024**, *40*, 1747–1760. doi: 10.1021/acs.langmuir.3c02948.
33. Kaur, K.; Sanskrita, D.; Sourabh, G. Regulation of Human Osteoblast-to-Osteocyte Differentiation by Direct-Write 3D Microperiodic Hydroxyapatite Scaffolds. *ACS Omega* **2019**, *4*, 1504–1513.
34. Verdelli, C.; Tavanti, G.S.; Forno, I.; Vaira, V.; Maggiore, R.; Vicentini, L.; Dalino Ciaramella, P.; Perticone, F.; Lombardi, G.; Corbetta, S. Osteocalcin Modulates Parathyroid Cell Function in Human Parathyroid Tumors. *Front. Endocrinol. (Lausanne)* **2023**, *14*, 1129930. doi: 10.3389/fendo.2023.1129930.
35. Cupp, M.; Adem, A.; Nayak, S.; Thomsen, W. Parathyroid Hormone (PTH) and PTH-Related Peptide Domains Contributing to Activation of Different PTH Receptor-Mediated Signaling Pathways. *J. Pharmacol. Exp. Ther.* **2013**, *345*, 10.1124/jpet.112.199752.
36. Dixit, M.; Poudel, S.B.; Yakar, S. Effects of GH/IGF Axis on Bone and Cartilage. *Mol. Cell Endocrinol.* **2021**, *519*, 111052. doi: 10.1016/j.mce.2020.111052.
37. Boraschi-Diaz, I.; Wang, J.; Mort, J.S.; Komarova, S.V. Collagen Type I as a Ligand for Receptor-Mediated Signaling. *Front. Phys.* **2017**, *5*, 12.
38. Vimalraj, S. Alkaline Phosphatase: Structure, Expression and Its Function in Bone Mineralization. *Gene* **2020**, *754*, 144855. doi: 10.1016/j.gene.2020.144855.
39. Marupanthorn, K.; Tantrawatpan, C.; Kheolamai, P.; Tantikanlayaporn, D.; Manochantr, S. Bone morphogenetic protein-2 enhances the osteogenic differentiation capacity of mesenchymal stromal cells derived from human bone marrow and umbilical cord. *Int. J. Mol. Med.* **2017**, *39*, 654–662. <https://doi.org/10.3892/ijmm.2017.2872>
40. Chen, G.; Deng, C.; Li, Y.P. TGF β and BMP signaling in osteoblast differentiation and bone formation. *Int. J. Biol. Sci.* **2012**, *8*, 272–288.
41. Deng, Z.; Fan, T.; Xiao, C.; Pan, W.; Li, H.; Chen, G.; Li, Y.; Liu, H.; Zhang, X.; Wu, C.; et al. TGF- β signaling in health, disease, and therapeutics. *Signal Transduct. Target. Ther.* **2024**, *9*, 61. <https://doi.org/10.1038/s41392-024-01764-w>
42. Saranya, I.; Selvamurugan, N. Regulation of TGF- β /BMP signaling during osteoblast development by non-coding RNAs: Potential therapeutic applications. *Life Sci.* **2024**, *355*, 122969. <https://doi.org/10.1016/j.lfs.2024.122969>
43. Maddaluno, L.; Urwyler, C.; Werner, S. Fibroblast growth factors: Key players in regeneration and tissue repair. *Development* **2017**, *144*, 4047–4060.
44. Charoenlarp, P.; Rajendran, A.K.; Iseki, S. Role of fibroblast growth factors in bone regeneration. *Inflamm. Regen.* **2017**, *37*, 10. <https://doi.org/10.1186/s41232-017-0043-8>
45. Su, N.; Jin, M.; Chen, L. Role of FGF/FGFR signaling in skeletal development and homeostasis: Learning from mouse models. *Bone Res.* **2014**, *2*, 14003. <https://doi.org/10.1038/boneres.2014.3>

46. Arnott, J.A.; Lambi, A.G.; Mundy, C.; Hendesi, H.; Pixley, R.A.; Owen, T.A.; Safadi, F.F.; Popoff, S.N. The role of connective tissue growth factor (CTGF/CCN2) in skeletogenesis. *Crit. Rev. Eukaryot. Gene Expr.* **2011**, *21*, 43–69. <https://doi.org/10.1615/critreveukargeneexpr.v21.i1.40>
47. Wight, T.N.; Kang, I.; Evanko, S.P.; Harten, I.A.; Chang, M.Y.; Pearce, O.M.T.; Allen, C.E.; Frevert, C.W. Versican—a critical extracellular matrix regulator of immunity and inflammation. *Front. Immunol.* **2020**, *11*, 512.
48. Dai, R.; Wu, Z.; Chu, H.Y.; Lu, J.; Lyu, A.; Liu, J.; Zhang, G. Cathepsin K: The action in and beyond bone. *Front. Cell Dev. Biol.* **2020**, *8*, 433. <https://doi.org/10.3389/fcell.2020.00433>
49. De Leon-Oliva, D.; Barrena-Blázquez, S.; Jiménez-Álvarez, L.; Fraile-Martínez, O.; García-Montero, C.; López-González, L.; Torres-Carranza, D.; García-Puente, L.M.; Carranza, S.T.; Álvarez-Mon, M.Á.; et al. The RANK-RANKL-OPG system: A multifaceted regulator of homeostasis, immunity, and cancer. *Medicina* **2023**, *59*, 1752. <https://doi.org/10.3390/medicina59101752>
50. Sellin, M.L.; Klinder, A.; Bergschmidt, P.; Bader, R.; Jonitz-Heincke, A. IL-6-induced response of human osteoblasts from patients with rheumatoid arthritis after inhibition of the signaling pathway. *Clin. Exp. Med.* **2023**, *23*, 3479–3499. <https://doi.org/10.1007/s10238-023-01103-3>
51. Chou, L.Y.; Chen, C.H.; Chuang, S.C.; Cheng, T.L.; Lin, Y.H.; Chou, H.C.; Fu, Y.C.; Wang, Y.H.; Wang, C.Z. Discoidin domain receptor 1 regulates Runx2 during osteogenesis of osteoblasts and promotes bone ossification via phosphorylation of p38. *Int. J. Mol. Sci.* **2020**, *21*, 7210. <https://doi.org/10.3390/ijms21197210>
52. Wu, F.; Ge, C.; Pan, H.; Han, Y.; Mishina, Y.; Kaartinen, V.; Franceschi, R.T. Discoidin domain receptor 2 is an important modulator of BMP signaling during heterotopic bone formation. *Bone Res.* **2025**, *13*, 7. <https://doi.org/10.1038/s41413-024-00391-z>
53. Croissant, C.; Tuariihihoa, A.; Bacou, M.; Souleyreau, W.; Sala, M.; Henriët, E.; Bikfalvi, A.; Saltel, F.; Auguste, P. DDR1 and DDR2 physical interaction leads to signaling interconnection but with possible distinct functions. *Cell Adhes. Migr.* **2018**, *12*, 324–334. <https://doi.org/10.1080/19336918.2018.1460012>
54. Wagner, E.; Eferl, R.; Hoebertz, A.; et al. Bone cell differentiation and the role of Fos/AP-1 proteins. *Arthritis Res. Ther.* **2003**, *5*(Suppl 3), 49. <https://doi.org/10.1186/ar850>
55. Bozec, A.; Bakiri, L.; Jimenez, M.; Schinke, T.; Amling, M.; Wagner, E.F. Fra-2/AP-1 controls bone formation by regulating osteoblast differentiation and collagen production. *J. Cell Biol.* **2010**, *190*, 1093–1106. <https://doi.org/10.1083/jcb.201002111>
56. Lim, S.S.; Chai, C.Y.; Loh, H.S. In vitro evaluation of osteoblast adhesion, proliferation, and differentiation on chitosan-TiO₂ nanotubes scaffolds with Ca²⁺ ions. *Mater. Sci. Eng. C Mater. Biol. Appl.* **2017**, *76*, 1445–1452.
57. Lee, M.N.; Hwang, H.S.; Oh, S.H.; Roshanzadeh, A.; Kim, J.W.; Song, J.H.; Kim, E.S.; Koh, J.T. Elevated extracellular calcium ions promote proliferation and migration of mesenchymal stem cells via increasing osteopontin expression. *Exp. Mol. Med.* **2018**, *50*, 116.
58. Sarem, M.; Heizmann, M.; Barbero, A.; Martin, I.; Shastri, V.P. Hyperstimulation of CaSR in human MSCs by biomimetic apatite inhibits endochondral ossification via temporal downregulation of PTH1R. *Proc. Natl. Acad. Sci. USA* **2018**, *115*, E6135–E6144.
59. González-Vázquez, A.; Planell, J.A.; Engel, E. Extracellular calcium and CaSR drive osteoinduction in mesenchymal stromal cells. *Acta Biomater.* **2014**, *10*, 2824–2833.

Disclaimer/Publisher’s Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.