

Review

Not peer-reviewed version

Metal-Organic Frameworks for Electrocatalytic CO₂ Reduction into Formic Acid

[Wen-Jun Xie](#) , Olga M. Mulina , [Alexander O. Terent'ev](#) , [Liang-Nian He](#) *

Posted Date: 6 July 2023

doi: 10.20944/preprints202307.0282.v1

Keywords: metal organic frameworks; electrocatalysis; CO₂ reduction; electrochemical reduction; formic acid



Preprints.org is a free multidiscipline platform providing preprint service that is dedicated to making early versions of research outputs permanently available and citable. Preprints posted at Preprints.org appear in Web of Science, Crossref, Google Scholar, Scilit, Europe PMC.

Copyright: This is an open access article distributed under the Creative Commons Attribution License which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Review

Metal-Organic Frameworks for Electrocatalytic CO₂ Reduction into Formic Acid

Wen-Jun Xie ¹, Olga M. Mulina ², Alexander O. Terent'ev ² and Liang-Nian ^{1,*}

¹ State Key Laboratory and Institute of Elemento-Organic Chemistry, College of Chemistry, Nankai University, Tianjin 300071 (China)

² Zelinsky Institute of Organic Chemistry, Russian Academy of Sciences, 47 Leninsky Prospect, Moscow, Russian Federation; terentev@ioc.ac.ru

* Correspondence: heln@nankai.edu.cn; Tel.: +86 22 2350 3878

Abstract: Metal organic frameworks (MOFs) are used in catalysis due to their high specific surface area and porous structure. The dispersed active sites and limited reaction space render MOFs have the potential for highly selective electrocatalytic CO₂ reduction reaction (ECO₂RR). Meanwhile, formic acid (HCOOH) is attracting attention as a liquid product with high economic benefits. This review summarizes the MOFs and their derivatives applied for ECO₂RR into HCOOH products. The preparation methods of MOFs as electrocatalysts and their unique advantages are discussed. A series of MOFs, and MOFs derivatives obtained by electrochemical reduction or carbonization processes are highlighted, including metal nanomaterials, carbon-based nanocomposites, single-atom catalysts, and bimetallic nanocomposites. Depending on the MOFs building units (metal ions and organic linkers) and the reaction conditions of derivatization, MOFs-based catalysts exhibit rich diversity and controllable modulation of catalytic performance. Finally, the challenges encountered at this stage and the future research directions of MOFs-based catalysts are proposed.

Keywords: metal organic frameworks; electrocatalysis; CO₂ reduction; electrochemical reduction; carbonization

1. Introduction

The increasing severity of the global climate problem caused by CO₂, the main component of greenhouse gases, has stimulated plenty of research and development projects on various ways to convert CO₂ to achieve sustainable development. A conscious shift is taking place that CO₂ is no longer seen as a waste but as an abundant renewable C₁ resource [1]. In this context, electrocatalytic CO₂ reduction reaction (ECO₂RR) has become a hot research topic. Compared with traditional thermochemical means, it can be carried out at normal temperature and pressure. The electricity generated by renewable energy, such as wind energy, water energy, solar energy, replaces the toxic and expensive equivalent reducing agent, which is a promising tool for CO₂ conversion [2]. The CO₂ molecule contains two σ bonds and two delocalized π^*_3 bonds with bond energies up to 750 kJ mol⁻¹, and possesses high thermodynamic stability and low electron affinity, thus it is difficult to activate CO₂. On the other hand, hydrogen evolution reaction (HER) becomes a competitive process kinetically, which should be avoided when ECO₂RR occurs in the aqueous electrolyte. Therefore, it is very important to develop efficient catalysts to promote the conversion of CO₂. The ideal electrocatalyst should have the following advantages: high efficiency conversion at low overpotential, high selectivity towards the target product and minimum hydrogen evolution in aqueous media, high stability, abundant in nature and low cost [3].

At present, the catalysts used in ECO₂RR can be divided into the following categories: (1) typical metal-based heterogeneous catalysts, being consisting of metals oxides, sulfides, alloys, etc., have high activity and conductivity, but ECO₂RR often occurs on the catalyst surface, which means low atomic utilization rate [4,5]; (2) molecular catalysts, mostly metal complexes, are usually used in

homogeneous systems. They have well-defined structure containing organic ligands and metal ions, which is conducive to the establishment of theoretical models and the exploration of mechanisms, as well as to further modification by organic synthesis. However, they are difficult to be separated from the resultants after reaction for reuse. In recent years, the supported molecular catalysts have received much more attention. Although atom utilization rate has been improved by anchoring the metal atom through coordination, aggregation between complexes can also lead to degradation of atom utilization rate, stability and catalytic performance [2]; (3) single-atom catalysts often anchor single metal atoms to conductive carbon-based support through N, C, O or S atoms to achieve the effect of high atom utilization rate, with high stability and activity [6]; (4) metal-free catalysts have also been developed and have obvious advantages of low price, but there is still a gap between them and the above catalysts in terms of catalytic efficiency [7].

Among the energy-related small molecules converted by CO_2 , CO and HCOOH are more economically effective products at the present stage. As a liquid product, HCOOH is more conducive to transportation and can easily generate H_2 through decomposition reaction, which has practical applications in hydrogen fuel cells [8]. In this respect, a series of metal-based catalysts (Sn, In, Bi, Pb, Pd) have shown good HCOOH selectivity [9,10]. The proposed mechanism of ECO_2RR to formic acid can be divided into four main categories (Figure 1): path (1) is considered that the binding between CO_2 anion radical intermediate and catalyst is so weak that the formation of HCOOH occurs via hydration of nonadsorbing CO_2 anion radical intermediate [5,11]; path (2) is accompanied by metal(M)-C bonding, forming $^*\text{COOH}$ intermediate [2,12]; path (3) is involved in the formation of M-O bonds, where CO_2 forms $^*\text{OCHO}$ intermediate after gaining electrons and proton [13]; path (4) is to insert CO_2 into M-H bond to obtain $^*\text{OCHO}$ intermediate, and then generate HCOOH in the subsequent reduction step [2,13].

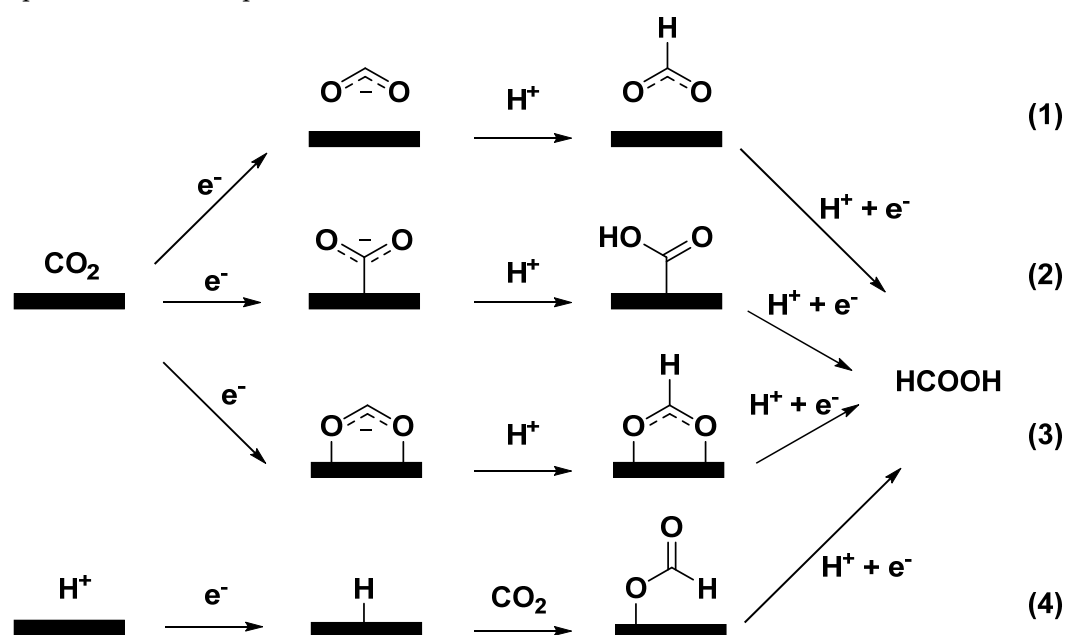


Figure 1. Proposed reaction pathways of ECO_2RR to HCOOH .

Metal-organic frameworks (MOFs) are becoming promising porous crystal materials, which are composed of metal ions or cluster nodes and organic ligands as linkers, and have a wide range of applications in numerous areas [14]. Almost all transitional and main group metals can be used for assembly with appropriate organic ligands to form functional MOFs. MOFs with custom structure, morphology, and pores can be designed and synthesized by changing metal nodes, organic linkers, or preparation conditions [15]. MOFs has the following advantages: (1) high specific surface area and ordered porous structure, which can promote the adsorption and activation of CO_2 [16], making it suitable for heterogeneous catalysis; (2) the metal nodes in the MOFs structure periodically distribute, which means the effective dispersion of active sites and the increased utilization rate of metal atoms

[17,18]; (3) the structure of the organic ligands used to construct MOFs can be adjusted and modified, which is conducive to regulating the electronic structure of the active site to affect the catalytic performance. The well-defined crystal structure is also conducive to the establishment of the theoretical models, so as to study the structure-activity relationship [19,20]. The above points make MOFs a promising catalyst for ECO₂RR.

However, the application of MOFs as electrocatalysts is largely limited by the low conductivity and the inevitable mass transfer limitation [21]. At the same time, some MOFs may have poor stability during the electroreduction process due to the weak coordination bonds between metal nodes and organic ligands [22]. On the other hand, MOFs are also attractive precursors or sacrifice templates, which can derive into metal (oxide) nanomaterials or metal nanocomposites containing porous carbon structure [23,24]. Compared to the parent MOFs, these derivatives tend to have enhanced intrinsic conductivity, catalytic activity, and stability, showing promising potential in ECO₂RR [25]. More importantly, MOFs derived materials may inherit the characteristics of MOFs, including high specific surface area, adjustable composition, uniform component distribution, and original morphology [26].

In this review, we are particularly concerned with the MOFs and the application as the electrocatalysts for ECO₂RR into formic acid/formate. Our aim in this review article is to summarize the current electrocatalytic performance of MOFs and their derivatives, to demonstrate methods for constructing catalysts from MOFs, and to provide some insights into the future development of MOF-related catalysts.

2. Evaluation of Catalyst Performances

Here we introduce some important metrics for catalyst evaluation, so as to also facilitate the comparison among various catalysts. In fact, there will be inevitable errors in the comparison of catalysts reported by different works, because the experimental conditions used are almost impossible to be completely consistent, including electrode for loading, electrolyte and electrolytic cell device. In addition, all catalysts discussed in this review are summarized in Table 1 and all structure of organic linkers are illustrated in Figure 2.

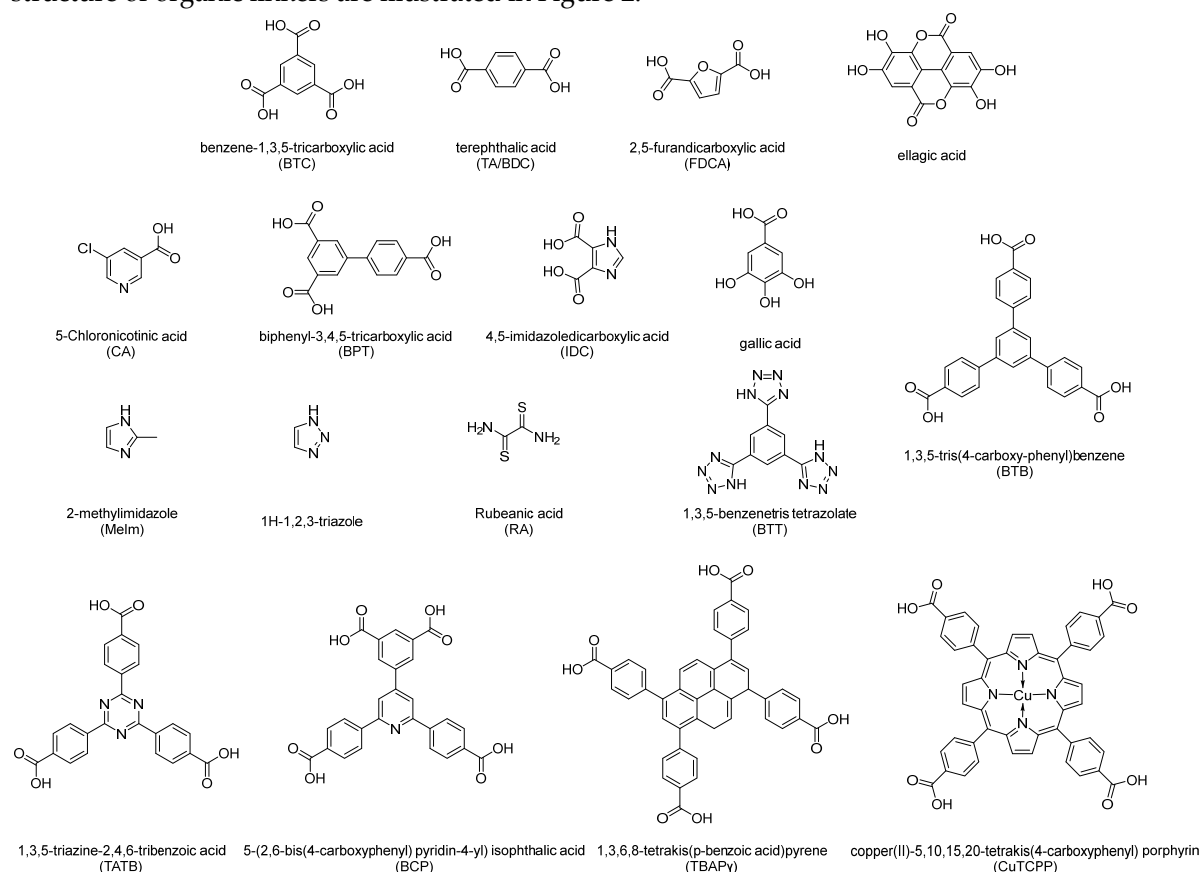


Figure 2. Structures and abbreviations of organic linkers for constructing MOFs discussed in this review.

2.1. FE

Faraday efficiency (FE) reflects the selectivity of the current to specific CO₂ reduction product, and is calculated as the ratio of the amount of charge consumed to produce a product to the total amount of charge consumed to flow through the circuit. High FE values will minimize product separation requirements and reduce the total current required for the target product yield.

2.2. Overpotential and applied potential

Overpotential is defined as the difference between the applied potential and the thermodynamic equilibrium potential of CO₂ reduction to a certain product. Theoretically, the closer the overpotential is to 0 V, the better the catalyst performance, which means the actual voltage required to reach a certain current density and the energy consumption are lower, and the catalytic activity is higher. Since most heterogeneous catalysts discussed in this review are in aqueous systems, where thermodynamic equilibrium potentials are consistent, applied potential is used for evaluation for convenience of introduction. In addition, the potential values below are all versus reversible hydrogen electrode (RHE) unless otherwise stated.

2.3. Current density and TOF

Current density reflects the reaction rate in the ECO₂RR and, to some extent, the conductivity of the catalyst. The value is the current passing through the electrode per unit area. The current density required for commercialization is generally > 200 mA cm⁻².

Turnover frequency (TOF) reflects the intrinsic activity of the catalyst, which is the number of moles of product transformed by the moles of catalytic active species per unit time. The higher the TOF value, the higher the activity of the catalyst. However, in the case of many heterogeneous systems, all catalysts supported are often regarded as active substances. In fact, only the catalyst on the surface plays a role, so the TOF obtained is often the minimum value, which has a large error, so it is not listed in the Table 1. However, for some works requiring special explanation, we still mention this metric.

Table 2. Heterogeneous MOF and MOF derived catalysts for ECO₂RR into HCOOH in this review. The full names of the abbreviations are as following: GO (graphene oxide), TBAB (tetrabutylammonium bromide), DMF (N,N-Dimethylformamide), EMIMBF₄ (1-ethyl-3-methylimidazolium tetrafluoroborate), NSs (nanosheets), MNS (MOF derived nanosheet), NPs (nanoparticles), NC (N-doped carbon matrix), BSG (bismuth subgallate), H (HKUST-1), SOR (surface-oxygen-rich), ZIF (zeolitic imidazolate framework).

MOF	Organic linkers	MOF-derived materials	cell	electrolyte	Potential (V vs. RHE)	FE _{HCOOH} (%)	Current density (mA/cm ⁻¹)	Stability (h)	refs
1. MOFs materials									
CR-MOF (Cu)	BDC	-	H-cell	0.5 M KHCO ₃	-1.2/-1.4/-1.6 vs. SHE	~>29.4	-	-	[18]
				0.1 M KHCO ₃	-0.1 vs. SCE	21	-	-	
Cu-MOF	BTC	-	H-cell	0.1 M TBAB/DMF	-0.6 vs. SCE	58	-	-	[27]

Cu ₂ (CuTCPP)CuTCPP	CuO, Cu ₂ O and Cu ₄ O ₃		H-cell	1M H ₂ O and 0.5 M EMIMBF ₄ /CH ₃ CN	-1.55 vs. Ag/Ag ⁺	68.4	-	-	[21]
PCN-222(Cu) (Zr)	CuTCPP	-				44.3	3.2	10	
PCN-224(Cu) (Zr)	CuTCPP	-	H-cell	0.5 M KHCO ₃	-0.7				[28]
						34.1	2.4	10	
Bi-BTB	BTB	Bi ₂ O ₂ CO ₃	H-cell	0.5 M KHCO ₃	-0.669	96.1	13.2	48	[29]
					-0.969	80	60.5	-	
Bi-MOF	BTC	Bi and Bi ₂ O _{2.5}	flow cell	1 M KOH	-0.64	92	150	-	[30]
			H-cell	0.1 M KHCO ₃	-1.1	80	10	30	
CAU-17 (Bi)	BTC	-	H-cell	0.1 M KHCO ₃	~-0.9	92.2	-	30	[10]
Bi-FDCA	FDCA	Bi ₂ O ₂ CO ₃	H-cell	0.1 M KHCO ₃	-1.2	95.1	19.6	-	[31]
BiBTB	BTB					95	5.4	-	
SU-100 (Bi)	BPT	Bi ₂ O ₂ CO ₃				90	8.0	-	
dense BiBTC	BTC					80	4.8	-	
CAU-17 (Bi)	BTC		H-cell	0.5 M KHCO ₃	-0.97	-	-	-	[32]
SU-101 (Bi)	ellagic acid	-				-	-	-	
BSG (Bi)	gallic acid	Bi ₂ O ₂ CO ₃				85	7.6	-	
In-BDC	BDC	-	H-cell	0.5 M KHCO ₃	-0.669	88	7.4	21	[33]
0.6SZ									
(ZIF-8 with Sn doping)	MeIm	-	H-cell	0.5 M KHCO ₃	-1.1	74	27	7	[17]
	MeIm								
Sn-N ₆ -MOF	and 1H-1,2,3-triazole	Sn nanoclusters	H-cell	0.5 M KHCO ₃	-1.23	85	23	6	[34]
MIL-53 (Al)	BDC	-	flow cell	0.05 M K ₂ CO ₃	-0.9 ~ -1.1	14 ~ 19	-	-	[35]
2. Metal Nanomaterials (Electrochemical Reduction)									
Cu-SIM NU-1000 (Zn)	TBAPy	Cu NPs	H-cell	0.1 M NaClO ₄	-0.82	28	1.2	-	[36]
H-Cu	BTC	HE-Cu	H-cell	0.1 M KHCO ₃	-1.03	40.1	-	-	[37]
CAU-17 (Bi)	BTC	Bi NSs	H-cell	0.1 M KHCO ₃	-1.1	92	~10.8	10	[38]
CAU-17 (Bi)	BTC	Bi NSs	flow cell	1 M KOH	-0.48	97.4	133	>10 (>200 mA cm ⁻²)	[39]
CAU-17 (Bi)	BTC	Bi/CC-17 NSs	H-cell	0.5 M KHCO ₃	-1.1	98	45	48	[40]
Bi-MOF	BDC	BiMNS	H-cell	0.5 M KHCO ₃	-0.8	98	23.5	40	[41]

BiMOLs	IDC	Bi-ene	H-cell	0.5 M KHCO ₃	-0.83 ~ -1.18	~100	72.0 (-1.18 V)	12 (-0.9 V)	[42]
			flow cell	1M KOH	-0.57/-0.75	99.8/99.2	100/200	-	
BiBTB	BTB	Bi NPs	H-cell	0.5 M KHCO ₃	-0.97	95	5.4	32	[43]
Pb-MOF	CA	Pb ₃ (CO ₃) ₂ (OH) ₂ (ER-HC)	H-cell	0.1 M KHCO ₃	-0.88	96.8	2.0	-	[44]
3. Carbon-based Nanocomposites (Carbonization)									
Cu-BTC	BTC	Cu ₂ O/Cu@NC-800	H-cell	0.1 M KHCO ₃	-0.68	70.5	-	30	[23]
Cu-BTT	BTT	Cu-N-C ₁₁₀₀	H-cell	0.1 M KHCO ₃	-0.9	38.1	3.7	-	[45]
			H-cell	0.5 M KHCO ₃	-0.9	92	8.0	10	
BiBTC	BTC	Bi ₂ O ₃ @C	flow cell	1 M KOH	-0.3 ~ -1.4	>93%	1.4-208	1	[25]
SU101 (Bi)	ellagic acid	SOR Bi@C NPs	H-cell	0.5 M KHCO ₃	-0.99	95	11.1	18 (-1.0 V)	
			flow cell	1 M KOH	-1.12	90	100	-	[46]
MIL-68 (In)	BDC	In ₂ O ₃ -x@C MIL-68-N ₂	flow cell	1 M KOH	-0.4/-1	84/97	13.1/221.65	120 (-1.0 V)	[47]
V11 (In)	BCP	CPs@V11	H-cell	0.5 M KHCO ₃	-0.84	90.1	7.62	20	[48]
ZIF-8 (Zn)	MeIm	InSAs/NC	H-cell	0.5 M KHCO ₃	-0.65	96	8.9	-	[49]
ZIF-8 (Zn)	MeIm	In-N-C	H-cell	0.5 M KHCO ₃	-0.79	80	8.5	20	[50]
5. Bimetallic Nanocomposites									
Cu, Bi bi-MOF	BTC	Cu ₁ -Bi/Bi ₂ O ₃ @C (Carbonization)	H-cell	0.5 M KHCO ₃	-0.94	93	~11.5	10	[16]
CuBi-MOF	BTC	CuBi75 (Carbonization)	H-cell	0.5 M KHCO ₃	-0.77	100	-	24	[51]
			H-cell	0.1 M KHCO ₃	-1.1	97.6	-	30	
In-Bi-MOF	BTC	BiIn alloy NPs (Electrochemical Reduction)	flow cell	1M KOH	-0.92	97.8	250	-	[52]
			MEA	0.1 M KHCO ₃	-	-	-	25 (120 mA cm ⁻²)	
Bi-In-MOF	BTC	BiIn ₅ -500@C (Carbonization)	H-cell	0.5 M KHCO ₃	-0.86	97.5	13.5	15	[53]
MOF-808 (Zr)	BTC	M-AuPd(20) (Chemical Reduction)	H-cell	0.1 M KHCO ₃	-0.25	>99	~7	-	[12]

3. MOFs Materials

3.1. Copper-Based MOFs

Cu is the only metal with the ability for hydrocarbon formation, and is one of the most promising candidates as an ECO₂RR catalyst. However, due to its ability to produce multiple products and the

complex reaction pathways of CO₂ reduction, copper-based catalysts are often less selective for one particular product.

In 2012, MOFs was first applied in the field of ECO₂RR [18]. Copper rubeanate MOF (CR-MOF) is synthesized with rubeanic acid (RA) as the organic linker and Cu²⁺ as the metal node. The initial CO₂ reduction potential of CR-MOF is more positive than that of Cu. At -1.2 V, -1.4 V and -1.6 V versus standard hydrogen electrode (vs. SHE), HCOOH accounts for more than 98% of CO₂ reduction products, although the FE for CO₂ reduction is only 30%. Both HCOOH selectivity and yield are much higher than that of Cu. HCOOH is believed to be easily produced under the condition of weak CO₂ adsorption. Cu²⁺ and the structure of MOF reduce the electron density in the active center, leading to weak adsorption of CO₂ at the active sites and selective generation of HCOOH. At the same time, the abundant pores in CR-MOF are speculated to restrict other reaction pathways in the active center, resulting in high HCOOH selectivity. This study has preliminarily demonstrated the application potential of MOF catalysts for ECO₂RR.

Cu-MOF constructed from benzene-1,3,5-tricarboxylic acid (BTC) is investigated in six electrolyte systems after mixing with graphene oxide (GO) [27]. In 0.1 M KHCO₃, the catalyst has the lowest starting potential and reaches FE_{HCOOH} of 21% at -0.1 V versus standard calomel electrode (vs. SCE). In 0.1 M tetrabutylammonium bromide/ N,N-Dimethylformamide (TBAB/DMF), the highest FE for HCOOH (FE_{HCOOH}) of 58% arrived at -0.6 V vs. SCE. GO improves the conductivity and product selectivity of the catalyst. Only FE of 38% is reached when Cu-MOF is used alone. In addition to HCOOH, a small amount of acetic acid is also produced.

Cu₂(CuTCPP) nanosheets (NSs) is synthesized by Cu₂(COO)₄ paddle wheels connected four copper(II)-5,10,15,20-tetrakis(4-carboxyphenyl) porphyrin (CuTCPP), which possesses two-dimensional lamellar porous mesh frame structure (Figure 3a). The use of CuTCPP as an organic linker for the construction of MOF catalysts is a special case because CuTCPP also contains active sites. During the initial process of electrolysis, the current density increases gradually, and chemical recombination may occur. The changes of catalysts at -1.55 V vs. Ag/Ag⁺ are detected by *ex situ* powder X-ray diffraction (XRD) (Figure 3b), and the unstable Cu²⁺ carboxylate nodes may be transformed into CuO, Cu₂O and Cu₄O₃, which with the CuTCPP synergistically promote the reduction of CO₂ to formate and acetic acid in 1 M H₂O and 0.5 M 1-ethyl-3-methylimidazolium tetrafluoroborate (EMIMBF₄)/CH₃CN systems. The highest value of FE for HCOO⁻ (FE_{HCOO⁻}) reaches 68.4% at -1.55 V vs. Ag/Ag⁺, while the FE for acetate also reaches 16.8% [21].

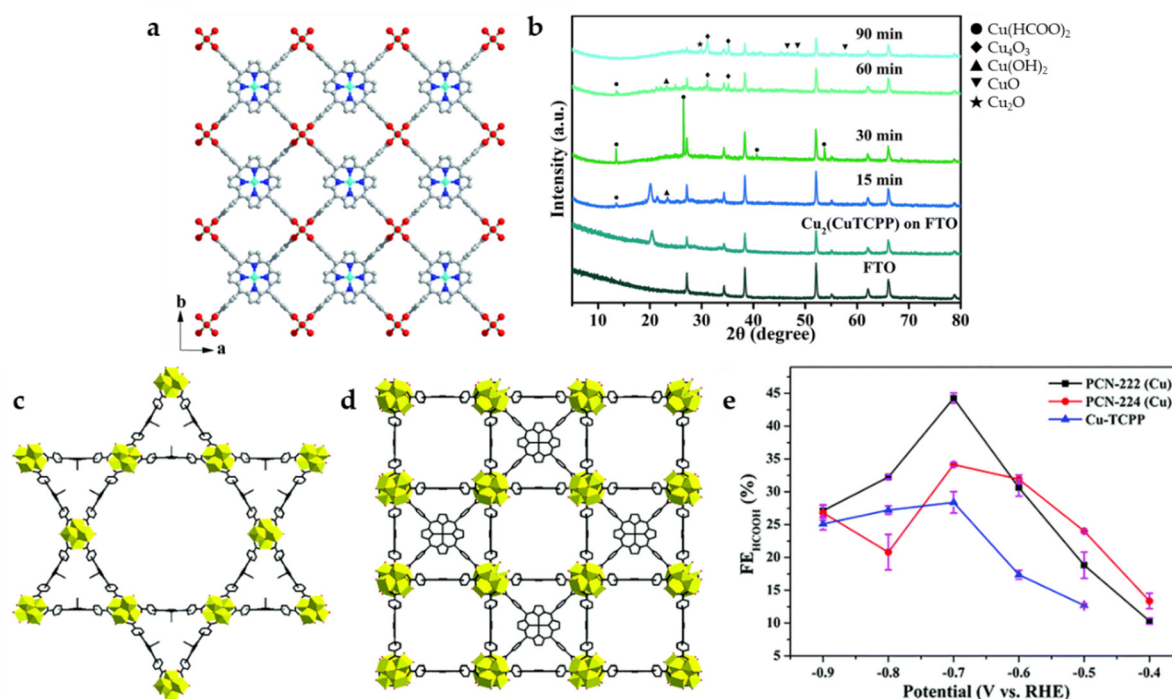


Figure 3. (a) Crystal structure of Cu₂(CuTCPP) NSs along the c axis. Red is O, blue is N, grey is C and cyan is Cu. (b) XRD of Cu₂(CuTCPP) NSs on a F-doped Tin oxide (FTO) electrode with different reaction times [21]. Copyright 2019, RSC. Structural models of (c) PCN-222(Cu) and (d) PCN-224(Cu). (e) FE_{HCOOH} in 0.5 M KHCO₃ solution [28]. Copyright 2020, RSC.

In order to explore the influence of MOFs catalysts with different structures on ECO₂RR performance, CuTCPP is used as an organic linker with Zr₆ cluster as a metal node to construct two types of porphyrin-based MOFs (PCN-222(Cu) and PCN-224(Cu)) with different internal structures (Figure 3c and d) [28]. Compared to PCN-224(Cu) with microporous interactively-across rectangular channel, PCN-222(Cu) with mesoporous tubular-like channel shows higher BET surface area, better CO₂ absorption and larger pore size, which is more conducive to mass transfer. PCN-222(Cu) shows higher catalytic activity and selectivity for HCOOH at -0.7 V (Figure 3e), and the FE reaches 44.3% with a current density of 3.2 mA cm⁻². On the other hand, PCN-224(Cu) has greater heat of adsorption and a higher affinity for CO₂, which can promote the exposure of active sites, so it has better performance at lower potentials (-0.4 - -0.6 V).

3.2. Bismuth-based MOFs

Bi has been identified as a potential catalyst with several advantages: (1) Bi is abundant in Earth and low in cost, being necessary for industrial applications; (2) Bi has low HER activity, which is a competitive reaction at cathode potential, and inhibiting hydrogen evolution can improve energy conversion efficiency [54]; (3) Bi has low adsorption energy of *CO intermediate and strong stabilization ability of *HCOO intermediate, which is conducive to the formation of HCOOH [39]. Although the bismuth-based catalysts has been reported to have the FE_{HCOOH} higher than 90%, the low current density (<10 mA cm⁻²) has hindered industrial applications [55]. Compared to bulk Bi, bismuth-based MOF-derived catalysts tend to have higher stability and conductivity, and show excellent catalytic activity, which is due to the large surface area and abundant unsaturated active sites.

Some Bi-carboxylate MOFs will be decomposed in KHCO₃ electrolyte and *in situ* converted into Bi₂O₂CO₃, which is the active material for ECO₂RR (Figure 4a). By XRD, obvious Bi₂O₂CO₃ correlated peaks can be observed after electrolysis or immersion of Bi-BTB in KHCO₃ electrolyte (Figure 4b). Bi-BTB MOF-derived Bi₂O₂CO₃ shows good catalytic activity and the product selectivity, and reaches FE_{HCOO⁻} of 96.1% with a current density of 13.2 mA cm⁻² at -0.699 V. At the same time, it has excellent structural stability with no obvious drop of current density occurs in 48 h electrolysis, and FE_{HCOO⁻} is maintained above 93%. Another Bi-MOF with 1,3,5-triazine-2,4,6-tribenzoic acid (TATB) as the organic linker can undergo similar *in situ* transformation, suggesting that the effect of HCO₃⁻ electrolyte-mediated dissociation is universal [29].

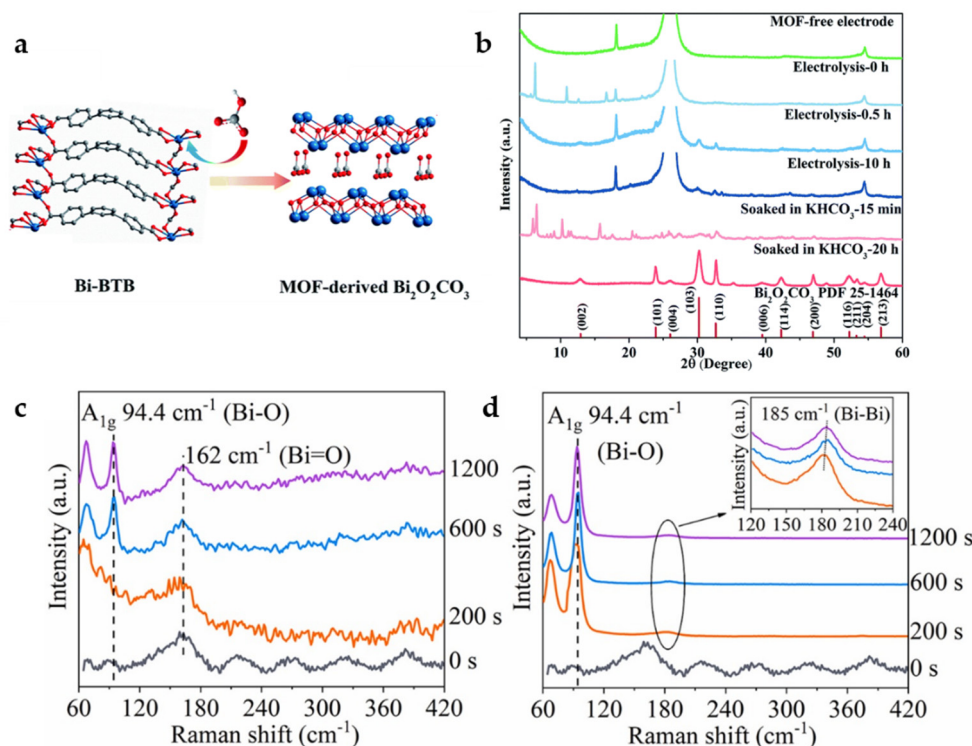


Figure 4. (a) Proposed mechanism for the formation of MOF-derived $\text{Bi}_2\text{O}_2\text{CO}_3$. (b) XRD patterns of carbon paper electrode (green), Bi-BTB/carbon paper electrode before electrolysis (sky blue), after 0.5 h electrolysis (steel blue) and after 10 h electrolysis (dark blue), and Bi-BTB soaked in KHCO_3 after 15 min (salmon) and after 20 h (firebrick) [29]. Copyright 2020, RSC. *In situ* Raman spectra of Bi-BTC during the catalytic process under various potentials: (c) -0.5 V and (d) -0.7 V at 0.1 M KHCO_3 [30]. Copyright 2022, Elsevier.

In addition, the electrolyte-mediated dissociation product $\text{Bi}_2\text{O}_2\text{CO}_3$ undergoes further transformation under the condition of electroreduction. Bi-BTC MOF observation by *in situ* Raman spectra shows that $\text{Bi}_2\text{O}_2\text{CO}_3$ gradually transforms into Bi and $\text{Bi}_2\text{O}_{2.5}$ at -0.7 V (Figure 4c and d), in which the rich Bi/Bi-O interface is the active site that can promote the reduction of the free energy barrier of $^*\text{HCOO}$ intermediate formation. In the flow cell, a maximum FE_{HCOOH} of 92% is achieved at -0.64 V with a current density of 150 mA cm^{-2} in 1.0 M KOH , and a long time stability of 30 h is achieved with FE_{HCOOH} above 80% in the H-cell [30]. Although it can be seen by XRD that MOF has been completely transformed into Bi and $\text{Bi}_2\text{O}_{2.5}$ mixture after reaction, the utilization of *in situ* skills is still an effective way to explore the intrinsic catalytic properties of such MOF-derived catalysts.

There are also some interesting findings in the study of Bi-BTC MOF (CAU-17). Through the the operando X-ray absorption fine structure (XAFS) analysis (Figure 5a and b), it is found that CAU-17 keep close to Bi^{3+} for more than 90 minutes at -0.9 V , while 2D Bi NSs, Bi_2O_3 nanotube completely transformed into Bi^0 within 1h. The MOF structure is thought to play a key role in maintaining Bi in the +3 oxidation state at the reduction potential, which is conducive to the long-term ECO_2RR . CAU-17 reaches FE_{HCOOH} of 92.2% at -0.9 V and maintains the product selectivity along with current density almost unchanged for 30 h (Figure 5c and d) [10].

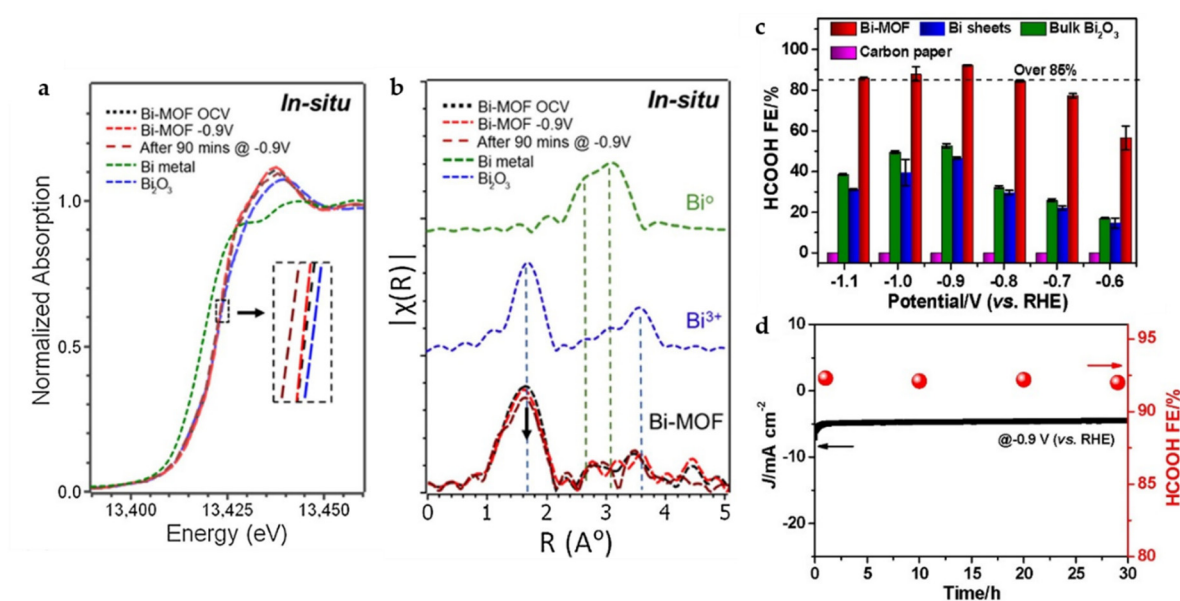


Figure 5. (a) X-ray absorption near-edge structure (XANES) and (b) Fourier transform of extended X-ray absorption structure (FT-EXAFS) spectra under *in-situ* electrochemical CO₂ reduction conditions for Bi-MOF along with those for Bi metal and Bi₂O₃ as reference standards. (c) FE_{HCOOH} of CAU-17, Bi sheets, bulk Bi₂O₃, and carbon paper electrodes in CO₂-saturated 0.1 M KHCO₃ solution. (d) Current density and FE_{HCOOH} of CAU-17 during long-term electrolysis at -0.9 V [10]. Copyright 2020, Elsevier.

Replacing terephthalic acid (TA) derived from fossil fuels with 2,5-furandicarboxylic acid (FDCA) derived from biomass platform molecule 5-hydroxymethylfurfural (HMF) as the organic linker of MOFs is a strategy with economic and environmental effects. The Bi-FDCA MOF also reaches a high FE_{HCOOH} of 95.1% with current density of 19.6 mA cm⁻² at -1.2 V. Interestingly, the FDCA can be obtained from the catalytic oxidation reaction of HMF in anode, which effectively establishes the coupling system of anode and cathode [31].

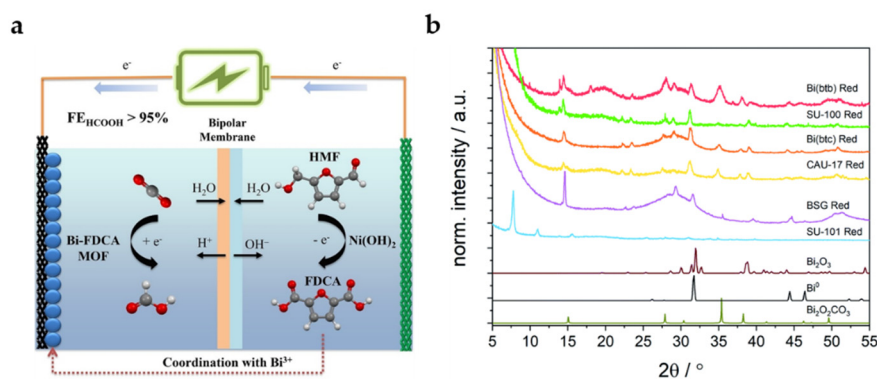


Figure 6. (a) Diagrammatic sketch for coupling system of ECO₂RR in cathode and oxidation reaction of HMF in anode [31]. Copyright 2022, Wiley-VCH. (b) Grazing incidence XRD data collected using Co Kα radiation ($\lambda = 1.79 \text{ \AA}$) on coordination polymers (CPs) deposited on glassy carbon electrodes after reduction for 30 min at -0.97 V. The diffraction patterns are compared with calculated patterns for Bi₂O₃, Bi, and Bi₂O₂CO₃ [32]. Copyright 2021, RSC.

Lock et al. summarized Bi coordination polymers (CPs) with different organic linkers, including CAU-17, dense BiBTC, BiBTB, SU-100 (BiBPT), SU-101 (Bi MOF with ellagic acid as the organic linker), and bismuth subgallate (BSG) [32]. The stability of CPs precursors is particularly important for their intrinsic catalytic activities. As XRD patterns shown, most CPs undergo solvent assisted linker exchange (SALE) after electrochemical reduction in HCO₃⁻ electrolyte and transform into the active species Bi₂O₂CO₃, which is similar with the electrolyte-mediated dissociation process

mentioned above. Only the most stable SU-101 is not found to undergo structural transformation, which is accompanied by low catalytic activity. At -0.97 V, SU-100 possesses the highest catalytic activity, while BiBTB shows the highest formate selectivity. Unfortunately, except for SU-101, no rule has been found between the porosity and local coordination of different MOFs and catalytic activity, which needs to be further explored.

3.3. Indium-Based MOFs

In has attracted more attention as a catalyst for ECO₂RR to formate due to its non-toxic and environmental properties. However, the low FE and poor stability of indium-based electrocatalysts seriously hinder their practical application [49]. Compared with In catalysts, In-terephthalic acid (In-BDC) MOF catalysts show higher formate selectivity, faster reaction kinetics, more active sites and higher TOF [33]. In-BDC performs a maximum FE_{HCOO⁻} of 88% at -0.669 V. In addition, unlike the Bi-carboxylate MOFs described above, SALE process is not observed on In-BDC in KHCO₃ electrolyte for long-term electrolysis. The Raman and In 3d XPS spectra (Figure 7a and b) indicate that the morphology and metal valence of In-BDC do not change after electrolysis, showing good stability of the catalyst.

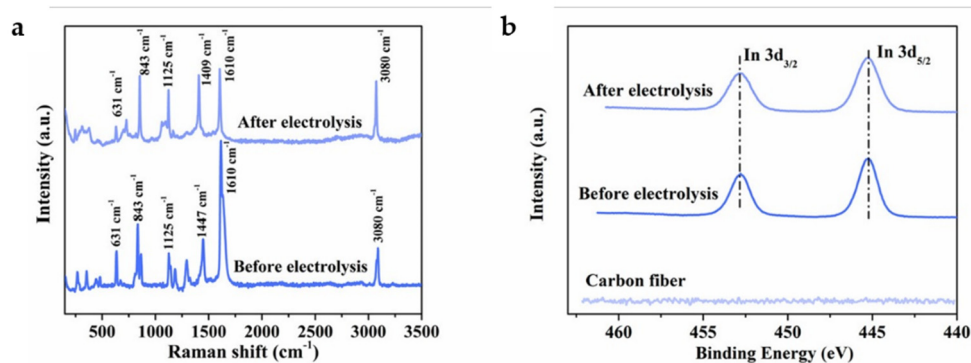


Figure 7. (a) Raman spectra of the In-BDC catalyst before and after electrolysis. (b) In 3d XPS spectra of the In-BDC catalyst before and after electrolysis [33]. Copyright 2020, ACS.

3.4. Tin-Based MOFs

New active sites can be introduced into MOFs by means of metal nodes exchange. Sn is successfully doped into zeolitic imidazolate framework-8 (ZIF-8) by ion exchange method (Figure 8a). The presence of Sn nodes further improves the CO₂ adsorption capacity of the material, and the combination with MOF shows a larger physical and electrochemical active surface area, as well as easy charge transfer, thus showing a better catalytic activity and product selectivity. It exhibits a FE_{HCOO⁻} of 74% and current density of 27 mA cm⁻² at -1.1 V [17].

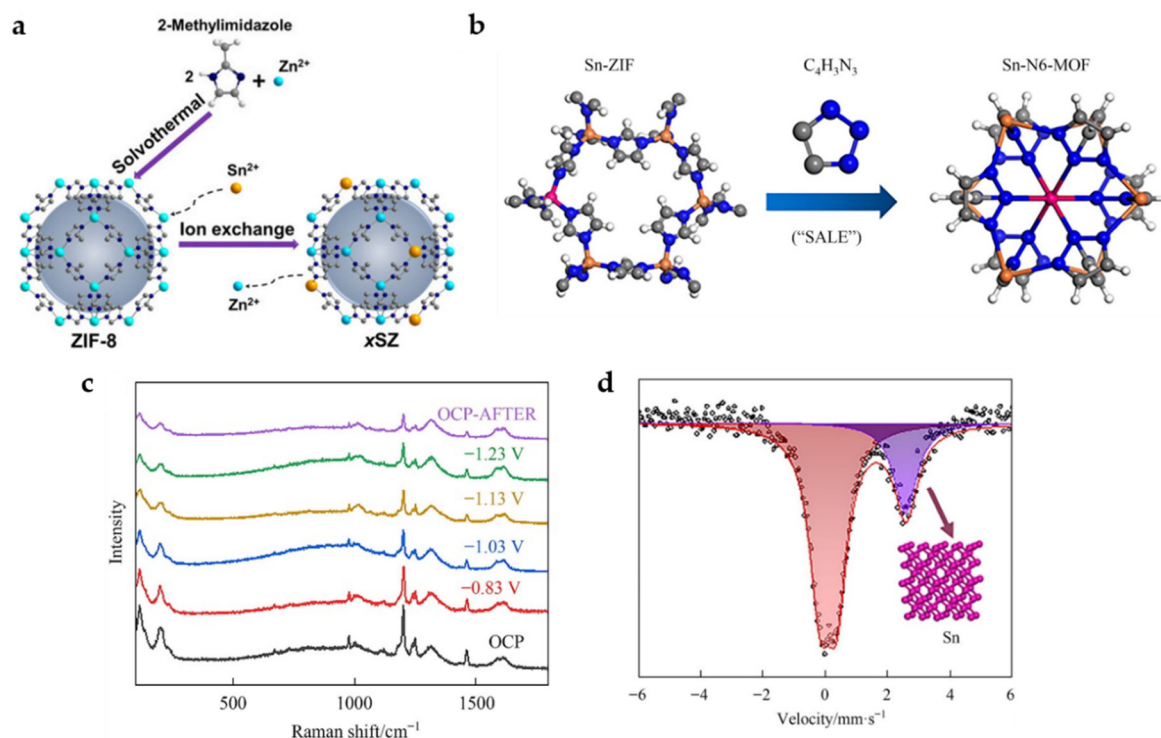


Figure 8. (a) Schematic illustration showing the preparation of Sn-doped ZIF-8 catalysts [17]. Copyright 2020, Wiley-VCH. (b) Diagram of the synthetic procedures for Sn-N6-MOF. (c) The in-situ Raman spectra measured with varying the applied potential at -1.23 V in CO₂-saturated 0.5 M KHCO₃ electrolyte. (d) Room temperature ¹¹⁹Sn Mössbauer spectra acquired after maintained at -1.23 V in CO₂-saturated 0.5 M KHCO₃ electrolyte for 1 h [34]. Copyright 2022, Elsevier.

In addition, organic ligands can also be exchanged. The Sn-doped ZIF-8 is successfully converted into 2% Sn-N6-MOF with six N coordination by SALE method in 1H-1,2,3-triazole (Figure 8b). *In situ* Raman spectra (Figure 8c) show that the characteristic Raman peaks attributed to C-N (1000–1400 cm⁻¹), C=C, C=N (1400–1600 cm⁻¹) and Sn (Zn)-N (197 cm⁻¹) gradually weakens with the increase of the applied potential from -0.83 to -1.23 V, suggesting the possible structural reconstruction of the 2% Sn-N6-MOF catalyst and loss of organic ligands. Room temperature ¹¹⁹Sn Mössbauer spectra (Figure 8d) further prove that the MOF structure recombines during electrolysis with Sn nanoclusters formed as the real active sites. The FE_{HCOOH} of 85% with a current density of 23 mA cm⁻² is achieved at -1.23 V [34].

3.5. Aluminum-Based MOFs

In addition to the above metals, Al also has a certain catalytic capacity for HCOOH product. Although the HCOOH selectivity is low, some interesting results have been obtained when combined Al with MOF. An Al-MOF constructed by BDC has been reported for ECO₂RR [35]. The limited reaction environment in the MOF is conducive to the stable electrochemical process for the generation of Al⁰ active centers, which are usually readily oxidized to Al³⁺ in air. Compared with Al(OH)₃, the structure of MOF changes the reaction environment leading to the occurrence of different reaction paths. In addition to the inherent catalytic activity of the original HCOOH formation, the ability to produce CO is also obtained, although the FEs for both products are low (19% for HCOOH and 21% for CO at -1.1 V).

4. MOFs-Derived Metal Nanomaterials

In situ electrochemical reduction is a mild and effective reduction method. For some unstable MOFs, the pretreatment process of electrochemical reduction is often accompanied by the dissociation of organic linkers and the aggregation of metal active centers to form metal nanomaterials. At the same time, compared with reducing agents, electrochemical reduction often retains some M-O species or organic ligands on the surface, which has an important impact on catalytic activity and stability. The structure of MOFs precursor also has an important impact on the morphology of the derived catalyst and the corresponding ECO₂RR performance.

4.1. Copper-Based Nanomaterials

The electrocatalytic activity of Cu catalysts can be significantly enhanced by reducing the particle size, especially in the particle size range of less than 10 nm. In addition, electrochemically reduced Cu nanoparticles (NPs) from copper oxide appear to be particularly suitable for ECO₂RR and have been shown to be superior to both polycrystalline Cu and hydrogen reduced Cu from copper oxide at high temperature. A solvothermal deposition in MOF method is adopted to deposit Cu²⁺ in a Zr-MOF (NU-1000). Cu NPs are further formed in electrochemical reduction, while the size of NPs are effectively limited by the pore size of MOF (Figure 9a), leading to a maximum FE_{HCOO⁻} of 28% at -0.82 V in 0.1 M KClO₄ electrolyte [36].

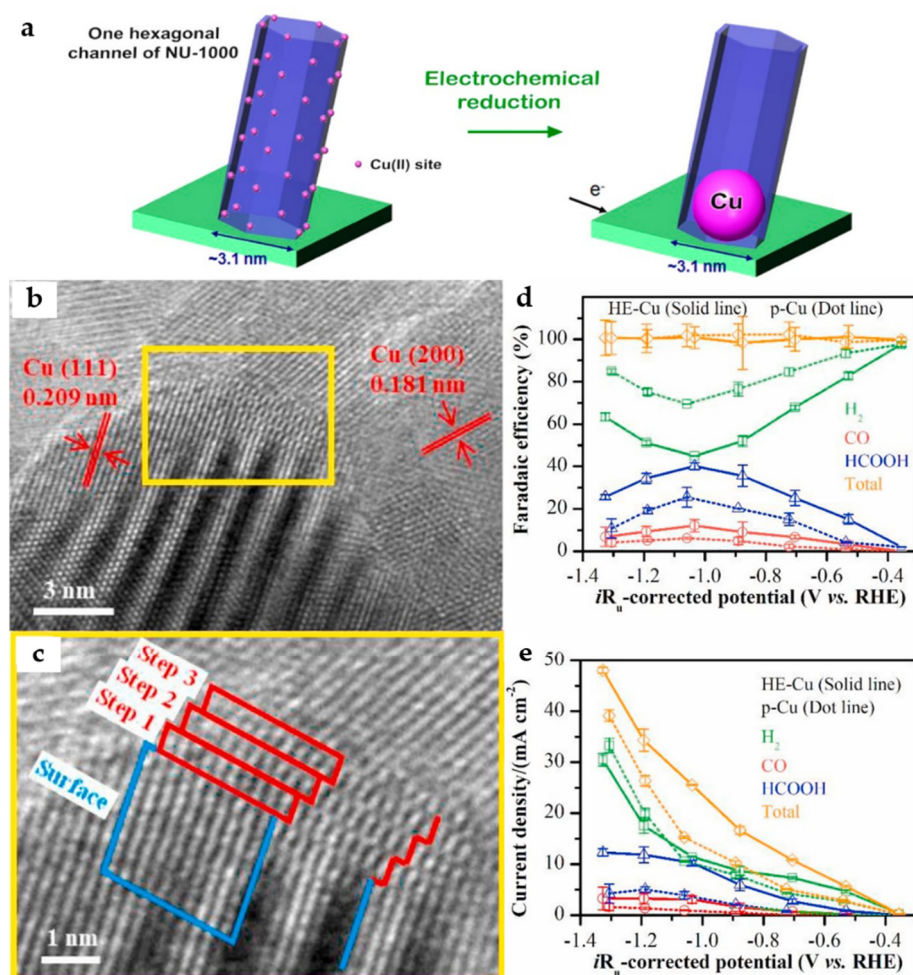


Figure 9. (a) Schematic representation of the electrochemical reduction of Cu²⁺ to generate metallic Cu NPs [36]. Copyright 2017, ACS. (b) The HRTEM images of the HE-Cu and (c) stepped Cu (211) surface of the selected area. (d) Faradaic efficiency and (e) current density of the ECO₂RR products for the HE-Cu and p-Cu electrodes in CO₂-saturated 0.1 M KHCO₃ solution [37]. Copyright 2021, Elsevier.

By *in situ* electroreduction, the HKUST-1-covered Cu foam electrode is transformed into HE-Cu electrode with the morphology of NSs. The step-like structure can be observed by high resolution transmission electron microscopy (HRTEM) images (Figure 9b and c), which is considered to be a Cu (211) surface. According to the DFT calculations, the stepped (211) surface of Cu catalyst is more favorable to the formation of HCOOH than the stepped (111) and stepped (200) surfaces. Moreover, it has suitable binding ability with $^*\text{CO}$, being conducive to further reduction to $^*\text{COH}/^*\text{CHO}$ intermediates, followed by producing C_2 products. Compared with the p-Cu without the stepped (211) surface, it has higher catalytic activity and HCOOH selectivity (Figure 9d and e), reaching a FE_{HCOOH} of 40.1% at -1.03 V, as well as the highest FEs for C_2H_4 and C_2H_6 of 2.93% and 2.58%, respectively at -1.19 V [37].

4.2. Bismuth-Based Nanomaterials

As mentioned above, the SALE process will occur in the HCO_3^- electrolyte for Bi-carboxylate MOFs, which then derive into $\text{Bi}_2\text{O}_2\text{CO}_3$. After further electrochemical reduction process, the Bi nanomaterial is obtained. In this regard, the CAU-17 will derive into $\text{Bi}_2\text{O}_2\text{CO}_3$ NSs in the HCO_3^- electrolyte, and the thickness of NSs is affected by the concentration of HCO_3^- , which influence the thickness of Bi NSs obtained in the next electrochemical reduction process. Bi NSs with thickness of 3.5 nm and 11 nm are obtained by 0.1 M and 1 M KHCO_3 electrolyte and electrochemical reduction, respectively. Thinner Bi NSs provide more accessible active sites and exhibit faster electron transfer, exhibiting higher catalytic activity and formate selectivity (Figure 10a and b). The 3.5 nm Bi NSs exhibit $\text{FE}_{\text{HCOO}^-}$ of 92% and partial current density of $\sim 10.8 \text{ mA cm}^{-2}$ at -1.1 V [38].

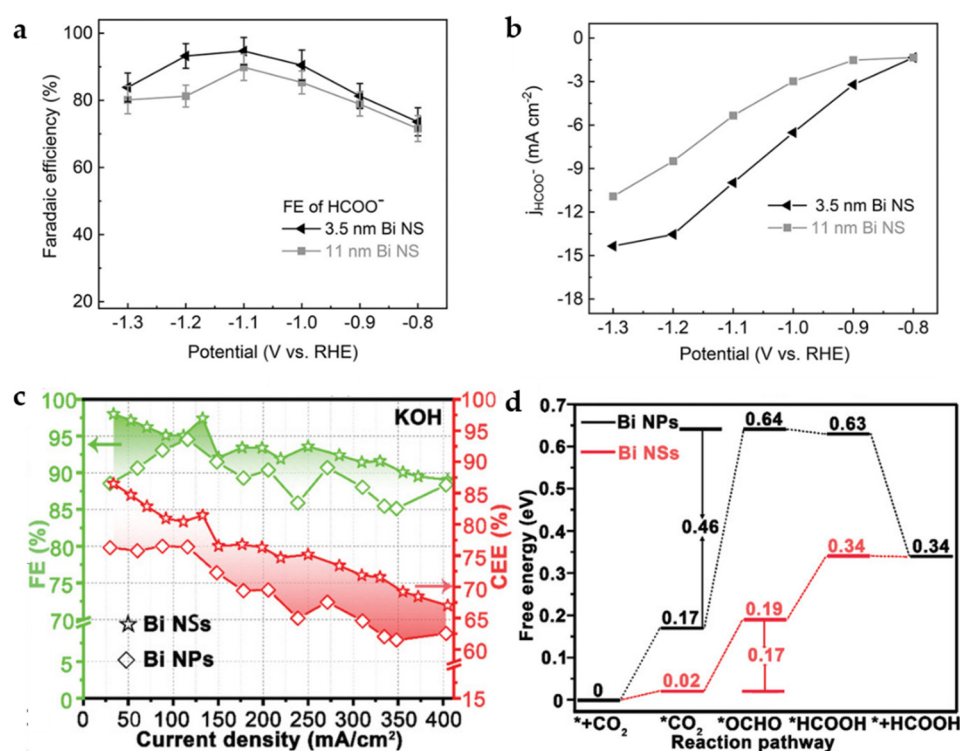


Figure 10. (a) $\text{FE}_{\text{HCOO}^-}$ of 3.5 nm and 11 nm Bi NSs in CO_2 -saturated 0.1 M KHCO_3 . (b) Partial current densities for HCOO^- of 3.5 nm and 11 nm Bi NSs [38]. Copyright 2021, Wiley-VCH. (c) FEs and CEEs for HCOOH of Bi NPs and Bi NSs in 1 M KOH. (d) Gibbs free energy diagrams for CO_2 electroreduction to HCOOH on Bi NPs and Bi NSs [39]. Copyright 2020, Wiley-VCH.

Residual Bi-O species are inevitable in the process of electrochemical reduction of CAU-17 to obtain Bi NSs. Compared to the Bi NPs obtained by reduction with the strong reducing agent e.g. sodium borohydride, the FEs and cathodic energetic efficiency (CEEs) for HCOOH of Bi NSs have shown obviously higher than that of Bi NPs without Bi-O species (Figure 10c). The DFT calculations

(Figure 10d) indicate that O atoms at the Bi-O surface of Bi NSs help to reduce the free energy barrier for forming $^*\text{OCHO}$ intermediate, resulting in a high FE_{HCOOH} of 97.4% with current density of 133 mA cm^{-2} at -0.48 V in the flow cell [39].

The corresponding Bi NPs can be obtained by CAU-7 with BTB as organic linker. However, compared to Bi-BTC, the larger BTB makes Bi^{3+} too far apart from each other, leading to unstable dissociative Bi^{3+} during the electroreduction dissociation process. Finally, only aggregated Bi NPs can be obtained. The NSs structure derived from Bi-BTC is more conducive to adhesion to the surface of the carbon cloth, which promotes the charge transfer between the substrate and the catalyst, and thus exhibits better catalytic activity [40].

Bi MOF-derived nanosheets (MNS) constructed from BDC can also be obtained by electrochemical reduction [41]. In this process, metal coordination bonds break and violent structural recombination occurs. The main components of BiMNS are Bi and a small amount of Bi_2O_3 . According to *in situ* Raman spectra (Figure 11a), the organic-associated peaks disappear with cyclic voltammetry (CV) cycles increasing, demonstrating the disappearance of the organic linkers. Compared with Bi NSs synthesized by conventional wet chemical, BiMNS shows better stability, because the residual ligands on the surface inhibit the dissolution and re-deposition of Bi atoms on the surface, preventing the deactivation of the active sites during long-term electrocatalysis (Figure 11b). This modification strategy can also be applied to synthesize indium-based catalyst, which also shows good activity and durability.

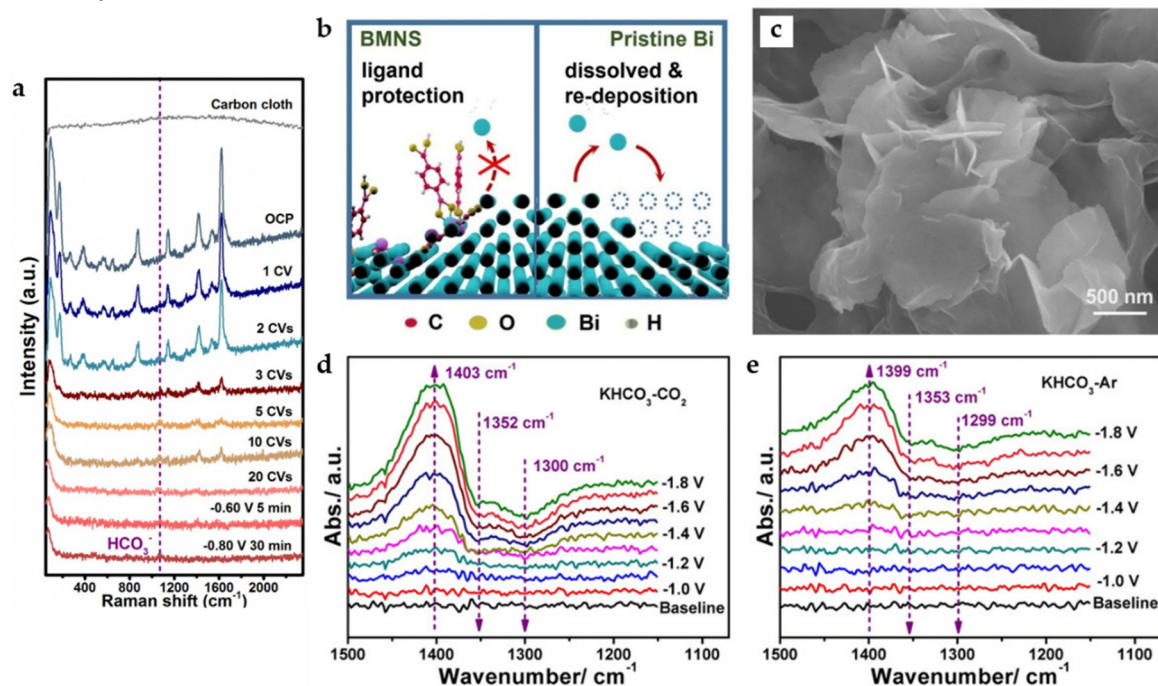


Figure 11. (a) *In situ* Raman spectra for showing the transformation from Bi-MOF to BMNS. (b) Proposed mechanism of action for ligands adsorbed on the surface of BiMNS preventing the deactivation of active sites [41]. Copyright 2021, Elsevier. (c) Scanning electron microscopy (SEM) images of Bi-ene. *In situ* ATR-IR spectra collected under different applied potentials in (d) CO_2 and (e) Ar-saturated 0.5 M KHCO_3 (all applied potentials are vs. Ag/AgCl in this part) [42]. Copyright 2020, Wiley-VCH.

Metallenes have also received attention due to their high atomic utilization rate. Bi metal organic layers (MOLs) constructed by 4,5-imidazoledicarboxylic acid (IDC) with unique bilayer structure and a tendency to grow in thin layers can be converted into bismuthene (Bi-ene) with fewer layers by electrochemical reduction. It has an ultra-thin NSs morphology similar to graphene (Figure 11c), and the thickness is only 1.28 - 1.45 nm, which is the thinnest Bi NSs reported so far. The phase transition involves not only the *in situ* electrochemical reduction of Bi^{3+} in Bi MOLs, but also the migration of Bi atoms due to the gradual loss of organic ligands, and the dissociated ligands may serve as soft

templates to control the final morphology of Bi-ene. The catalyst reaches FE_{HCOO^-} of nearly 100% in the potential range of -0.83 to -1.18 V, and maintains this formate selectivity in flow cell at the current density of 200 mA cm⁻². The *in situ* attenuated total reflection-infrared (ATR-IR) spectra (Figure 11d) suggest that the *OCHO intermediate (the upward peaks at 1403 cm⁻¹) is formed while the absorbed HCO₃⁻ groups (the downward peaks at 1352 cm⁻¹ and 1300 cm⁻¹) are consumed. Surprisingly, the similar phenomenon is also observed in *in situ* ATR-IR spectra under Ar condition (Figure 11e), while formate is detected after electrolysis in Ar-saturated KHCO₃. A new mechanism is proposed: when the applied overpotential is low, some easily absorbed HCO₃⁻ groups can directly participate in the formation of formate. With the increase of the applied overpotential, formate are produced mainly through the reduction of CO₂ in the feed gas and the dissociation of adsorbed HCO₃⁻ groups [42].

In addition, it has also been reported that Bi NSs clusters are usually dense, and the atomic utilization rate of Bi NSs is relatively low because only the surface Bi atoms are active. Highly dispersed Bi NPs derived from BiBTB MOF have FE_{HCOO^-} of 95% at -0.97 V. More importantly, the strategy of using MOF as a pre-catalyst introduces a low load of metal atoms, so the BiBTB-derived electrocatalyst achieves a Bi mass activity of 158 A g⁻¹ at -0.97 V, which is superior to most advanced bismuth-based catalysts reported for ECO₂RR to formate [43].

4.3. Lead-Based Nanomaterials

Pb-MOF with 5-Chloronicotinic acid (CA) as the organic linker is effectively dispersed on the Pb electrode, and the nanocolumn structure of MOF collapses under the condition of electrochemical reduction. In this process, the inner layer of Pb²⁺ is reduced to Pb⁰, while the outer layer of Pb²⁺ is etched by HCO₃⁻ and undergoes the insertion of OH⁻ to form hydrocerussite [Pb₃(CO₃)₂(OH)₂] thin film (ER-HC). The formed hydrocerussite film is uniformly and closely attached to Pb and have abundant surface defects, which can improve the activity of ECO₂RR and selectivity for HCOOH while effectively inhibiting the HER of Pb which is originally strong. At -0.88 V, the optimal FE_{HCOOH} is 96.8% with a current density of 2.0 mA cm⁻² [44].

5. MOFs-Derived Carbon-Based Nanocomposites

MOF-derived carbon-based nanocomposites can usually be synthesized by carbonizing MOFs. Organic frameworks act as the templates during the carbonization process, effectively dispersing metal NPs, and at the same time affect the nano size of active substances in the derivatives. Some of the MOFs stable under the condition of electrochemical reduction can also be carbonized, with great enhancement on conductivity and stability.

5.1. Copper-Based Nanocomposites

Cu MOF constructed from BTC derive into Cu₂O/Cu carbon-based nanocomposites under pyrolysis. In order to increase N amount doped in the material, nitrogenous benzimidazoles are also added during the synthesis of the Cu MOF. The high content of N doping into the Cu₂O/Cu lattice changes its electronic structure, reduces the binding energy of *OCHO and promotes the production of formate. The Cu₂O/Cu@NC-800 catalyst synthesized by carbonization at 800 °C has a high Cu content and a good distribution of Cu NPs on the porous carbon skeleton, thus resulting in a higher HCOO⁻ selectivity than Cu₂O/Cu@NC-700 and Cu₂O/Cu@NC-900 (Figure 12a). The Cu₂O/Cu@NC-800 reaches the highest FE_{HCOO^-} of 70.5% at -0.68 V [23].

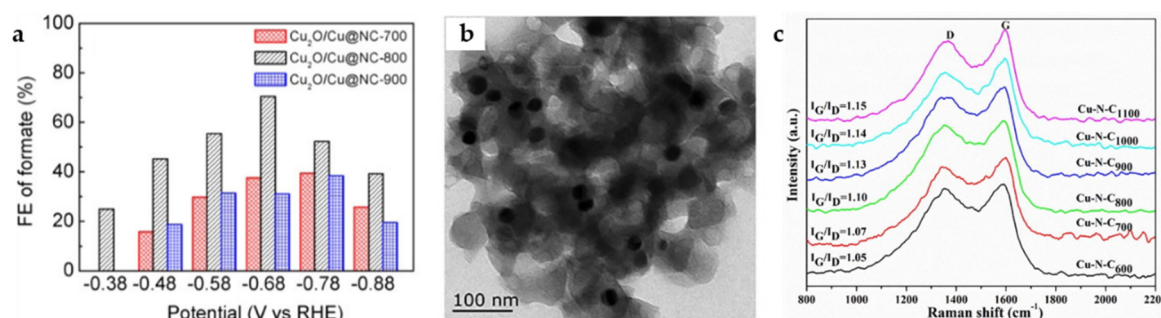


Figure 12. (a) FE_{HCOO^-} for ECO₂RR of Cu₂O/Cu@NC-700, Cu₂O/Cu@NC-800, and Cu₂O/Cu@NC-900 [23]. Copyright 2020, ACS. (b) TEM image for Cu-N-C₁₁₀₀. (c) Raman spectra of Cu-N-C_r composite catalyst [45]. Copyright 2021, Elsevier.

The calcination of Cu-1,3,5-benzenetris tetrazolate (Cu-BTT) MOF at different temperatures imbeds Cu NPs into porous carbon matrix with different N and C contents. When the calcination temperature reaches 1100 °C, the pore of Cu-N-C₁₁₀₀ catalyst is the largest, which is conducive to electron transfer and mass transfer. It has abundant pyrrolic N and Cu-N_x active sites. As TEM image shown in Figure 12b, Cu NPs (27 ± 2 nm) are effectively dispersed without severe aggregation. The Raman spectra indicate (Figure 12c) that the higher the carbonization temperature, the higher the degree of graphitization, more conducive to electron transfer. Because smaller NPs have stronger CO binding capacity and lower mobility of CO_{ad} and H_{ad}, desorption occurs before further reaction, which inhibits further reactions to form other hydrocarbons, thus effectively improving the selectivity for HCOOH. The Cu-N-C₁₁₀₀ catalyst reaches the maximum FE_{HCOOH} of 38.1% at -0.9 V, while FE_{CO} of 40.8% is obtained [45].

5.2. Bismuth-Based Nanocomposites

Calcination in air is an effective way for introducing oxides. Bi-BTC MOF is carbonized at 800 °C to obtain Bi@C and further oxidized in air (200 °C) to obtain Bi₂O₃@C-800 (Figure 13a). The presence of Bi₂O₃ facilitates the improvement of reaction kinetics and product selectivity, while the carbon matrix synergistically helps to further increase the activity and current density, showing superior catalytic performance compared to Bi@C. Bi₂O₃@C-800 reaches FE_{HCOO^-} of 92% with a current density of 7.5 mA cm⁻² at -0.9 V, and can maintain more than FE_{HCOO^-} of 93% for 10 h with a current density of 200 mA cm⁻² in the flow cell [25].

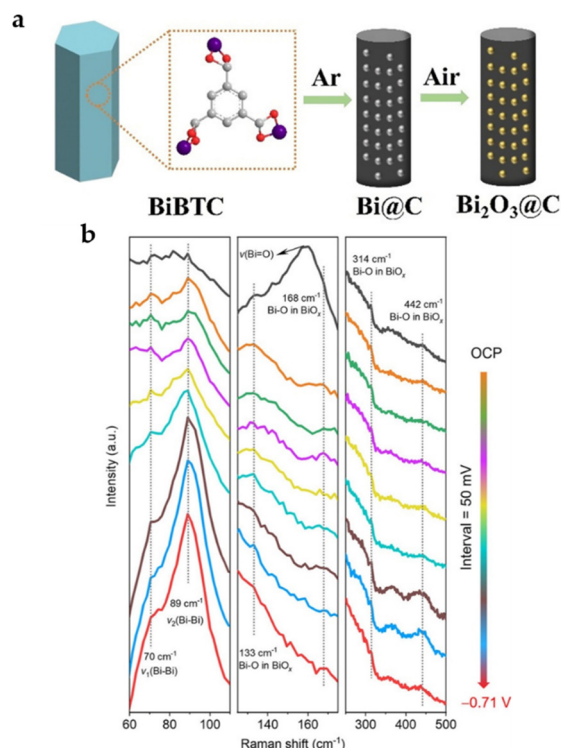


Figure 13. (a) Preparation of Bi@C and Bi₂O₃@C catalysts [25]. Copyright 2020, Wiley-VCH. (b) *In situ* Raman spectra of the (surface-oxygen-rich) SOR Bi@C NPs catalyst as a function of the applied potential in 1.0 M KOH electrolyte at various potentials [46]. Copyright 2022, ACS.

To obtain a more stable Bi-O structure, the most stable Bi MOF SU-101 under electrochemical reduction is carbonized to obtain surface-oxygen-rich carbon-nanorod-supported Bi NPs (SOR Bi@C NPs) with uniform distribution of active sites, retaining the original nanorod morphology of SU-101 with a large number of Bi-O species present on the surface. The maximum FE_{HCOO^-} of 95% and the corresponding partial current density of 10.5 mA cm⁻² are obtained at -0.99 V. As shown in *in situ* Raman spectra (Figure 13b), three Raman peaks located at 133, 314 and 442 cm⁻¹ remained at different reduction potentials, demonstrating that Bi-O/Bi species are structurally stable during ECO₂RR [46].

5.3. Indium-Based Nanocomposites

Interestingly, calcination under N₂ can produce more oxygen vacancies compared to air. The corn-like In₂O_{3-x}@C nanocomposite is obtained by carbonization of MIL-68 (In MOF) with BDC as the organic linker. The combination of abundant oxygen vacancies and amorphous carbon rods contributes to the increase in electrical conductivity and catalytic activity. According to DFT calculations (Figure 14d), In₂O_{3-x} exhibits a tendency to spontaneously form HCOO* (*OCHO) intermediates, while effectively raising the energy barrier for the formation of *COOH intermediates, thus greatly improving the selectivity for HCOOH products. In addition, the valence state changes during the reaction are probed by operando X-ray absorption spectroscopy (XAS). As shown in the Figure 14c, at -0.445 V, the In valence state is below +2 with almost no HCOOH produced. When the potential is increased to -1.045 V, the FE_{HCOOH} increases to more than 85%, and the In valence state is about +3. When the potential is further increased to -1.445 V, the FE_{HCOOH} decreases to 51% with the valence state of In decreases to ~+2.5. This suggests a possible reaction mechanism (Figure 14d): the catalyst may shift to In⁰ during the initial reduction phase, transform back to In³⁺ after electron transfer to CO₂, and maintain the valence as the active sites [47].

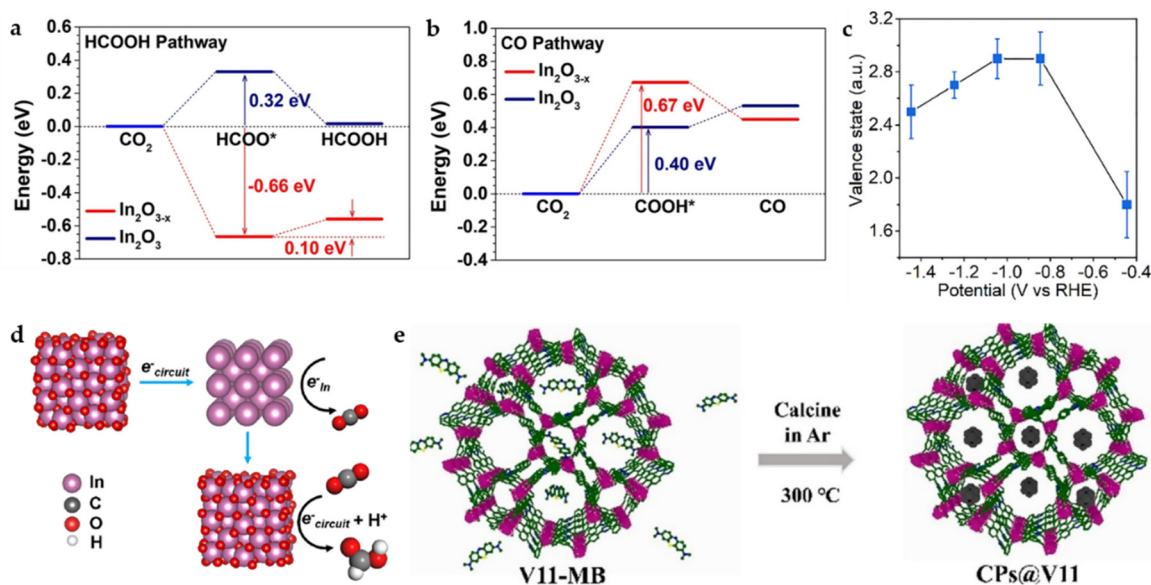


Figure 14. (a) Free energy diagrams for CO_2 electroreduction to HCOOH and (b) CO on In_2O_3 and $\text{In}_2\text{O}_{3-x}$. (c) Changes of In valence state in MIL-68- N_2 under different applied potentials, which are examined by using the K-edge energy shift with respect to the commercial In_2O_3 sample. (d) The proposed reaction mechanism based on the operando measurements [47]. Copyright 2022, Springer Nature. (e) Illustration of the preparation process of CPs@V11 [48]. Copyright 2021, Wiley-VCH.

The In MOF $\{(\text{Me}_2\text{NH}_2)[\text{In}(\text{BCP})]\cdot 2\text{DMF}\}_n$ (V11) constructed by 5-(2,6-bis(4-carboxyphenyl)pyridin-4-yl) isophthalic acid (BCP), exhibits certain catalytic potential as well as good thermal stability, but the poor conductivity limits its catalytic efficiency, which can be effectively improved by the introduction of carbon materials. Methylene blue (MB) meets the integrating conditions considering the molecular structure size and carbonization temperature. MB transforms into carbon nanoparticles at temperatures above 250°C , while V11 can maintain structural stability at 380°C , and thus V11 framework-loaded carbon nanoparticles (CPs) can be formed in this temperature range (Figure 14e). MB-derived CPs are used as promoters to improve the conductivity of the material and expose more active sites, which facilitates the charge and mass transfer during the reaction. Importantly, this strategy can also be applied to other classical MOFs, demonstrating the generality of this strategy [48].

Single-atom catalysts with almost 100% atomic utilization rate have been shown to be ideal catalysts for ECO_2RR . Once dispersed into single atomic form, the electronic structure of the active component is significantly altered, favoring the stabilization of reaction intermediates (e.g., CO_2^-) and limiting the configurations of the intermediates [56].

The pyrolysis process of ZIF-8 (Zn MOF) with In doping leads to the formation of a single-atom catalyst In-SAs/NC. HAADF-STEM image as well as Fourier transform curve of extended X-ray absorption fine structure (EXAFS) spectra (Figure 15a and b) demonstrate the apparent In- N_4 single-atom structure. The catalyst demonstrates a very high TOF of 12500 h^{-1} at -0.95 V and a $\text{FE}_{\text{HCOO}^-}$ of 96% at -0.65 V with a current density of 8.87 mA cm^{-2} . According to DFT calculations (Figure 15c), the In- N_4 structure effectively lowers the formation energy barrier of $^*\text{OCHO}$ intermediate. Notably, the single-atom synthesis strategy can also be applied on Sn and Sb, and the obtained single-atom catalyst also exhibits high selectivity for formate products [49]. The similar reported single-atom catalyst In-N-C also exhibit high HCOOH selectivity and atomic utilization rate, with TOF reaching 26671 h^{-1} at -0.99 V [50].

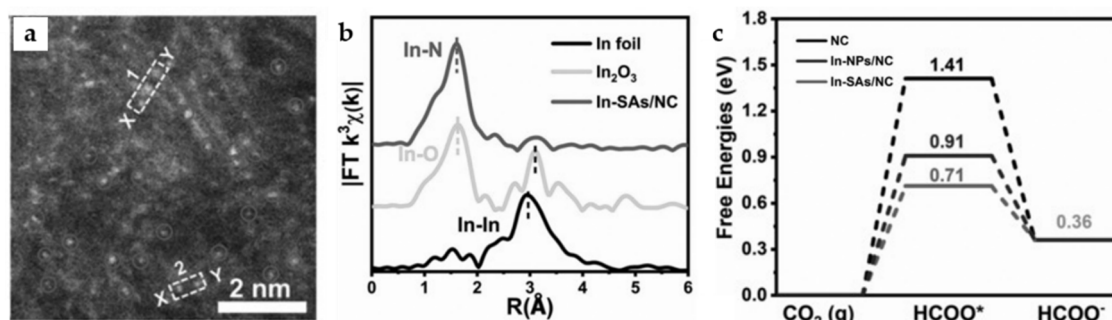


Figure 15. (a) High angle annular dark-field scanning transmission electron microscope (HAADF-STEM) image of In-SAs/NC. (b) In K-edge FT-EXAFS spectrum of In-SAs/NC. (c) The calculated potential free-energy diagrams for CO₂ electroreduction to formate [49]. Copyright 2022, Wiley-VCH.

6. Bimetallic MOFs-derived Nanocomposites

Compared with monometallic sites, bimetallic sites can change the atomic arrangement and modulate the electronic structure through the interaction of adjacent metal atoms [53]. Bimetallic electrocatalysts with rational design can effectively reduce the energy barrier between CO₂ and reduction intermediates through synergistic effects and inhibits the competitive HER, resulting in low overpotential and enhanced selectivity for ECO₂RR [51]. Carbonization and electrochemical reduction of bimetallic MOFs are both effective ways to construct MOFs-derived bimetallic nanocomposite catalysts.

6.1. Copper and Bismuth-based Bimetallic Nanocomposites

The carbon-based nanomaterial Cu_x-Bi/Bi₂O₃@C with bimetallic composition is obtained by a calcination process from Cu, Bi bi-MOF (x represents the mass ratio of Cu(NO₃)₂·3H₂O and Bi(NO₃)₃·5H₂O in the synthesis). Compared to Bi/Bi₂O₃@C without Cu, the HCOOH selectivity is significantly enhanced, reaching a high FE of 93% at -0.94 V (Figure 16a). This can be attributed to the synergistic effect between Cu and Bi, where the introduction of Cu can substantially inhibit HER and enhance the adsorption capacity of CO₂⁻ intermediates, effectively reducing the CO₂ activation energy barrier. With the increase of Cu content, the content of Bi³⁺ decreases while that of Bi⁰ increases, and the appropriate Cu doping also favors the increase of oxygen defects. In addition, a suitable Bi⁰/Bi³⁺ ratio and the synergistic coordination of Bi⁰ and Bi³⁺ are considered to contribute to the enhancement of ECO₂RR. Cu₁-Bi/Bi₂O₃@C exhibits better catalytic activity and HCOOH selectivity compared to Cu_{0.5}-Bi/Bi₂O₃@C (Figure 16a and b) [16].

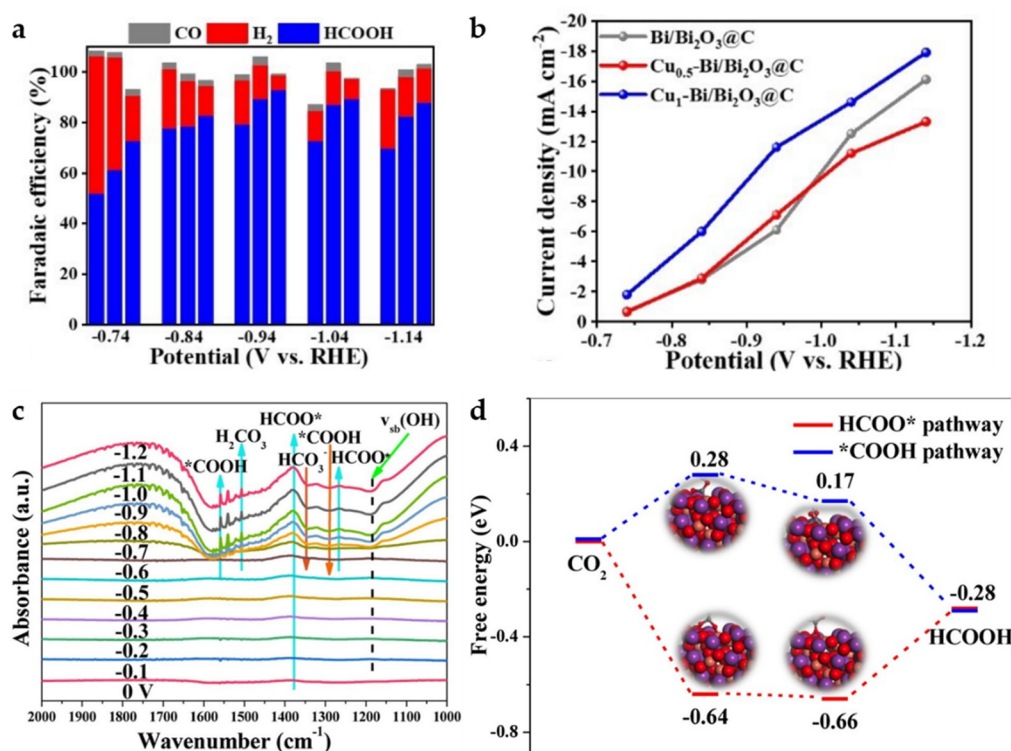


Figure 16. (a) FE of H₂, CO, HCOOH for Cu_x-Bi/Bi₂O₃@C (x = 0, 0.5, 1). (b) Partial current density of HCOOH of different catalysts [16]. Copyright 2022, Wiley-VCH. (c) The *in situ* FT-IR spectra on CuBi75 catalyst at different applied potential from 0 V to -1.2 V. (d) The free energy diagrams of different pathway for CO₂ electroreduction to HCOOH on CuBi75 (211) plane [51]. Copyright 2021, Elsevier.

A similar Bi and Cu bimetallic MOF-derived catalyst was reported in the same year. CuBi75 (75 represents that the molar mass ratio of Cu(NO₃)₂ and Bi(NO₃)₃ added is 75:25 in the synthesis) is found to produce an unique Bi₂CuO₄ structure at the interface between Cu and Bi, leading to a greatly enhanced activity and formate selectivity of the bimetallic Cu Bi catalyst. A significant increase in the peak intensity of HCOO* at ~1379 cm⁻¹ is found by *in situ* FT-IR (Figure 16c) from 0 V to -1.2 V, indicating that the accumulation of HCOO* intermediates on CuBi75 exceeds the consumption, making the reaction pathway more inclined to HCOO⁻ generation. The DFT calculations (Figure 16d) also suggest that Bi₂CuO₄ favors the promotion of the HCOO* (*OCHO) pathway while inhibiting the *COOH reaction pathway to achieve high formate selectivity. FE_{HCOO⁻} of the catalyst achieves more than 93.7% over a wide potential range of 900 mV (-0.57 V to -1.47 V), with a maximum FE_{HCOO⁻} of 100% at -0.77 V [51].

6.2. Bismuth and Indium-based Bimetallic Nanocomposites

Bi has a relatively weak binding energy to *OCHO, which makes it difficult to promote HCOOH production in ECO₂RR. The electronic structure can be regulated through interaction with In. In-Bi-MOF is synthesized by a solvothermal method and ion-exchange process. The subsequent Bi-In alloy NPs are obtained by electrochemical reduction. The electronic interaction between In and Bi in Bi-In alloy NPs is demonstrated by XPS spectra (Figure 17a and b). The XPS peaks of Bi 4f shift toward a lower binding energy compared to Bi NPs, while the XPS peaks of In 3d shift toward a higher binding energy compared to In NPs, indicating electron transfer from In to Bi. Bi-In alloy NPs reach a maximum FE_{HCOOH} of 97.8% in H-cell at -0.92 V and a FE_{HCOOH} of 92.5% with a high current density of 300 mA cm⁻² in flow cell. In addition, the Bi-In alloy NPs achieve long-term electrolysis for more than 25 h in the MEA system at a current density of 120 mA cm⁻², maintaining FE_{HCOOH} of above 80%. The

results of DFT calculations (Figure 17c and d) demonstrate that the bimetallic sites provide the best $^*\text{OCHO}$ binding energy and promote the generation of HCOOH [52].

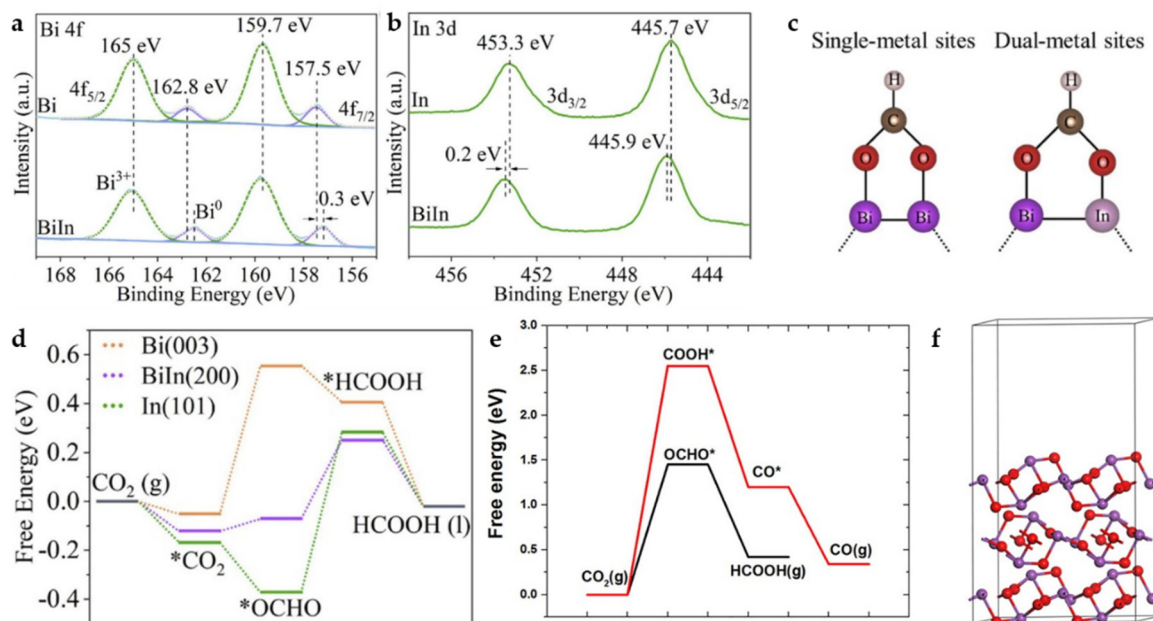


Figure 17. (a) Bi 4f XPS spectra of Bi-In alloy NPs and Bi NPs. (b) In 3d XPS spectra of Bi-In alloy NPs, and In NPs. (c) $^*\text{OCHO}$ adsorption in single-metal (left) and dual-metal (right) catalytic systems through side-on configurations. (d) Calculated free energy diagrams for CO_2 electroreduction to HCOOH on Bi (003), BiIn (200), and In (101) [52]. Copyright 2022, Elsevier. (e) Free energy diagrams for CO_2 electroreduction to HCOOH and CO on $\text{Bi}_2\text{O}_3(010)$. (f) Optimized structures of $\text{Bi}_2\text{O}_3(010)$ [53]. Copyright 2021, Elsevier.

In addition, the $\text{BiIn}_5\text{-500@C}$, a carbon-based nanocomposite catalyst containing In_2O_3 and Bi_2O_3 , is synthesized by carbonizing In-Bi-MOF [53]. A significant synergistic effect is observed at 5% In doping, and almost no In aggregation occurs. The DFT calculations (Figure 17e and f) show that the addition of In to Bi significantly reduces the free energy of formation of $^*\text{OCHO}$ intermediates. The catalyst achieves a FE_{HCOOH} of 97.5% at -0.86 V and a current density of 13.5 mA cm^{-2} , showing higher activity and HCOOH selectivity compared to Bi-500@C .

6.3. Palladium and Gold-based Bimetallic Nanocomposites

Pd is a catalyst capable of ECO_2RR to HCOOH at a very low overpotential [57]. However, palladium-based electrocatalysts present significant challenges in terms of long-term stability, as trace amounts of CO are inevitably generated during ECO_2RR , which can strongly adsorb on the Pd surface and leads to poisoning. Reduction of Pd precursors in the limited space of MOFs generates significant local tensile strain in the Pd NPs, which remains when a certain amount of Au is added to form M-AuPd. As the Cs-TEM image shown (Figure 18a), the pink dots indicate the dislocations and lattice distortions on the surface of catalyst. Interestingly, the generation of tensile strain on the Pd surface typically enhances the adsorption energy of ECO_2RR intermediates, including $^*\text{COOH}$ and $^*\text{OOCH}$ ($^*\text{OCHO}$), while the dispersal of a single Au atom on the tensile-strained Pd surface selectively destabilizes $^*\text{CO}$ without affecting the other adsorbates. At a very positive potential, -0.25 V, FE_{HCOOH} of above 99% and a current density of $\sim 7 \text{ mA cm}^{-2}$ are obtained, far exceeding commercial Pd/C and M-Pd without Au in catalytic activity and selectivity for formate (Figure 18b and c) [12].

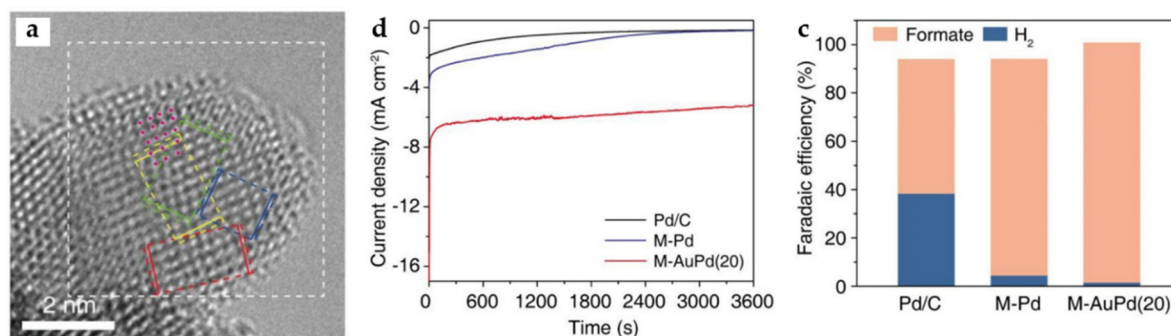


Figure 18. (a) Cs-corrected TEM (Cs-TEM) image of M-AuPd(20). The dislocations are indicated with pink dots. (b) Chronoamperometric curves, (c) FE_{HCOOH} of Pd/C, M-Pd, and M-AuPd(20) at -0.25 V for 1 h [12]. Copyright 2021, ACS.

7. Summary and Outlook

In conclusion, we summarize the MOFs and MOFs-derived catalysts applied in ECO_2RR for $HCOOH$. MOFs are widely used for catalysis due to their high specific surface area and porous structure. Their high CO_2 adsorption capacity, uniformly distributed active sites and restricted reaction space makes them have the potential for ECO_2RR . However, the application of pristine MOFs in electrocatalysis must face the problems of poor conductivity and instability under electroreduction conditions, and some MOFs even undergo SALE/electrolyte-mediated dissociation processes during immersion in HCO_3^- electrolyte. Interestingly, the latter problem becomes a solution to the former one. A series of MOFs undergo structural decomposition under electrochemical reduction conditions to form derived metal nanomaterials, accompanied by an increase in electrical conductivity and stability. Compared to conventional reduction methods, the electroreduction process is gentler and retains M-O species, and the M-O species become an important factor in optimizing catalytic performance. Another important derivation method is calcination/carbonization to obtain carbon-based metal nanocomposites. MOF structures as the precursor can effectively decrease the degree of metal aggregation and improve the atomic utilization rate, and can even be a method for synthesizing single-atom catalysts. At the same time, MOF structures often act as templates to influence the morphology of carbonization-derived catalysts. Depending on different reaction conditions and structural units, including metal ions and organic linkers, it is therefore easy to tune and optimize the performance of MOFs-derived catalysts, which have rich variability and application range.

On the other hand, the most widely reported bismuth-based MOFs catalysts dominate in ECO_2RR for $HCOOH$, with FE_{HCOOH} generally exceeding 90%, and the advantages of low cost and low toxicity make Bi the most promising catalysts for practical applications at this stage. In and tin-based MOFs also show good $HCOOH$ selectivity. Palladium-based MOFs exhibit impressive low overpotential property, but may be difficult for applications due to their noble metal status and susceptibility to poisoning. However, Cu is the only catalyst capable of CO_2 reduction to highly reduced products such as CH_4 , CH_3COOH , C_2H_4 , and further exploration in this field should be directed toward C-C coupling and C_{2+} products. In addition, two-component or multi-component metal MOFs are more complex. How to determine the active sites and the synergistic effect between multiple components still need to be further explored.

The design of efficient catalysts is challenging, and although so much works have been done to show that MOFs undergo recombination by carbonization or electrochemical reduction, how to rationally control the recombination process to form a more reactive structure remains to be further investigated. A sufficient understanding of the catalytic system is required. Therefore, the correlation between catalytic activity and the physical parameters of MOFs, such as the ligand structure, composition, specific surface area, pore structure, morphology, needs to be further constructed. Future directions will include the study for the role of substituents on organic linkers to develop MOFs with more efficient CO_2 capture and high ECO_2RR performance [35]. *In situ* studies are also necessary for tracing the evolution of catalysts during the electrolysis process and further

understanding the mechanism of ECO₂RR catalyzed by metal active sites in MOFs and their derivatives, where Operando Raman, IR and XAFS are powerful and widely used tools to obtain information on catalyst structure, adsorbates on the catalyst surface such as CO₂ reduction intermediates, metal valence and coordination number [47].

Acknowledgments: This work was financially supported by the National Natural Science Foundation of China (22171149, 21975135), the National Key Research and Development Program of China (2022YFB4101800), the Natural Science Foundation of Tianjin Municipal Science and Technology Commission (21JCZDJC00100), and the Fundamental Research Funds for the Central Universities, Nankai University, and Nankai Cangzhou Bohai New Area Green Chemical Research Co. LTD (Grant No 20220130).

Conflicts of Interest: The authors declare no conflict of interest. The funders had no role in the design of the study; in the collection, analyses, or interpretation of data; in the writing of the manuscript; or in the decision to publish the results.

References

1. Abdelkader-Fernández, V. K.; Fernandes, D. M.; Freire, C., Carbon-based electrocatalysts for CO₂ electroreduction produced via MOF, biomass, and other precursors carbonization: A review. *J. CO₂ Util.* **2020**, *42*, 101350.
2. Yang, Z. W.; Chen, J. M.; Qiu, L. Q.; Xie, W. J.; He, L. N., Molecular Engineering of Metal Complexes for Electrocatalytic Carbon Dioxide Reduction: From Adjustment of Intrinsic Activity to Molecular Immobilization. *Angew. Chem. Int. Ed.* **2022**, *61*, e202205301.
3. Mahmood, A.; Guo, W.; Tabassum, H.; Zou, R., Metal-Organic Framework-Based Nanomaterials for Electrocatalysis. *Adv. Energy Mater.* **2016**, *6*, 1600423.
4. Zhang, W.; Hu, Y.; Ma, L.; Zhu, G.; Wang, Y.; Xue, X.; Chen, R.; Yang, S.; Jin, Z., Progress and Perspective of Electrocatalytic CO₂ Reduction for Renewable Carbonaceous Fuels and Chemicals. *Adv. Sci.* **2018**, *5*, 1700275.
5. Raciti, D.; Wang, C., Recent Advances in CO₂ Reduction Electrocatalysis on Copper. *ACS Energy Lett.* **2018**, *3*, 1545-1556.
6. Wang, Y.; Su, H.; He, Y.; Li, L.; Zhu, S.; Shen, H.; Xie, P.; Fu, X.; Zhou, G.; Feng, C.; Zhao, D.; Xiao, F.; Zhu, X.; Zeng, Y.; Shao, M.; Chen, S.; Wu, G.; Zeng, J.; Wang, C., Advanced Electrocatalysts with Single-Metal-Atom Active Sites. *Chem. Rev.* **2020**, *120*, 12217-12314.
7. Masood ul Hasan, I.; Peng, L.; Mao, J.; He, R.; Wang, Y.; Fu, J.; Xu, N.; Qiao, J., Carbon-based metal-free catalysts for electrochemical CO₂ reduction: Activity, selectivity, and stability. *Carbon Energy* **2020**, *3*, 24-49.
8. Fellay, C.; Yan, N.; Dyson, P. J.; Laurenczy, G., Selective formic acid decomposition for high-pressure hydrogen generation: a mechanistic study. *Chem. Eur. J.* **2009**, *15*, 3752-3760.
9. Duarah, P.; Haldar, D.; Yadav, V. S. K.; Purkait, M. K., Progress in the electrochemical reduction of CO₂ to formic acid: A review on current trends and future prospects. *J. Environ. Chem. Eng.* **2021**, *9*, 106394.
10. Li, F.; Gu, G. H.; Choi, C.; Kolla, P.; Hong, S.; Wu, T.-S.; Soo, Y.-L.; Masa, J.; Mukerjee, S.; Jung, Y.; Qiu, J.; Sun, Z., Highly stable two-dimensional bismuth metal-organic frameworks for efficient electrochemical reduction of CO₂. *Appl. Catal., B* **2020**, *277*, 119241.
11. Zhang, R.-Z.; Wu, B.-Y.; Li, Q.; Lu, L.-L.; Shi, W.; Cheng, P., Design strategies and mechanism studies of CO₂ electroreduction catalysts based on coordination chemistry. *Coord. Chem. Rev.* **2020**, *422*, 213436.
12. Bok, J.; Lee, S. Y.; Lee, B. H.; Kim, C.; Nguyen, D. L. T.; Kim, J. W.; Jung, E.; Lee, C. W.; Jung, Y.; Lee, H. S.; Kim, J.; Lee, K.; Ko, W.; Kim, Y. S.; Cho, S. P.; Yoo, J. S.; Hyeon, T.; Hwang, Y. J., Designing Atomically Dispersed Au on Tensile-Strained Pd for Efficient CO₂ Electroreduction to Formate. *J. Am. Chem. Soc.* **2021**, *143*, 5386-5395.
13. Kortlever, R.; Shen, J.; Schouten, K. J.; Calle-Vallejo, F.; Koper, M. T., Catalysts and Reaction Pathways for the Electrochemical Reduction of Carbon Dioxide. *J. Phys. Chem. Lett.* **2015**, *6*, 4073-4082.
14. Li, X.; Yang, X.; Xue, H.; Pang, H.; Xu, Q., Metal-organic frameworks as a platform for clean energy applications. *EnergyChem* **2020**, *2*, 100027.
15. Chughtai, A. H.; Ahmad, N.; Younus, H. A.; Laypkov, A.; Verpoort, F., Metal-organic frameworks: versatile heterogeneous catalysts for efficient catalytic organic transformations. *Chem. Soc. Rev.* **2015**, *44*, 6804-6849.
16. Xue, Y.; Li, C.; Zhou, X.; Kuang, Z.; Zhao, W.; Zhang, Q.; Chen, H., MOF-Derived Cu/Bi Bi-metallic Catalyst to Enhance Selectivity Toward Formate for CO₂ Electroreduction. *ChemElectroChem* **2022**, *9*, e202101648.
17. Geng, W.; Chen, W.; Li, G.; Dong, X.; Song, Y.; Wei, W.; Sun, Y., Induced CO₂ Electroreduction to Formic Acid on Metal-Organic Frameworks via Node Doping. *ChemSusChem* **2020**, *13*, 4035-4040.

18. Hinogami, R.; Yotsuhashi, S.; Deguchi, M.; Zenitani, Y.; Hashiba, H.; Yamada, Y., Electrochemical Reduction of Carbon Dioxide Using a Copper Rubinate Metal Organic Framework. *ECS Electrochem. Lett.* **2012**, *1*, H17-H19.
19. Wang, R.; Liu, J.; Huang, Q.; Dong, L. Z.; Li, S. L.; Lan, Y. Q., Partial Coordination-Perturbed Bi-Copper Sites for Selective Electroreduction of CO₂ to Hydrocarbons. *Angew. Chem. Int. Ed.* **2021**, *60*, 19829-19835.
20. Zhuo, L. L.; Chen, P.; Zheng, K.; Zhang, X. W.; Wu, J. X.; Lin, D. Y.; Liu, S. Y.; Wang, Z. S.; Liu, J. Y.; Zhou, D. D.; Zhang, J. P., Flexible Cuprous Triazolate Frameworks as Highly Stable and Efficient Electrocatalysts for CO₂ Reduction with Tunable C₂H₄/CH₄ Selectivity. *Angew. Chem. Int. Ed.* **2022**, *61*, e202204967.
21. Wu, J. X.; Hou, S. Z.; Zhang, X. D.; Xu, M.; Yang, H. F.; Cao, P. S.; Gu, Z. Y., Cathodized copper porphyrin metal-organic framework nanosheets for selective formate and acetate production from CO₂ electroreduction. *Chem. Sci.* **2019**, *10*, 2199-2205.
22. Zheng, W.; Lee, L. Y. S., Metal-Organic Frameworks for Electrocatalysis: Catalyst or Precatalyst? *ACS Energy Lett.* **2021**, *6*, 2838-2843.
23. Li, D.; Liu, T.; Yan, Z.; Zhen, L.; Liu, J.; Wu, J.; Feng, Y., MOF-Derived Cu₂O/Cu Nanospheres Anchored in Nitrogen-Doped Hollow Porous Carbon Framework for Increasing the Selectivity and Activity of Electrochemical CO₂-to-Formate Conversion. *ACS Appl. Mater. Interfaces* **2020**, *12*, 7030-7037.
24. Guan, B. Y.; Yu, X. Y.; Wu, H. B.; Lou, X. W. D., Complex Nanostructures from Materials based on Metal-Organic Frameworks for Electrochemical Energy Storage and Conversion. *Adv. Mater.* **2017**, *29*, 1703614.
25. Deng, P.; Yang, F.; Wang, Z.; Chen, S.; Zhou, Y.; Zaman, S.; Xia, B. Y., Metal-Organic Framework-Derived Carbon Nanorods Encapsulating Bismuth Oxides for Rapid and Selective CO₂ Electroreduction to Formate. *Angew. Chem. Int. Ed.* **2020**, *59*, 10807-10813.
26. Wang, J.; Zhang, Y.; Ma, Y.; Yin, J.; Wang, Y.; Fan, Z., Electrocatalytic Reduction of Carbon Dioxide to High-Value Multicarbon Products with Metal-Organic Frameworks and Their Derived Materials. *ACS Mater. Lett.* **2022**, *4*, 2058-2079.
27. Hwang, S. M.; Choi, S. Y.; Youn, M. H.; Lee, W.; Park, K. T.; Gothandapani, K.; Grace, A. N.; Jeong, S. K., Investigation on Electroreduction of CO₂ to Formic Acid Using Cu₃(BTC)₂ Metal-Organic Framework (Cu-MOF) and Graphene Oxide. *ACS Omega* **2020**, *5*, 23919-23930.
28. Liu, M. J.; Cao, S. M.; Feng, B. Q.; Dong, B. X.; Ding, Y. X.; Zheng, Q. H.; Teng, Y. L.; Li, Z. W.; Liu, W. L.; Feng, L. G., Revealing the structure-activity relationship of two Cu-porphyrin-based metal-organic frameworks for the electrochemical CO₂-to-HCOOH transformation. *Dalton Trans.* **2020**, *49*, 14995-15001.
29. Yuan, W.-W.; Wu, J.-X.; Zhang, X.-D.; Hou, S.-Z.; Xu, M.; Gu, Z.-Y., In situ transformation of bismuth metal-organic frameworks for efficient selective electroreduction of CO₂ to formate. *J. Mater. Chem. A* **2020**, *8*, 24486-24492.
30. Liu, L.; Yao, K.; Fu, J.; Huang, Y.; Li, N.; Liang, H., Bismuth metal-organic framework for electroreduction of carbon dioxide. *Colloids Surf., A* **2022**, *633*, 127840.
31. Yang, Z. W.; Chen, J. M.; Liang, Z. L.; Xie, W. J.; Zhao, B.; He, L. N., Anodic Product-Derived Bi-MOF as Pre-catalyst for Cathodic CO₂ Reduction: A Novel Strategy for Paired Electrolysis. *ChemCatChem* **2022**, *15*, e202201321.
32. Frank, S.; Svensson Grape, E.; Bøjesen, E. D.; Larsen, R.; Lamagni, P.; Catalano, J.; Inge, A. K.; Lock, N., Exploring the influence of atomic level structure, porosity, and stability of bismuth(III) coordination polymers on electrocatalytic CO₂ reduction. *J. Mater. Chem. A* **2021**, *9*, 26298-26310.
33. Hou, S. Z.; Zhang, X. D.; Yuan, W. W.; Li, Y. X.; Gu, Z. Y., Indium-Based Metal-Organic Framework for High-Performance Electroreduction of CO₂ to Formate. *Inorg. Chem.* **2020**, *59*, 11298-11304.
34. Deng, Y.; Wang, S.; Huang, Y.; Li, X., Structural reconstruction of Sn-based metal-organic frameworks for efficient electrochemical CO₂ reduction to formate. *Chin. J. Chem. Eng.* **2022**, *43*, 353-359.
35. Lee, M.; De Riccardis, A.; Kazantsev, R. V.; Cooper, J. K.; Buckley, A. K.; Burroughs, P. W. W.; Larson, D. M.; Mele, G.; Toma, F. M., Aluminum Metal-Organic Framework Triggers Carbon Dioxide Reduction Activity. *ACS Appl. Energy Mater.* **2020**, *3*, 1286-1291.
36. Kung, C.-W.; Audu, C. O.; Peters, A. W.; Noh, H.; Farha, O. K.; Hupp, J. T., Copper Nanoparticles Installed in Metal-Organic Framework Thin Films are Electrocatalytically Competent for CO₂ Reduction. *ACS Energy Lett.* **2017**, *2*, 2394-2401.
37. Wang, D.; Xu, J.; Zhu, Y.; Wen, L.; Ye, J.; Shen, Y.; Zeng, T.; Lu, X.; Ma, J.; Wang, L.; Song, S., HKUST-1-derived highly ordered Cu nanosheets with enriched edge sites, stepped (211) surfaces and (200) facets for effective electrochemical CO₂ reduction. *Chemosphere* **2021**, *278*, 130408.
38. Yao, D.; Tang, C.; Vasileff, A.; Zhi, X.; Jiao, Y.; Qiao, S. Z., The Controllable Reconstruction of Bi-MOFs for Electrochemical CO₂ Reduction through Electrolyte and Potential Mediation. *Angew. Chem. Int. Ed.* **2021**, *60*, 18178-18184.

39. Yang, J.; Wang, X.; Qu, Y.; Wang, X.; Huo, H.; Fan, Q.; Wang, J.; Yang, L. M.; Wu, Y., Bi-Based Metal-Organic Framework Derived Leafy Bismuth Nanosheets for Carbon Dioxide Electroreduction. *Adv. Energy Mater.* **2020**, *10*, 2001709.
40. Zhang, B.; Cao, S.; Wu, Y.; Zhai, P.; Li, Z.; Zhang, Y.; Fan, Z.; Wang, C.; Zhang, X.; Hou, J.; Sun, L., Metal-Organic-Framework-Derived Bismuth Nanosheets for Electrochemical and Solar-Driven Electrochemical CO₂ Reduction to Formate. *ChemElectroChem* **2021**, *8*, 880-886.
41. Li, N.; Yan, P.; Tang, Y.; Wang, J.; Yu, X.-Y.; Wu, H. B., In-situ formation of ligand-stabilized bismuth nanosheets for efficient CO₂ conversion. *Appl. Catal., B* **2021**, *297*, 120481.
42. Cao, C.; Ma, D. D.; Gu, J. F.; Xie, X.; Zeng, G.; Li, X.; Han, S. G.; Zhu, Q. L.; Wu, X. T.; Xu, Q., Metal-Organic Layers Leading to Atomically Thin Bismuthene for Efficient Carbon Dioxide Electroreduction to Liquid Fuel. *Angew. Chem. Int. Ed.* **2020**, *59*, 15014-15020.
43. Lamagni, P.; Miola, M.; Catalano, J.; Hvid, M. S.; Mamakhel, M. A. H.; Christensen, M.; Madsen, M. R.; Jeppesen, H. S.; Hu, X. M.; Daasbjerg, K.; Skrydstrup, T.; Lock, N., Restructuring Metal-Organic Frameworks to Nanoscale Bismuth Electrocatalysts for Highly Active and Selective CO₂ Reduction to Formate. *Adv. Funct. Mater.* **2020**, *30*, 1910408.
44. Wang, D.; Dong, S.; Wen, L.; Yu, W.; He, Z.; Guo, Q.; Lu, X.; Wang, L.; Song, S.; Ma, J., Highly selective electrocatalytic reduction of CO₂ to HCOOH over an in situ derived hydrocerussite thin film on a Pb substrate. *Chemosphere* **2022**, *291*, 132889.
45. Cao, S.-M.; Chen, H.-B.; Dong, B.-X.; Zheng, Q.-H.; Ding, Y.-X.; Liu, M.-J.; Qian, S.-L.; Teng, Y.-L.; Li, Z.-W.; Liu, W.-L., Nitrogen-rich metal-organic framework mediated Cu-N-C composite catalysts for the electrochemical reduction of CO₂. *J. Energy Chem.* **2021**, *54*, 555-563.
46. Liu, S.; Fan, Y.; Wang, Y.; Jin, S.; Hou, M.; Zeng, W.; Li, K.; Jiang, T.; Qin, L.; Yan, Z.; Tao, Z.; Zheng, X.; Shen, C.; Liu, Z.; Ahmad, T.; Zhang, K.; Chen, W., Surface-Oxygen-Rich Bi@C Nanoparticles for High-Efficiency Electroreduction of CO₂ to Formate. *Nano Lett.* **2022**, *22*, 9107-9114.
47. Qiu, C.; Qian, K.; Yu, J.; Sun, M.; Cao, S.; Gao, J.; Yu, R.; Fang, L.; Yao, Y.; Lu, X.; Li, T.; Huang, B.; Yang, S., MOF-Transformed In₂O_{3-x}@C Nanocorn Electrocatalyst for Efficient CO₂ Reduction to HCOOH. *Nano-Micro Lett.* **2022**, *14*, 167.
48. Zhu, Z. H.; Zhao, B. H.; Hou, S. L.; Jiang, X. L.; Liang, Z. L.; Zhang, B.; Zhao, B., A Facile Strategy for Constructing a Carbon-Particle-Modified Metal-Organic Framework for Enhancing the Efficiency of CO₂ Electroreduction into Formate. *Angew. Chem. Int. Ed.* **2021**, *60*, 23394-23402.
49. Shang, H.; Wang, T.; Pei, J.; Jiang, Z.; Zhou, D.; Wang, Y.; Li, H.; Dong, J.; Zhuang, Z.; Chen, W.; Wang, D.; Zhang, J.; Li, Y., Design of a Single-Atom Indium^{δ+}-N₄ Interface for Efficient Electroreduction of CO₂ to Formate. *Angew. Chem. Int. Ed.* **2020**, *59*, 22465-22469.
50. Lu, P.; Tan, X.; Zhao, H.; Xiang, Q.; Liu, K.; Zhao, X.; Yin, X.; Li, X.; Hai, X.; Xi, S.; Wee, A. T. S.; Pennycook, S. J.; Yu, X.; Yuan, M.; Wu, J.; Zhang, G.; Smith, S. C.; Yin, Z., Atomically Dispersed Indium Sites for Selective CO₂ Electroreduction to Formic Acid. *ACS Nano* **2021**, *15*, 5671-5678.
51. Yang, Z.; Wang, H.; Fei, X.; Wang, W.; Zhao, Y.; Wang, X.; Tan, X.; Zhao, Q.; Wang, H.; Zhu, J.; Zhou, L.; Ning, H.; Wu, M., MOF derived bimetallic CuBi catalysts with ultra-wide potential window for high-efficient electrochemical reduction of CO₂ to formate. *Appl. Catal., B* **2021**, *298*, 120571.
52. Yao, K.; Wang, H.; Yang, X.; Huang, Y.; Kou, C.; Jing, T.; Chen, S.; Wang, Z.; Liu, Y.; Liang, H., Metal-organic framework derived dual-metal sites for electroreduction of carbon dioxide to HCOOH. *Appl. Catal., B* **2022**, *311*, 121377.
53. Guan, Y.; Zhang, X.; Zhang, Y.; Karsili, T. N. V.; Fan, M.; Liu, Y.; Marchetti, B.; Zhou, X. D., Achieving high selectivity towards electro-conversion of CO₂ using In-doped Bi derived from metal-organic frameworks. *J. Colloid Interface Sci.* **2022**, *612*, 235-245.
54. Xing, Y.; Kong, X.; Guo, X.; Liu, Y.; Li, Q.; Zhang, Y.; Sheng, Y.; Yang, X.; Geng, Z.; Zeng, J., Bi@Sn Core-Shell Structure with Compressive Strain Boosts the Electroreduction of CO₂ into Formic Acid. *Adv. Sci.* **2020**, *7*, 1902989.
55. Liu, S.; Lu, X. F.; Xiao, J.; Wang, X.; Lou, X. W. D., Bi₂O₃ Nanosheets Grown on Multi-Channel Carbon Matrix to Catalyze Efficient CO₂ Electroreduction to HCOOH. *Angew. Chem. Int. Ed.* **2019**, *58*, 13828-13833.
56. Yang, X.-F.; Wang, A.; Qiao, B.; Li, J.; Liu, J.; Zhang, T., Single-Atom Catalysts: A New Frontier in Heterogeneous Catalysis. *Acc. Chem. Res.* **2013**, *46*, 1740-1748.
57. Jiang, B.; Zhang, X. G.; Jiang, K.; Wu, D. Y.; Cai, W. B., Boosting Formate Production in Electrocatalytic CO₂ Reduction over Wide Potential Window on Pd Surfaces. *J. Am. Chem. Soc.* **2018**, *140*, 2880-2889.