

# Microwave assisted the Boudouard reaction: Highly effective reduction of the greenhouse gas CO<sub>2</sub> to useful CO feedstock with semi-coke

Huan Dai<sup>1,2</sup>, Hong Zhao<sup>1,\*</sup>, Siyuan Chen<sup>3</sup> and Biao Jiang<sup>3,\*</sup>

<sup>1</sup> Green Chemical Engineering Research Center, Shanghai Advanced Research Institute, Chinese Academy of Sciences, Shanghai 201210, China; daihuan2018@sari.ac.cn (H.D.); zhaoh@sari.ac.cn (H.Z.)

<sup>2</sup> University of Chinese Academy of Sciences, Beijing 100049, China; daihuan2018@sari.ac.cn

<sup>3</sup> Shanghai Green Chemical Engineering Research Center, Shanghai Institute of Organic Chemistry, Chinese Academy of Sciences, Shanghai 200032, China; jiangb@mail.sioc.ac.cn (B.J.); chensy@sioc.ac.cn (S.C.)

\* Correspondence: jiangb@sioc.ac.cn; zhaoh@sari.ac.cn

**Abstract:** The conversion of CO<sub>2</sub> into more synthetically flexible CO is an effective and potential method for CO<sub>2</sub> remediation, utilization and carbon emission reduction. In this paper, the reaction of carbon-carbon dioxide (Boudouard reaction) was performed in a microwave fixed bed reactor using semi-coke (SC) as both the microwave absorber and reactant and was systematically compared with that heated in a conventional thermal field. The effects of the heating source, SC particle size, CO<sub>2</sub> flow rate and additives on CO<sub>2</sub> conversion and CO output were investigated. By microwave heating (MWH), CO<sub>2</sub> conversion reached more than 99 %, while by conventional heating (CH), the maximum conversion of CO<sub>2</sub> was approximately 29% at 900 °C. Meanwhile, for the reaction with 5 wt% Barium Carbonate added as a promoter, the reaction temperature was significantly reduced to 750 °C with almost quantitative conversion of CO<sub>2</sub>. Further kinetic calculations showed that the apparent activation energy of the reaction under microwave heating was 46.3 kJ/mol, which was only one-third of that observed under conventional heating. The microwave-assisted Boudouard reaction with catalytic barium carbonate is a promising method for carbon dioxide utilization.


**Keywords:** Microwave heating; CO<sub>2</sub> conversion; Semi-coke; Boudouard reaction

---

## 1. Introduction

In the face of climate change due to global warming, converting carbon dioxide into synthetic, flexible and useful molecules, rather than capturing CO<sub>2</sub> for storage is the most attractive approach to climate change mitigation solutions (Scheme 1) [1]. Nevertheless, the dynamics and thermodynamic stability of CO<sub>2</sub> severely limit conversion. Efficient reducing agents and precious metal catalysts are required to facilitate its conversion into useful chemicals [2]. A simple and well-known response is the Boudouard reaction ( $C+CO_2=2CO$ ), in which CO<sub>2</sub> reacts with carbon to produce carbon monoxide [3]. CO is not only the feedstock for Fischer-Tropsch's synthetic oils and waxes but also a raw material of carbonylation reactions to synthesize a number of fine chemicals [4], and it provides important hydrogen energy through water-gas shift reactions [5].

---

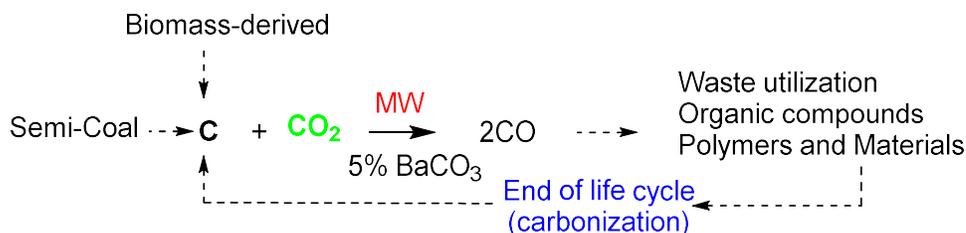

**Scheme 1.** The Boudouard reaction in sustainable total carbon recycling.

However, the Boudouard reaction is a highly endothermic gas-solid reaction with a large positive enthalpy (172 kJ/mol at 298 K), in which very high temperatures, typically above 700 °C, are required to shift the equilibrium towards CO production [3]. Over the past decade, interest in using microwaves to activate chemical reactions has become widespread, creating significant advantages in the field of heterogeneous catalysis [6]. In particular, high-temperature microwaves have a special advantage in inducing chemical reactions derived from heterogeneous catalysts with unique opportunities to control the energy input [7]. Therefore, the ideal "microwave catalyst" has a dual role, both as a catalyst for chemical reactions and as an efficient converter of the thermal energy required for the event and reaction activation from microwave energy [8]. Carbonaceous materials are known as excellent microwave receptors [9], and the high temperatures required for the Boudouard reaction could be provided by microwave irradiation [10]. Microwave-enhanced CO<sub>2</sub> gasification of oil palm shell char [11, 12], coconut shell char [13], and sewage sludge waste has been studied [14]. The results showed that microwave radiation was more effective than conventional heating, and the reaction temperature was reduced by approximately 200 °C in a short time. The reactivity of biochar was found to be dependent on the pore structure of char and its morphology, catalytic activity of the associated ash, availability of carbon active sites as well as catalytic active sites on the char, thermal history of the char during pyrolysis and type of carbon source.

China is a coal-rich country and implementing carbon neutrality is the country's strategy for mitigating climate change. Semi-coke, named blue coal, is prepared from Jurassic low-quality coal, with reserves of 100 billion tons in China [15]. As a new type of carbon material, with its high fixed carbon content, high chemical activity, and low ash content, semi-coke can replace char (metallurgical coke) and is widely used in the chemical, smelting, gasification and other industries. In this paper, we report the results of an investigation specifically focused on the conversion of CO<sub>2</sub> into CO with semi-coke under microwave irradiation and catalysis. To the best of our knowledge, similar data are not found in the literature, and the Boudouard reaction was carried out with a CO<sub>2</sub> conversion rate of 99 % at 900 °C with excellent microwave absorption performance of the semi-coke. When barium carbonate was added as a promoter, the reaction temperature was significantly reduced to 750 °C with almost quantitative conversion of CO<sub>2</sub>.

## 2. Results and Discussions

### 2.1. Temperature correction of the microwave fixed bed reactor

The application of microwave irradiation to gas-solid reaction has been studied for more than 20 years. However, due to the practical difficulties on the temperature measurement and uniform temperature distribution in MW field, the comparing reaction performances under CH and MWH always would be explained as the formation of hot spots in the reaction system as a consequence of MWH. In this paper, we obtained a relatively even temperature field in the microwave fixed bed by using three silicon carbide rings with the width of 0.5 cm as thermal loads which were sheathed outside the quartz tube. Moreover, three optical radiation pyrometers were used to monitor the surface temperature of the bed. Before the Boudouard reaction experiments, we corrected the heating temperature and confirmed the constant temperature area in the microwave fixed bed reactor.

We used silicon carbide rod with a length of 13 cm and a diameter of 3.5 cm as heat carrier for temperature range correction (SiC is an excellent microwave absorber material [16, 17]). Figure 3. exhibited the temperature distribution of the bed with an error of  $\pm 10$  °C, showed that the uniformity of the temperature distribution. After that, we measured the temperature distribution using SC as heat carrier. The SC bed exhibited a relatively even temperature zone ranged about  $\pm 3$  cm from the center of the temperature zone, which met the needs of our experiments. The temperature distribution of the fixed bed was shown in Figure 1 and the error of it was within  $\pm 25$  °C, which met the need of our experiments.


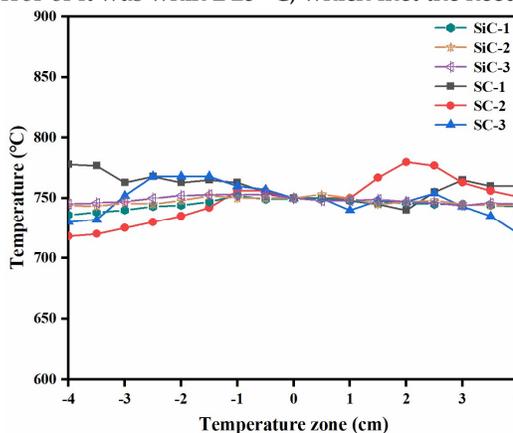


Figure 1. Temperature correction diagram of SiC and SC.

## 2.2. The Boudouard reaction in both microwave and conventional thermal fields

To investigate the characteristics of the CO<sub>2</sub> gasification of SC in both microwave and conventional thermal fields, typical experiments were conducted with a SC particle size of 0.200-0.450 mm and CO<sub>2</sub> space velocity of 3.20 m<sup>3</sup>/(m<sup>3</sup>(SC)·h) at 750 °C. The effect of the temperature on the Boudouard reaction in both fields is shown in Figure 2(a,b). As we can see from Figure 2a, by conventional heating, CO<sub>2</sub> conversion and SC conversion increased slowly with increasing temperature but were at a low level. CO<sub>2</sub> conversion increased from 5.0 % at 800 °C to 10.3 %, 14.4 % and 29.1 % at 850 °C, 900 °C and 950 °C (29.1 %), respectively. The results were consistent with the strong endotherm of the Boudouard reaction. The high temperature pushed the balance to CO production when heated by conventional methods. Figure 2b shows the experimental results when heated by microwave irradiation. Clearly, when the reaction temperature was 750 °C, the CO<sub>2</sub> conversion rate was 77.2 %, which was much higher than that carried out at 950 °C by conventional heating. When the reaction temperature was increased to 900 °C, the CO<sub>2</sub> conversion increased to 99.7 %. In addition, Figure 2c compares the CO output of the two heating sources. From Fig. 4c, it can be clearly seen that by conventional heating, the CO output ranged from 8.1 mmol at 800 °C to 59.1 mmol at 950 °C, while by microwave heating, the CO output increased from 1163 mmol at 750 °C to 2000 mmol at 900 °C, which was more than 60 times that obtained by conventional heating. The clear CO output at 950 °C was only approximately one-twentieth of that carried out in the microwave reactor at 750 °C. We know that SC is a good heating conductor, and the possible temperature gradient derived from the characteristics of microwave heating would not be great enough to cause such distinct Boudouard reaction performance between the two thermal fields. Therefore, the obviously higher CO<sub>2</sub> conversion and CO output obtained in the microwave reactor were not caused by incorrect temperature measurements or uneven temperature distributions in the microwave reactor. The fact that the Boudouard reaction under microwave heating proceeded more easily suggested great enhancement of the Boudouard reaction with microwave heating.

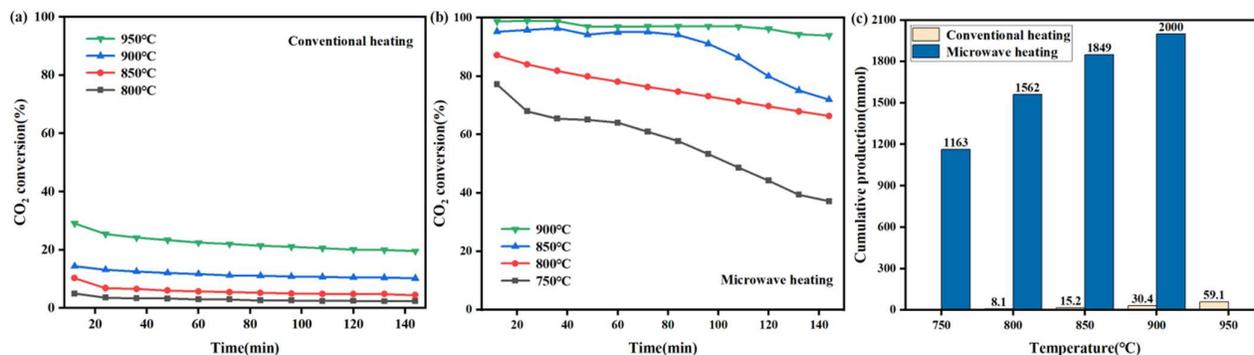

**Figure 2.** (a) Effect of gasification temperature under the conventional heating; (b) Effect of gasification temperature under the microwave heating; (c) Production of CO under the microwave heating and conventional heating.


This superior performance of microwaves is believed to be related to the mechanism of microwave heating [18]. SC is an excellent material for absorbing microwaves that can be firmly coupled with microwaves to carry out chemical reactions. When the microwave acted on the SC, the microwave energy could directly couple with carbon molecules so that the dielectric heating effect of the microwave could effectively heat the raw material. Different from conventional heating, the main mechanism of microwave absorption in dielectric materials is to excite electronic oscillations at the frequency of the microwave source.

### 2.3. Influence of the SC particle size

The effect of the SC particle size on CO<sub>2</sub> conversion and CO output in the microwave reactor was investigated at a temperature of 800 °C and CO<sub>2</sub> flow rate of 125 ml/min. As shown in Figure 3a, the CO<sub>2</sub> conversion improved from 83.0 % for particles in the range of 0.850-1.400 mm to 98.0 % for particles in the range of 0.200-0.450 mm; at the same time, the CO<sub>2</sub> conversion was maintained above 90 %. As the particle size of the SC decreased, the gasification reactivity was improved. This is because in the gasification process, the smaller particles of SC have better heat and mass transfer processes. Within a certain particle size range, the decreased SC particle size would give a larger contact area between CO<sub>2</sub> and SC, causing a more complete reaction. In addition, the reduced SC particle size was helpful to reduce the effects of internal diffusion, which could also increase the gasification reaction rate. It can be seen that the CO<sub>2</sub> conversion of the SC particle size <0.200 mm was generally lower than that of the SC particle size 0.200-0.450 mm as the reaction time increased, and this may be because too small of a particle size would give larger external diffusion resistance and the CO<sub>2</sub> reactant was more difficult to evenly diffuse into the SC bed. Figure 3b shows the effect of different particle sizes on the CO output. We can see that the CO output also shows the same trend as the CO<sub>2</sub> conversion. When the SC particle size was 0.200-0.450 mm, the maximum CO output was 1371 mmol.

### 2.4. Influence of the CO<sub>2</sub> gas flow rate


Figure 3c shows the influence of the CO<sub>2</sub> gas flow rate on the CO<sub>2</sub> conversion of SC. The CO<sub>2</sub> conversion decreased from 97.3 % to 67.2 % when the CO<sub>2</sub> flow increased from 125 ml/min to 200 ml/min. This was because the increase in CO<sub>2</sub> flow shortened the residence time of CO<sub>2</sub> gas in the carbon bed and then reduced the chance of CO<sub>2</sub> conversion, therefore causing a significant drop in CO<sub>2</sub> conversion. Figure 3d shows the CO output under the different gas flows. The results indicated that the CO output increased from 1462 mmol to 1581 mmol when the CO<sub>2</sub> flow increased from 125 ml/min to 200 ml/min. However, with the increase in CO<sub>2</sub> flow, the output of CO was not obviously changed. This might be due to the increase in CO<sub>2</sub> flow, resulting in the reduction in CO<sub>2</sub> external diffusion resistance and the increase in CO<sub>2</sub> diffusion into SC particles, which intensified the CO<sub>2</sub> conversion reaction.

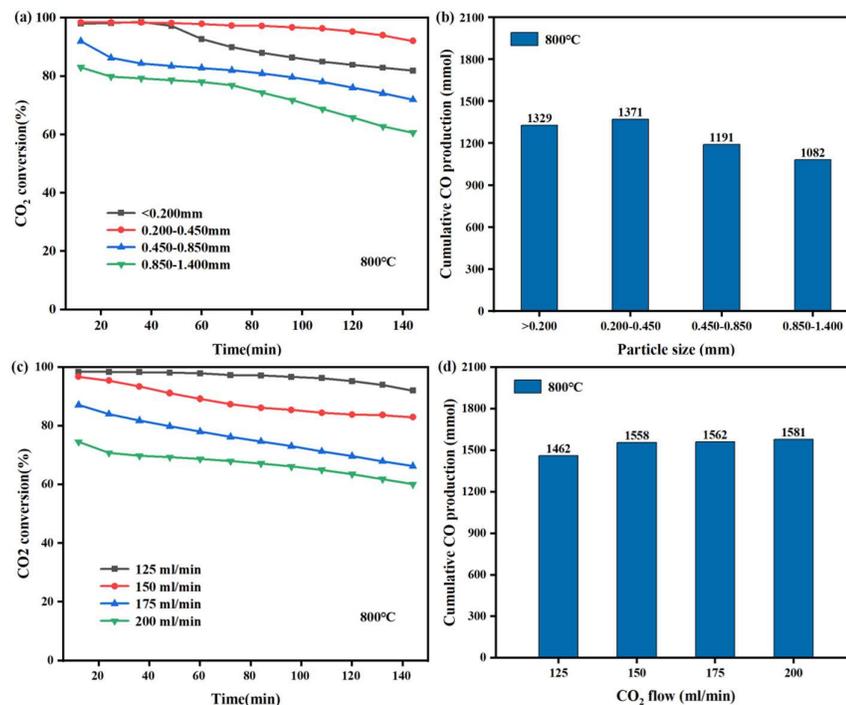

**Figure 3.** (a) Effect of SC particle size on CO<sub>2</sub> conversion, (b) CO output at different particle sizes, Reaction conditions: the CO<sub>2</sub> flow of 125 ml/min, the reaction temperature of 800 °C; (c) Effect of gas flow rate on CO<sub>2</sub> conversion, (d) CO output at different gas flow rates, Reaction conditions: the SC particle size of 0.200-0.450 mm, the reaction temperature of 800 °C.


## 2.5. Influence of the catalyst

It was reported that the salts of alkali metals and alkaline earth metals, such as Na, K, and Ca, have good catalytic performance for char gasification reactions [19-21], but the effect of barium salt on the Boudouard reaction was merely investigated. Here, BaCO<sub>3</sub> was used as a catalyst and compared with CaO in the gasification reaction of SC and CO<sub>2</sub> under microwave radiation. Figure 4a exhibits the CO<sub>2</sub> conversion of the SC with/without 5 wt% CaO and BaCO<sub>3</sub> addition at a reaction temperature of 750 °C and CO<sub>2</sub> flow rate of 175 ml/min under microwave heating. Without catalyst, the initial CO<sub>2</sub> conversion at 750 °C was 86.2 % and then decreased quickly to approximately 40 % after 144 min. Under the catalysis of BaCO<sub>3</sub> and CaO, the initial CO<sub>2</sub> conversion was 99.9 %, but BaCO<sub>3</sub> exhibited a better catalytic life. Figure 4b shows that the CO output was also increased significantly from 1689 mmol to 2392 mmol and 2520 mmol when CaO and BaCO<sub>3</sub> were used as catalysts. The experimental results indicated that BaCO<sub>3</sub> and CaO had excellent catalytic performance for the Boudouard reaction and reduced the reaction temperature. The reason for the higher reactivity of SC catalyzed by BaCO<sub>3</sub> would be that BaCO<sub>3</sub> improved the adsorption capacity of SC for CO<sub>2</sub>, thereby obtaining higher reactivity.

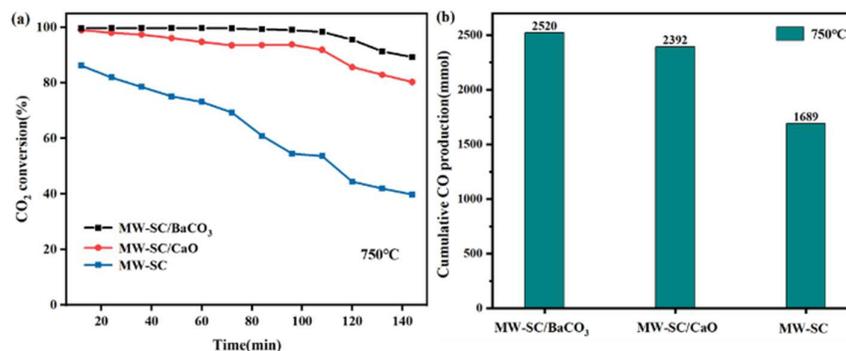

**Figure 4.** (a) Comparison of SC, SC/BaCO<sub>3</sub> and SC/CaO gasification reactivity under MW at 750 °C;(b) CO output at different experiment reactions.

Figure 5 shows the surface morphologies of gasified SC before and after reaction under different reaction conditions. It can be seen from Figure 5a that the ungasified SC has a relatively smooth surface, and the carbon layer structure is complete and without obvious pores inside the bulk SC particles. By conventional heating, the SC particles shown in Figure 5b exhibited an inconspicuous lamellar structure with some large pores, and the carbon layer structure was relatively complete. The possible reason is that gasified SC hardly occurs at low temperatures in conventional heating. The morphology of gasified SC under microwave radiation is shown in Figure 5c. The surface of SC is obviously damaged, and some large pores are formed. As shown in Figure 5d, BaCO<sub>3</sub> particles on gasified SC obtained at 750 °C show that the carbon layer structure is further destroyed, and the surface carbon structure is more uniformly distributed. The results indicate that the reaction rate of CO<sub>2</sub> on the surface of SC is more intense in the presence of barium salt. Table 1 shows the specific surface areas and volume pores for SCs heated by different techniques. The specific surface area and pore volume of raw SC are 2.16 m<sup>2</sup>/g and 1.30×10<sup>-3</sup> cm<sup>3</sup>/g, respectively. After conventional and microwave heating, the specific surface area was increased from 2.16 m<sup>2</sup>/g to 3.60 m<sup>2</sup>/g for CH-SC, 18.2 m<sup>2</sup>/g for MW-SC, and 14.3 m<sup>2</sup>/g for MW-SC/BaCO<sub>3</sub>, while the pore volume also showed the same trend. The results indicate that microwaves enhance the reactivity of SC, resulting in higher CO<sub>2</sub> conversion and CO output.

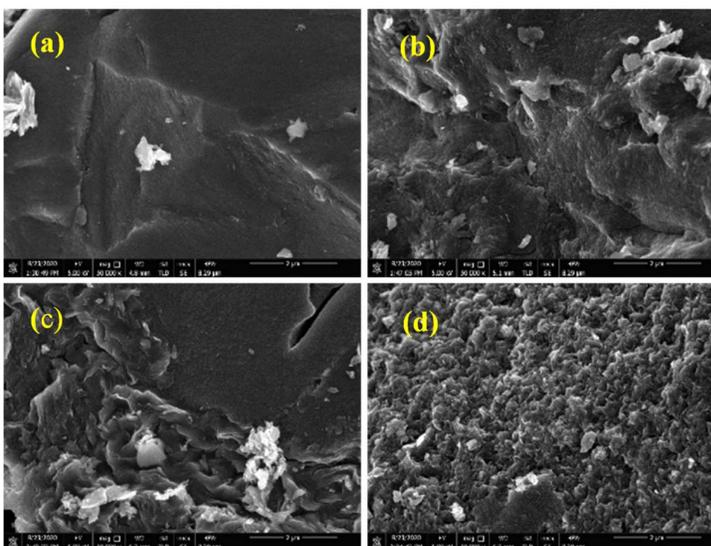

**Figure 5.** SEM micrographs of (a) Raw SC; (b) SC after CO<sub>2</sub> gasification in CH; (c) SC after CO<sub>2</sub> gasification in MW; (d) SC/BaCO<sub>3</sub> after CO<sub>2</sub> gasification in MW. Reaction conditions: the SC particle size of 0.200-0.450 mm, the reaction temperature of 750 °C.

**Table 1.** BET and volume

Sample	Raw SC	CH-SC	MW-SC	MW-SC/BaCO <sub>3</sub>
S <sub>bet</sub> (m <sup>2</sup> /g)	2.2	3.6	18.2	14.3
V <sub>total</sub> (cm <sup>3</sup> /g)	1.3x10 <sup>-3</sup>	1.7x10 <sup>-3</sup>	2.8x10 <sup>-3</sup>	2.5x10 <sup>-3</sup>

## 2.6. Analysis of gasification kinetic

In order to compare the reaction performances in both thermal fields, the gasification kinetics in two thermal fields were studied. we know the volume reaction model was a commonly used kinetic model in Boudouard reaction. The volume reaction model (VRM) assumes that the gasification reaction occurs at the active site and is evenly distributed throughout the carbon particles [22-25]. By the kinetic analysis of the isothermal gasification experiment, and then conversion of the first-order kinetics into the Arrhenius relationship the kinetics of several coal conversion processes could be represented. Therefore, we will perform kinetic calculations on the experimental results under conventional and microwave (non-catalysis) thermal fields. The reaction rate equation was expressed as follows:

$$r = \frac{dX}{dt} = k_{VRM}(1 - X) \quad (1)$$

$$\ln(1 - X) = -k_{VRM}t \quad (2)$$


From the graph of  $\ln(1 - x) - t$ , the value of the first-order reaction rate constant  $k_{VRM}$  at each temperature can be obtained. The temperature dependence of  $k_{VRM}$  is expressed by the Arrhenius equation as follows:

$$k_{VRM} = A \exp\left(-\frac{E_a}{RT}\right) \quad (3)$$

$$\ln k_{VRM} = -\frac{E_a}{RT} + \ln A \quad (4)$$

In the formula, the  $k_{VRM}$  is rate constant, min<sup>-1</sup>; the A is previous factor, min<sup>-1</sup>; the  $E_a$  is reaction activation energy, kJ/mol; the R is gas constant (8.314 J/mol/K); the X is SC conversion.

Figure 6a and Figure 6b show the relationship between the microwave and conventional reaction times and carbon conversions. The slope of the fitted straight line was the reaction rate constant at this temperature. It was suggested that the reaction rate constant increased with increasing temperature in the two heating methods, which indicates that when the temperature increases, the reaction rate increases. Figure 6c shows the Arrhenius diagram of microwave and conventional reactions. For microwave and conventional reaction experiments, higher regression coefficients were obtained. The activation energy and pre-exponential factor are obtained from the slope of the fitted straight line. Table 2 shows the activation energy and pre-exponential energy under microwave and conventional heating. The activation energies were 47.1 kJ·mol<sup>-1</sup> and 148.9 kJ·mol<sup>-1</sup>, respectively. The activation energy was much smaller than that under conventional heating. The large difference between the microwave-induced reaction rate and the thermal reaction rate indicated that the rate constant must have a fundamentally different dependence on temperature, which was demonstrated in the Arrhenius parameter. In addition, as shown in Table 2, the exponential factor of the microwave heating reaction is significantly smaller than that of the conventional thermal reaction by more than 1,000 orders of magnitude. Hunt et al. [26] suggested the lower reaction temperature in the microwave experiment caused the lower collision frequency of reactants to reduce the pre-exponential term. That was to say, microwave heating should lead to the more efficient collision frequency of reactants.

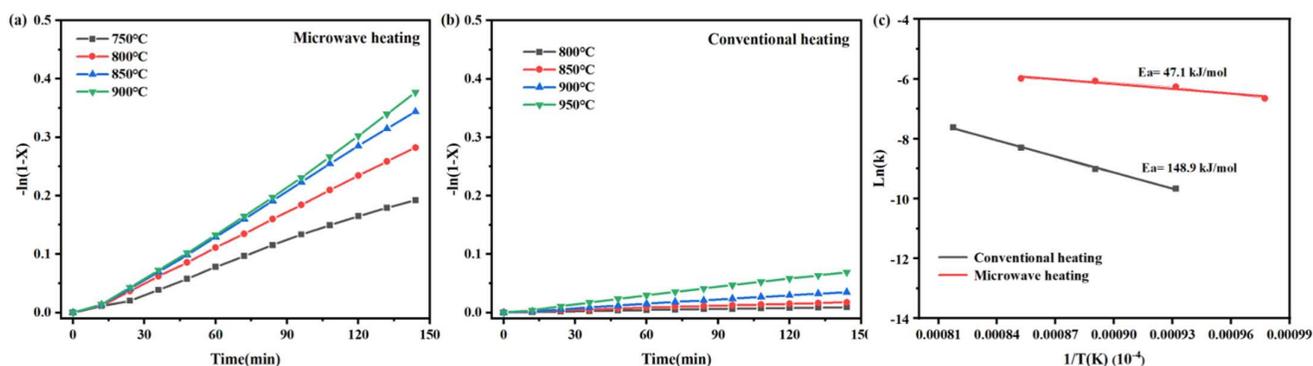

**Figure 6.** (a) Conversion vs. time under MW, (b) Conversion vs. time under CH; (c) Obtain dynamic parameters through Arrhenius diagram.

**Table 2.** Kinetic parameters under microwave heating and conventional heating.

Parameters	Raw SC	CH-SC
$E_a/\text{kJ}\cdot\text{mol}^{-1}$	47.1	148.9
$A/\text{min}^{-1}$	0.3	1088.6

### 3. Materials and methods

#### 3.1. Materials

The semi-coke was provided by the Shanxi Lu'an Coal Industry. The ultimate analysis and proximate analysis are shown in Table 3. The semicoke was dried, crushed and sieved into four particle sizes of <0.200 mm, 0.200-0.450 mm, 0.450-0.850 mm and 0.850-1.40 mm. Before the experiment, the semi-coke was continuously dried at 105 °C for 12 hours and then stored in a well-sealed dryer for use in the experiment. This article named semi-coke as SC. Ar and CO<sub>2</sub> (purity of 99.9 %), calcium oxide (CaO, 99 % from Aldrich), and barium carbonate (BaCO<sub>3</sub>, 99 % from Aldrich) were used in the experiment.

**Table 3.** The ultimate and proximate analysis of SC

Ultimate analysis (%)					Proximate analysis (%)			
C	H	N	O	S	FC	M	V	Ash
82.3	0.7	1.15	14.8	0.9	81.7	1.5	2.9	14.8

#### 3.2. Methods

The reactions heated by microwaves were carried out in a microwave fixed bed reactor, and the experimental schematic diagram is shown in Figure S1. The microwave fixed bed reactor was heated by a monomodal cavity with a magnetron generator operating at 2.45 GHz (the maximum output power is 1500 W). The reactor was equipped with a temperature automatic control system and a quartz glass tube with an inner diameter of 38 mm and a length of 90 cm. For conventional heating, the reactions were carried out in a fixed-bed reactor under the same conditions. In the experiment, approximately  $40.0 \pm 0.01$  g of SC was first put into a quartz glass tube. Before the reaction, Ar was introduced into the reactor at a flow rate of 100 ml/min for 30 min. When the temperature reached the desired value, CO<sub>2</sub> gas was precisely introduced into the reactor, and the reaction started. The composition of the gas products was analyzed online by a gas chromatograph (GC) (SHIMADZU, 2014C) equipped with a thermal conductivity detector (TCD) and a packed column (Porapak Q 80-100 mesh, 2 m x 4 mm), and the reacted SC was analyzed after the reaction.

#### 3.3. Carbon characterization and data analysis

---

The pore structures of SC were measured using a Micromeritics ASAP 2460 N<sub>2</sub> adsorption analyzer. SC (0.1 g) was weighed and placed in a quartz tube for high-temperature vacuum degassing and then placed in a bottle containing liquid nitrogen at -196 °C for the N<sub>2</sub> adsorption/desorption experiments. The specific surface area was calculated using the BET equation, and the average pore size data were calculated from the H-K equation. The surface structure of SC was observed by scanning electron microscopy (SEM) (FEI Nova Nono 450) with an accelerating voltage of 5.0 kV.

The real-time composition of the outlet gas was measured by GC, and the CO<sub>2</sub> conversion, CO output and SC conversion were calculated according to the changes before and after the CO<sub>2</sub> reaction as follows:

$$X_{SC} = \frac{m - m_t}{m - m_{as}} \quad (5)$$

where  $m$ ,  $m_t$ , and  $m_{ash}$  represent the initial mass of SC, the mass of SC after the reaction, and the mass of ash in SC, respectively.

$$X_{CO_2} = \frac{n_b - n_a}{n_b} \quad (6)$$

where  $n_b$  and  $n_a$  represent the moles of CO<sub>2</sub> before the reaction and the moles of CO<sub>2</sub> after the reaction, respectively.

#### 4. Conclusion

The CO<sub>2</sub> gasification of semi-coke has been studied through microwave radiation. It is found that microwaves do have an excellent enhancement effect on the reaction. The experimental results show that the maximum CO<sub>2</sub> conversion was 99.9 % in the presence of barium carbonate. Based on the kinetic study, the activation energy for microwave heating was 47.1 kJ/mol, while this value was 148.9 kJ/mol for conventional heating, indicating that microwaves could increase the Boudouard reaction and reduce the reaction activation energy. Thus, BaCO<sub>3</sub> for the enhanced microwave chemical Boudouard reaction makes the "zero emission" of CO<sub>2</sub> and the clean utilization of coal resources possible.

**Supplementary Materials:** The following are available online, Figure S1: Schematic diagram of microwave experiment device; Table S1: Experiment data.

**Author Contributions:** Conceptualization, B.J. and H.Z.; investigation, H.D.; methodology, H.D.; software, H.D.; validation, B.J., H.Z. and H.D.; formal analysis, H.D.; resources, X.X.; data curation, X.X.; writing—original draft preparation, H.D.; writing—review and editing, B.J. and H.Z.; supervision, B.J. and H.Z.; project administration, H.Z.; funding acquisition, B.J. All authors have read and agreed to the published version of the manuscript.

**Funding:** This work was supported by the Shanghai Science and Technology Committee(15DZ1206800).

**Conflicts of Interest:** The authors declare no conflict of interest.

#### References

1. Song, C., Global challenges and strategies for control, conversion and utilization of CO<sub>2</sub> for sustainable development involving energy, catalysis, adsorption and chemical processing. *Catal. Today* 2006, 115, 2-32.
2. Das Neves Gomes, C.; Blondiaux, E.; Thuery, P.; Cantat, T., Metal-free reduction of CO<sub>2</sub> with hydroboranes: two efficient pathways at play for the reduction of CO<sub>2</sub> to methanol. *Chemistry* 2014, 20, 7098-106.
3. Lahijani, P.; Zainal, Z. A.; Mohammadi, M.; Mohamed, A. R., Conversion of the greenhouse gas CO<sub>2</sub> to the fuel gas CO via the Boudouard reaction: A review. *Renewable Sustainable Energy Rev.* 2015, 41, 615-632.
4. Beller, M., Catalytic Carbonylation Reaction. *Organomet. Chem.* 2006, 18, 1-283.
5. Ratnasamy, C.; Wagner, J. P., Water Gas Shift Catalysis. *Catalysis Reviews* 2009, 51, 325-440.
6. Leadbeater, N. E., *Microwave Heating as a Tool for Sustainable Chemistry*. CRC Press: 2017.
7. Yu V Bykov; K I Rybakov; Semenov., V. E., High temperature microwave processing. *Applied Physics* 2001, 34, 55-75.
8. Camelia Gabriel; Sami Gabriel; Edward H. Grant; Ben S. J. Halstead; Mingos., D. M. P., Dielectric parameters relevant microwave dielectric. *Chem. Soc. Rev.* 1998, 27, 213-223.

- 
9. Zirui Jia, K. L., Guanglei Wu, Hui Xing and Hongjing Wu, Recent Progresses of High-Temperature Microwave-Absorbing Materials. *NANO: Brief Reports and Reviews* 2018, 13, 1830005.
  10. Bermúdez, J. M.; Ruisánchez, E.; Arenillas, A.; Moreno, A. H.; Menéndez, J. A., New concept for energy storage: Microwave-induced carbon gasification with CO<sub>2</sub>. *Energy Convers. Manage.* 2014, 78, 559-564.
  11. Lahijani, P.; Mohammadi, M.; Zainal, Z. A.; Mohamed, A. R., Improvement of biomass char-CO<sub>2</sub> gasification reactivity using microwave irradiation and natural catalyst. *Thermochim. Acta* 2015, 604, 61-66.
  12. Lahijani, P.; Zainal, Z. A.; Mohamed, A. R.; Mohammadi, M., Microwave-enhanced CO<sub>2</sub> gasification of oil palm shell char. *Bioresour. Technol.* 2014, 158, 193-200.
  13. Chun, Y. N.; Song, H. G., Microwave-induced carbon-CO<sub>2</sub> gasification for energy conversion. *Energy* 2020, 190, 1-9.
  14. Chun, Y. N.; Song, H. G., Microwave-enhanced gasification of sewage sludge waste. *Environ. Eng. Res.* 2018, 24, 591-599.
  15. Lartey-Young, G.; Ma, L., Remediation with semicoke-preparation, characterization, and adsorption application. *Materials* 2020, 13, 1-23.
  16. Ramirez, A.; Hueso, J. L.; Abian, M.; Alzueta, M. U.; Mallada, R.; Santamaria, J., Escaping undesired gas-phase chemistry: Microwave-driven selectivity enhancement in heterogeneous catalytic reactors. *Sci. Adv.* 2019, 5, eaau9000.
  17. Sugawara, H.; Kashimura, K.; Hayashi, M.; Ishihara, S.; Mitani, T.; Shinohara, N., Behavior of microwave-heated silicon carbide particles at frequencies of 2.0–13.5 GHz. *Appl. Phys. Lett.* 2014, 105, (3).
  18. E.T. Thostenson, T.-W. C., Microwave processing fundamentals and applications. *Compos Part A-Appl. S.* 1999, 30, 1055-1071.
  19. Liu, Y.; Guan, Y.; Zhang, K., CO<sub>2</sub> gasification performance and alkali/alkaline earth metals catalytic mechanism of Zhundong coal char. *Korean J. Chem. Eng.* 2018, 35, 859-866.
  20. Uwaoma, R. C.; Strydom, C. A.; Bunt, J. R.; Okolo, G. N.; Matjie, R. H., The catalytic effect of Benfield waste salt on CO<sub>2</sub> gasification of a typical South African Highveld coal. *J. Therm. Anal. Calorim.* 2019, 135, 2723-2732.
  21. Lahijani, P.; Mohammadi, M.; Mohamed, A. R., Catalytic CO<sub>2</sub> gasification of rubber seed shell-derived hydrochar: reactivity and kinetic studies. *Environ Sci Pollut Res Int* 2019, 26, 11767-11780.
  22. Irfan, M. F.; Usman, M. R.; Kusakabe, K., Coal gasification in CO<sub>2</sub> atmosphere and its kinetics since 1948: A brief review. *Energy* 2011, 36, 12-40.
  23. Wen, X. D.; Man, S. F.; Long, Y.J.; Xin, J.; Yan, Z. h.; Jian, G. Q.; Xin, L. J., Combustion characteristics of unburned pulverized coal and its reaction kinetics with CO<sub>2</sub>. *Int. J. Miner. Metall. Mater.* 2019, 26, 811-821.
  24. Zhang, Y.; Geng, P.; Zheng, Y., Exploration and practice to improve the kinetic analysis of char-CO<sub>2</sub> gasification via thermogravimetric analysis. *Chem. Eng. J.* 2019, 359, 298-304.
  25. Bhui, B.; Vairakannu, P., Experimental and kinetic studies on in-situ CO<sub>2</sub> gasification based chemical looping combustion of low ash coal using Fe<sub>2</sub>O<sub>3</sub> as the oxygen carrier. *J. CO<sub>2</sub> Util.* 2019, 29, 103-116.
  26. Hunt, J.; Ferrari, A.; Lita, A.; Crosswhite, M.; Ashley, B.; Stieglman, A. E., Microwave-Specific Enhancement of the Carbon-Carbon Dioxide (Boudouard) Reaction. *J. Phy. Chem. C* 2013, 117, 26871-26880.