

Article

Comparison of Compressive Stress-Relaxation Behavior in Osteoarthritic (ICRS Graded) Human Articular Cartilage

Rajesh Kumar ^{1,*}, David M. Pierce ², Vidar Isaksen ³, Catharina de Lange Davies ⁴, Jon O. Drogset ⁵ and Magnus B. Lilledahl ⁶

¹ Department of Physics, Norwegian University of Science and Technology (NTNU), N-7491, Trondheim, Norway; rajesh.kumar@ntnu.no

² Departments of Mechanical Engineering/Biomedical Engineering/Mathematics, University of Connecticut, United States of America; dmpierce@engr.uconn.edu

³ Department of Medical Biology, The Arctic University of Norway (UiT), Tromsø, Norway; vidar.isaksen@unn.no

⁴ Department of Physics, Norwegian University of Science and Technology (NTNU), N-7491, Trondheim, Norway; catharina.davies@ntnu.no

⁵ Department of Orthopaedic Surgery, N-7491, Trondheim University Hospital, Norway. jon.o.drogset@ntnu.no

⁶ Department of Physics, Norwegian University of Science and Technology (NTNU), N-7491, Trondheim, Norway; magnus.lilledahl@ntnu.no

* Correspondence e-mail: 101rajesh@gmail.com; Tel.: +47-46958379

Abstract: Osteoarthritis (OA) is a common joint disorder found mostly in elderly people. The role of mechanical behavior in the progression of OA is complex and remains unclear. The stress-relaxation behavior of human articular cartilage in clinically defined osteoarthritic stages may have importance in diagnosis and prognosis of OA. In this study we investigated differences in the biomechanical responses among human cartilage of ICRS grades I, II and III using polymer dynamics theory. We collected 24 explants of human articular cartilage (eight each of ICRS grade I, II and III) and acquired stress-relaxation data applying a continuous load on the articular surface of each cartilage explant for 1180 s. We observed a significant decrease in Young's modulus, stress-relaxation time, and stretching exponent in advanced stages of OA (ICRS grade III). The stretch exponential model indicated that significant loss in hyaluronic acid polymer might be the reason for the loss of proteoglycan in advanced OA. This work encourages further biomechanical modelling of osteoarthritic cartilage utilizing these data as input parameters to enhance the fidelity of computational models aimed at revealing how mechanical behaviors play a role in pathogenesis of OA.

Keywords: stress-relaxation; polymer dynamics; biomechanical characterization; articular cartilage; osteoarthritis

1. Introduction

Articular cartilage is the tissue that covers the bone ends in diarthroidal, synovial joints. It acts like a cushion between the ends of two bones, minimizes the stress by distributing loads, and with very low frictional properties facilitates smooth joint movement. The mechanical properties of articular cartilage depend on the structural integrity of the constituents of the matrix composed mainly of collagen, proteoglycan (PG) and water [1].

Osteoarthritis (OA) is the most prevalent musculoskeletal disorders among elderly people [2] and is one of the fastest increasing causes of individual and social economic burden [3]. It is articular cartilage that is primarily affected during the progression of OA. The event and stimuli that initiate cartilage degradation is still unknown. Early degenerative changes in articular cartilage associated with OA are most often not visible by standard clinical imaging system (e.g., X-ray, MRI, Ultrasound, Arthroscopy). Our previous studies have shown biochemical and structural changes in early stage of osteoarthritic cartilage [4-6]. In addition to the biochemical and structural changes, the biomechanical properties of the articular cartilage have been shown to evolve with the stage of OA [7]. Current understanding about the changes in biomechanical properties and its consequences in cartilage degradation during progression of OA is limited. Therefore, knowledge about the changes in mechanical behavior of articular cartilage at various stages of OA can help in understanding the mechanisms of disease progression. Moreover, such knowledge aims to improve diagnostically relevant information used by orthopaedic surgeons during arthroscopic indentation [8].

Previous studies relevant to the biomechanical characterization of osteoarthritic articular cartilage were performed using normal and/or degenerative cartilage [8-15]. The International Cartilage Repair Society (ICRS) grade is a clinical, standard grading system used by orthopaedic surgeons to evaluate morphologically the degeneration of osteoarthritic cartilage [16]. More precise investigations with use of different stages of human osteoarthritic cartilage, i.e., the inclusion of early (ICRS grade-I), intermediate (ICRS grade-II) and, advanced stage (ICRS grade-III) osteoarthritic cartilage in biomechanical characterization is seldom. However, Klemann et. al., showed the creep behavior characteristics of progressively osteoarthritic cartilage [7]. The investigation of stress-relaxation behavior can help further in characterizing the viscoelastic behavior of osteoarthritic cartilage.

In this study intact *ex-vivo* cartilage sections were characterized by mechanical indentation. The stress-relaxation data acquired were fitted to the stretch exponential model that is described elsewhere [17-20]. This stretch exponential model is an empirical approach that describe relaxation processes for a wide variety of systems including polymers [16, 20-22]. The cartilage matrix is composed of several molecules that provide varying molecular environments, resulting in an overlap of many relaxation rates often observed as stretched exponential kinetics. The model represents the polymeric mechanism of cartilage viscoelasticity. This is a flow-independent viscoelastic model suitable for the unconfined compression analysis, the environment under which the data were acquired. In the stretch exponential model, stress relaxation is described by

$$\sigma = (\sigma_{in} - \sigma_{eq}) e^{-(t/\tau)^\beta} + \sigma_{eq} \quad (1)$$

where, σ_{in} , σ_{eq} , τ , and β is the instantaneous stress, equilibrium stress, time constant, and the stretching exponent, respectively. The stress relaxation time constant (τ) and stretching exponent parameter (β) were determined by nonlinear curve fitting using Matlab® (The MathWorks, 2014). The stress-relaxation time constant represents the viscoelastic characteristic of the cartilage while the stretching exponent parameter represents the distribution of relaxation time and is related to the specific type of polymer motion, i.e., reptation.

In this work, we hypothesized that the parameters derived from the stretch exponential model can describe the biomechanical characteristics of osteoarthritic articular cartilage. Therefore, the aim was to compare the stress-relaxation constant (τ) and the stretching-exponent parameter (β) between ICRS grades I, II and, III and find any relation, if existing, with the biochemical content.

2. Materials and Methods

2.1. Sample preparation

The use of human samples was approved (2013/265 REK, Norway) by the Regional Committee for Medical Research Ethics. Articular cartilage samples were obtained from osteoarthritic patients undergoing total knee replacement surgery. It was confirmed that no patient had suffered prior knee injury or surgery. Eight cartilage sections of each ICRS grade I, II, and III were obtained. Thus, in

total 24 sections of articular cartilage (from 14 patients) were entered into the study. The contribution of each patient in the collection of cartilage sections is shown in Table 1. To reduce age-associated variation in the articular cartilage, all patients selected in this study were older than 65 years. Any two cartilage sections presenting the same ICRS grade from the same patient were not included in this study. ICRS grade-IV usually includes only remnants of cartilage and mostly exposed bone and therefore, was not included in the study. Cartilage sections were acquired from the femoral condyle of the knee during arthroplasty. The assignment of ICRS grade was performed by two experienced orthopedic surgeons, who were blinded to the classification of each other. Only samples assigned the same ICRS grade by both orthopedic surgeons were included in this study.

2.2. Data acquisition and analysis

The stress-relaxation tests were performed uniaxially by a macroscopic indentation device developed in the laboratory (Figure 1a). A deformation equivalent to a load of 1.2 kg was suddenly imposed on the articular surface of the cartilage section (Figure 1b). Due to the fixed, applied deformation, a transient decrease (i.e., relaxation) in compressive force (and therefore stress) in the cartilage matrix occurs that was captured with a load cell (S/N: 1258426, Honeywell Sensotec Sensors, USA). The deformation on the articular surface of cartilage was imposed by using a flat-ended, cylindrical, impermeable indenter of diameter 4 mm (Figure 1b). The stress-relaxation data were acquired for 1180 s (Figure 1c). The initial stress-relaxation was set to $t = 0$ s and termed instantaneous stress (σ_{in}) while the stress-relaxation measured at $t = 1180$ s was set as the equilibrium stress (σ_{eq}). The instantaneous Young's modulus (Y_{in}) and the equilibrium Young's modulus (Y_{eq}) are the point measurements and, were calculated using the value of σ_{in} , σ_{eq} and the strain (i.e., deformation due to applied stress) of the cartilage. The cartilage section was immersed in phosphate-buffered saline (PBS) at all times during the data acquisition.

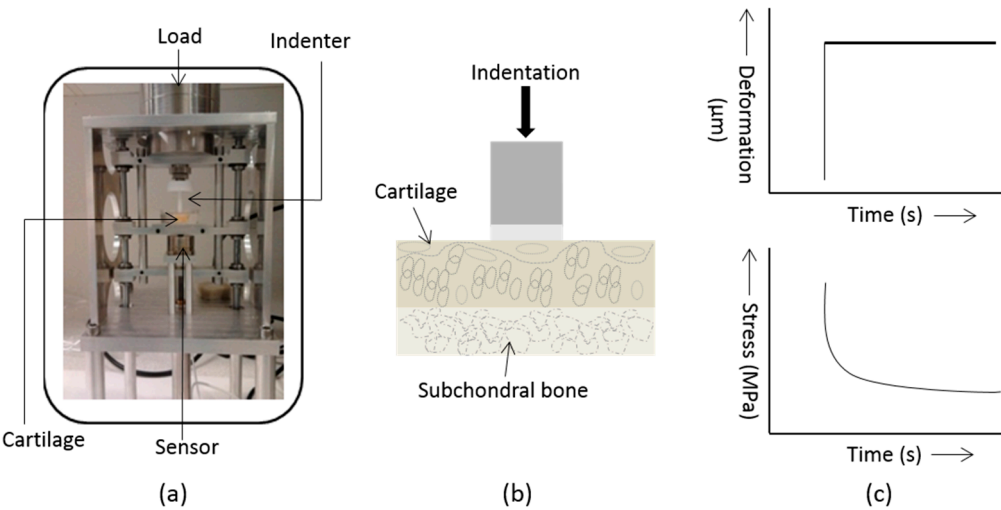


Figure 1. (a) A photograph of indentation instrument (b) Indentation was imposed on articular surface of cartilage by a preload (c) Deformation of articular surface due to applied load and acquisition of stress-relaxation data.

2.3. Statistical analyses

Multiple-group statistical comparisons among different ICRS osteoarthritic grades were assessed using the nonparametric Kruskal-Wallis ANOVA test in Matlab®. Box plots display median values and interquartile ranges. In all multiple-group pairwise comparisons, a p -value of less than 0.05 was considered indicative of statistical significance.

2.4. Histological assessment

After data acquisition of the stress relaxation with each ICRS grade cartilage section, tissue section was stored in 10% neutral-buffered formalin (NBF), and further processed for histological

evaluation. Histological assessment was performed using the Osteoarthritis Research Society International (OARSI) grading system [21]. Based on morphology and Safranin-O color evaluation, each tissue sample was assigned an OARSI grade.

3. Results and Discussions

The stress relaxation data acquired from 24 cartilage sections are shown in Figure 2a. A statistically significant and high correlation was observed between the ICRS and OARSI grades ($R^2 = 0.682$, $p < 0.05$). Therefore, histological evaluation (OARSI grade) confirmed the progressive degradation of osteoarthritic cartilage in addition to the evaluation (ICRS grade) performed by the orthopaedic surgeons.

A comparison between the mean relaxation curves of ICRS grades I, II, and III is shown (Figure 2b). The difference in mean relaxation behavior of different ICRS grades of osteoarthritic cartilage was observed. To measure a quantitative difference, the stress-relaxation curves were fit to equation (1). The results obtained are summarized in Table 2.

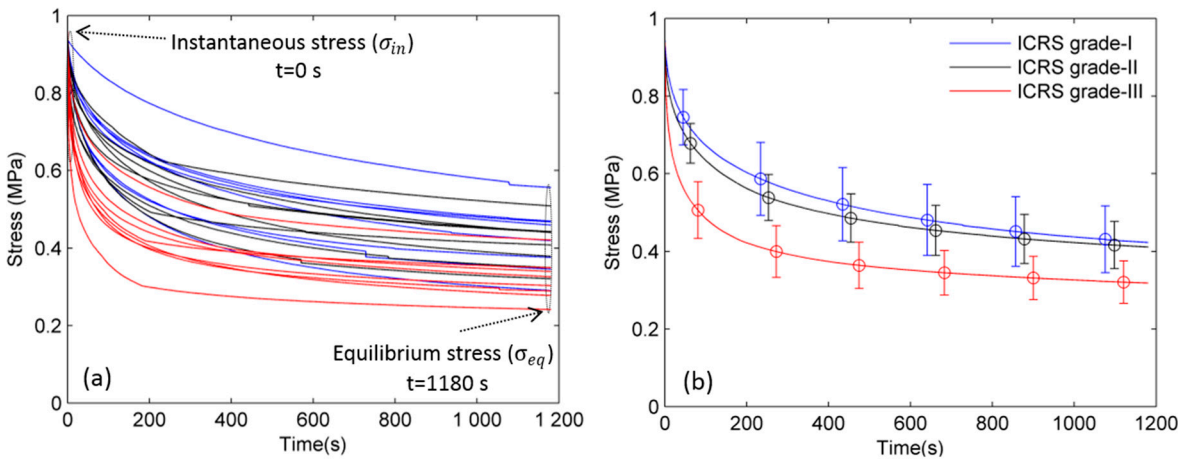


Figure 2. (a) Stress-relaxation data acquired from 24 cartilage sections. (b) Mean stress-relaxation curve ($n = 8$ curve) of ICRS grades I, II, and III. Bars represent the standard deviation at the selected time points.

3.1. Young's modulus

Although the same load was applied to all cartilage sections, the induced deformations (i.e., strains) due to the applied load were observed to be different in different ICRS grades of osteoarthritic cartilage. Analysis of the Young's modulus shows that there is a significant ($p < 0.05$) decrease in Y_{in} (Figure 3a) and Y_{eq} (Figure 3b) values between grades I and III, and between grades II and III, but no significant ($p < 0.05$) difference observed between grades I and II.

In our previous study, a comparison among ICRS grades of osteoarthritic cartilage was reported that showed a significant reduction in PG content between grades I and III, and between grades II and III, but not between grades I and II [22]. This means that the change in Young's modulus shows the same trend as the change in PG content between the ICRS grades I, II, and III. Earlier studies have shown that there is a strong positive correlation between compressive stiffness and the PG content of cartilage [23, 24]. Therefore, our result agrees with the earlier findings that the compressive modulus in cartilage is related to the PG content in the ECM of the cartilage [23, 24]. In advanced stage (ICRS grade-III) of osteoarthritic cartilage, the lowest Y_{in} was observed due to the highest induced deformation. The resistance to the deformation of tissue depends on the interactions between macromolecules and fluid-flow through the cartilage matrix. Using an OA model, Mansour et. al. [25], has described that decreasing PG content allow more space in the tissue for fluid and subsequently lower resistance to flow in the advanced stages of OA in cartilage. Therefore, the lowest PG content in ICRS grade-III causes the highest induced deformation. This explains why lowest Y_{in} is observed in the ICRS grade-III.

Table 1. ICRS classification of osteoarthritic cartilage sample. L and M represent lateral and medial femoral condyle section of articular cartilage respectively.

Cartilage section (Total n=24)	Assignment of ICRS Grade		
	Grade-I (n=8)	Grade-II (n=8)	Grade-III (n=8)
Patient 1	Section-1 (L)	X	X
Patient 2	X	X	Section-2 (M)
Patient 3	X	Section-3 (L)	X
Patient 4	Section-4 (M)	Section-5 (M)	Section-6 (L)
Patient 5	X	Section-7 (M)	Section-8 (L)
Patient 6	Section-9 (L)	X	Section-10 (M)
Patient 7	Section-11 (L)	Section-12 (M)	X
Patient 8	Section-13 (L)	Section-14 (L)	Section-15 (M)
Patient 9	Section-16 (M)	X	X
Patient 10	X	Section-17 (M)	Section-18 (M)
Patient 11	Section-19 (L)	Section-20 (M)	X
Patient 12	Section-21 (L)	X	Section-22 (M)
Patient 13	X	X	Section-23 (M)
Patient-14	X	Section-24 (L)	X

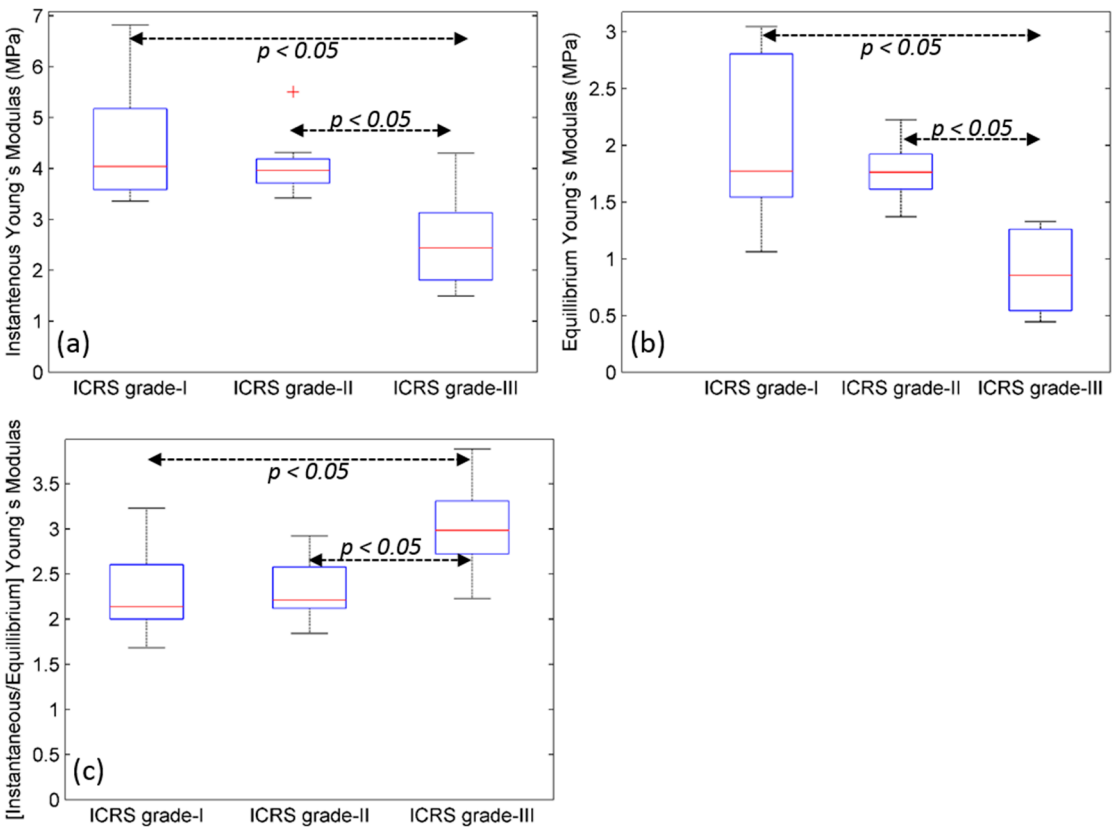


Figure 3. A relative comparison of (a) instantaneous Young's modulus (Y_{in}) and (b) equilibrium Young's modulus (Y_{eq}) between three ICRS grades of human osteoarthritic cartilage. Significant reduction in 'Y_{in}' and 'Y_{eq}' between grade-I and -III and, grade-II and -III were observed. No significant change between grade-I and -II was observed. (c) A relative comparison of Y_{in}/Y_{eq}

between three ICRS grades of human osteoarthritic cartilage. The Young's modulus ratio represents the viability of cartilage (the smaller the value, the more healthy the cartilage).

The magnitude of the ratio in Young's moduli (i.e., Y_{in}/Y_{eq}) was evaluated (Figure 3c). The Young's modulus ratio has been used to assess the viability of cartilage [13, 26]. The viability shows the mechanical strength and ability to perform loading and unloading processes under normal functioning of articular cartilage. The smaller the ratio, the more viable the cartilage. The Young's modulus ratio (Y_{in}/Y_{eq}) was found to be highest in ICRS grade-III (Table 2).

Using the creep test on articular cartilage, Kleeman et al. reported a reduction in Young's modulus with progressive ICRS grade [7]. However, neither the stress-relaxation test (in the present analysis) nor the dynamic impact test reported by Kos et al. [27] observed a significant difference in Young's modulus between ICRS grades I and II.

3.2. Stress relaxation time (τ)

A comparison of stress-relaxation times (τ) between three ICRS grades I, II and III was performed. Figure 4a shows that the median value of the stress relaxation time (τ) decreases with the ICRS grade. The difference was statistically significant ($p < 0.05$) between grades I and III and between grades II and III but not between grades I and II.

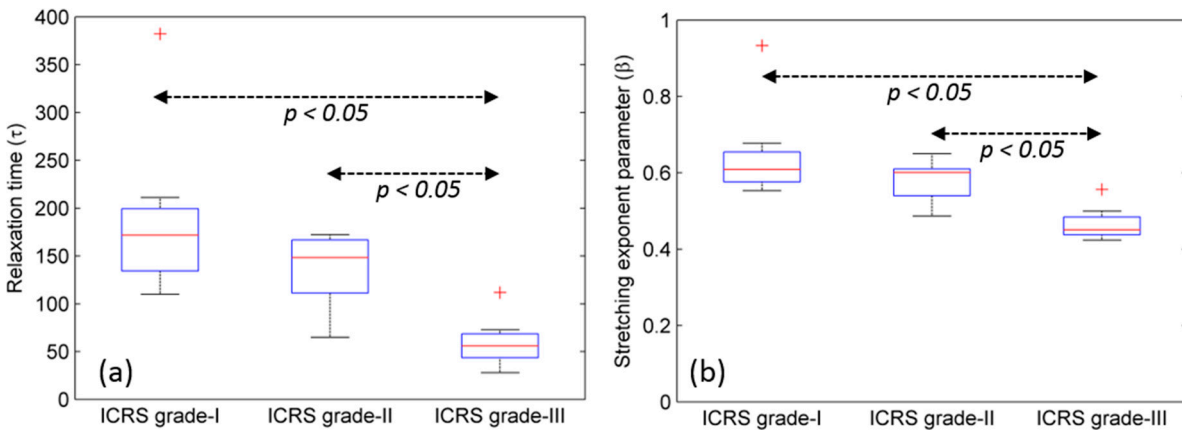


Figure 4. A relative comparison of (a) stress relaxation times (τ) and (b) stretching-exponent parameter (β) between three ICRS grades of human osteoarthritic cartilage. Significant reduction in ' τ ' between grade-I and -III and grade-II and -III were observed. No significant reduction between grade-I and -II was observed.

It was observed that the stress-relaxation time (τ) in ICRS grade-III cartilage is ~2 times shorter than the ICRS grade-I (Table 2). However, no significant difference was observed between ICRS grade-I and ICRS grade-II. Therefore, we hypothesize that in the advanced stage (i.e., ICRS grade-III), a significant decrease in PG content allows more space in ECM for fluid. An increase in water content correlates with an increase in permeability. Increasing permeability allows fluid to flow out of the cartilage matrix more easily and rapidly, resulting in a lower-stress relaxation time [28, 29]. Moreover, polymer dynamics theory predicts that a decrease in the stress-relaxation time constant and a loss in modulus (stiffness) occurs due to the decrease in average molecular length of the polymer [30]. June et al. showed a decrease in relaxation time by cleaving the collagen triple-helix molecule at multiple locations and cleaving hyaluronan but not glycosaminoglycans [17, 31, 32]. Taking both effects into the account, we believe that the decrease in average molecular length of the polymer (i.e., degradation in collagen fibers) and the reduction in proteoglycan content are together responsible for a significant decrease in stress-relaxation time in the advanced stages of OA.

Table-2

#Sample	Stress-relaxation time constant (τ)	Instant ^s Young's modulus i.e., Y_{in} (at t=0 s)	Equilib ^m Young's modulus i.e., Y_{eq} (at t=1180 s)	Ratio (Y_{in}/Y_{eq})	Stretching exponent (β)	Histological grade (OARSI)
<u>ICRS grade-I</u>						
#Section-1	211.2	6.816000	6.816000	2.236544	0.6776	1
#Section-2	136.0	3.426691	3.426691	3.228219	0.6013	2
#Section-4	382.4	4.559351	4.559351	1.684617	0.9331	1
#Section-9	157.6	3.748800	3.748800	2.005482	0.5947	2
#Section-11	187.6	5.797113	5.797113	1.996035	0.631	1
#Section-13	185.9	3.360478	3.360478	2.039817	0.6165	2
#Section-14	110.0	4.172465	4.172465	2.493802	0.5537	1
#Section-16	132.5	3.910431	3.910431	2.713876	0.5578	1
<u>ICRS grade-II</u>						
#Section-3	116.4	3.997535	3.997535	2.920333	0.6004	2
#Section-6	172.3	5.506050	5.506050	2.475084	0.6501	2
#Section-7	151.3	4.317236	4.317236	2.681396	0.6163	1
#Section-18	64.82	4.065479	4.065479	2.297605	0.4867	2
#Section-19	172.0	3.928383	3.928383	2.129691	0.5743	2
#Section-20	106.1	3.736842	3.736842	2.126649	0.5062	2
#Section-21	145.3	3.421194	3.421194	2.116525	0.6046	2
#Section-24	161.3	3.685106	3.685106	1.842395	0.6004	1
<u>ICRS grade-III</u>						
#Section-5	64.28	1.497124	0.443423	3.376287	0.4393	3
#Section-8	43.52	2.203448	0.712712	3.091636	0.4363	3
#Section-10	55.04	4.301901	1.327796	3.239881	0.4687	4
#Section-12	56.87	1.687635	0.586799	2.876001	0.4422	3
#Section-15	43.9	2.677714	0.997392	2.684714	0.4584	3
#Section-17	111.6	2.870444	1.288061	2.228499	0.5566	3
#Section-22	72.66	3.397942	1.231759	2.758608	0.4996	4
#Section-23	27.74	1.927954	0.496422	3.883696	0.4236	3

3.3. Stretching exponent parameter (β)

A relative comparison of the stretching exponent (β) between the three ICRS grades revealed a statistically significant ($p < 0.05$) decrease between grades I and III and between grades II and III but not between grades I and II (Figure 4b).

The parameter β represents the width of the of relaxation-time distribution. The numerical value of β lies between 0 and 1. A narrow distribution has a β -value close to 1, while wider distributions result in lower β values. Physically, β is associated with a specific type of polymer motion called reptation. Fyhrie et al. showed that the stress-relaxation response of cartilage follows the reptation dynamics of the polymers [33]. However, which biopolymer (chondroitin sulfate, proteoglycan, or hyaluronic acid polymer) play dominant roles in the reptation was not described. Following this study, Ruberti et al. determined that the reptation dynamics in cartilage is mainly due to the hyaluronic acid chains and not due to proteoglycan and chondroitin sulfate side chains that are attached to them [34]. These side chains are sufficiently stiff so that their retraction times are very short [30] and hence their contribution to reptation is not significant [34]. This indicates that there is a significant loss of hyaluronic acid accompanied by the loss of PG in advanced stage OA. In the ECM of cartilage, PG molecules are attached to the long backbone chain of the hyaluronic acid. Therefore, significant loss in hyaluronic acid polymer might be a reason for the loss of PG in advanced OA.

4. Conclusions

This work focused on characterization of the different stages (i.e., ICRS grades-I, II, and III) of human osteoarthritic cartilage. Applying polymer dynamics theory, a reduction in stress-relaxation time and stretch-exponent parameter were observed in advanced OA (i.e., ICRS grade-III). In addition, a loss in compressive Young's modulus and reduced mechanical viability were also observed in ICRS grade-III. The reduction in PG content could be the reason for the loss in compressive Young's modulus and faster stress relaxation in the ICRS grade-III osteoarthritic cartilage. The stretch-exponent parameter indicated a significant loss of hyaluronic acid accompanied by the loss of PG in ICRS grade-III. Furthermore, in numerical modeling of osteoarthritic articular cartilage, the experimental data of this work can be utilized as input parameters to minimize the error between model and experiments. The future work aims to reveal how the change in mechanical behavior plays a role in pathogenesis of early stage OA. More detailed information about cartilage biomechanics are essential and have practical importance for not only understanding cartilage mechanics but also for enhancing the knowledge of disease progression.

Acknowledgments: We are pleased to acknowledge Astrid Bjørkøy for her assistance in the development of mechanical indentation device in the laboratory. The funding to carry out this study was received from the Helse Midt-Norge (HMN), Regional Co-operation Body for Education, Research and Innovation (RHF) in Norway.

Author Contributions: "R.K. and M.B.L. conceived and designed the experiments; R.K. performed the experiments and analyzed the data; D.M.P. provided the academic resource. J.O.D. and C.D. contributed reagents/materials/analysis tools; V.I. contributed in the histological analysis. R.K., D.M.P., J.O.D., C.D and M.B.L wrote the paper."

Conflicts of Interest: The authors declare no conflicts of interest. The funding sponsors had no role in the design of the study; in the collection, analyses, or interpretation of data; in the writing of the manuscript, and in the decision to publish the results.

References

- Laasanen, M. S.; Toyras, J.; Korhonen, R. K.; Rieppo, J.; Saarakkala, S.; Nieminen, M. T.; Hirvonen, J.; Jurvelin, J. S., Biomechanical properties of knee articular cartilage. *Biorheology* **2003**, 40, (1-3), 133-40.

- 299 2. Hamerman, D., Clinical implications of osteoarthritis and ageing. *Annals of the rheumatic diseases* **1995**,
300 54, (2), 82-85.
- 301 3. Hunter, D. J.; Schofield, D.; Callander, E., The individual and socioeconomic impact of osteoarthritis.
302 *Nat Rev Rheumatol* **2014**, 10, (7), 437-441.
- 303 4. Kumar, R.; Grønhaug, K. M.; Davies, C. L.; Drogset, J. O.; Lilledahl, M. B., Nonlinear optical
304 microscopy of early stage (ICRS Grade-I) osteoarthritic human cartilage. *Biomedical optics express* **2015**,
305 6, (5), 1895-1903.
- 306 5. Kumar, R.; Grønhaug, K. M.; Afseth, N. K.; Isaksen, V.; de Lange Davies, C.; Drogset, J. O.; Lilledahl,
307 M. B., Optical investigation of osteoarthritic human cartilage (ICRS grade) by confocal Raman
308 spectroscopy: a pilot study. *Analytical and bioanalytical chemistry* **2015**, 407, (26), 8067-77.
- 309 6. Kumar, R.; Grønhaug, K. M.; Romijn, E. I.; Drogset, J. O.; Lilledahl, M. B. Analysis of human knee
310 osteoarthritic cartilage using polarization sensitive second harmonic generation microscopy, *Proc.*
311 *SPIE, Biophotonics: Photonic Solutions for Better Health Care IV* **2014**, 9129, 91292Z1-9.
- 312 7. Kleemann, R. U.; Krockner, D.; Cedraro, A.; Tuischer, J.; Duda, G. N., Altered cartilage mechanics and
313 histology in knee osteoarthritis: relation to clinical assessment (ICRS Grade). *Osteoarthritis and cartilage*
314 */ OARS, Osteoarthritis Research Society* **2005**, 13, (11), 958-63.
- 315 8. Toyra, J.; Lyyra-Laitinen, T.; Niinimäki, M.; Lindgren, R.; Nieminen, M. T.; Kiviranta, I.; Jurvelin, J. S.,
316 Estimation of the Young's modulus of articular cartilage using an arthroscopic indentation instrument
317 and ultrasonic measurement of tissue thickness. *Journal of biomechanics* **2001**, 34, (2), 251-6.
- 318 9. Wilson, W.; van Donkelaar, C. C.; van Rietbergen, R.; Huiskes, R., The role of computational models in
319 the search for the mechanical behavior and damage mechanisms of articular cartilage. *Medical*
320 *Engineering & Physics* **2005**, 27, (10), 810-826.
- 321 10. Richard, F.; Villars, M.; Thibaud, S., Viscoelastic modeling and quantitative experimental
322 characterization of normal and osteoarthritic human articular cartilage using indentation. *Journal of the*
323 *mechanical behavior of biomedical materials* **2013**, 24, 41-52.
- 324 11. Brown, C. P.; Houle, M. A.; Chen, M.; Price, A. J.; Légaré, F.; Gill, H. S., Damage initiation and
325 progression in the cartilage surface probed by nonlinear optical microscopy. *Journal of the mechanical*
326 *behavior of biomedical materials* **2012**, 5, (1), 62-70.
- 327 12. Cao, L.; Youn, I.; Guilak, F.; Setton, L. A., Compressive properties of mouse articular cartilage
328 determined in a novel micro-indentation test method and biphasic finite element model. *Journal of*
329 *biomechanical engineering* **2006**, 128, (5), 766-71.
- 330 13. Juras, V.; Bittsanky, M.; Majdisova, Z.; Szomolanyi, P.; Sulzbacher, I.; Gabler, S.; Stampfl, J.; Schuller,
331 G.; Trattng, S., In vitro determination of biomechanical properties of human articular cartilage in
332 osteoarthritis using multi-parametric MRI. *Journal of magnetic resonance (San Diego, Calif. : 1997)* **2009**,
333 197, (1), 40-7.
- 334 14. Athanasiou, K. A.; Rosenwasser, M. P.; Buckwalter, J. A.; Malinin, T. I.; Mow, V. C., Interspecies
335 comparisons of in situ intrinsic mechanical properties of distal femoral cartilage. *Journal of orthopaedic*
336 *research : official publication of the Orthopaedic Research Society* **1991**, 9, (3), 330-40.
- 337 15. Hayes, W. C.; Mockros, L. F., Viscoelastic properties of human articular cartilage. *Journal of applied*
338 *physiology* **1971**, 31, (4), 562-8.
- 339 16. Mats Brittberg et al. In *ICRS Cartilage Injury Evaluation Package*, 3rd ICRS Meeting in Göteborg,
340 Sweden., 2000; 2000.

- 341 17. June, R. K.; Fyhrie, D. P., Enzymatic digestion of articular cartilage results in viscoelasticity changes
342 that are consistent with polymer dynamics mechanisms. *BioMedical Engineering OnLine* **2009**, *8*, 32-32.
- 343 18. June, R. K.; Fyhrie, D. P., A comparison of cartilage stress-relaxation models in unconfined
344 compression: QLV and stretched exponential in combination with fluid flow. *Computer Methods in*
345 *Biomechanics and Biomedical Engineering* **2013**, *16*, (5), 565-576.
- 346 19. Lee, K. C.; Siegel, J.; Webb, S. E.; Leveque-Fort, S.; Cole, M. J.; Jones, R.; Dowling, K.; Lever, M. J.;
347 French, P. M., Application of the stretched exponential function to fluorescence lifetime imaging.
348 *Biophysical journal* **2001**, *81*, (3), 1265-74.
- 349 20. Szymanski, C. Investigation of photophysical and photochemical processes in conjugated polymer
350 nanoparticles by single particle and ensemble spectroscopy. Clemson University, 2009.
- 351 21. Pritzker, K. P.; Gay, S.; Jimenez, S. A.; Ostergaard, K.; Pelletier, J. P.; Revell, P. A.; Salter, D.; van den
352 Berg, W. B., Osteoarthritis cartilage histopathology: grading and staging. *Osteoarthritis and cartilage /*
353 *OARS, Osteoarthritis Research Society* **2006**, *14*, (1), 13-29.
- 354 22. Rajesh Kumar, K. M. G., Nils K. Afseth, Vidar Isaksen, Catharina de Lange Davies, Jon O. Drogset and
355 Magnus B. Lilledahl, Optical investigation of osteoarthritic human cartilage (ICRS Grade) by confocal
356 Raman spectroscopy: A pilot study. *Analytical and Bioanalytical Chemistry (Springer)* **2015**, In review.
- 357 23. Kempson, G. E.; Muir, H.; Swanson, S. A.; Freeman, M. A., Correlations between stiffness and the
358 chemical constituents of cartilage on the human femoral head. *Biochimica et biophysica acta* **1970**, *215*, (1),
359 70-7.
- 360 24. Akizuki, S. A.; Mow, V. C.; Lai, W. M.; Pita, J.; Howell, D. S., Topographical variations of the biphasic
361 indentation properties of human tibial plateau cartilage. *Trans. Orthop. Res. Soc.* **1986**, 11:406.
- 362 25. Mansour, J. M., Biomechanics of cartilage. In *Kinesiology: The Mechanics and Pathomechanics of Human*
363 *Movement: Second Edition*, 2013; pp 69-83.
- 364 26. Brown, C. P.; Crawford, R. W.; Oloyede, A., An alternative mechanical parameter for assessing the
365 viability of articular cartilage. *Proceedings of the Institution of Mechanical Engineers. Part H, Journal of*
366 *engineering in medicine* **2009**, *223*, (1), 53-62.
- 367 27. Kos, P.; Varga, F.; Handl, M.; Kautzner, J.; Chudáček, V.; Držík, M.; Povýšil, C.; Trč, T.; Amler, E.;
368 Hanus, M., Correlation of dynamic impact testing, histopathology and visual macroscopic assessment
369 in human osteoarthritic cartilage. *International Orthopaedics (SICOT)* **2011**, *35*, (11), 1733-1739.
- 370 28. McDevitt, C. A.; Muir, H., Biochemical changes in the cartilage of the knee in experimental and natural
371 osteoarthritis in the dog. *The Journal of bone and joint surgery. British volume* **1976**, *58*, (1), 94-101.
- 372 29. Lane, J. M.; Chisena, E.; Black, J., Experimental knee instability: early mechanical property changes in
373 articular cartilage in a rabbit model. *Clinical orthopaedics and related research* **1979**, (140), 262-5.
- 374 30. Feldman, D., The theory of polymer dynamics, by M. Doi and S. F. Edwards, the Clarendon Press,
375 Oxford University Press, New York, 1986, 391 pp. Price: \$78.50. *Journal of Polymer Science Part C:*
376 *Polymer Letters* **1989**, *27*, (7), 239-240.
- 377 31. Van Wart, H. E.; Steinbrink, D. R., Complementary substrate specificities of class I and class II
378 collagenases from *Clostridium histolyticum*. *Biochemistry* **1985**, *24*, (23), 6520-6.
- 379 32. Ohya, T.; Kaneko, Y., Novel hyaluronidase from streptomyces. *Biochimica et biophysica acta* **1970**, *198*,
380 (3), 607-9.
- 381 33. Fyhrie, D. P.; Barone, J. R., Polymer dynamics as a mechanistic model for the flow-independent
382 viscoelasticity of cartilage. *Journal of biomechanical engineering* **2003**, *125*, (5), 578-84.

- 383 34. Ruberti, J. W.; Sokoloff, J. B., Theory of the short time mechanical relaxation in articular cartilage.
384 *Journal of biomechanical engineering* **2011**, 133, (10), 104504.

385