

Article

Valorization of Municipal Waterworks Sludge to Produce Ceramic Floor Tiles

Lara P. Rodrigues¹ and José Nilson F. Holanda^{1,*}

¹ Group of Ceramic Materials, Laboratory of Advanced Materials, Northern Fluminense State University, 28013-602 Campos dos Goytacazes-RJ, Brazil; larapessin@hotmail.com

* Correspondence: jose.holanda@pesquisador.cnpq.com.br; Tel.: +55-22-2739-7322

Abstract: In municipal waterworks large amounts of waste in the form of sludge have to be discarded. This investigation focuses on the processing of ceramic floor tiles incorporated with a municipal waterworks sludge. Four floor tile formulations containing up to 10 wt. % of the municipal waterworks sludge in replacement of kaolin were prepared. The floor tile processing route consisted of dry powder granulation, uniaxial pressing, and firing between 1190 and 1250 °C using a fast-firing cycle (<60 min). The densification behavior and technological properties of the floor tile pieces as function of the sludge addition and firing temperature were determined. The development of the microstructure was followed by XRD and SEM/EDS. The results show that the replacement of kaolin with municipal waterworks sludge, in the range up to 10 wt. %, allows the production of ceramic floor tiles (group BIb and group BIIa, ISO 13006 Standard) at lower firing temperatures. These results suggest a new possibility for valorization of municipal waterworks sludge with many economical and environmental benefits.

Keywords: municipal waterworks sludge; waste; recycling; valorization; floor tiles

1. Introduction

The municipal waterworks are units based on the physical and chemical treatments of raw fresh-water mainly for human consumption, which produces huge amounts of wastes in form of sludge worldwide [1,2]. Waterworks sludge varies widely in terms of physical and chemical characteristics as a function of the nature of the raw fresh-water and chemical compounds applied during treatments. At present, the non-treated municipal waterworks sludges are disposed in places unsuitable around the world, in many cases near watercourses and landfill sites, with negative impacts to the fauna, flora and human health. Thus, an important issue for the municipal waterworks and ecologists is to find new solutions for the final disposal of this abundant waste material in an economical and ecological way.

Chemically, the municipal waterworks sludges are rich in SiO₂, Al₂O₃, and Fe₂O₃, and also minor amounts of K, Na, Mg, and Ca oxides [3]. The waterworks sludges are very similar in terms of chemical composition to common clays used to manufacture of clay-based products. For this reason, the municipal waterworks sludges attract high interest in view to prepare clay-based products contributing at the same time to reduce environmental impacts. In fact, previous studies [4-11] have shown promising results for the reuse of municipal waterworks sludges in the production of clay bricks, roofing tiles, and soil-cement bricks. However, the reuse of municipal waterworks sludge in the processing of ceramic floor tiles has not yet been investigated. Floor tiles are ceramic materials widely used in the civil construction sector. They are vitrified materials with heterogeneous microstructure and good technical properties in terms of mechanical strength, water absorption, and durability. The floor tile formulations are composed essentially of a mixture of non-renewable natural raw materials such as clays, feldspars, and quartz [12]. In particular, the floor tile formulations contain large amounts (30–40 %) of natural clays (plastic clay and kaolin), which provide favorable processing conditions, green strength, and rigidity of fired product. Thus, the

municipal waterworks sludge could be a suitable replacement for natural clays in ceramic floor tile formulations.

The purpose of this study is to investigate the possibility of valorization of a municipal waterworks sludge, a renewable raw material, into ceramic floor tile formulation for use in civil construction.

2. Materials and Methods

Four floor tile formulations using triaxial mixtures of kaolin + municipal waterworks sludge, albite, and quartz were prepared. A representative municipal waterworks sludge (MWS) sample was collected from a municipal waterworks located in south-eastern Brazil (Campos dos Goytacazes-RJ). After drying, the MWS sample takes the form of a clay-like powder. Table 1 gives the chemical composition of the MWS sample. From the mineralogical point of view, the MWS sample was mainly composed of kaolinite, with quartz, gibbsite, and goethite as accessory minerals. The standard formulation of floor tile used as a reference consisted of 40.0 wt.% kaolin, 47.5 wt.% albite, and 12.5 wt.% quartz. In this work, kaolin was partially replaced with increasing amounts of municipal waterworks sludge. Each formulation is labeled as follows: ML0 contains 0-wt.% MWS; ML1 contains 2.5 wt.% MWS; ML2 contains 5.0 wt.% MWS; and ML3 contains 10.0 wt.% MWS.

The raw materials were dry-ground separately using a laboratory grinder, and then passed through a 325-mesh (< 45 µm ASTM) sieve. The floor tile formulations were mixed, homogenized, and granulated by the dry process [13].

Table 1. Chemical composition of the sludge sample (wt.%).

SiO ₂	Al ₂ O ₃	Fe ₂ O ₃	K ₂ O	Na ₂ O	MgO	CaO	TiO ₂	MnO	*LoI
30.11	31.73	10.39	1.29	-	-	0.35	1.06	0.14	24.93

*LoI - loss on ignition

The chemical compositions of the floor tile formulations were determined by using an energy-dispersive X-ray spectrometer (Shimadzu, EDX 700). X-ray diffraction analysis was done in a conventional powder diffractometer (Shimadzu, XRD 7000) by using monochromatic Cu-Kα radiation (λ = 0.154056 nm) at a scanning speed of 1.5 (2θ)/min. Mineral phases were identified by using the JCPDS-ICDD data files. The plastic properties were determined by the Atterberg method according to NBR 6459 and NBR 7180 standardized procedures. The Hausner ratio was obtained as the ratio of the tap density to apparent density of the granulated tile powders. The screen residue (> 63 µm) has been also determined.

The floor tile powders were moistened with 7 wt.% water, pressed into test bars (11.50 × 2.54 cm²) under a load of 50 MPa, and then dried at 110 °C. The green tile pieces were fast-fired between 1190 and 1250 °C in air using a laboratory kiln for a fast-firing cycle of less than 60 min, including cooling. The fast-firing cycle used in this investigation was selected to simulate an actual firing process used in the ceramic tile industry.

The following as-fired technological properties of the floor tile pieces have been determined in accordance with standardized procedures: linear shrinkage, water absorption, apparent density, and flexural strength. Linear shrinkage values upon drying and firing were evaluated from variation of the main dimension (length) of the pieces. The water absorption values were determined from the weight differences between the as-fired and water-saturated samples (immersed in boiling water for 2 h). The apparent density was determined using the Arquimedes principle. The flexural strength (average of five specimens for each value) was determined by a three-point bending test using an Instron model 1125 universal mechanical testing machine at a loading rate of 0.5 mm/min. The flexural strength (FS) was calculated by $FS = 3PL/2ab^2$ in which P is the load of rupture, L is the distance between supports, a is the specimen width, and b its thickness.

The microstructural characterization of the gold-coated fracture surfaces of fired specimens was examined via secondary electron images using a scanning electron microscopy (Shimadzu, SSX-550) operating at 15 kV. The mineral phases after fast-firing cycle were identified by X-ray diffraction analysis.

3. Results and Discussion

The chemical compositions of the floor tile formulations are given in Table 2. In terms of chemical composition the SiO₂, Al₂O₃, and Na₂O were the most abundant components (90.08 - 92.25 wt.%). These oxides are responsible for the main chemical and physical activities of the floor tile formulations during the fast-firing cycle. The effect of the incorporation of the MWS into tile formulations was to increase both the amount of iron oxide (Fe₂O₃) and loss on ignition. As shown in Table 1, the MWS sample contains appreciable amount of Fe₂O₃ (10.39 wt.%) and loss on ignition (24.93 wt.%). This can play an important role in the firing behavior and floor tile quality.

Table 2. Chemical compositions of the floor tile formulations (wt.%).

Oxides	ML0	ML1	ML2	ML3
SiO ₂	64.98	64.48	64.01	63.07
Al ₂ O ₃	22.47	22.42	22.35	22.27
Fe ₂ O ₃	0.16	0.41	0.67	1.17
TiO ₂	0.02	0.04	0.07	0.12
Na ₂ O	4.80	4.78	4.76	4.74
K ₂ O	1.51	1.49	1.48	1.44
CaO	0.20	0.21	0.21	0.21
MgO	0.03	0.07	0.07	0.06
MnO	0.04	0.04	0.04	0.05
*LoI	5.79	6.06	6.34	6.82

*LoI - loss on ignition

Table 3. Physical parameters of the floor tile formulations.

Formulation	UPL [%]	LPL [%]	PI [%]	SR [%]	Hr
ML0	31.8	20.5	11.3	3.1	1.29
ML1	32.8	20.5	12.3	0.7	1.57
ML2	34.4	21.5	12.9	1.4	1.42
ML3	35.3	22.8	12.5	1.5	1.57

UPL-upper plastic limit; LPL-lower plastic limit; PI-plastic index; SR-screening residue; Hr-Hausner ratio

Table 3 gives important physical parameters of the floor tile formulations. It was verified that the IP value (IP = UPL – LPL) tends to lightly increase (11.3 to 12.9 %) with the partial replacement of kaolin with MWS. According to these results, all tile formulations presented plastic properties adequate for industrial processing of floor tiles [14]. It can also be seen in Table 3 that that the screening residue tends to decrease (higher degree of grinding) with the addition of MWS. Despite this, all floor tile powders exhibited low value of screening residue [15], which was in line with the good level of comminution of the raw materials. This tends to favor the reactivity of the fine particles during the fast-firing cycle, resulting in higher densification of the floor tile pieces. The tile formulations had Hausner ratio values from 1.29 to 1.57. The effect of the incorporation of MWS was

to increase the Hausner ratio, resulting in reduced flowability of the floor tile powders. This effect limits the addition of high amounts of MWS in replacement of kaolin in floor tile formulations.

The XRD patterns of the floor tile formulations are presented in Fig. 1. The crystalline phases found in ML0 formulation (MWS-free formulation) were kaolinite ($\text{Al}_2\text{O}_3 \cdot 2\text{SiO}_2 \cdot 2\text{H}_2\text{O}$), albite ($\text{NaAlSi}_3\text{O}_8$), quartz (SiO_2), and micaceous mineral. For the MWS containing formulations (ML2 and ML3 formulations), diffraction peaks of gibbsite and goethite were also detected. This indicates that the replacement of kaolin with MWS into tile formulation modifies its mineralogical composition. In addition, the crystalline phases identified via XRD are in agreement with the results of chemical composition (Table 2).

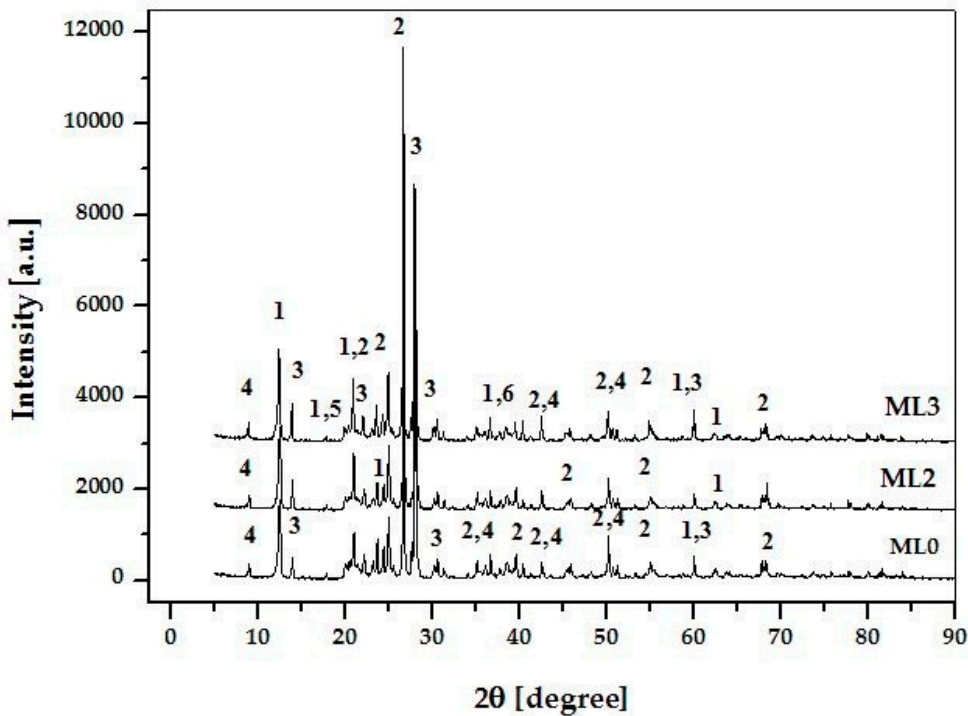


Figure 1. X-ray diffraction patterns of the floor tile formulations (1 – kaolinite; 2 – quartz; 3 – albite; 4 – mica; 5 – gibbsite; 6 – goethite).

Fig. 2 shows the typical XRD patterns of the floor tile pieces for the ML3 formulation fired between 1190 and 1250 °C. For all firing temperatures, the main identified crystalline phases were mullite ($3\text{Al}_2\text{O}_3 \cdot 2\text{SiO}_2$) and quartz. This result is in agreement with the $\text{Na}_2\text{O}-\text{Al}_2\text{O}_3-\text{SiO}_2$ phase diagram [16]. Mullite found in the fired specimens results from the decomposition of kaolinite, whereas the residual quartz is related to the starting raw materials. Note that albite has been detected in small amount as a remaining mineral unreacted during the fast-firing cycle (< 60 min). In addition, there is evidence of the presence of hematite as a residual iron mineral of the MWS sample. Thus, the partial replacement of kaolin with MWS influenced the phase evolution of the floor tile formulations during the employed fast-firing cycle.

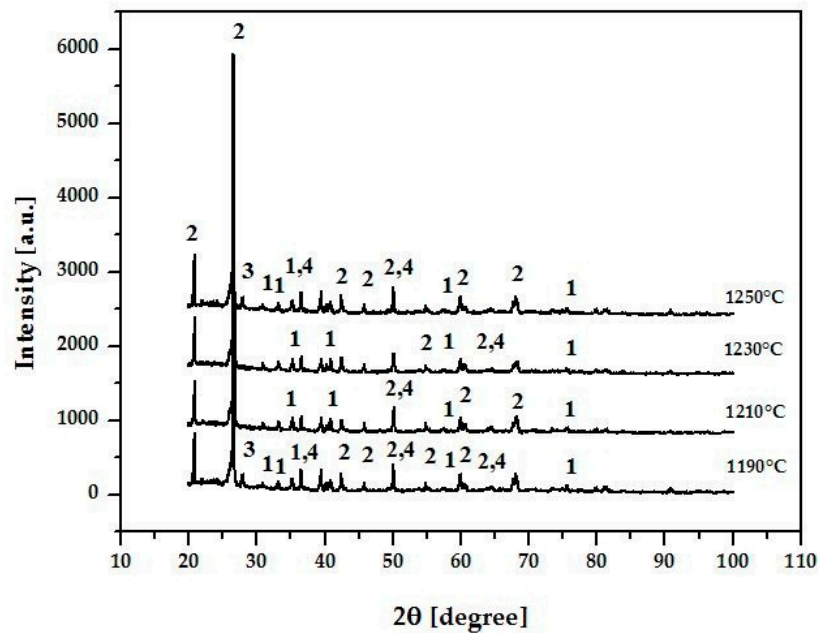


Figure 2. X-ray diffraction patterns of the ML3 formulation fired at various temperatures (1 – mullite; 2 – quartz; 3 – albite; 4 – hematite).

Fig. 3 shows the fractured surfaces of the sludge bearing floor tile pieces (ML3 formulation) fired between 1190 and 1250 °C. SEM micrographs show the typical sequence of enhanced densification as firing temperature increases.

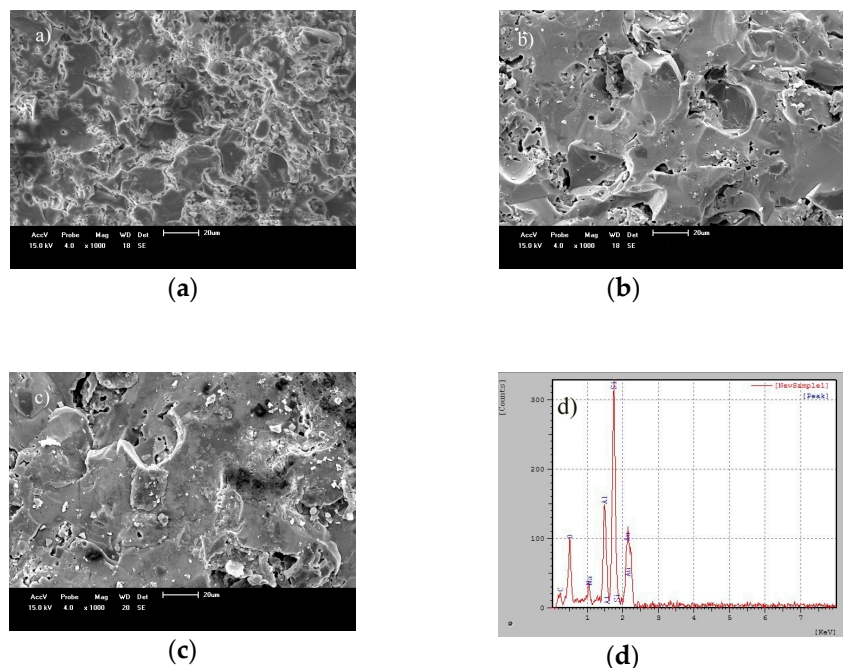


Figure 3. SEM micrographs of the fracture surfaces of the ML3 formulation fired at various temperatures: a) 1190 °C; b) 1230 °C; c) 1250 °C; and d) SEM/EDS spectrum at 1250 °C.

At 1190 °C (Fig. 3a), the microstructure revealed a rough fracture surface with presence of substantial open porosity connected with dense regions (glassy phase). At 1230 °C (Fig. 3b) and 1250 °C (Fig. 3c), however, the open porosity was substantially reduced, an indication that the development of the glassy phase during the fast-firing cycle has continued. At higher firing temperatures, transgranular fractures can be also observed. A line spectrum for the floor tile piece fired at 1250 °C using SEM/EDS is shown in Fig. 3d, where Si, Al, and Na were detected. These results are consistent with the chemical composition data (Table 2) and XRD patterns (Fig. 2).

The densification behavior of the floor tile pieces during the fast-firing cycle was monitored through the gresification diagram, apparent density, and mechanical strength. The gresification diagrams of the floor tile pieces are shown in Fig. 4. This diagram allows evaluating the efficiency of the sintering process during the fast-firing cycle. The densification behavior of the tile pieces was influenced by both firing temperature and added MWS amount. For all formulations, linear shrinkage increases and water absorption (open porosity) decreases with rising firing temperature (Fig. 4). This behavior can be attributed to a dominant viscous flow sintering mechanism during the firing process that closes the open porosity, resulting in higher densification [17].

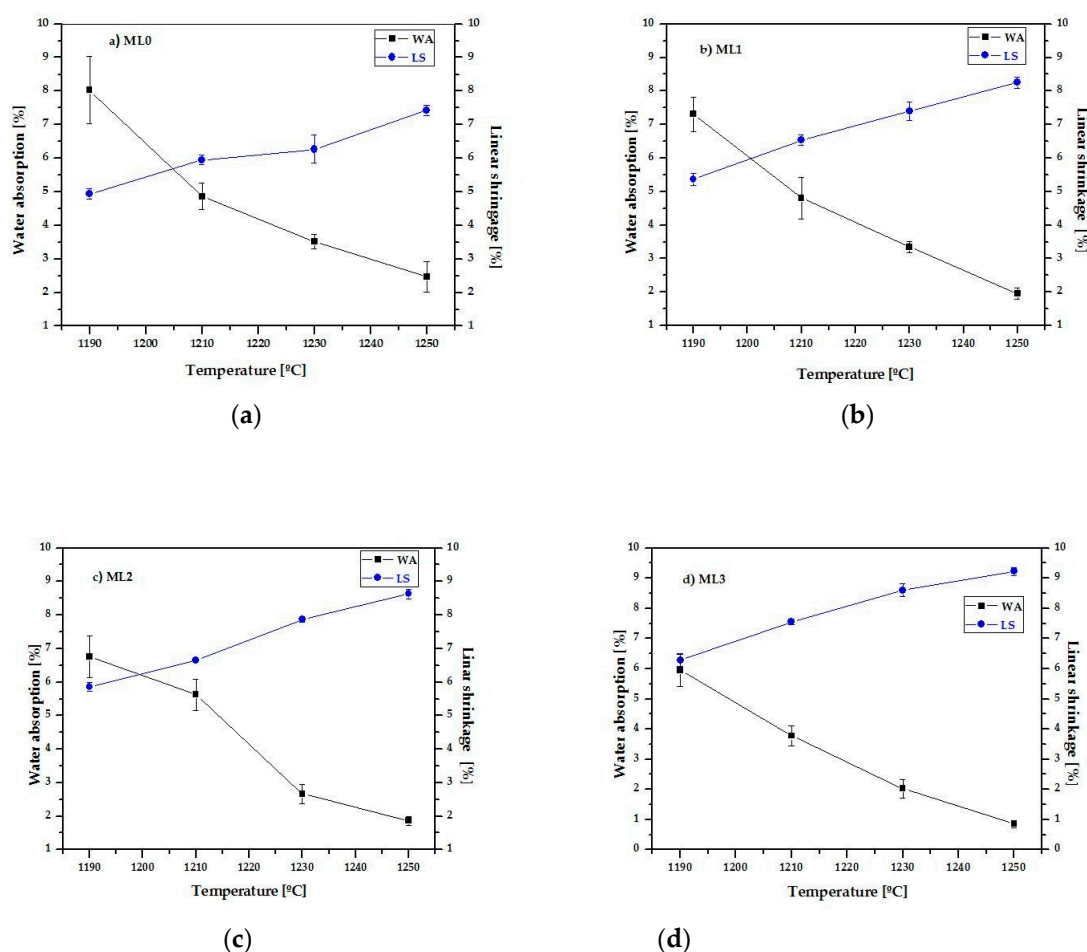


Figure 4. Gresification diagrams of the floor tile formulations: a) ML0; b) ML1; c) ML2; and d) ML3.

Linear shrinkage values between 4.94-9.23 % were obtained for the floor tile pieces, indicative of good dimensional control. Note also that, at any firing temperature, the MWS-added tile pieces presented higher linear shrinkage and lower water absorption than those of the MWS-free pieces (ML0 formulation). This finding was mainly due to the presence of iron oxide (Fe_2O_3) in the MWS sample (Table 1), which acts as an auxiliary fluxing agent that lowers the viscosity of the liquid phase on firing [18,19].

The apparent density of the floor tile pieces is shown in Fig. 5. The results showed that the apparent density depends on both the added MWS amount and the firing temperature. Note that the MWS-added tile pieces had higher apparent density. This increase in apparent density is in line with the chemical and physical characteristics of the MWS sample, leading to accelerated densification of the floor tile pieces. As expected, the effect of the firing temperature was to improve the densification of the tile pieces due to vitrification, independently of the added MWS amount. These results are in accordance with the gresification diagrams (Fig. 4a-d).

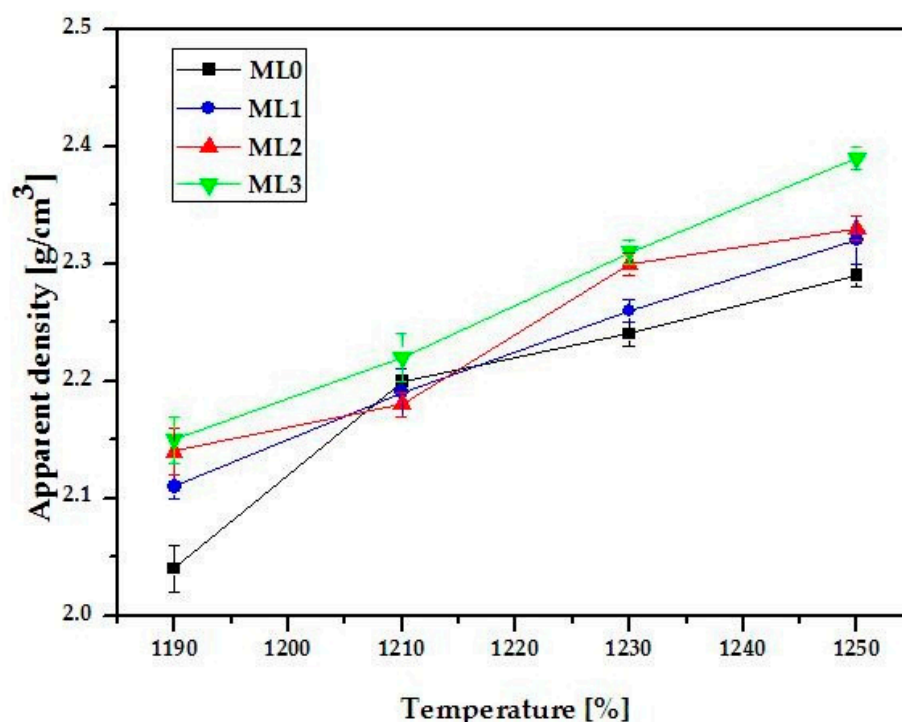


Figure 5. Apparent density as a function of MWS waste amount and firing temperature.

The flexural strength of the floor tile pieces is shown in Fig. 6. The mechanical behavior is quite correlated with all the other investigated technological properties and sintered microstructure. Such data indicate a tendency to higher flexural strength with higher MWS amount. This finding was expected, given that MWS addition leads to an increase of the densification degree during the fast-firing cycle.

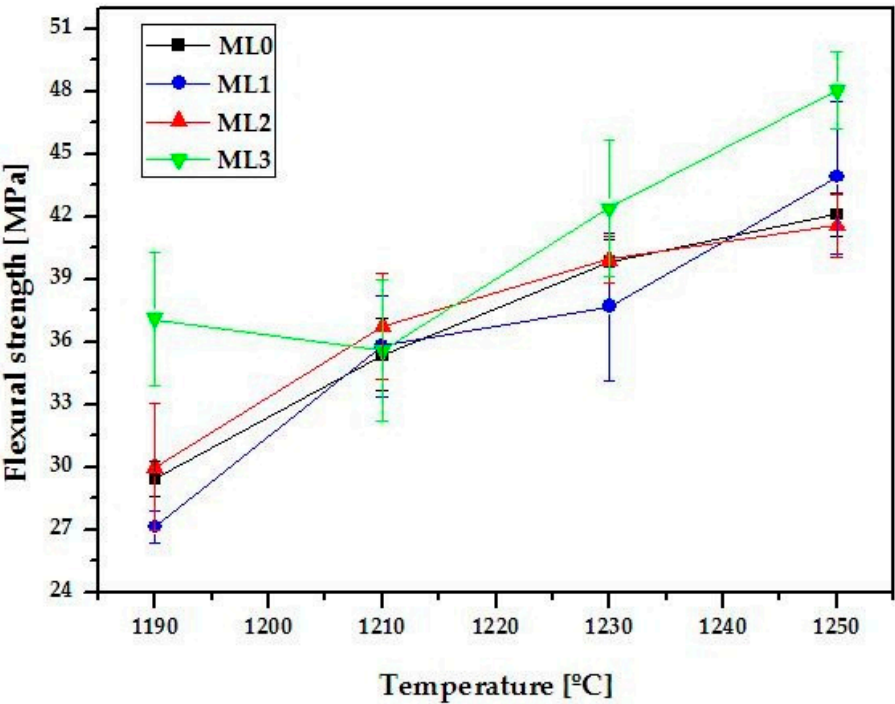


Figure 6. Flexural strength as a function of MWS waste amount and firing temperature.

Table 4. Classification of the ceramic floor tiles containing MWS waste according to the ISO standard 13006.

Formulation	1190 °C	1210 °C	1230 °C	1250 °C
ML0	BI Ib	BI Ia	BI Ia	BI b
ML1	BI Ib	BI Ia	BI Ia	BI b
ML2	BI Ib	BI Ia	BI b	BI b
ML3	BI Ia	BI Ia	BI b	BI b

From the standpoint of the ceramic industrial processing, it is very important to evaluate the feasibility of the use of MWS in the production of ceramic floor tiles. Water absorption (wa) and flexural strength (FS) are technological properties which, according to ISO 13006 standard [20], define floor tile product specification. In this study different ceramic floor tiles were obtained depending on the MWS amount and firing temperature (Table 4). It can be observed that the partial replacement of kaolin with MWS produced important changes in the floor tile quality. For example, low water absorption floor tile (ISO 13006 standard Group BIb – 0.5 % < wa ≤ 3.0 % and FS ≥ 30 MPa) could be obtained with ML2 and ML3 formulations fired at 1230 °C, while medium water absorption floor tile (ISO 13006 standard Group BIIa – 3.0 % < wa ≤ 6.0 % and FS ≥ 22 MPa) could be obtained with ML3 formulation fired at 1190 °C. These results can have significant economic and environmental benefits due to the possibility of using a shorter firing cycle (energy savings) and MWS as a renewable raw material (zero cost) in the processing of ceramic floor tiles.

4. Conclusions

The following conclusions may be drawn from the experimental results and their discussion.

- It was found that the municipal waterworks sludge used in this investigation is a renewable raw material that could partially replace natural kaolin in ceramic floor tile formulations.
- The incorporation of municipal waterworks sludge positively influenced the densification behavior and technological properties of the floor tile pieces during the fast-firing cycle. It was demonstrated that the replacement of kaolin with up to 10 wt.% of municipal waterworks sludge allowed important effects in the tile quality, such as the production of group BIb (low water absorption floor tile) and group BIIa (medium water absorption floor tile) of ISO 13006 standard at lower temperatures (energy savings).
- The processing of ceramic floor tiles could be an interesting technological solution for the valorization and final disposal of municipal waterworks sludges.

Acknowledgments: The authors acknowledge the CNPq (Process number 305928/2016-3) and FAPERJ (Process number E-26/203.013/2016) for the financial support, and the Águas do Paraíba by the supply of the municipal waterworks sludge.

Author Contributions: Lara P. Rodrigues conducted the research presented in this manuscript under the supervision of José Nilson F. Holanda.

Conflicts of Interest: The authors declare no conflict of interest.

References

- Bernardo, L.D.; Dantas, A.D.B. *Métodos e Técnicas de Tratamento de Água*, 2nd ed.; RIMA: São Carlos, Brazil, 2005.
- Davis, M.L.; Cornwell, D.A. *Introduction to Environmental Engineering*, 5th ed.; McGrawHill: New York, USA, 2013.
- Oliveira, E.M.S.; Sampaio, V.G.; Holanda, J.N.F. Evaluation of the suitability of municipal waterworks waste as raw material for red ceramic brick production. *Ind. Ceram.* **2006**, *26*, 23-28.
- Oliveira, E.M.S.; Sampaio, V.G.; Holanda, J.N.F. Effect of waterworks waste addition on densification and properties of clay ceramics. *Ind. Ceram.* **2007**, *27*, 1-7.
- Teixeira, S.R.; Santos, G.T.A.; Souza, A.E.; Alessio, P.; Souza, S.A.; Souza, N.R. The effect of incorporation of a Brazilian water treatment plant sludge on the properties of ceramic materials. *Appl. Clay Sci.* **2011**, *53*, 561-565. DOI: <https://doi.org/10.1016/j.clay.2011.05.004>.
- Torres, P.; Hernández, D.; Paredes, D. Productive use of sludge from a drinking water treatment plant for manufacturing ceramic bricks. *Rev. Ing. Constr.* **2012**, *27*, 145-154. DOI: <http://dx.doi.org/10.4067/S0718-50732012000300003>.
- Victoria, A.N. Characterisation and performance evaluation of waterworks sludge as brick material. *Int. J. Eng. Appl. Sci.* **2013**, *3*, 69-79.
- Rodrigues, L.P.; Holanda, J.N.F. Influence of the incorporation of water treatment plant (WTP) sludge on the technological properties of soil-cement bricks. *Cerâmica* **2013**, *59*, 551-556. DOI: <http://dx.doi.org/10.1590/S0366-69132013000400010>.
- Fungaro, D.A.; Silva, M.V. Utilization of water treatment plant sludge and coal fly ash in brick manufacturing. *Am. J. Environ. Protec.* **2014**, *2*, 83-88. DOI: 10.12691/env-2-5-2.
- Silva, E.M.; Morita, D.M.; Lima, A.C.N.; Teixeira, L.G. Manufacturing ceramic bricks with polyaluminum chloride (PAC) sludge from a water treatment plant. *Wat. Sci. Tech.* **2015**, *71*, 1638-1645. DOI: 10.2166/wst.2015.132.
- Wolff, E.; Schwabe, W.K.; Conceição, S. V. Utilization of water treatment plant sludge in structural ceramics. *J. Clean. Prod.* **2015**, *96*, 282-289. DOI: <https://doi.org/10.1016/j.jclepro.2014.06.018>.
- Barba, A.; Beltrán, V.; Felú, C.; García, J.; Ginés, F.; Sánchez, E.; Sanz, V. *Materias primas para la fabricación de soportes de baldosas cerámicas*, 2nd ed.; Instituto de Tecnología Cerámica: Castellón, Spain, 2002.

13. Sampaio, V.G.; Pinheiro, B.C.A.; Holanda, J.N.F. Dry granulation of a ceramic paste for porcelain stoneware tile. *Cerâmica* **2007**, *53*, 295-299. DOI: <http://dx.doi.org/10.1590/S0366-69132007000300013>.
14. Sanchez, E.; García, J.; Ginés, F.; Negre, F. Aspectos a serem melhorados nas características e homogeneidade de argilas vermelhas empregadas na fabricação de placas cerâmicas. *Cerâmica Ind.* **1996**, *1*, 13-22.
15. Oliveira, A.P.N. Tecnologia de fabricação de revestimentos cerâmicos. *Cerâmica Ind.* **2000**, *5*, 37-47.
16. Osburn, E.F. *Phase equilibrium diagrams of oxide systems*, American Ceramic Society: New York, USA, 1960.
17. Reed, J.S. *Principles of ceramic processing*, 2nd ed.; Wiley-Interscience: New York, USA, 1995.
18. Segadães, A.M. Use of phase diagrams to guide ceramic production from wastes. *Adv. Appl. Ceram.* **2006**, *105*, 46-54. DOI: <https://doi.org/10.1179/174329006X82927>.
19. Bou, E.; Quereda, M.F.; Lever, D.; Boccaccini, A.R.; Cheeseman, C.R. Production of pulverized fuel ash tiles using conventional ceramic production processes. *Adv. Appl. Ceram.* **2009**, *108*, 44-49. DOI: <https://doi.org/10.1179/174367509X345006>.
20. ISO 13006. *Ceramic tiles: definitions, classifications, characteristics and marking*; International Organization for Standardization: Switzerland, 2012.