

Supporting Information

Preparation of hierarchically porous graphitic carbon spheres and their applications in supercapacitors and dye adsorption

Saisai Li¹, Faliang Li¹, Junkai Wang¹, Liang Tian¹, Haijun Zhang^{1*}, Shaowei Zhang^{2*}

1 The State Key Laboratory of Refractories and Metallurgy, Wuhan University of Science and Technology, Wuhan 430081, China

2 College of Engineering, Mathematics and Physical Sciences, University of Exeter, Exeter EX4 4QF, UK

*Corresponding authors, Prof. Dr. Haijun Zhang, E-mail: zhanghaijun@wust.edu.cn, TEL: +86-27-68862829, FAX: +86-27-68862829;

Prof. Dr. Shaowei Zhang, E-mail: s.zhang@exeter.ac.uk.

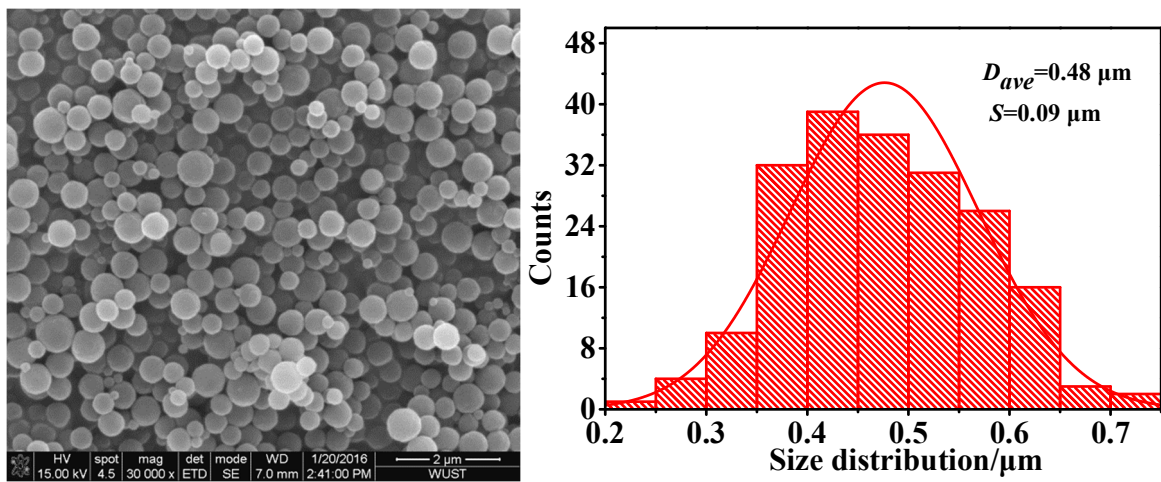


Fig. S1 SEM image and particle size distribution of carbon spheres prepared by hydrothermal carbonization at 180 °C for 12 h.

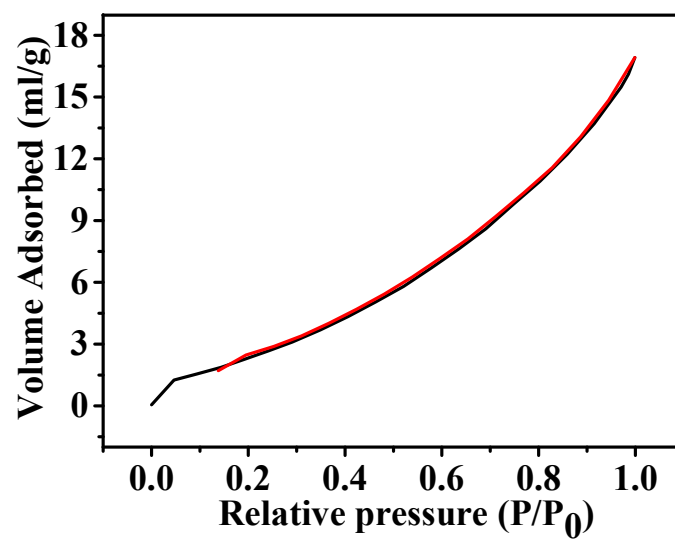


Fig. S2 Nitrogen adsorption/desorption isotherms of the pre-synthesized carbon spheres.

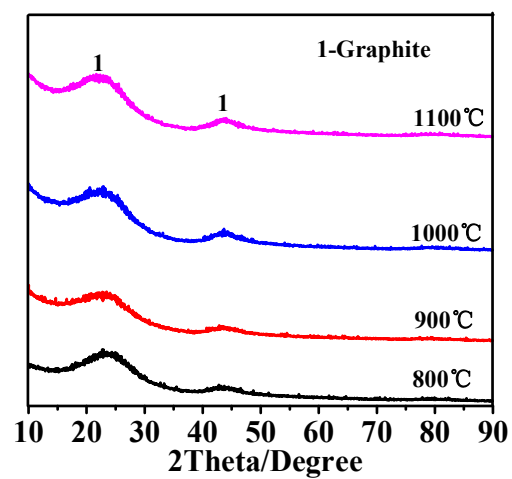


Fig. S3 XRD patterns of HGCS resultant from 3 h firing of pre-synthesized carbon spheres at different temperatures without using Fe catalyst (ICDD: 01-075-1621 (Graphite)).

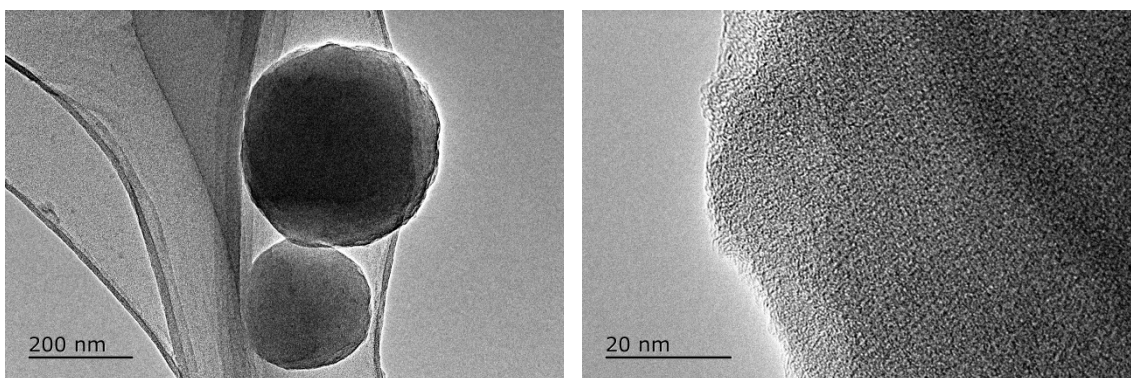


Fig. S4 TEM images of carbon spheres prepared by hydrothermal carbonization at 180 °C for 12 h.

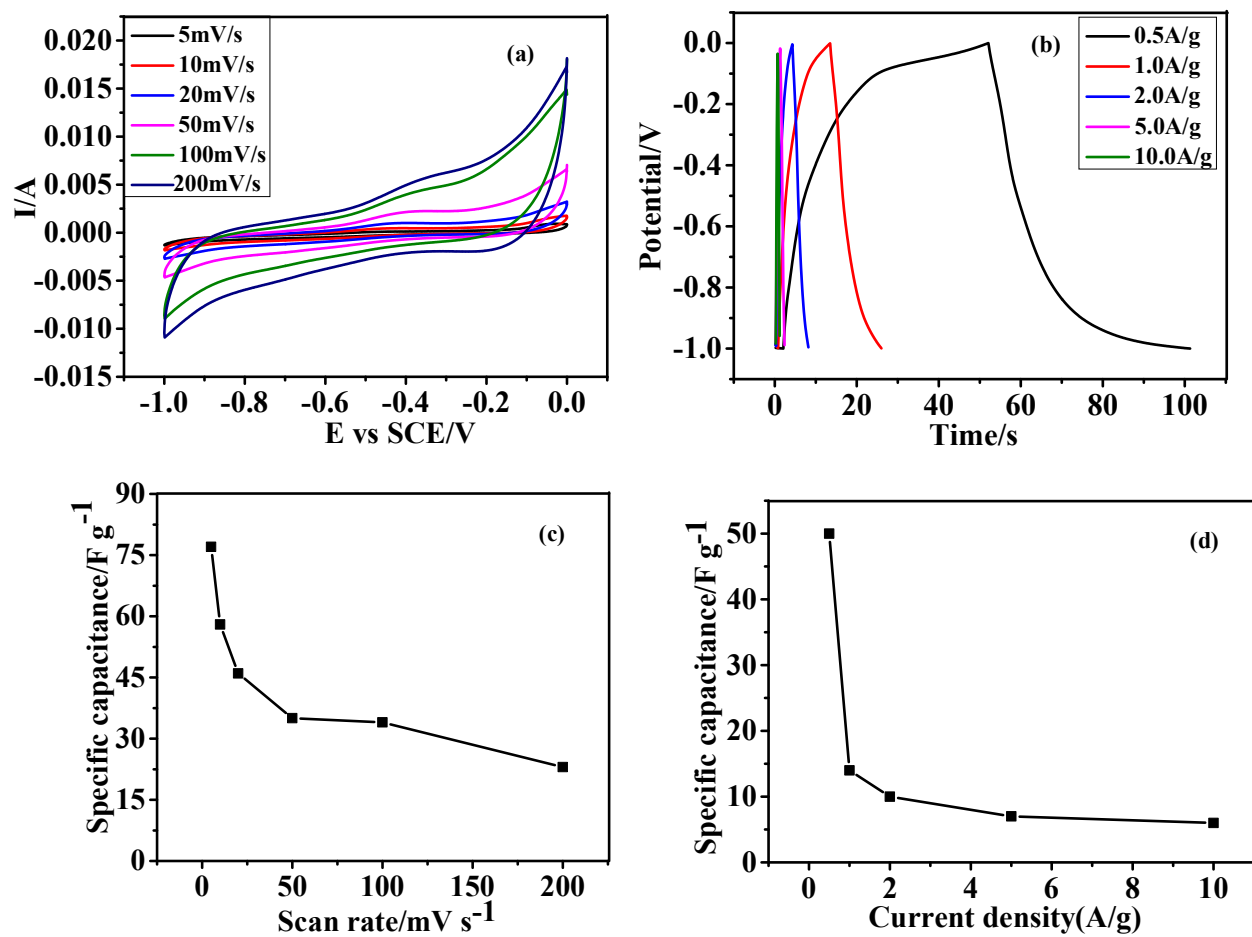


Fig. S5 CV curves (a), galvanostatic charge/discharge curves (b), specific capacitance versus scan rate (c) and specific capacitance versus current density (d), in the case of pre-synthesized carbon spheres.

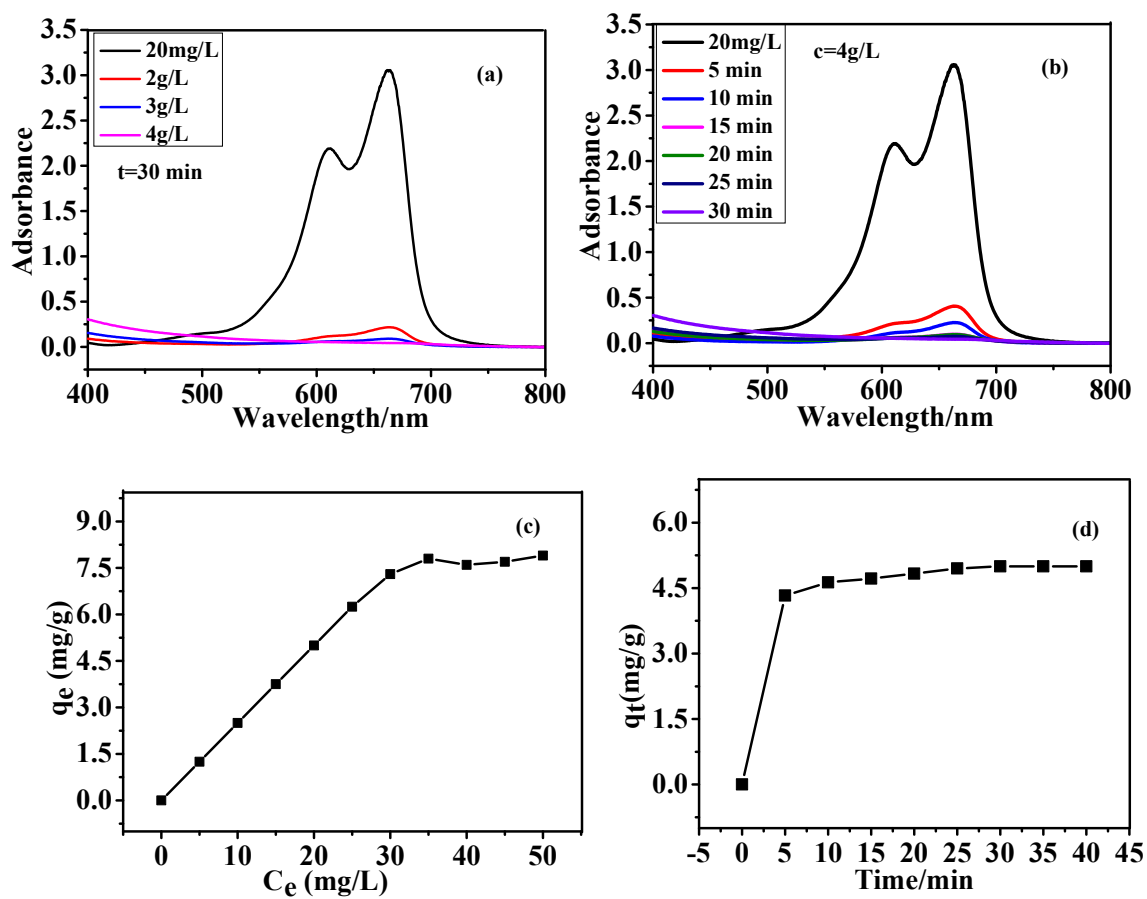


Fig. S6 UV curves corresponding to concentration (a) and time (b), adsorption isotherms (c), and adsorption kinetics (d), in the case of pre-synthesized carbon spheres.

Table S1 Comparison of graphitic carbon materials investigated to date

Samples	Carbon precursor	Preparation method	Specific surface area/m ² /g	Specific capacitance F/g	Refs
Mesoporous FeNi/graphitic carbon	Natural soybean oil	Template method	360~430	-	[1]
Nanoporous graphitic carbon	Iron phthalocyanine	Template method	960~1200	-	[2]
Porous graphitic carbon monoliths	Phenolic resin	Double template	725	-	[3]
Nanoporous graphitic carbon	Sucrose	Soft-template method	329	120 (0.2 A/g)	[4]
Mesoporous carbon spheres	Ethylene	Template method	666.8	59 (0.2 A/g)	[5]
HGCS	Glucose	Catalytic carbonization	564	140 (0.2 A/g)	This work

Table S2 Comparison of porous amorphous carbon materials reported to date

Samples	S_{BET} (m ² /g)	C (1A/g) (F/g)	$C_{\text{S}}=C/S_{\text{BET}}$ (F/m ²)	Refs
Hierarchical porous carbon nanospheres	1227	353	0.28	[6]
Activated hollow porous carbon spheres	1290	303.9	0.235	[7]
Nitrogen enriched carbon	1003	300	0.3	[8]
Hierarchically porous carbon spheres	1974	300	0.15	[9]
Hierarchical porous carbon	1513	300	0.198	[10]
Micro-meso- porous carbon spheres	2502	230	0.09	[11]

Hierarchical				
porous carbon	1939	165	0.085	[12]
spheres				
Activated carbon	1672	275	0.16	[13]
Nitro-doped				
ordered				
mesoporous	1741	220	0.126	[14]
carbons				
Hierarchically				
graphitic carbon	564	113	0.2	This work
spheres				

References

- [1] Y. Wang, M. Yao, Y. Chen, Y. Zuo, X. Zhang, L. Cui, General synthesis of magnetic mesoporous FeNi/graphitic carbon nanocomposites and their application for dye adsorption, *J. Alloy. Compd.* 627 (2015) 7–12.
- [2] P. Srinivasu, A. Islam, S. P. Singh, L. Han, M. L. Kantam, S. K. Bhargava, Highly efficient nanoporous graphitic carbon with tunable textural properties for dye-sensitized solar cells, *J. Mater. Chem.* 22 (2012) 20866–20869.
- [3] Y. Liu, B. Lin, D. Li, X. Zhang, Y. Sun, H. Yang, Hierarchically porous graphitic carbon monoliths containing nickel nanoparticles as magnetically separable adsorbents for dyes, *J. Appl. Polym. Sci.* 132 (2015) 41322.
- [4] M. Xie, J. Yang, J. Liang, X. Guo, W. Ding, In situ hydrothermal deposition as an efficient catalyst supporting method towards low-temperature graphitization of amorphous carbon, *Carbon.* 77 (2014) 215–225.
- [5] K. Wilgosz, X. Chen, K. Kierzek, J. Machnikowski, R. J. Kalenczuk, E. Mijowska, Template method synthesis of mesoporous carbon spheres and its applications as supercapacitors, *Nanoscale Res. Lett.* 7 (2012) 1–5.
- [6] S. W. L. Ng, G. Yilmaz, L. O. Wei, G. W. Ho, One-step activation towards spontaneous etching of hollow and hierarchical porous carbon nanospheres for enhanced pollutant adsorption and energy storage, *Appl. Catal. B* 220 (2017) 533–541.
- [7] J. Liu, X. Wang, J. Gao, Y. Zhang, Q. Lu, M. Liu, Hollow porous carbon spheres with hierarchical nanoarchitecture for application of the high performance supercapacitors, *Electrochim. Acta.* 211 (2016) 183–192.
- [8] X. Yang, C. Li, R. Fu, Nitrogen-enriched carbon with extremely high mesoporosity and

tunable mesopore size for high-performance supercapacitors, *J. Power Sources*. 319 (2016) 66–72.

- [9] D. Zhang, J. Gao, Z. Li, S. He, J. Wang, Synthesis of hierarchically porous carbon spheres by an emulsification-crosslinking method and its application in supercapacitor, *RSC Adv.* 6 (2016) 54880–54888.
- [10] Y. Han, S. Liu, D. Li, X. Li, Three-dimensionally hierarchical porous carbon creating high-performance electrochemical capacitors, *Electrochim. Acta*. 138 (2014) 193–199.
- [11] Y. Fan, X. Yang, B. Zhu, P. F. Liu, H. T. Lu, Micro-mesoporous carbon spheres derived from carrageenan as electrode material for supercapacitors, *J. Power Sources*. 26 (2014) 584–590.
- [12] J. Pang, W. Zhang, H. Zhang, J. Zhang, H. Zhang, G. Cao, Sustainable nitrogen-containing hierarchical porous carbon spheres derived from sodium lignosulfonate for high-performance supercapacitors, *Carbon*. 132 (2018) 280–293.
- [13] L. Zhang, H. Gu, H. Sun, F. Cao, Y. Chen, G. Z. Chen, Molecular level one-step activation of agar to activated carbon for high performance supercapacitors, *Carbon*. 2018. doi.org/10.1016/j.carbon.2018.02.100
- [14] Q. Shi, R. Zhang, Y. Lv, Y. Deng, A. A. Elzatahrya, D. Zhao, Nitrogen-doped ordered mesoporous carbons based on cyanamide as the dopant for supercapacitor, *Carbon*. 84 (2015) 335–346.