

Article

A 3D printable thermal energy storage crystalline gel using mask-projection stereolithography

Yuchen Mao ^{1,2}, Takuya Miyazaki ³, Kohei Sakai ³, Jin Gong ^{1,3,*}, Meifang Zhu ^{2,*}, Hiroshi Ito ^{1,*}

¹ Department of Polymer Science and Engineering, Graduate School of Organic Materials Science, Yamagata University, 4-3-16 Jonan, Yonezawa, Yamagata 992-8510, Japan; maoyc91@gmail.com (Y.M.)

² State Key Laboratory for Modification of Chemical Fibers and Polymer Materials, College of Materials Science and Engineering, Donghua University, Shanghai 201620, China

³ Department of Mechanical Systems Engineering, Graduate School of Science and Engineering, Yamagata University, 4-3-16 Jonan, Yonezawa, Yamagata 992-8510, Japan

* Correspondence: jingong@yz.yamagata-u.ac.jp (J.G.); zmf@dhu.edu.cn (M.Z.); ihiroshi@yz.yamagata-u.ac.jp (H.I.); Tel: +81-238-26-3135 (J.G.); Tel: +86-21-67792865 (M. Z.); Tel: +81-238-26-3081 (H.I.)

Abstract: Most of the phase change materials (PCMs) have been limited to use as functional additions or sealed in containers, and extra auxiliary equipment or supporting matrix is needed. The emergence of 3D printing technique has dramatically advanced the developments of materials and simplified production processes. This study focuses on a novel strategy to model thermal energy storage crystalline gels with three-dimensional architecture directly from liquid resin without supporting materials through light-induced polymerization 3D printing technique. A mask-projection stereolithography printer was used to measure the 3D printing test, and the printable characters of crystalline thermal energy storage P(SA-DMAA) gels with different molar ratios were evaluated. For the P(SA-DMMA) gels with small fraction of SA, the 3D fabrication was realized with higher printing precision both on mili- and micro- meter scales. As a comparison of 3D printed samples, P(SA-DMAA) gels made by other two methods, post-UV curing treatment after 3D printing and UV curing using conventional mold, were prepared. The 3D printed P(SA-DMAA) gels shown high crystallinity. Post-UV curing treatment was beneficial to full curing of 3D printed gels, but did not lead to the further improvement of crystal structure to get higher crystallinity. The P(SA-DMAA) crystalline gel having the highest energy storage enthalpy that reached 69.6 J·g⁻¹ was developed. Its good thermoregulation property in the temperature range from 25 to 40 °C was proved. The P(SA-DMAA) gels are feasible for practical applications as one kind of 3D printing material with thermal energy storage and thermoregulation functionality.

Keywords: crystalline gel; 3D printing; mask-projection stereolithography; thermal energy storage; phase change material; thermoregulation

1. Introduction

Energy is the foundation of all creatures on the planet and essential for the development and evolution of mankind. The fast and worldwide development contributes to a huge demand of energy. Recovering waste heat and storage/release thermal energy are important for saving energy and reducing dependency on conventional fossil energy. Latent heat energy storage system can use residual heat and store energy in the character of highly efficient and environmentally friendly. Phase change materials (PCMs) are considered one of the most reliable latent heat storage and

thermoregulation materials by absorbing or releasing the enthalpy of phase changes in certain temperature ranges. Now PCMs have been successfully utilized in aerospace and aviation, building, textile, freshness keeping and environmental control [1-4]. Latent heat storage systems can be generally divided into two groups: compact and encapsulated [5]. In compact system, PCMs are enclosed within a large container with an embedded heat exchanger, integrated with heat transfer fluid. Encapsulation technology is the prominent for utilization of the PCMs [6]. Micro or nano encapsulation is the process by which individual particles or droplets of solids or liquid materials (the core) are surrounded or coated with a continuous film of polymeric materials (the shell) [7,8]. However, in all above, PCMs are used as functional additions or sealed in containers, and extra auxiliary equipment or supporting materials are needed. If PCMs can be modeled with three-dimensional architecture, and in-situ processed without supporting materials, it will open the possibility of PCMs for broader applications.

Since developed in 1980s, three-dimensional (3D) printing, also known as additive manufacturing (AM), has been presented in art, architecture, tissue engineering, biomedical devices and manufacturing, such as rapid pattern making and rapid tooling using printing technologies [9-12]. 3D printing technology provides a possible method to manufacture objects with complex and precise structures, and unique physical properties for archiving optimal performance [13,14]. By ingenious design, 3D printing subjects can improve initial properties and get more structure functions [15,16]. Fused decomposition modeling, selective laser sintering, stereolithography (SLA) and 3D plotting/ direct-writing/ bioprinting are the common 3D printing methods [16-19]. Among all, we are most interested in mask-projection SLA, which is an easy and quick 3D printing method using liquid ultraviolet (UV) curable photo-polymer and a UV laser to build solid objects by printing thin layers on one top of the other [11,20]. The advantages of SLA are the ability to create complex shapes with internal architectures, ease of removal of unpolymerized resin and extremely high feature resolution ($\sim 1.2 \mu\text{m}$).

In our group, much of the work revolves around crystalline gels. We have developed crystalline gels with high toughness, high flexibility, and functions as shape memory, humidity regulation, thermal expansion and thermal energy storage, etc [21-25]. These crystalline gels are synthesized by radical photo-polymerization that involves photo-reactive reagents having the property of curing from liquid to solid with light of a sufficient energy. Note that the mask-projection SLA uses the same principle of photo-polymerization as the synthesis of crystalline gels. Therefore, we are interested in the 3D printing of crystalline gels in order to make their three-dimensional objects directly from the reactive liquid resin.

We designed a bulk photo-polymerization reaction system and combined it with 3D printing technique to synthesize and fabricate the energy storage crystalline gels at the same time on a 3D printer. The energy storage crystalline P(SA-DMAA) gels were synthesized by using stearyl acrylate (SA) and N, N- dimethylacrylamide (DMAA) as monomers, N, N' -methylenebisacrylamide (MBAA) as crosslinking agent, and 2-isopropylthioxanthone (ITX) and ethyl 4-dimethylaminobenzoate (EDAB) as co-initiation system. The synthesis scheme of P(SA-DMAA) gel is shown in Figure 1. The structure of SA consists of a vinyl group and a long alkane chain with eighteen methylene units. The vinyl group has reactivity to form a polymer with the aid of photo initiators, while the long alkane chain promises the high crystallinity providing the thermal energy storage capacity [24]. The rapid curing time of acrylic monomers, which is normally within a range of seconds, promises the great potential of P(SA-DMAA) gel as a 3D printable material [26,27]. In this research, using a mask-projection stereolithography 3D printer, we discussed the 3D printing test, and evaluated the printable characters of thermal energy storage crystalline P(SA-DMAA) gels.

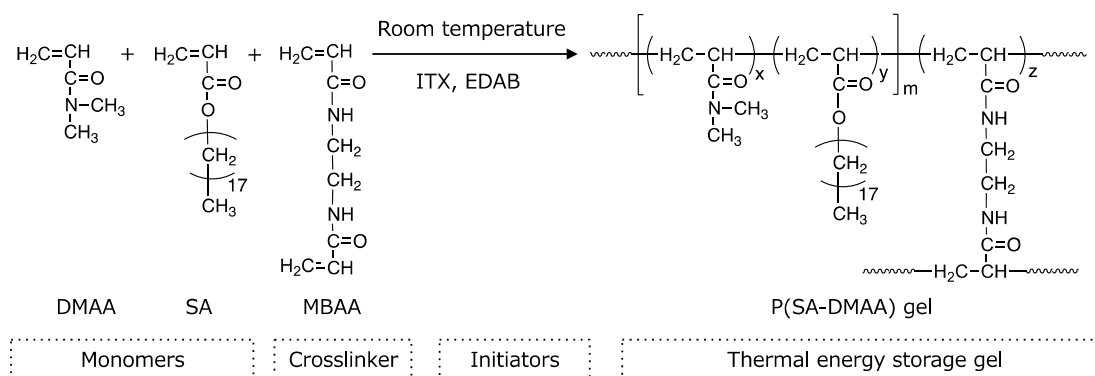


Figure 1. Synthesis scheme of the thermal energy storage crystalline P(SA-DMAA) gel.

2. Materials and Methods

2.1 Materials

SA and DMAA were purchased from Tokyo Chemical Industry Co., Ltd., Tokyo, Japan and used as monomers. Crosslinking agent of MBAA and photo initiators of ITX and EDAB were bought from Wako Pure Chemical Industries Ltd., Osaka, Japan. All the above reagents were used without further purification.

2.2 3D printing

A mask-projection SLA printer normally consists of a light source, a moveable platform for holding a printed object and a resin container. The light source also acts as a dynamic mask generator for obtaining diverse structures. A computer-controlled laser, a LED screen or a project can be used as light source. Typically, there are two different working principles of mask-projection SLA, bottom-up system and top-down system. Figure 2 shows their working principles and schematics. The difference between bottom-up system and top-down system is the moving direction of the moveable platform. In bottom-up system, the holding platform goes down to reach the next position. On the contrary, in top-down system, the holding platform moves upward to the next position. No matter in bottom-up system or top-down system, the layer is cured one after another. After one layer cured, the platform with the cured object moves to the next position, and then uncured liquid resin spreads over the previous layer. The following layer is now ready to be patterned. When object printing finished, the liquid unpolymerized resin is removed. To a 3D printer, these configurations, including the power of light source, exposure time and scanning speed, affect the layer thickness, accuracy of object and printing fidelity. The 3D printing speed can also be controlled by the chemical designs, monomer structures, formulation and the concentration of photo initiators [28-31]. Usually, post-curing in an UV oven is needed to convert unreacted groups, and strength of the structure.

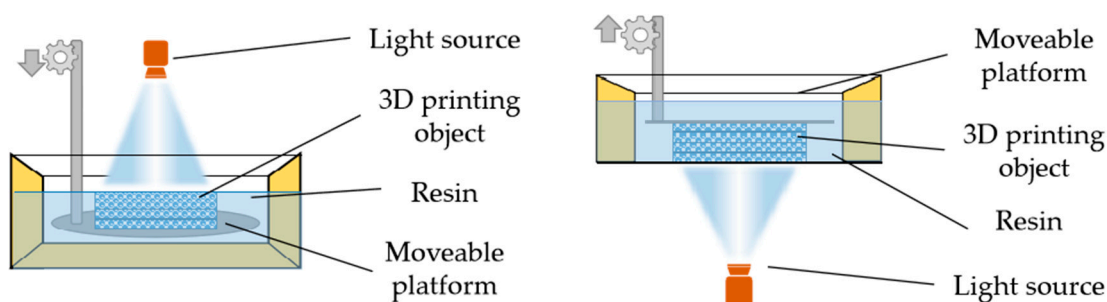


Figure 2. The schematics of mask-projection stereolithography for bottom-up system (left) and top-down system (right). The light source is scanning laser or digital light projection.

We used a mask-projection SLA printer LumiForge made by Lumi industries, Italy (Figure 3) to conduct the 3D printing of the thermal energy storage P(SA-DMAA) gels. This printer is a commercial printer based on top-down working principle. LumiForge consists of a UV-vis light source, a resin container and a moveable platform for holding a cured object mounted on a linear actuator. The building volume of LumiForge is 100 mm in diameter and 100 mm in height. LumiForge provides three optional Z slicing resolution (μm), including 100, 75 and 37.5. The light source is provided by a projector (Acer P1500 DLP Projector) as a dynamic mask generator, which shows the image of each layer for the certain exposure time in the curing process. The maximum resolution of the projector is 1920*1080, ensuring precise structures and a great fidelity in printing. The wavelengths of the light source are in visible light, which close to the working range of the ITX-EDAB co-initiation system. Thus, the ITX-EDAB initiation system is selected in this work.

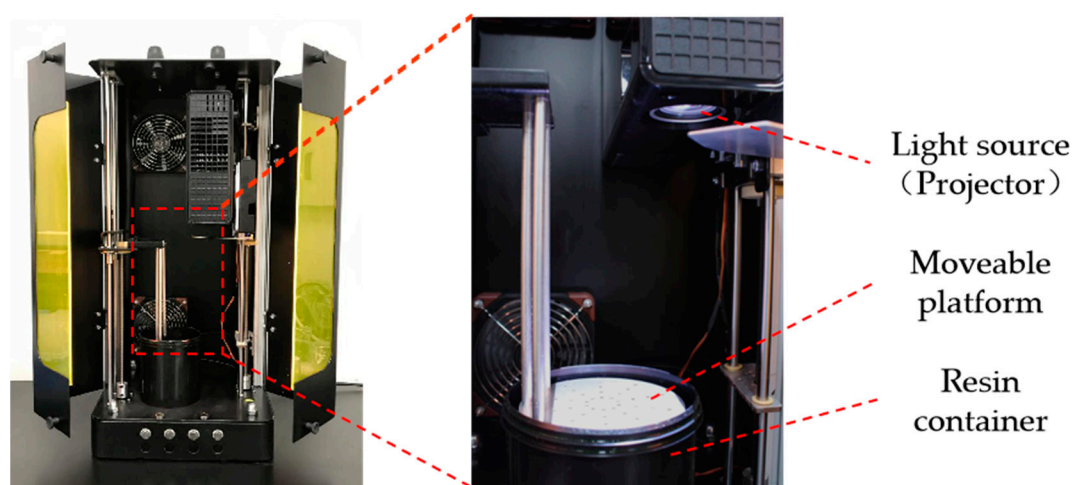


Figure 3. LumiForge -- A mask-projection stereolithography 3D printer working in bottom-up principle.

The structural and functional test samples were 3D printed by adapting and optimizing the print parameters including layer thickness, layer exposure time, light source, and base layers, etc. The thermal energy storage crystalline P(SA-DMAA) gels were used as printing material. The uncured liquid gel solution, known as the printing ink, consists of monomers SA and DMAA, oil-soluble initiators ITX and EDAB, and crosslinking agent MBAA. ITX-EDAB co-initiation system shows high efficiency under UV-vis light. ITX, EDAB, and MBAA were dissolved in DMAA firstly, then melted SA was added to prepare a homogeneous printing ink. The prepared printing ink was transferred into the resin container of LumiForge. The digital data of 3D model files were designed and edited by an open-source software 123D Design to make sure an available size for LumiForge. Specialized LumiCreator software was used to control this 3D printer. After loading the digital datum of a 3D model in Stl file format, the Z slicing increment was set to 37.5 μm , which was the maximum slicing resolution of LumiForge. The first layer was cured on the surface of movable platform. The platform would immerse a bit further into the resin before re-joining the correct position. The exposure time of the first 5 to 8 layers was lengthened to 45 s ensuring a perfect adherence of the object to the platform. After one layer cured, the platform moved downward to the next position, and another layer of uncured resin spread over the top layer. The exposure time for curing each layer was 30 s. The above processes repeated till the designed object was built up on LumiForge. Three printing inks with the molar ratios of SA to DMAA at 0.50:1.00, 0.33:1.00 and 0.25:1.00 were used to fabricate P(SA-DMAA) gel objects, named 3DP 0.50, 3DP 0.33 and 3DP 0.25, respectively. The 3D printed P(SA-DMAA) gel sheets were used for characterization. 3D data and printed gel sheets are shown in Figure 4 (a) and (b). In order to investigate the influence of post-UV curing treatment, those printed sheet samples treated by post-UV irradiation for 24 h at 30 $^{\circ}\text{C}$

(Figure 4 (c)) marked as Post-UV 3DP 0.50, Post-UV 3DP 0.33 and Post-UV 3DP 0.25, respectively, were also prepared.

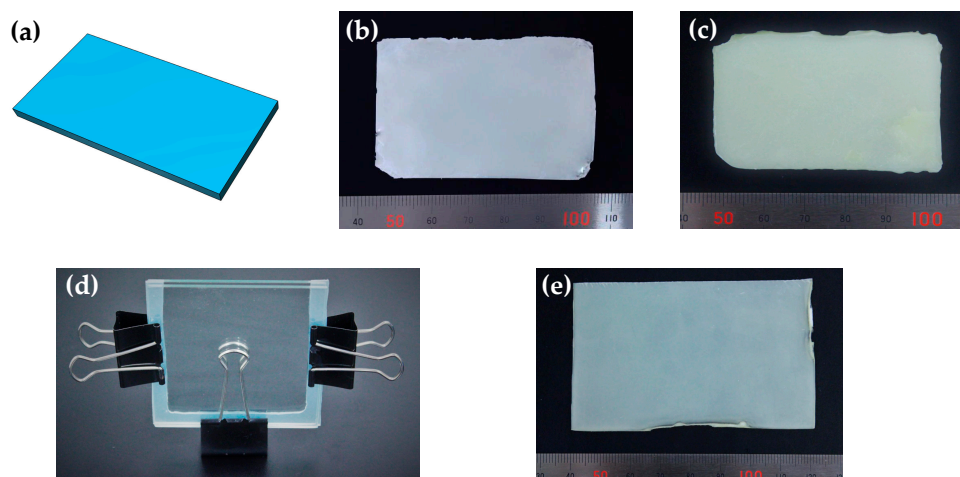


Figure 4. The 3D sheet model designed by 123D Design (a), P(SA-DMAA) gel sheet of 3DP 0.25 (printed on LumiForge) (b), Post-UV 3DP 0.25 (after post-UV treatment) (c) and Mold 0.25 (e) prepared using conventional mold (d).

2.3 Preparation of gel sheets by conventional mold

As a comparison of 3D printed gel sheets, we synthesized three P(SA-DMAA) gel sheets as the same ingredients as 3DP 0.50, 3DP 0.33 and 3DP 0.25 by conventional mold (Figure 4 (d)). The reactive gel liquid resin was injected into the mold with 1 mm thickness and cured under UV irradiation for 48 h at 30 °C. The prepared conventional P(SA-DMAA) gels were named Mold 0.50, Mold 0.33 and Mold 0.25, and the photograph of gel sheet for Mold 0.25 is shown in Figure 4 (e).

2.4 Characterization

2.4.1. Fourier Transform Infrared Spectrometer (FTIR)

Chemical structures of P(SA-DMAA) gels were evaluated using a Fourier transform infrared spectrometer (FT/IR-460 Plus, JASCO International Co., Ltd., Tokyo, Japan). Each spectrum was recorded with 32 scans in transmittance mode with a resolution of 0.5 cm⁻¹ within the range of 600 to 3300 cm⁻¹.

2.4.2. Wide-Angle X-Ray Scattering (WAXS)

To determine the crystallinity of P(SA-DMAA) gels, wide-angle X-ray scattering (WAXS) was performed on an X-ray diffractometer (Ultima IV, Rigaku Corporation, Akishima, Japan) with nickel-filtered Cu K α radiation at a scanning rate of 5 °·min⁻¹. The degree of crystallinity (W_c , %) was evaluated according to the following formula reported by W. Ruland [32]:

$$W_c = \frac{I_c}{I_c + I_a} \times 100 \% \quad (1)$$

where I_c and I_a are the scattering intensities of crystalline region and amorphous region, respectively.

2.4.3. Differential Scanning Calorimetry (DSC)

The thermal energy storage capacity and phase change behaviour of the P(DMMA-SA) gels were investigated using a differential scanning calorimeter (DSC) (Q-2000, TA instruments Japan

Inc., Tokyo, USA) operating under a nitrogen flow. Samples of about 5 mg were heated to 75 °C at a heating rate of 5 °C·min⁻¹ and held for 1 min to eliminate the thermal prehistory. Next, samples were cooled down to 0 °C at a cooling rate of 5 °C·min⁻¹ and held for 1 min, and finally reheated up to 75 °C at the same rate. Premium hermetic pans (TA Instruments Tzero #901683.901) were used for the measurements.

2.4.4. Infrared thermography

Thermal storage and release properties of 3D printed crystalline P(SA-DMAA) gels were evaluated by infrared thermal graphic camera (FLIR E6, FLIR Systems Inc., Wilsonville, USA). The samples were heated up to 70 °C and then cooled down to 0 °C on a hot stage.

3. Results and Discussion

3.1 Printing performance of thermal energy storage crystalline gels

Three thermal energy storage crystalline gels with different molar ratios of SA to DMAA at 0.50:1.00 (3DP 0.50), 0.33:1.00 (3DP 0.33) and 0.25:1.00 (3DP 0.25) were printed to evaluate the printing characters and performances. Characters 'YU', abbreviation of Yamagata University, were printed on LumiForge under the same conditions. These 3DP objects were designed to be 2 mm in thickness. The thickness in Stl file was sliced by LumiCreator into 53 layer with maximum Z slicing resolution of 37.5 µm, so the printed thickness theoretically was about 1.98 mm. Figure 5 displays the printing results. It is shown that the printing test succeed for all the three P(SA-DMAA) gels with the average thickness about 1.74 mm, and the printing performances improved with the decreasing molar fraction of SA. The 3DP 0.50 object was printed with extra parts on the structure (Figure 5 (a)), which was considered because the nearby liquid resin was also initiated and cured in the printing process. The object printed with 3DP 0.33 shows a clearer shape than 3DP 0.50 (Figure 5 (b)). As shown in Figure 5 (c), when the molar fraction of SA reached 0.25, the 3DP 0.25 could be printed with a relatively higher resolution and a good fidelity than other two gels. The printed P(SA-DMAA) gel objects were flexible and ductile.

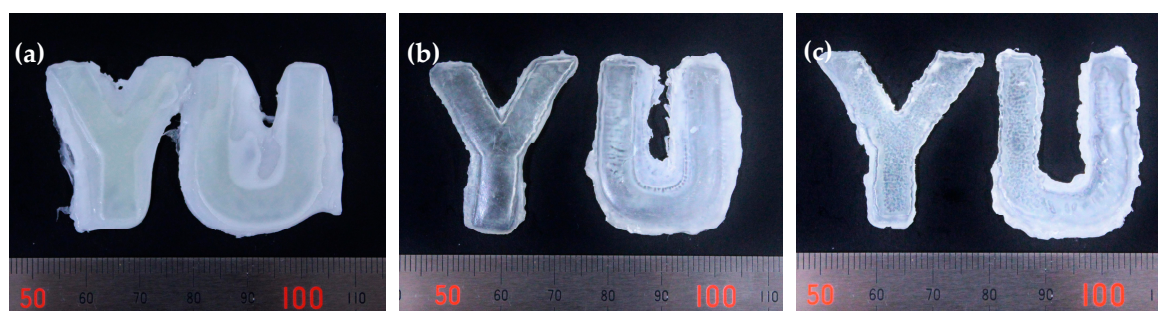


Figure 5. Characters 'YU' printed on LumiForge under the same condition with different molar ratios of SA to DMAA at 0.50:1.00 (3DP 0.50) (a), 0.33:1.00 (3DP 0.33) (b) and 0.25:1.00 (3DP 0.25) (c).

We also designed the objects with more complex shapes of honeycomb and tentacle using software 123D Design, and printed them on LumiForge. The P(SA-DMAA) gel with the small amount of SA, the molar ratio of SA to DMAA at 0.25:1.00 was used. As shown in Figure 6, the printing tests were successful and the printed objects had a good printing fidelity. The manufactured honeycomb was flexible and its hexagon structure near the center was relatively complete with the size of 40*40*2 mm, which is almost the same as the designed size. In case of the tentacle model, the small suckers on tentacle on micrometer scale were also fabricated clearly. The above test results prove that 3D fabrication of P(SA-DMAA) gels with a higher printing precision both on mili- and micro- meter scales were feasible for practical applications.

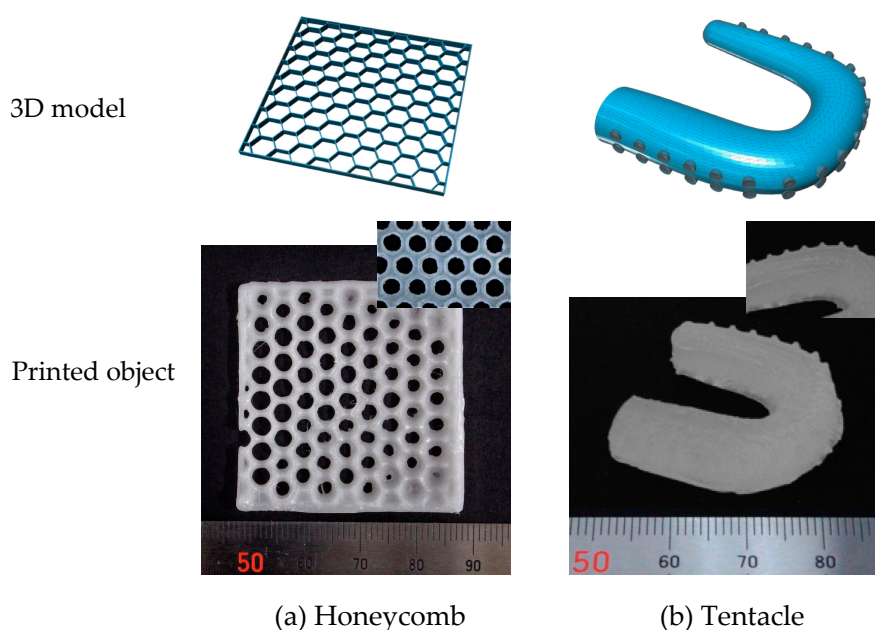


Figure 6. 3D model data designed by software 123D Design, and 3D objects fabricated on LumiForge with more complex shapes of honeycomb (a) and tentacle (b).

3.2 Chemical composition and structure

The chemical composition and structure of 3D printed P(SA-DMAA) gels were evaluated by FTIR spectroscopy. Figure 7 shows the infrared spectra of these gel samples. Thermal energy storage crystalline P(SA-DMAA) gels had a similar spectrum profile containing a series of characteristic absorption. All samples shown strong double intensive absorption peaks appearing at 2920 cm^{-1} , 2850 cm^{-1} due to the alkyl C–H stretching vibrations of the methylene group. There was an absorption band at 1728 cm^{-1} , which is attributed to the C=O stretching vibration of the ester group. The peaks at 1260 cm^{-1} , 1160 cm^{-1} and 1130 cm^{-1} , which can be assigned to the C–O stretching vibration of the ester group, were typical of acrylic ester. The infrared spectra also exhibited an absorption peak at 722 cm^{-1} corresponding to the in-plane rocking vibration of methylene groups belonging to the *n*-alkane side chain derived from SA. It was noted that two absorption bands near 1630 cm^{-1} and 985 cm^{-1} in the infrared spectra had significant changes after polymerization. All P(SA-DMAA) gels shown the same strong absorption peak at 1630 cm^{-1} as P(DMAA), which is owing to the C=O stretching vibration of the tertiary amide. There were two characteristic absorption peaks for C=C. One was derived from SA at 1635 cm^{-1} , and the other was derived from DMAA at 1610 cm^{-1} . In addition, the characteristic absorption peak attributed to C–H stretching vibration of the end vinyl group presents at 985 cm^{-1} . The two peaks at 1635 cm^{-1} and 1610 cm^{-1} almost disappeared for 3D printed samples 3DP 0.50, 3DP 0.33 and 3DP 0.25 (Figure 7 (e), (f) and (g)), which indicates the radical reaction went well, and the P(SA-DMAA) gel objects could be synthesized and fabricated simultaneously on 3D printer LumiForge. It is noticed that the weak absorption peak at 985 cm^{-1} for 3DP 0.33 and 3DP 0.25 disappeared after post-UV curing treatment (Figure 7 (i) and (j)). The peak at 985 cm^{-1} also disappeared for the gel samples prepared by conventional mold under UV curing for 48 h (Figure 7 (k), (l), (m)). This reveals post-UV curing treatment is advantageous to get the 3D printed objects fully cured. We can get the same conclusions from the color of gel samples (Figure 4). The 3D printed gel sheet is cream white (Figure 4 (b)), the color of which is close to that of monomer SA. After 24 h post-UV curing

treatment, the printed gel sheet (Figure 4 (c)) shows milk yellow, which is the similar color to that of the gel sheet prepared by conventional mold (Figure 4 (e)).

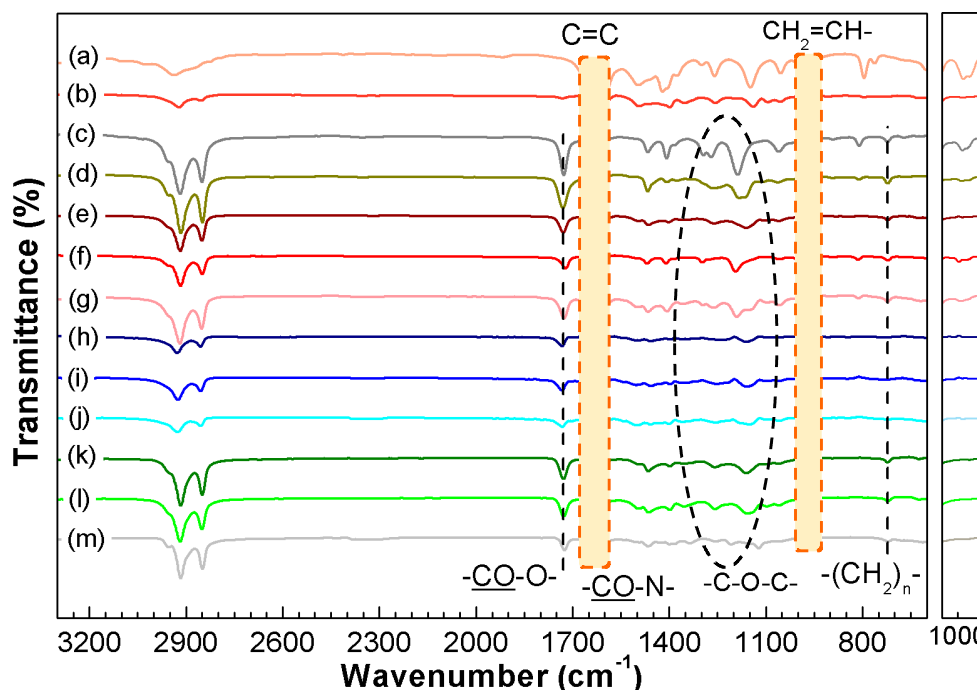


Figure 7. FTIR spectra of P(SA-DMAA) gels and their partial enlargement around 1000 cm^{-1} . (a) DMAA, (b) P(DMAA), (c) SA, (d) P(SA), (e) 3DP 0.50, (f) 3DP 0.33, (g) 3DP 0.25, (h) Post-UV 3DP 0.50, (i) Post-UV 3DP 0.33, (j) Post-UV 3DP 0.25, (k) Mold 0.50, (l) Mold 3DP 0.33, (m) Mold 3DP 0.25.

3.3 Crystalline structure

The crystallization behaviours of 3D printed thermal energy storage crystalline P(SA-DMAA) gels were investigated by WAXS analysis. WAXS patterns of 3DP gels along with post-UV curing treatment samples and conventional UV mold curing ones are shown in Figure 8. From the view point of SA amount, it was found that the peak intensity increases with the increasing amount of SA. The high peak intensity and sharpness means the high crystallinity. Accordingly, the P(SA-DMAA) gels with the highest SA amount, 3DP 0.50, Post-UV 3DP 0.50 and Mold 0.50 shown the sharpest and strongest-intensity diffraction peak at 21.74° , indicating the highest crystallinity. The degree of crystallinity (W_c) was estimated from the areas under the curves of the crystal region and amorphous region [25,32,33], and the values of W_c for all P(SA-DMAA) gels are listed in Table 1. The W_c of 3DP 0.50, Post-UV 3DP 0.50 and Mold 0.50 were around 40%, the highest among all P(SA-DMAA) gels. The main reason is considered that the addition of crystalline SA contributes to the polymer chain packing closely in a crystalline fashion, which increases the W_c of P(SA-DMAA) gels. The highest crystallinity and W_c promises a great potential for thermal energy storage. On the other hand, from the view point of preparation method, although the 3DP and post-UV 3DP samples show a little higher crystallinity than samples prepared by conventional mold, no obvious influence of methods on crystallinity was observed. The result suggests that the post-UV curing treatment is beneficial to the further reaction, but not able to affect the further improvement of crystal structure to get higher crystallinity.

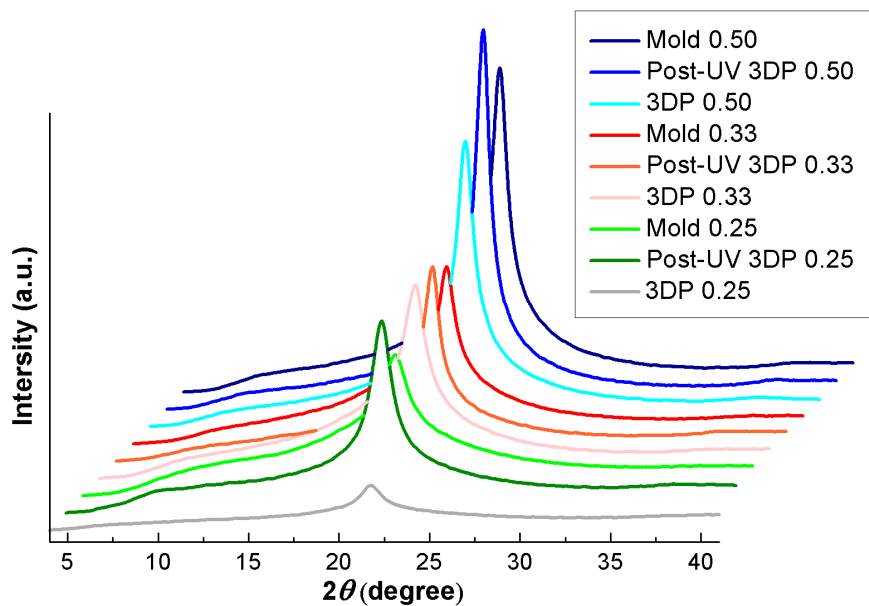


Figure 8. WAXS patterns of thermal energy storage P(SA-DMAA) gels.

Table 1. The degree of crystallinity (W_c) evaluated from WAXS patterns for P(SA-DMAA) gels.

Sample	W_c (%)	Sample	W_c (%)	Sample	W_c (%)
Mold 0.50	39.16	3DP 0.50	41.24	Post-UV 3DP 0.50	41.52
Mold 0.33	27.61	3DP 0.33	28.79	Post-UV 3DP 0.33	26.30
Mold 0.25	19.05	3DP 0.25	23.57	Post-UV 3DP 0.25	22.52

3.4 Energy storage capacity

Thermal energy storage/release behaviours, phase change temperatures and their ranges, and phase change enthalpies are important parameters determining the thermoregulation capacities of phase change materials. Thermal energy storage capacity of crystalline P(SA-DMAA) gel was investigated through DSC test. The DSC curves of gel samples, including 3DP, post-UV curing treatment and conventional UV mold curing gels, are shown in Figure 9. Their phase transition temperatures and phase change enthalpies measured by DSC are summarized and listed in Table 2. Under all the preparation methods, with the increasing amount of SA, the crystallization temperature (T_c), the enthalpy of crystallization process (ΔH_c), the melting temperature (T_m), and the enthalpy of melting process (ΔH_m) increases. That is, by increasing amount of SA, energy storage capacity of P(SA-DMAA) gels were effectively improved. The increasing amount of crystalline SA leads to the amount of crystalline alkane side chains, which form better side-chain crystal regions for generating stronger crystalline/melting peaks and higher phase change enthalpies. Naturally, we can draw the conclusion that the increasing of SA contributes to better a thermal energy storage capacity.

P(SA-DMAA) crystalline gels with molar fraction of SA at 0.50 had the highest energy storage capacity in higher temperature ranges than other samples, reached over $69 \text{ J}\cdot\text{g}^{-1}$. It is noted that Mold 0.50 and Post-UV 3DP 0.50 presented a crystallization peak accompanied by one and two shoulders, whereas a single endothermic peak corresponding to the phase change of fusion. Many investigations on the crystallization behaviours of *n*-alkane indicate that there are metastable rotator phases with transformation temperature in a few degrees above the crystallization temperature before the isotropic liquid completely converted into crystalline solid [34]. Rotator phases pass

through one or more than one rotator phases between isotropic phase and crystal phase, due to the gradual breakdown of orientation order. These transitions between different phases correspond to the breaking of some symmetry [35]. Such phase transition causes a multi-modal crystallization behaviour for P(SA-DMAA) gels.

The phase transition behaviours of 3DP P(SA-DMAA) gels were distinctive from conventional UV mold curing gels and post-UV curing treatment samples. At the same molar fraction of SA, the phase transition temperatures and phase change enthalpies of 3D printed gels are the highest among all P(SA-DMAA) gels prepared by the three methods. The post-UV curing treatment makes the melting behaviours closer to samples made by conventional UV mold method. After post-UV curing treatment, phase transition temperatures of these 3D printed gels increased by about 2 °C, and their phase change enthalpy shown a decrease tendency. The difference in phase change behaviours of 3D printed samples with and without post-UV curing treatment indicated that the post-UV curing treatment improved the further progress of polymerization and crosslinking reaction [31]. The higher ΔH_c and ΔH_m for 3DP 0.50 may partly derive from that of not-fully-reacted SA, that can be evidenced by FTIR results (Figure 7).

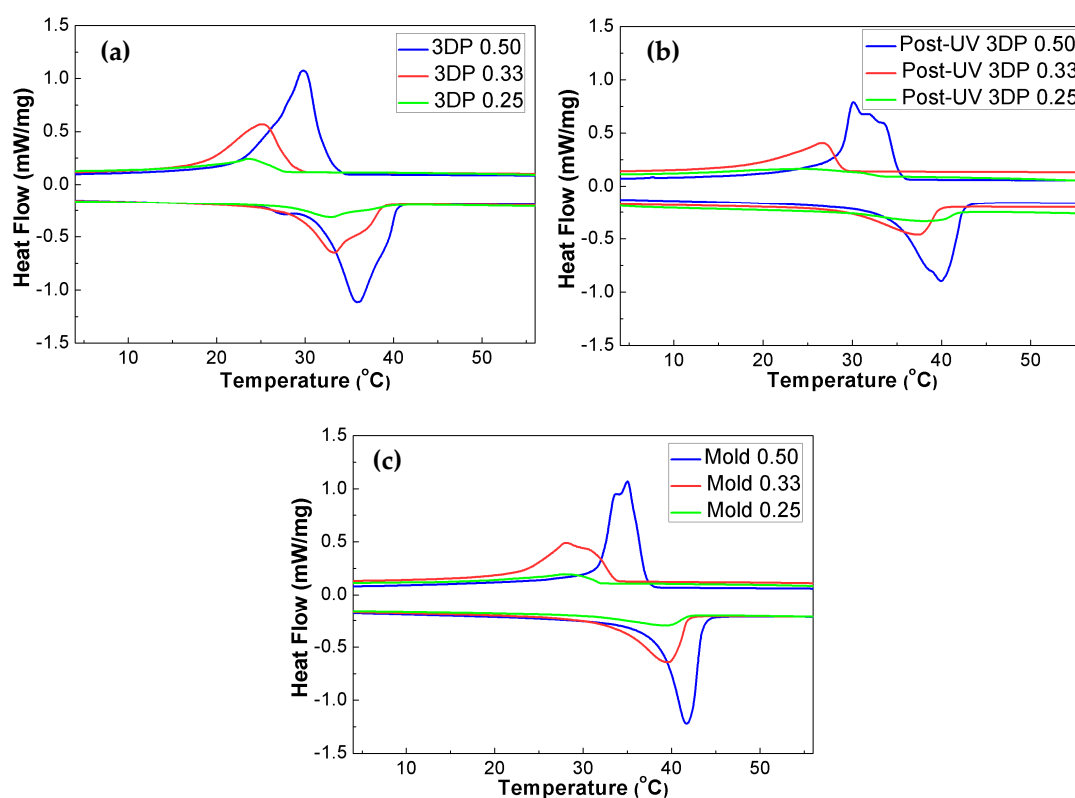


Figure 9. DSC curves of thermal energy storage crystalline P(SA-DMAA) gels prepared from 3D printing (a), 3D printing with post-UV curing treatment (b), and curing with conventional UV mold (c).

Table 2. Phase transition temperatures and phase change enthalpies measured by DSC for P(SA-DMAA) gels.

Sample	T_c (°C)	ΔH_c (J·g ⁻¹)	T_m (°C)	ΔH_m (J·g ⁻¹)
3DP 0.50	29.78	69.22	35.88	69.58
3DP 0.33	25.27	37.65	33.16	41.24

3DP 0.25	23.55	12.04	32.67	13.49
Post-UV 3DP 0.50	30.10	53.01	39.88	56.68
Post-UV 3DP 0.33	26.89	23.53	37.32	23.95
Post-UV 3DP 0.25	24.48	11.54	37.76	11.71
Mold 0.50	35.03	53.73	41.66	53.42
Mold 0.33	28.01	36.12	39.56	34.48
Mold 0.25	28.01	9.54	39.00	10.58

T_c : crystallization temperature, ΔH_c : enthalpy of crystallization process, T_m : melting temperature, ΔH_m : enthalpy of melting process.

To further evaluate the thermal energy storage capacity of P(SA-DMAA) gel, the logo of Yamagata University (Figure 10 (a)) was printed on cotton fabric using LumiForge (Figure 10 (b)), and its infrared thermal pictures were detected to give a visual image of difference in temperature due to the thermal energy storage capacity (Figure 10 (c)). The crystalline P(SA-DMAA) gels were successfully printed on cotton fabric, even the complex characters '山形大学' could be recognized. The thermoregulation properties of printed samples were measured on a hot stage. In the heating process, the temperature of hot stage was set at 70 °C, and 0 °C in the cooling process. The detected temperature changes with time in the heating and cooling process supplied by an infrared thermal graphic camera were plotted and given in Figure 11. A buffer zone and the temperature differences between 3DP gel samples and hot stage were clearly observed in one heating and cooling cycle. In the heating process, the temperatures of gels were lower than surroundings, and in the cooling process were higher, which gives a direct evidence for energy storage capacity of P(SA-DMAA) gels. Compared to 3DP 0.25, owing to the high phase change enthalpy, 3DP 0.33 and 3DP 0.50 prolonged the time to reach the setting point and slow down the temperature changing rate, indicating a better energy storage capacity. In the temperature range of 30–40 °C to the heating process and 35–20 °C to the cooling process, 3D printed P(SA-DMAA) gels shown the thermoregulation property to store phase change energy. In addition, noted that 3DP 0.50 provided a thermoregulation property approximately 4 °C higher than 3DP 0.33, owing to the higher molar fraction of SA, and higher phase transition temperature. These results are consistent with DSC results mentioned above.



Figure 10. The logo of Yamagata University (a), the printed logo on cotton fabric using P(SA-DMAA) gel (3DP 0.25) as printing material on LumiForge (b), and its infrared thermal picture supplied by an infrared thermal graphic camera (c).

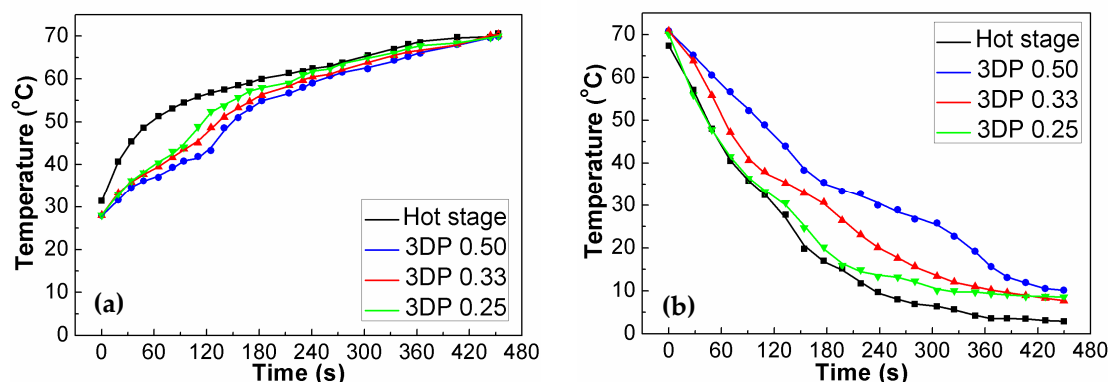


Figure 11. Temperature change as a function of time detected by an infrared thermal graphic camera for 3D printed crystalline P(SA-DMAA) gels in one heating (a) and cooling (b) cycle.

4. Conclusions

A mask-projection SLA printer -- LumiForge, working in bottom-up principle, was chosen to print gels with the characteristic of easily control and simple production process. Three energy storage crystalline P(SA-DMAA) gels with the molar ratios of SA to DMAA at 0.50:1.00, 0.33:1.00 and 0.25:1.00 were used as 3D printing materials. The objects with three-dimensional architecture were synthesized and fabricated directly from liquid resin on LumiForge. By optimizing the 3D printing conditions, including layer thickness, chemical designs, formulation and the concentration of photo initiators, all P(SA-DMAA) gels were 3D printed successfully. With the decreasing molar fraction of SA, the printing resolution and fidelity became better. For the P(SA-DMAA) gel with small fraction of SA at 0.25, the 3D fabrication could be realized with higher printing precision both on mili- and micro- meter scales. As a comparison of 3D printed samples, P(SA-DMAA) gels made by other two methods, post-UV curing treatment after 3D printing and UV curing using conventional mold, were prepared. The 3D printed P(SA-DMAA) gels shown high crystallinity, ensuring their good thermal energy storage capacity. Post-UV curing treatment for 24 h was beneficial to 3D printed gels fully cured, but not able to affect the further improvement of crystal structure to get higher crystallinity. By increasing the molar fraction of SA, energy storage capacity was effectively improved, due to the increasing amount of crystalline *n*-alkane side chains, which is advantageous to form side-chain crystal regions for generating stronger crystalline/melting peaks and higher phase change enthalpies. P(SA-DMAA) crystalline gels with molar fraction of SA at 0.50 had the highest energy storage enthalpy that reached $69.6 \text{ J}\cdot\text{g}^{-1}$. The infrared thermal testing results proved 3D printed crystalline P(SA-DMAA) gels provided a good thermoregulation property in the temperature range from 25 to 40 °C.

We confirmed that the 3D printable P(SA-DMAA) gels had good thermal energy storage capacity, and their 3D printing were successful. The objects with complex 3D structure, also the designed patterns on cotton fabric were printed with a good precision. The P(SA-DMAA) gels are feasible for practical applications as one kind of 3D printing material with thermal energy storage and thermoregulation functionality. We expect the 3D printable P(SA-DMAA) gels can provide a novel complicated-in-structure and wearable thermal-energy-storage device.

Acknowledgments: The financial support of this work from the Asahi Glass Foundation for the Promotion of Science & Engineering (2016, No.17), the Iketani Science and Technology Foundation (0281059-A), the Ogasawara Foundation for the Promotion of Science & Engineering (2015, No.5), the Shiseido Female Researcher Science Grant (2014, No.3), the MEXT Program that supports the research activities of female researchers (2015-2017), and JSPS KAKENHI (Grant Number 25810123) are gratefully acknowledged.

Author Contributions: Yuchen Mao and Jin Gong conceived and designed the experiments; Yuchen Mao performed the experiments; Yuchen Mao, Jin Gong, Meifang Zhu and Hiroshi Ito analyzed the data; Takuya

Miyazaki and Kohei Sakai contributed reagents/materials/analysis tools; Yuchen Mao and Jin Gong wrote the paper.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Yataganbaba, A.; Ozkahraman, B.; Kurtbas, I. Worldwide trends on encapsulation of phase change materials: A bibliometric analysis (1990–2015). *Applied Energy* **2017**, *185*, 720–731, doi: 10.1016/j.apenergy.2016.10.107.
2. Castellón, C.; Martorell, I.; Cabeza, L.F.; Fernández, A.I.; Manich, A.M. Compatibility of plastic with phase change materials (pcm). *Int J Energ Res* **2011**, *35*, 765–771, doi: 10.1002/er.1723.
3. S, M. Phase change materials for smart textiles – an overview. *Applied Thermal Engineering* **2008**, *28*, 1536–1550, doi: 10.1016/j.applthermaleng.2007.08.009.
4. Mahlia, T.M.I.; Saktisahdan, T.J.; Jannifar, A.; Hasan, M.H.; Matseelar, H.S.C. A review of available methods and development on energy storage; technology update. *Renewable and Sustainable Energy Reviews* **2014**, *33*, 532–545, doi: 10.1016/j.rser.2014.01.068.
5. Pereira da Cunha, J.; Eames, P. Thermal energy storage for low and medium temperature applications using phase change materials – a review. *Applied Energy* **2016**, *177*, 227–238, doi: 10.1016/j.apenergy.2016.05.097.
6. Tyagi, V.V.; Kaushik, S.C.; Tyagi, S.K.; Akiyama, T. Development of phase change materials based microencapsulated technology for buildings: A review. *Renewable and Sustainable Energy Reviews* **2011**, *15*, 1373–1391, doi: 10.1016/j.rser.2010.10.006.
7. Kalaiselvam, S.; Parameshwaran, R.; Harikrishnan, S. Analytical and experimental investigations of nanoparticles embedded phase change materials for cooling application in modern buildings. *Renewable Energy* **2012**, *39*, 375–387, doi: 10.1016/j.renene.2011.08.034.
8. Huang, M.; Eames, P.; Hewitt, N. The application of a validated numerical model to predict the energy conservation potential of using phase change materials in the fabric of a building. *Solar Energy Materials and Solar Cells* **2006**, *90*, 1951–1960, doi: 10.1016/j.solmat.2006.02.002.
9. Hegde, M.; Meenakshisundaram, V.; Chartrain, N.; Sekhar, S.; Tafti, D.; Williams, C.B.; Long, T.E. 3d printing all-aromatic polyimides using mask-projection stereolithography: Processing the nonprocessable. *Adv Mater* **2017**, *29*, doi: 10.1002/adma.201701240.
10. Zhang, Y.S.; Davoudi, F.; Walch, P.; Manbachi, A.; Luo, X.; Dell'Erba, V.; Miri, A.K.; Albadawi, H.; Arneri, A.; Li, X., *et al.* Bioprinted thrombosis-on-a-chip. *Lab Chip* **2016**, *16*, 4097–4105, doi: 10.1039/c6lc00380j.
11. Chia, H.N.; Wu, B.M. Recent advances in 3d printing of biomaterials. *J Biol Eng* **2015**, *9*, 4, doi: 10.1186/s13036-015-0001-4.
12. Patra, S.; Young, V. A review of 3d printing techniques and the future in biofabrication of bioprinted tissue. *Cell Biochem Biophys* **2016**, *74*, 93–98, doi: 10.1007/s12013-016-0730-0.

13. Senatov, F.S.; Zadorozhnyy, M.Y.; Niaza, K.V.; Medvedev, V.V.; Kaloshkin, S.D.; Anisimova, N.Y.; Kiselevskiy, M.V.; Yang, K.-C. Shape memory effect in 3d-printed scaffolds for self-fitting implants. *European Polymer Journal* **2017**, *93*, 222-231, doi: 10.1016/j.eurpolymj.2017.06.011.
14. Kuznetsov, V.; Solonin, A.; Urzhumtsev, O.; Schilling, R.; Tavitov, A. Strength of pla components fabricated with fused deposition technology using a desktop 3d printer as a function of geometrical parameters of the process. *Polymers* **2018**, *10*, doi: 10.3390/polym10030313.
15. Zhang, M.; Vora, A.; Han, W.; Wojtecki, R.J.; Maune, H.; Le, A.B.A.; Thompson, L.E.; McClelland, G.M.; Ribet, F.; Engler, A.C., *et al.* Dual-responsive hydrogels for direct-write 3d printing. *Macromolecules* **2015**, *48*, 6482-6488, doi: 10.1021/acs.macromol.5b01550.
16. Ge, Q.; Sakhaei, A.H.; Lee, H.; Dunn, C.K.; Fang, N.X.; Dunn, M.L. Multimaterial 4d printing with tailorable shape memory polymers. *Sci Rep* **2016**, *6*, 31110, doi: 10.1038/srep31110.
17. Pirlo, R.K.; Wu, P.; Liu, J.; Ringeisen, B. Plga/hydrogel biopapers as a stackable substrate for printing huvec networks via biolp. *Biotechnol Bioeng* **2012**, *109*, 262-273, doi: 10.1002/bit.23295.
18. Oesterreicher, A.; Wiener, J.; Roth, M.; Moser, A.; Gmeiner, R.; Edler, M.; Pinter, G.; Griesser, T. Tough and degradable photopolymers derived from alkyne monomers for 3d printing of biomedical materials. *Polym. Chem.* **2016**, *7*, 5169-5180, doi: 10.1039/c6py01132b.
19. Rodriguez, J.N.; Zhu, C.; Duoss, E.B.; Wilson, T.S.; Spadaccini, C.M.; Lewicki, J.P. Shape-morphing composites with designed micro-architectures. *Sci Rep* **2016**, *6*, 27933, doi: 10.1038/srep27933.
20. Scalfani, V.F.; Turner, C.H.; Rupar, P.A.; Jenkins, A.H.; Bara, J.E. 3d printed block copolymer nanostructures. *Journal of Chemical Education* **2015**, *92*, 1866-1870, doi: 10.1021/acs.jchemed.5b00375.
21. Gong, J.; Azusa, S.; Makino, M.; Kawakami, M.; Furukawa, H. 3d printing of medical and edible gels. *Journal of the Japan Society for Abrasive Technology* **2016**, *60*, 134-137.
22. Gong, J.; Igarashi, S.; Sawamura, K.; Makino, M.; Hasnat Kabir, M.; Furukawa, H. Gel engineering materials meso-decorated with polymorphic crystals. *Advanced Materials Research* **2013**, *746*, 325-329, doi: 10.4028/AMR.746.325.
23. Gong, J.; Furukawa, H. Smart optical device of varifocal lens developed with high transparent shape memory gels. *Expected Materials for the Future* **2013**, *13*, 5-8.
24. Mao, Y.; Gong, J.; Zhu, M.; Ito, H. Excellent thermal stability p(bea-co-mma) microcapsules with high thermal energy storage capacity. *Polymer* **2018**, *150*, 267-274, doi: 10.1016/j.polymer.2018.07.040.
25. Gong, J.; Hosaka, E.; Sakai, K.; Ito, H.; Shibata, Y.; Sato, K.; Nakanishi, D.; Ishihara, S.; Hamada, K. Processing and thermal response of temperature-sensitive-gel(tsg)/polymer composites. *Polymers* **2018**, *10*, 486, doi: 10.3390/polym10050486.
26. Schmidt, L.E.; Leterrier, Y.; Vesin, J.-M.; Wilhelm, M.; Månson, J.-A.E. Photorheology of fast uv-curing multifunctional acrylates. *Macromolecular Materials and Engineering* **2005**, *290*, 1115-1124, doi: 10.1002/mame.200500229.

27. De Beer, N. Advances in three dimensional printing - state of the art and future perspectives. *Journal for New Generation Sciences* **2006**, *4*, 21-49, doi: org/10.1108/13552540610670717.
28. Mao, Y.; Yu, K.; Isakov, M.S.; Wu, J.; Dunn, M.L.; Jerry Qi, H. Sequential self-folding structures by 3d printed digital shape memory polymers. *Sci Rep* **2015**, *5*, 13616, doi: 10.1038/srep13616.
29. Kong, Z.; Wang, C.; Ren, Y.; Gu, M.; Hu, Y.; Yue, B.; He, H. Synthesis, structure, and properties of two supramolecular compounds based on silicotungstic acid and transition metal(ii) coordinated isonicotinic acid. *Chinese Journal of Chemistry* **2012**, *30*, 759-764, doi: 10.1002/cjoc.201100439.
30. Heller, C.; Schwentenwein, M.; Russmueller, G.; Varga, F.; Stampfl, J.; Liska, R. Vinyl esters: Low cytotoxicity monomers for the fabrication of biocompatible 3d scaffolds by lithography based additive manufacturing. *Journal of Polymer Science Part A: Polymer Chemistry* **2009**, *47*, 6941-6954, doi: 10.1002/pola.23734.
31. Han, D.; Lu, Z.; Chester, S.A.; Lee, H. Micro 3d printing of a temperature-responsive hydrogel using projection micro-stereolithography. *Sci Rep* **2018**, *8*, 1963, doi: 10.1038/s41598-018-20385-2.
32. Ruland, W. X-ray determination of crystallinity and diffuse disorder scattering. *Acta Crystallographica* **1961**, *14*, 1180-1185, doi: 10.1107/S0365110X61003429.
33. Mo, Z.; Zhang, H. The degree of crystallinity in polymers by wide-angle x-ray diffraction (waxd). *Journal of Macromolecular Science, Part C* **1995**, *35*, 555-580, doi: 10.1080/15321799508021751.
34. Zhang, Y.; Wang, X.; Wu, D. Design and fabrication of dual-functional microcapsules containing phase change material core and zirconium oxide shell with fluorescent characteristics. *Solar Energy Materials and Solar Cells* **2015**, *133*, 56-68, doi: 10.1016/j.solmat.2014.10.035.
35. Mukherjee, P.K. Phase transitions among the rotator phases of the normal alkanes: A review. *Physics Reports* **2015**, *588*, 1-54, doi: 10.1016/j.physrep.2015.05.005.