

Article

Physicochemical characterization of FRET-labelled chitosan nanocapsules and model degradation studies

Stefan Hoffmann¹, Christian Gorzelanny², Bruno Moerschbacher³, Francisco M. Goycoolea^{1,4,*}

¹ Institute of Plant Biology and Biotechnology (IBBP), Westfälische Wilhelms-Universität Münster, Schlossplatz 8, 48143, Münster, Germany; stefan.hoffmann@wwu.de

² Department of Dermatology and Venerology, University Medical Center Hamburg-Eppendorf, Hamburg, Germany; c.gorzelanny@uke.de

³ Institute of Plant Biology and Biotechnology (IBBP), Westfälische Wilhelms-Universität Münster, Schlossplatz 8, 48143, Münster, Germany; moersch@uni-muenster.de

⁴ School of Food Science and Nutrition, University of Leeds, LS2 9JT, United Kingdom F.M.Goycoolea@leeds.ac.uk

* Correspondence: F.M.Goycoolea@leeds.ac.uk; Tel.: +44-113-343-1412

Abstract: Sub-micron o/w emulsions coated with chitosan have been used for drug delivery, quorum sensing inhibition and vaccine development. To study interactions with biological systems, nanocapsules have been fluorescently labelled in previous works, but it is often difficult to distinguish the released label from intact nanocapsules. In this study, we present advanced labelling strategies based on FRET measurements for chitosan-coated nanocapsules and investigate their dissolution and degradation. We used FRET measurements of nanocapsules loaded with equimolar concentrations of two fluorescent dyes in their oily core and correlated them with DLS count rate measurement and absorbance measurements during their disintegration by dissolution. Using count rate measurements, we also investigated the enzymatic degradation of nanocapsules using pancreatin and how protein corona formation influences their degradation. Of note, nanocapsules dissolved in ethanol, where FRET decreased simultaneously with count rate, and absorbance caused by nanocapsule turbidity, indicating increased distance between dye molecules after their release. Nanocapsules were degradable by pancreatin in a dose dependent manner, and showed a delayed enzymatic degradation after protein corona formation. We present here novel labelling strategies for nanocapsules that allow us to judge their status and an *in vitro* method to study nanocapsule degradation and the influence of surface characteristics.

Keywords: chitosan; nanocapsules; degradation; FRET; protein corona; bioimaging; (List three to ten pertinent keywords specific to the article; yet reasonably common within the subject discipline.)

1. Introduction

Nanomedicine has been field a of continued growing traction in the recent decades. Particularly, in drug delivery, diagnosis and medical imaging research. Many applications are currently investigated, in clinical trials, or already are commercialised. Among pharmaceutical formulations already clinically approved include liposomes [1,2], albumin nanoparticles [3] and polymeric micelles [4]. The advocated advantages of these systems rely in enhanced delivery of drugs or other therapeutics that are challenging to deliver as free molecules [4], prolonged circulation time [3,5] or specific targeting, hence, overall lower off target toxicity [6,7].

Despite the contrasted effectiveness of these systems, their mode of action still begs many unanswered questions and leaves much to be understood. Indeed, the mechanisms whereby macromolecular drugs and nanoparticles offered advantages over conventional dosage forms, were previously thought to be established. Such was the case for the enhanced permeability and retention (EPR) effect in the passive targeting of nanoparticles to cancer tumours [8–10], mostly by systemic

delivery, has been recently questioned as more nuanced as previously thought with several properties of the nanoparticles and patient characteristics influencing its effectiveness [6,7]. Multiple biological processes are thought to be at play when accounting for differences found in the EPR effect of different type of nanoparticles (*e.g.*, interactions of proteins present in in body fluids and formation of nanoparticles protein corona, and differences in extravasation and subsequent interaction with the tumour microenvironment). To make educated statements about the relevancy of the EPR of nanoparticles in a certain pathology, the properties of nanoparticles that influence the previously mentioned biological processes should be studied in detail, *i.e.* size, shape, surface makeup, charge, density, *etc.* Some of these biological processes can be studied *in vitro*, like the formation of protein corona [11]. Investigating other processes, like extravasation and tumour accumulation, can be more challenging and must be studied *in* or *ex vivo* models using magnetic resonance imaging or fluorescence microscopy. Another challenging aspect in studying systemic delivery of nanoparticles are their circulation times and degradation and metabolic pathways. Nanoparticles injected into the bloodstream are mostly cleared by opsonization and the mononuclear phagocyte system in liver, spleen, lungs and bone marrow [12]. On the other hand, nanoparticles intended for transmucosal oral delivery, of inherent greater patient compliance than any other administration route, are mainly used to enhance the bioavailability of drugs, particularly highly insoluble, non-Lipinski molecules and delicate biological macromolecules (known also as “biologics”). They face a different set of challenges because of the acidic conditions encountered in the gastric tract and abundance of degradative enzymes as part of the digestive system [13].

Förster resonance energy transfer (FRET) is the transfer of energy from an excited donor chromophore to an acceptor chromophore and occurs if the emission spectrum of the former is overlapping with the absorption spectrum of the latter, given their distance is below 10 nm and the molecules are in a certain steric orientation. It has been widely used to study conformation changes in proteins and has been called the ‘spectroscopic ruler’ [14]. More recently, FRET measurements have been applied to the *in vitro* and *in vivo* study of nanoparticle systems to expand upon previously used simple fluorescent labelling [15–19]. FRET measurements with nanoparticles can determine whether they are still in their intact state or have been degraded, since FRET is rapidly lost when the proximity of donor and acceptor increases. This is advantageous when compared to simple fluorescent labelling, where it is often difficult to tell if the label is still associated with the nanoparticles or was released.

Nanoemulsions (NEs) are liquid sub-micron colloidal oil droplets dispersed in water (o/w) with a lipophilic oily core, usually stabilized by a surfactant covered interface with the aqueous phase. In drug delivery applications NEs are mostly used to deliver lipophilic drugs with a low bioavailability loaded into their hydrophobic core, like previously mentioned polymeric micelles. Hydrophilic therapeutic large macromolecules like proteins or nucleic acids can also be loaded onto the shell of the system by adsorbing them. The o/w interface can be coated with a polymer too, usually by electrostatic interactions between the surfactant and an oppositely charged polyelectrolyte, giving rise to a nanocapsule (NC) system with different physicochemical properties. By coating nanoemulsions with a negative zeta potential with the cationic polymer chitosan, NCs with a positive surface charge are obtained. Such chitosan-coated NCs are known to exhibit improved colloidal stability [20]. Besides, they are muco- [21] and bioadhesive towards negatively charged biological membranes [22]. These NCs have been used as a drug delivery platform for insulin [23], flavonoids that interfere with bacterial quorum sensing [24], poorly water-soluble capsaicin [25,26], or vaccines [27]. Despite the fact that these NCs have consistently shown efficacy as drug delivery carriers, the precise mechanistic aspects that govern the interactions with the body and cellular fate upon being administered, are not fully understood.

This study aims to examine the labelling of CS NCs by FRET and perform a physicochemical characterization of the labelled systems in comparison with unlabelled ones. FRET is studied using donor quenching and sensitized emission of the acceptor dye and compared between dyes in solution and dyes associated with NCs. FRET was measured in NCs that contain both donor and acceptor dyes and mixtures of NCs that contained either donor or acceptor to determine if intra-NC and inter-NC FRET occurred. As a model of NC disintegration, ethanol was used to dissolve NCs and FRET,

absorbance at 650 nm and count rate were measured. Finally, we studied the *in vitro* degradation of NCs using pancreatin and that protein corona formation affects their degradation rates by dynamic light scattering (DLS) measurements.

2. Materials and Methods

2.1 Materials

Chitosan HMC 70/5 (Batch No. 212-140311-02) with a degree of acetylation of 32% (as determined by ^1H NMR) and $M_w=5.01 \times 10^4$ g/mol and $I_p=2.18$ (as determined by SEC-HPLC with MALLS-DRI-IV multidetection in 0.3 M acetic acid/0.2 M sodium acetate buffer) was obtained from Heppe Medical Chitosan GmbH (Halle, Germany). Miglyol® 812 (a neutral oil formed by esters of caprylic and capric fatty acids and glycerol) was kindly provided by Peter Cremer Oleo (Hamburg, Germany). The surfactant lecithin (Epikuron® 145v, a phosphatidylcholine enriched fraction of soybean lecithin) was kindly supplied by Cargill Germany (Krefeld, Germany). Lipophilic dyes 3,3'-Diocetadecyloxacarbocyanine perchlorate (DiO), 1,1-Dioctadecyl-3,3,3,3-tetramethylindocarbocyanine iodide (DiI), 1,1'-dioctadecyl-3,3,3',3'-tetramethylindodicarbocyanine, 4-chlorobenzenesulfonate salt (DiD) and 1,1-dioctadecyl-3,3,3,3-tetramethylindotricarbocyanine iodide (DiR) were purchased from Santa Cruz Biotechnology (Heidelberg, Germany). Pancreatin from porcine pancreas was purchased from Merck (Darmstadt, Germany), dissolved in PBS (pH 7.4, Merck) and clarified by centrifugation at $5000 \times g$ for 10 min. Afterwards, the supernatant was filtered through $0.45 \mu\text{m}$ syringe filters to avoid interference of insoluble protein with dynamic light scattering measurements. Bovine serum albumin was purchased from Merck. MilliQ water with a resistivity of $18.2 \text{ M}\Omega$ at 25°C and passed through a filter with a pore size of $0.22 \mu\text{m}$ was used throughout. All other reagents used were of analytical grade if not specified otherwise.

2.2. Nanocapsule preparation

NCs and NEs were prepared by the solvent displacement technique first described by Calvo *et al.* [28], with some modifications. Briefly, an organic phase was formed by dissolving 40 mg of lecithin in 1 mL of ethanol, followed by the addition of $125 \mu\text{L}$ of Miglyol® 812 and lipophilic dyes DiO, DiI, DiD and/or DiR and adding ethanol up to 10 mL (in the original protocol of Calvo *et al.* [28], acetone is used in the organic phase instead of ethanol). This organic phase was immediately poured over 20 mL of the aqueous phase composed of a chitosan solution (0.5 mg/mL dissolved in water with 5 % stoichiometric with 1 M HCl excess). NCs were formed spontaneously due to the organic solvents diffusion and Marangoni effects of the organic phase [29]. Finally, the ethanol and part of the water were evaporated at 40°C under vacuum on a R-210 Rotavapor (Büchi Labortechnik GmbH, Essen, Germany) and the volume of the formulations was reduced to 10 mL. The association efficiency of dyes was determined using Vivaspin 2 ultrafiltration cartridge filters of polyethersulfone (PES) with a molecular weight cut-off of 30,000 kDa membrane purchased from Sartorius (Göttingen, Germany). To this end, NCs were diluted 1:100 in water and centrifuged through the ultrafiltration membranes at $4000 \times g$ for 10 min. Afterwards, absorbance scans were recorded of both the original dispersion and the filtrate (see details below).

2.3. Size, count rate and zeta potential measurements

Nanocapsules were characterized regarding their average size distribution, size polydispersity, count rate and zeta potential. Particle size, polydispersion index and count rate were determined by dynamic light scattering with non-invasive back scattering (DLS-NIBS) with a measurement angle of 173° . The autocorrelation functions were fitted with the default non-negative least squares (NNLS) fit to calculate the intensity size distribution plots and thus evaluate the Z-average diameter. For count rate, derived count rate values were used, which are independent from the used attenuator setting. The zeta potential was measured by mixed laser Doppler velocimetry and phase analysis light scattering (M3-PALS). A Malvern Zetasizer NanoZS (Malvern, UK) fitted with a red laser ($\lambda=632.8 \text{ nm}$) was used for both methods. The Zeta Sizer Software (v 7.12) was used to acquire and

evaluate the data. Samples were diluted 1:100 before the measurements, and these were carried out in triplicate.

2.4. Absorbance and fluorescence measurements

Absorbance measurements were recorded using a JASCO V-630 spectrophotometer (Groß-Umstadt, Germany) with 1 mL Hellma quartz cells (Mühlheim, Germany) with a light path length of 10 mm. We used absorbance measurements at 650 nm, where absorbance of the dyes (DiO-DiI) was negligible to determine the presence of NCs by turbidity of the dispersion.

Fluorescence measurements were performed using a Tecan Safire Microplate reader (Crailsheim, Germany). Due to potentially variable distances and orientations of donor and acceptor molecules in the core of the NCs, the standard equations to calculate FRET efficiencies do not apply. Therefore, relative values for FRET were calculated as the FRET index by measuring the donor emission in presence and absence of the donor using the following formula [30]:

$$F_I = 1 - \frac{I_{DA}}{I_D} \quad (1)$$

With F_I =FRET index, I_{DA} = donor emission in presence of acceptor and I_D = donor emission in absence of the acceptor.

2.5. Enzymatic degradation

Enzymatic degradation was studied using a constant concentration of NCs constant and varying the concentration of soluble fraction of pancreatin. Measurements were performed in PBS (pH 7.4) by dissolving the indicated amount of enzyme in PBS and diluting the NCs 1:100 in the PBS-enzyme solution. For measurements studying the influence of protein corona on the enzymatic degradation of NCs by pancreatin, the NCs were diluted 1:100 in a PBS solution containing 4% BSA except for the BSA-control for 20 min while derived count rate was recorded. After 20 min ($t=0$ min) pancreatin was added to the appropriate samples and the measurements continued for further 50 min. All derived count rate measurements were normalized to the timepoint $t= -20$ min to account for differences in derived count rate due to presence or absence of BSA.

3. Results and Discussion

3.1. Physicochemical characterization of NCs

Figure 1 shows the physical characteristics, namely the hydrodynamic diameter distribution and average zeta potential, of unloaded CS-coated NCs, NCs loaded with DiO, DiI, a 1:1 mixture of both DiO-loaded NCs and DiI-loaded NCs, and individual NCs labelled with both dyes. Of note, there were almost no differences in the size distribution curves (Figure 1a) when we compared the labelled and unlabelled NCs. The size of all different formulations oscillated around a Z-average hydrodynamic diameter of ~130 nm and zeta potential around ~+45 mV. Whereas mixing DiO- with DiI-loaded NCs resulted in a slightly elevated zeta potential (+50 mV) in comparison with their individual components, this increase could be related to the greater concentration of NCs in that sample. Regarding the association efficiency of the fluorescent dyes, we analysed the amount of unassociated fraction of each by centrifuging a DiO-DiI-NC dispersion over the PES membranes that prevented NCs to pass through the membrane (see Figure A1). By dividing the peak absorbance for DiO and DiI after filtration by peak absorbance before filtration we obtained association efficiencies of 98.28% and 98.37% respectively. We found similar association efficiencies for closely related dyes listed in Table A1 which allowed flexibility in the labelling into the near-infrared range.

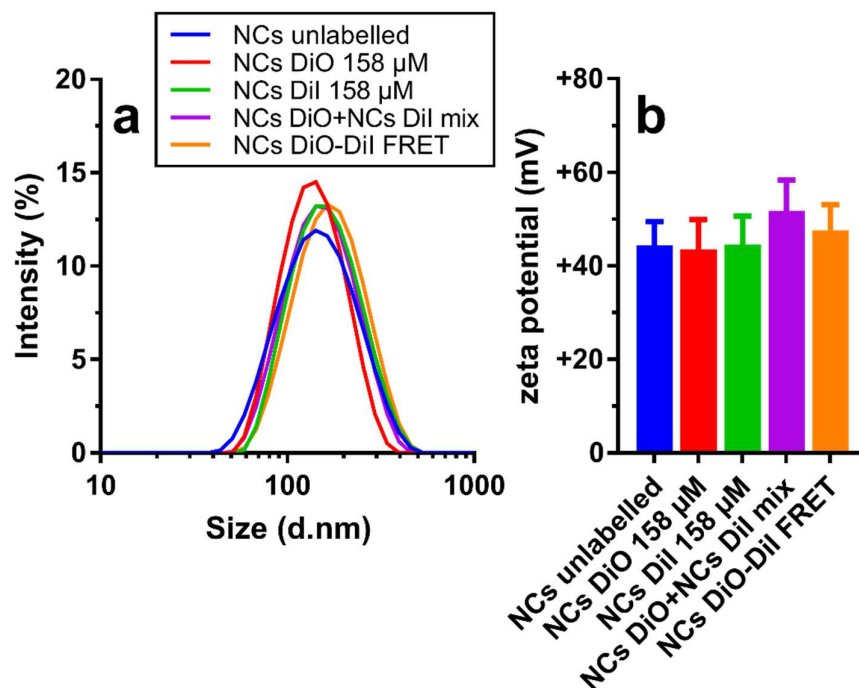


Figure 1. Physicochemical characterization of loaded and unloaded nanocapsules (NCs) by DLS-NIBS. a. Scattering intensity over size; and b. Zeta potential measured by diluting NC stocks 1:100 in water at 25 °C. Error bars represent zeta deviation in mV (n=3).

The similarity between the Z-average size and zeta potential values of the developed dye-loaded NCs and those previously reported for NCs formulations using chitosans of varying M_w (9572-279200 g.mol⁻¹) and DA (1.6 – 57%) [20,25,26,28], suggests that the overall physical characteristics of these NCs seem to be hardly affected by the amount and nature of the compound encapsulated in the oil core [25], as we have confirmed in this study for dye molecules that are more lipophilic than the previously studied molecules (e.g., capsaicin; predicted log P DiO: 18.13 [31]; log P capsaicin: 3.81 [32]). The overall higher log P of the two examined dye molecules probably increased their capacity to associate within the oily core of the NCs to close to 100%, a value greater than the ~60-96% association efficiency previously determined for capsaicin-loaded NCs [25,26].

Strong affinity of the fluorescent dye for the NCs is a desired property, since this abrogates the need to isolate labelled NCs from free dye molecules. Although in this case, the extremely low water solubility of the dye molecules poses a challenge when trying to determine its release *in vitro* using completely aqueous environments. However, in experiments including cells in culture or *in vitro* (i.e. in the presence of cell membranes), the lipophilic dye molecules are readily able to associate with cell membranes upon release from the nanoparticles [16,19].

Figure 2 shows a comparison of absorbance spectra and fluorescence emission spectra of equimolar mixtures DiO/DiI at varying total concentrations (between 4.9 μ M and 158 μ M) in ethanol on their own, and at similar concentrations and measured in PBS upon loading them in nanocapsules. The absorbance measurements have shown overall higher absorbance for the encapsulated dyes due to added turbidity by the NCs, although the dye peaks can easily be distinguished up to a dye concentration of 39.5 μ M. Of note, when diluted in ethanol, upon exciting DiO (λ_{ex} =484 nm), its fluorescence emission band (λ_{em} =505 nm) clearly increased with concentration. Also, a slight bleedthrough to the acceptor (DiI) was also noticed at λ =565 nm (Figure 2b). By contrast, upon encapsulation, the DiO emission was almost completely quenched even at the highest concentration, while the acceptor emission strongly increased when compared with measurements in ethanol. Direct

excitation of DiI ($\lambda_{\text{ex}}=549$ nm) in both environments, only showed slightly higher emission for the encapsulated dyes (Figure 2c).

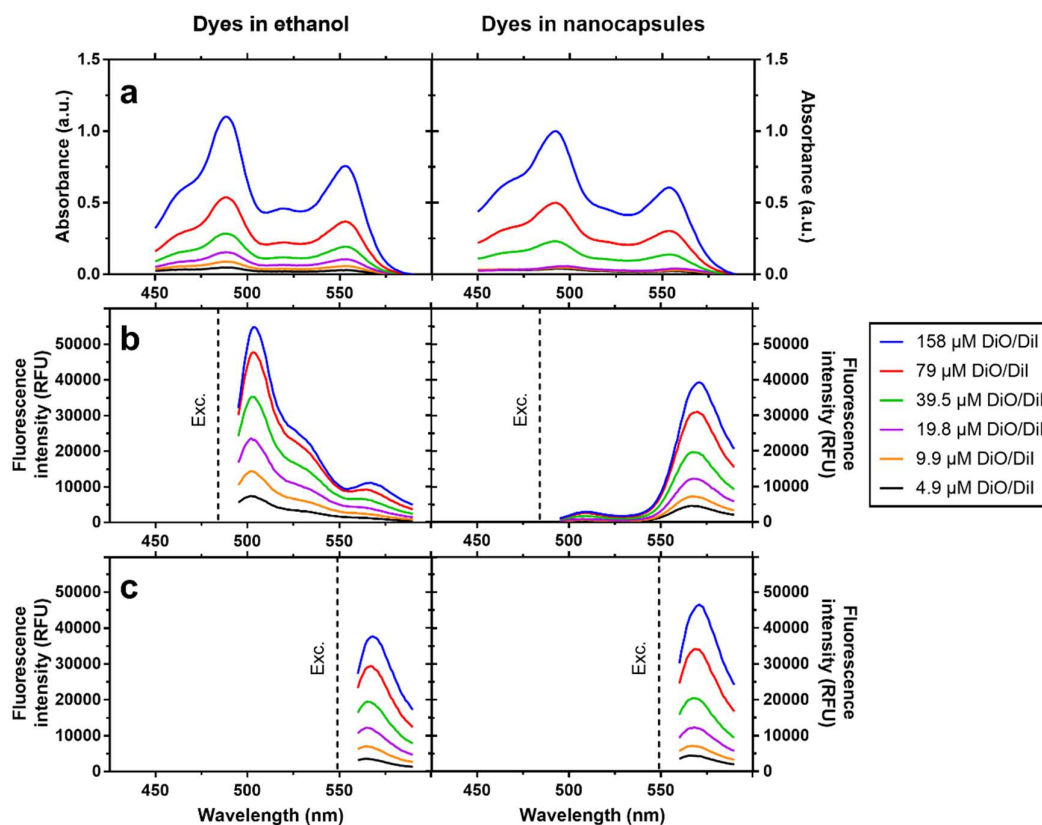


Figure 2. Spectroscopic properties of equimolar mixtures of DiO/DiI diluted in ethanol and equivalent concentrations of DiO/DiI in nanocapsules diluted in PBS (as shown in label). a. Absorbance spectra. b. Fluorescence emission spectra of DiO (donor), upon excitation (indicated by dotted line, $\lambda_{\text{ex}}=484$ nm). c. Fluorescence emission spectra of DiI upon excitation (indicated by dotted line, $\lambda_{\text{ex}}=549$ nm).

The extinction measured by spectrophotometry of a NC dispersion is the combined effect of absorbance and scattering. In our case, this is due to dye molecules with a strong absorbance in the visible spectrum and to the scattering caused by dispersed capsules. Given the sizes reported for the NCs above, scattering can be attributed to a mixture of Mie scattering ($R_H \sim \lambda$) and Rayleigh scattering ($R_H \sim \frac{1}{10}\lambda$) [33], assuming a previously reported spherical shape of the chitosan coated NCs [25]. From 450 to 590 nm R_H is greater than $\frac{1}{10}\lambda$ and Mie scattering predominates, meaning that all wavelengths of the visible spectrum are scattered equally. This results in a higher overall absorbance of the dilutions of the dyes in NCs compared to the dyes dissolved in ethanol. The strong fluorescence quenching observed when exciting the donor in presence of the acceptor in the case of NCs in comparison with the dyes dissolved in ethanol, while the acceptor emission is almost unaffected when excited directly, is an unequivocal hallmark of FRET at play. Due to the larger distance between dye molecules and overall greater mobility, no energy transfer can take place when dyes are diluted in ethanol, whereas the increased spatial proximity inside NCs (*i.e.*, oil volume was 80-fold smaller compared to aqueous medium at the highest dye concentration) provided an environment for efficient energy transfer between dye molecules. FRET labelling of nanoscale systems using lipophilic tracer dyes, with a similar approach and findings as in this study, has been adopted to examine synthetic polymeric particles [19] and polymer coated and uncoated synthetic nanoemulsions [17,18].

Figure 3 shows that upon mixing NCs containing either the donor or acceptor dyes, only a slight negative shift of the donor emission from that of the controls is obtained by measuring donor and acceptor NCs individually. By contrast, NCs containing both the donor and acceptor dyes showed the previously shown behaviour of donor quenching and enhanced acceptor emission, deviating strongly from the spectra obtained for donor and acceptor NCs.

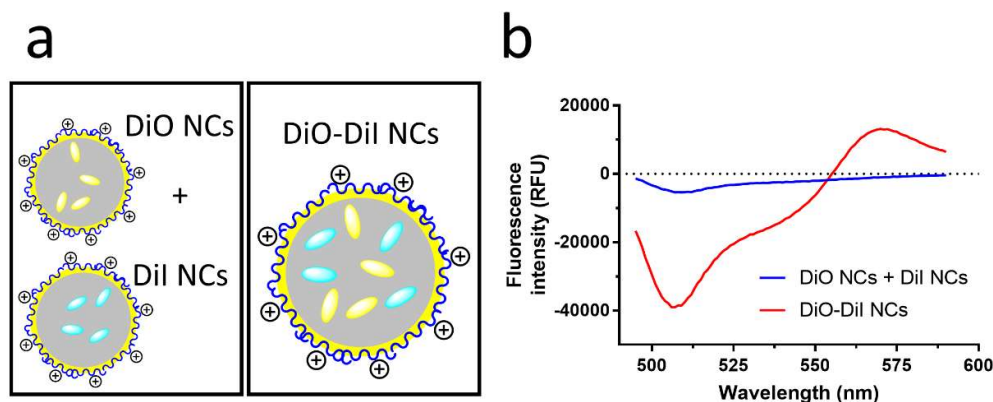


Figure 3. a. Scheme of a mix of DiO- and DiI-loaded nanocapsules (NCs) and DiO/DiI-loaded NCs, and b. Differential fluorescence spectra corrected by subtracting spectra of DiO NCs and DiI NCs from spectra of a physical blend of DiO- and DiI-loaded (0.158 μM) NCs and equimolar DiO/DiI-loaded NCs (0.158 μM) at the peak DiO excitation wavelength (λ_{ex} =484 nm).

The slight negative emission observed for the mixed donor- and acceptor-loaded NCs can be accounted for by the doubling in concentration of NCs needed to obtain the same concentration of both dyes in the dispersion. The NCs themselves scatter some of the incident and emitted light, while functioning as an inner filter, thus resulting in slightly lower fluorescence intensities [34]. The absence of FRET in this case indicates that the distance between capsules and hence, the distance between dye molecules, is too large (> 10 nm) to establish inter-capsular FRET. When both dyes are loaded into the same NC, intra-capsular FRET is at play.

3.2. Dissolution and enzymatic degradation of NCs

The idea of FRET-labelling of drug delivery nanoparticles stems in the difficulty of studying their fate and the release of the payload when administered to cells in culture or in *in vivo* models. In this paper, we present an *in vitro* model to examine the degradation of NCs. For this purpose, we first dissolved dye-loaded NCs at different water/ethanol mixtures and measured their FRET index, absorbance at 650 nm, and derived count rate and particle size (Figure 4). The FRET index (F_I), calculated by measuring the intensity of the donor in presence of the acceptor divided by the intensity of the donor in absence of the acceptor (Eq. 1), showed a decrease of F_I for the NCs that contain both dyes (donor and acceptor) in the same NCs, starting at ethanol concentrations higher than 0.4 (v/v) and decreased further up to pure ethanol (Fig 4a). By contrast, physical blends of NCs that contained either donor or acceptor and showed no FRET in an aqueous environment (Fig. 3b), exhibited FRET upon addition of ethanol at 0.4 and 0.6 (v/v) as shown in Figure 4a. Also, the derived count rate (DCR) showed a sharp decrease with increasing ethanol/water ratios. Indeed, the DCR changed from 100,000 to 200 kcps upon addition of ethanol at ratios of 0.45 and 0.6 (v/v). This change was also accompanied by an increase in the Z-average sizes and PDI, albeit under a less pronounced trend than the decrease in DCR. Absorbance (λ =650 nm) also showed a step decrease at ethanol/water ratios (Figure 4c) of 0.4 to 0.6 (v/v). Additionally, for NCs containing only DiO a slight shift of the DiO emission peak from 507 to 504 nm was observed from water to ethanol (Figure A2, Table A2).

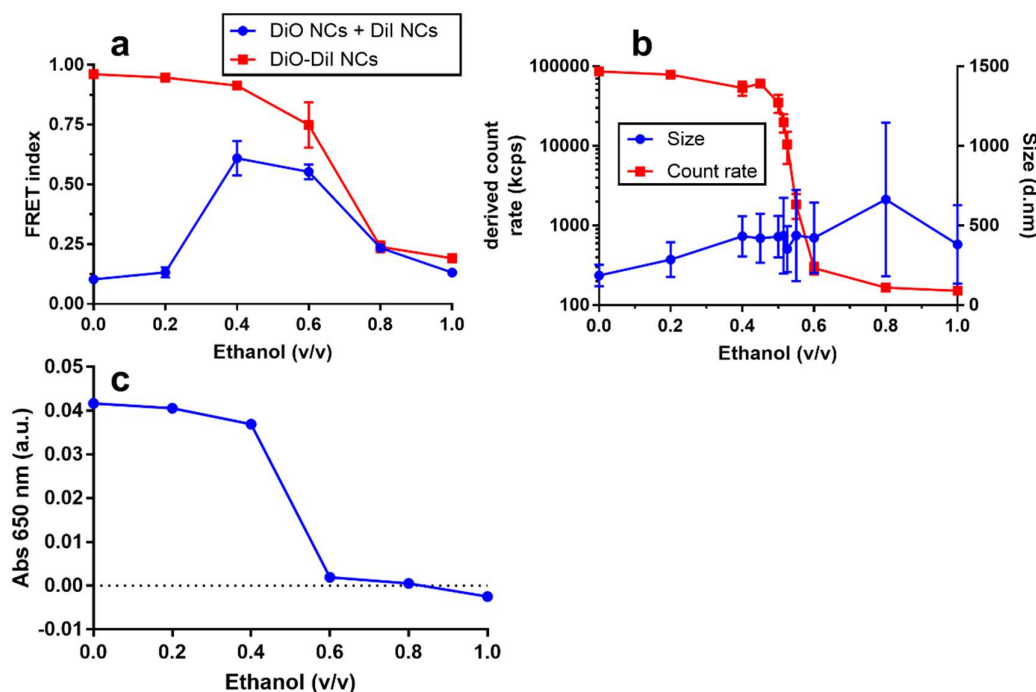


Figure 4. Effect of dissolution of fluorescently labelled nanocapsules (NCs) with increasing concentrations of ethanol, as characterized, by: a. FRET index of a physical blend of DiO- and DiI-loaded (0.158 μM) NCs and equimolar DiO/DiI-loaded NCs (0.158 μM); b. Derived count rate and Z-average size of equimolar DiO/DiI-loaded NCs (0.158 μM) by DLS-NIBS; and c. Absorbance ($\lambda=650$ nm) of equimolar DiO/DiI-loaded NCs. FRET index was calculated by measuring DiO (donor) emission in presence and absence of DiI (acceptor) using Eq. (1). Full spectra used to calculate FRET index are shown in Figure A1. Error bars represent standard deviation of triplicate measurements in all cases except for size, where error bars represent mean PDI width in nm of triplicate measurements.

The diminishing F_I at increasing ethanol ratios observed for DiO/DiI-loaded NCs, alongside with the change in the DiO peak emission wavelength and strongly decreasing count rate, all are diagnostic evidence that the NCs are dissolved as the ethanol/water ratio attains a critical value lying between 0.4 to 0.6 (v/v). It was interesting to see that for mixtures of DiO NCs and DiI NCs, that did not exhibit FRET in aqueous environments, did start to exhibit a FRET at ethanol/water ratios >0.2 (v/v), with maximal F_I values only slightly below those of DiO/DiI-loaded NCs. We suggest that this is the consequence of an increased solubility of the strongly hydrophobic dyes, originally trapped in the oily core of the NCs, in the ethanol/water mixed solvent and their resulting ability to interchange donor and acceptor dye molecules between NCs. Another possibility would be that the change in the overall polarity of the solvent brought by the addition of ethanol, leads to NCs to flocculate and coalesce, thus bringing donor and acceptor dyes in close contact. This proposal would be supported by the larger sizes attained with increasing ethanol ratios. The accompanying observed drastic drop in DCR at ethanol/water ratio of ~ 0.45 (v/v), could be interpreted as the result of the decrease in the overall number of coalescing particles. However, given that the size distribution measured by intensity of light scattering by DLS-NIBS is sensitive to both the size and the overall number of particles, we can only offer a speculative interpretation to these results. Other complementary techniques, such as nanotracking analysis (NTA) which are amenable for characterizing the particle size distribution by number, may be informative in this regard in future studies.

The putative interexchange of dye molecules between NCs at intermediate ethanol/water compositions could have interesting implications on the behaviour of lipophilic molecules during the formation of the NCs using the solvent displacement technique. NCs are originally formed at a 0.33

ethanol/water ratio and from our results it seems feasible that loaded molecules, especially more hydrophilic molecules than the dyes used for this study, could still be exchanging between NCs. Release experiments in aqueous media often poorly predict release of lipophilic drugs due the lack of acceptors like cell membranes and lipid particles that are present *in vivo*. Previous studies have shown the use of single dye transfer between different lipophilic carriers like liposomes and lipid nanoparticles [35,36]. The use of dyes capable of FRET with different fat solubility or loading in separate NCs to study transfer kinetics could remove the need for separation by centrifugation or flow cytometry.

Fluorescence emission intensity and peak shifts of lipophilic dyes are frequently used to determine critical micellar concentrations (CMC) of surfactants [37,38]. Even when our experimental set-up was not designed to measure surfactant CMCs (e.g. of lecithin), the observed DiO emission blue shift could be taken as indicator for a polarity change in its environment (i.e., a change from the strongly hydrophobic environment of the oily core of the NCs to the moderately hydrophobic environment of an ethanol-oil-lecithin solution). We did not observe a strong difference in fluorescence intensity between dye molecules associated with the NC oily core and NCs dissolved in ethanol that is usually observed in DiO and related dyes [38]. Differences in fluorescence intensity are not expected to be as strong between the oily core and ethanol as previously reported differences between aqueous solutions and organic solvents because of a lower difference in polarity. The absence of emission intensity differences could also be due to an inner filter effect of the NCs quenching the incident and emission light.

Figure 5 shows the results of enzymatic degradation of NCs using pancreatin. Notice in Figure 5a and b that the normalized DCR size measurements were found constant when no pancreatin was present, whereas at higher enzyme concentration the degradation velocity increased in a linear fashion, as indicated by a linearly increasing rate constant between 0.001 and 0.01 mg/mL added pancreatin concentration. NC size decreased in samples containing pancreatin, with greater reduction the higher the pancreatin concentration is, however, there was a large overlap between concentrations. In a separate experiment, we determined the influence of a protein corona (BSA) on the degradability of the NCs (Fig. 5d). Addition of 4% BSA yielded a slow decrease of DCR over 70 min, whereas in PBS without BSA count rate was stable until pancreatin was added. After addition of pancreatin in samples without BSA, count rate was rapidly reduced to below 10% after 10 min. By contrast, the decrease was lower in samples containing BSA, reaching about 40% after 10 min, even though it had already decreased to about 80% before the addition of pancreatin due to BSA alone.

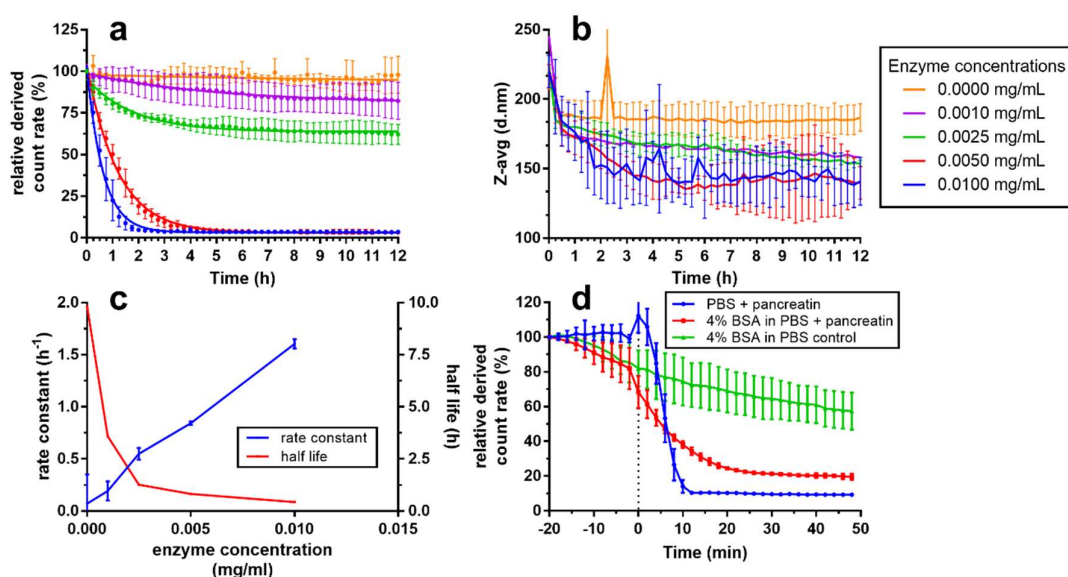


Figure 5. Enzymatic degradation of fluorescently labelled NCs using pancreatin measured by a. derived count rate relative to initial value and b. Z-avg particle size as measured by DLS. c. Rate constant and half-life in dependence of enzyme concentration calculated from a. d. Degradation of CS NCs as diluted 1:100 in PBS and PBS with 4% bovine serum albumin as measured by derived count rate relative to initial values. Pancreatin was added at timepoint zero (dotted line) to a final concentration of 0.1 mg/mL for non-control samples. All measurements were performed at 37°C (n=3).

Enzymatic digestion of nanoparticles is an important aspect to consider before their pre-clinical *in vivo* administration studies or clinical applications can be translated. This knowledge is necessary to ensure biocompatibility and full clearance of degraded components from the body's tissues and prevent accumulation to toxic levels. Depending on the route of administration, nanoparticles will be in contact with different enzymes, pancreatin being an example of a mixture of enzymes present in the gastrointestinal tract relevant to oral administration. Pancreatin is a mixture of α -amylase, lipase, phospholipase and protease, which should be able to degrade all components of the NCs except CS. In our experiments, however, we have shown that the CS-coated nanocapsules are readily degradable by pancreatin in PBS, as evidenced by the rapid reduction in DCR upon contact with the enzymes. Interestingly, the Z-average size did not decrease to zero even after 10 h, even when the DCR values reached their lowest level at a pancreatin concentration of 0.01 mg/mL. This could potentially be due to either a processive mode of enzymatic degradation, where there is a population of NCs that are destabilized and being degraded, while others remain intact, or a residual population of NCs that persists undegraded, which tend to be overestimated by the DLS measurements when compared to the decreasing size of NCs that are being degraded [39,40]. Unfortunately, unlike the dissolution of the NCs using ethanol, we were not able to probe the *in vitro* enzymatic degradation using the FRET approach presented in this paper, due to an overall decrease in fluorescence of both donor and acceptor upon enzymatic degradation of the NCs. Attempts to increase the solubility of the fluorescent dyes using surfactants failed due to inactivation of pancreatic enzymes. This could be addressed in future *in vitro* or *in vivo* experiments, given that cell membranes present could perform as acceptors for lipophilic dyes, as has been shown in previous studies [18].

The formation of a protein corona (PC) around nanoparticles is an expected phenomenon when they enter in contact with the proteins occurring in biological fluids. The influence of PC on the pharmacokinetics, biodistribution and biocompatibility has been of major interest recently [41–45]. Even though the combination of intestinal pancreatin and nanoparticles coated with a PC of BSA is an unrealistic *in vivo* scenario, simple *in vitro* models to elucidate the effects of protein adsorption on nanoparticles are in need to establish structure-function relationships prior to *in vivo* testing and clinical trials [42,46]. In our study, we found that adsorption of BSA slightly decreased the DCR of chitosan-coated NCs over time, probably due to an aggregation and sedimentation effect, given that NC size did not increase concomitantly. BSA was effective in forming a PC around NCs, which decreased accessibility of the NC to pancreatic enzymes, as detected by the lower degradation rates. We propose that DCR measurements recorded by DLS-NIBS are a readily accessible experimental parameter for quickly assessing either dissolution by solvents or enzymatic degradation of nanoparticles. Measurement of DCR allows a first screening of interactions of nanoparticles with model biological relevant environments, such as presence of pancreatic enzymes or BSA.

5. Conclusions

Altogether, our results have demonstrated that the labelling of CS-coated NCs using lipophilic tracer dyes did not affect their size distribution and zeta potential. When FRET donor (e.g. DiO) and acceptor (e.g. DiI) dye pair is co-loaded at equimolar ratios in NCs, the fluorescence emission of the donor dye is strongly quenched, whereas that of the acceptor dyes is enhanced when compared to the corresponding fluorescence of the dyes dissolved in ethanol. By contrast, no FRET was observed when dyes were loaded individually into NCs and mixed, thus indicating that FRET was only possible inside the oily core of the same NC, but not between different NCs. Dissolution of the NCs by partial addition of ethanol showed a decreasing FRET index for NCs loaded with both DiO and

DiI. This was accompanied by a decrease in count rate and decrease in turbidity. On the other hand, physical blends of NCs loaded with either DiO or DiI under an identical treatment, first increased in FRET index and then decreased in a similar manner as DiO-DiI loaded NCs, which we interpret either as an exchange of lipophilic dye molecules at intermediate ethanol concentrations, before the complete dissolution of the NCs at high ethanol concentrations, or as the consequence of flocculation and coalescence of the nanoparticles. Lastly, we showed that the NCs were degraded by pancreatin in a dose dependent manner and that a protein corona made from BSA decreased the rate of degradation. Ultimately, only further research, either *in vitro* or *in vivo*, will clarify the significance and allow to fully realize the application of the results presented here.

Author Contributions: Conceptualization, S.H., C.G., B.M. and F.M.G.; Methodology, S.H. and F.M.G.; Formal Analysis, S.H.; Investigation, S.H.; Resources, B.M. and F.M.G.; Writing-Original Draft Preparation, S.H. and F.M.G.; Writing-Review & Editing, S.H., C.G., B.M., F.M.G.; Visualization, S.H.; Supervision, C.G., B.M. and F.M.G.; Funding Acquisition, B.M. and F.M.G.

Funding: This project has received funding from the European Union's Seventh Framework Programme for research, technological development and demonstration under grant agreement n°613931. For the APC we acknowledge support by Open Access Publication Fund of University of Muenster.

Acknowledgments: We would like to thank Yadira Gonzalez Espinosa for the chitosan characterization by SEC-HPLC with MALLS-DRI-IV.

Conflicts of Interest: The authors declare no conflict of interest.

Appendix A

Table A1. Excitation and emission maxima and predicted LogP for dyes encapsulated in NCs for this study.

Tracer dye	Excitation maximum (nm) ¹	Emission maximum (nm) ¹	Log P ²
DiO	484	501	15.1
DiI	549	565	18.1
DiD	644	665	18.7
DiR	750	780	19.2

¹ Data according to manufacturer manual

² Software prediction[31]

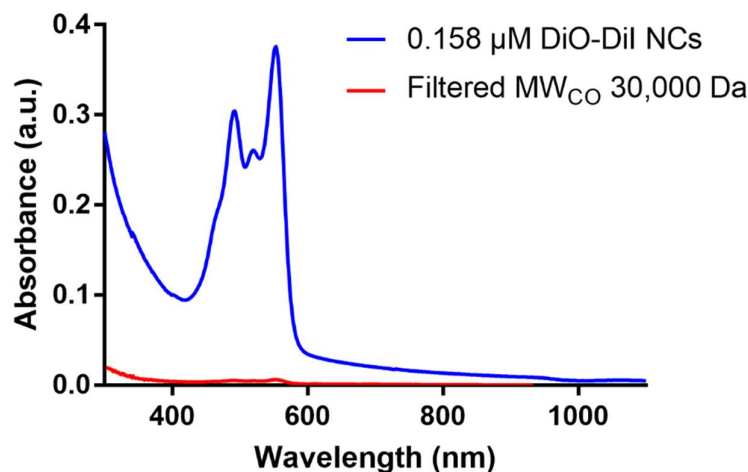


Figure A1. Absorbance scan of a 1:100 dilution of DiO-DiI NCs before (blue line) and after filtration (red line) through a 30,000 Da filter membrane for 10 min at 4000 x g.

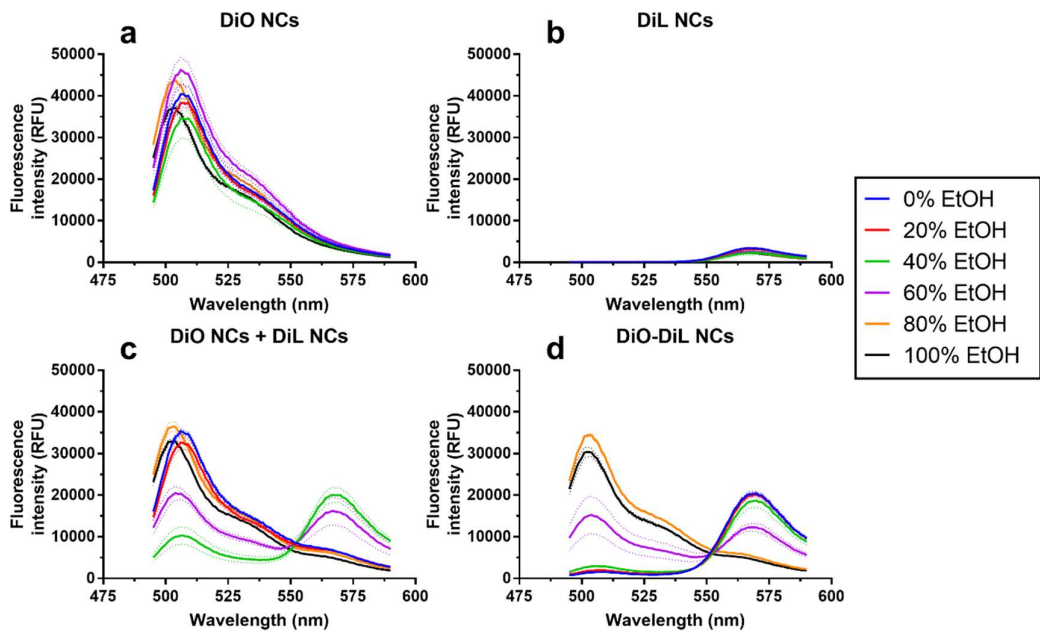


Figure A2. Emission spectra of a. DiO NCs, b. DiI NCs, c. DiO NCs + DiI NCs and d. DiO-DiI NCs at different Ethanol concentrations (v/v in water) upon excitation at $\lambda=484$ nm.

Table A2. Peak absorbance/peak emission of 1.59 μ M DiO/DiI NCs (1:100 dilution) at different ethanol fractions in water (see full emission spectra in Figure A2).

Ethanol fraction (v/v)	0	0.2	0.4	0.6	0.8	1	$\Delta 0-1$
DiO peak absorbance (nm)	491	491	491	488	488	487	4
DiO peak emission (nm)	507 ± 0.6	508 ± 1.7	507 ± 1.5	506 ± 0.0	504 ± 0.0	504 ± 0.6	3
DiI peak absorbance (nm)	552	553	553	550	551	551	1
DiI peak emission (nm)	567 ± 0.0	568 ± 1.0	569 ± 1.5	568 ± 1.2	566 ± 0.6	566 ± 0.6	1

References

1. Bozzuto, G.; Molinari, A. Liposomes as nanomedical devices. *Int. J. Nanomedicine* **2015**, *10*, 975–999, doi:10.2147/IJN.S68861.

2. Bulbake, U.; Doppalapudi, S.; Kommineni, N.; Khan, W. Liposomal formulations in clinical use: An updated review. *Pharmaceutics* **2017**, *9*.

3. An, F. F.; Zhang, X. H. Strategies for preparing albumin-based nanoparticles for multifunctional bioimaging and drug delivery. *Theranostics* **2017**, *7*, 3667–3689, doi:10.7150/thno.19365.

4. Varela-Moreira, A.; Shi, Y.; Fens, M. H. A. M.; Lammers, T.; Hennink, W. E.; Schiffelers, R. M. Clinical application of polymeric micelles for the treatment of cancer. *Mater. Chem. Front.* **2017**, *1*, 1485–1501, doi:10.1039/C6QM00289G.

5. Anselmo, A. C.; Zhang, M.; Kumar, S.; Vogus, D. R.; Menegatti, S.; Helgeson, M. E.; Mitragotri, S.

- Elasticity of nanoparticles influences their blood circulation, phagocytosis, endocytosis, and targeting. *ACS Nano* **2015**, *9*, 3169–3177, doi:10.1021/acsnano.5b00147.
6. Bertrand, N.; Wu, J.; Xu, X.; Kamaly, N.; Farokhzad, O. C. Cancer nanotechnology: The impact of passive and active targeting in the era of modern cancer biology. *Adv. Drug Deliv. Rev.* **2014**, *66*, 2–25, doi:10.1016/j.addr.2013.11.009.
 7. Shi, J.; Kantoff, P. W.; Wooster, R.; Farokhzad, O. C. Cancer nanomedicine: Progress, challenges and opportunities. *Nat. Rev. Cancer* **2017**, *17*, 20–37, doi:10.1038/nrc.2016.108.
 8. Matsumura, Y.; Maeda, H. A new concept for macromolecular therapeutics in cancer chemotherapy: mechanism of tumoritropic accumulation of proteins and the antitumor agent smancs. *Cancer Res.* **1986**, *46*, 6387–92.
 9. Maeda, H. SMANCS and polymer-conjugated macromolecular drugs: Advantages in cancer chemotherapy. *Adv. Drug Deliv. Rev.* **2001**, *46*, 169–185, doi:10.1016/S0169-409X(00)00134-4.
 10. Duncan, R. Drug-polymer conjugates: Potential for improved chemotherapy. *Anticancer. Drugs* **1992**, *3*, 175–210, doi:10.1097/00001813-199206000-00001.
 11. Nguyen, V. H.; Lee, B. J. Protein corona: A new approach for nanomedicine design. *Int. J. Nanomedicine* **2017**, *12*, 3137–3151, doi:10.2147/IJN.S129300.
 12. Grislain, L.; Couvreur, P.; Lenaerts, V.; Roland, M.; Deprez-Decampeneere, D.; Speiser, P. Pharmacokinetics and distribution of a biodegradable drug-carrier. *Int. J. Pharm.* **1983**, *15*, 335–345, doi:10.1016/0378-5173(83)90166-7.
 13. Lundquist, P.; Artursson, P. Oral absorption of peptides and nanoparticles across the human intestine: Opportunities, limitations and studies in human tissues. *Adv. Drug Deliv. Rev.* **2016**, *106*, 256–276, doi:10.1016/J.ADDR.2016.07.007.
 14. Truong, K.; Ikura, M. The use of FRET imaging microscopy to detect protein–protein interactions and protein conformational changes in vivo. *Curr. Opin. Struct. Biol.* **2001**, *11*, 573–578, doi:10.1016/S0959-440X(00)00249-9.
 15. Fuenzalida, J. P.; Weikert, T.; Hoffmann, S.; Vila-Sanjurjo, C.; Moerschbacher, B. M.; Goycoolea, F. M.; Kolkenbrock, S. Affinity protein-based FRET tools for cellular tracking of chitosan nanoparticles and determination of the polymer degree of acetylation. *Biomacromolecules* **2014**, *15*, 2532–2539, doi:10.1021/bm500394v.
 16. Lee, S. Y.; Tyler, J. Y.; Kim, S.; Park, K.; Cheng, J. X. FRET imaging reveals different cellular entry routes of self-assembled and disulfide bonded polymeric micelles. *Mol. Pharm.* **2013**, *10*, 3497–3506, doi:10.1021/mp4003333.
 17. Lainé, A. L.; Gravier, J.; Henry, M.; Sancey, L.; Béjaud, J.; Pancani, E.; Wiber, M.; Texier, I.; Coll, J. L.; Benoit, J. P.; Passirani, C. Conventional versus stealth lipid nanoparticles: Formulation and in vivo fate prediction through FRET monitoring. *J. Control. Release* **2014**, *188*, 1–8, doi:10.1016/j.jconrel.2014.05.042.

18. Gravier, J.; Sancey, L.; Hirsjärvi, S.; Rustique, E.; Passirani, C.; Benoît, J.-P.; Coll, J.-L.; Texier, I. FRET Imaging Approaches for in Vitro and in Vivo Characterization of Synthetic Lipid Nanoparticles. *Mol. Pharm.* **2014**, *11*, 3133–3144, doi:10.1021/mp500329z.
19. Zou, P.; Chen, H.; Paholak, H. J.; Sun, D. Noninvasive fluorescence resonance energy transfer imaging of in vivo premature drug release from polymeric nanoparticles. *Mol. Pharm.* **2013**, *10*, 4185–4194, doi:10.1021/mp4002393.
20. Santander-Ortega, M. J.; Peula-García, J. M.; Goycoolea, F. M.; Ortega-Vinuesa, J. L. Chitosan nanocapsules: Effect of chitosan molecular weight and acetylation degree on electrokinetic behaviour and colloidal stability. *Colloids Surfaces B Biointerfaces* **2011**, *82*, 571–580, doi:10.1016/j.colsurfb.2010.10.019.
21. Menchicchi, B.; Fuenzalida, J. P.; Bobbili, K. B.; Hensel, A.; Swamy, M. J.; Goycoolea, F. M. Structure of Chitosan Determines Its Interactions with Mucin. *Biomacromolecules* **2014**, *15*, 3550–3558, doi:10.1021/bm5007954.
22. Qin, X.; Engwer, C.; Desai, S.; Vila-Sanjurjo, C.; Goycoolea, F. M. An investigation of the interactions between an E. coli bacterial quorum sensing biosensor and chitosan-based nanocapsules. *Colloids Surfaces B Biointerfaces* **2017**, *149*, 358–368, doi:10.1016/j.colsurfb.2016.10.031.
23. Prego, C.; Torres, D.; Alonso, M. J. Chitosan nanocapsules: A new carrier for nasal peptide delivery. *J. Drug Deliv. Sci. Technol.* **2006**, *16*, 331–337, doi:10.1016/S1773-2247(06)50061-9.
24. Omwenga, E. O.; Hensel, A.; Shitandi, A.; Goycoolea, F. M. Chitosan nanoencapsulation of flavonoids enhances their quorum sensing and biofilm formation inhibitory activities against an E.coli Top 10 biosensor. *Colloids Surfaces B Biointerfaces* **2018**, *164*, 125–133, doi:10.1016/j.colsurfb.2018.01.019.
25. Goycoolea, F. M.; Valle-Gallego, A.; Stefani, R.; Menchicchi, B.; David, L.; Rochas, C.; Santander-Ortega, M. J.; Alonso, M. J. Chitosan-based nanocapsules: physical characterization, stability in biological media and capsaicin encapsulation. *Colloid Polym. Sci.* **2012**, *290*, 1423–1434, doi:10.1007/s00396-012-2669-z.
26. Kaiser, M.; Pereira, S.; Pohl, L.; Ketelhut, S.; Kemper, B.; Gorzelanny, C.; Galla, H.-J.; Moerschbacher, B. M.; Goycoolea, F. M. Chitosan encapsulation modulates the effect of capsaicin on the tight junctions of MDCK cells. *Sci. Rep.* **2015**, *5*, 10048, doi:10.1038/srep10048.
27. Peleteiro, M.; Presas, E.; González-Aramundiz, J. V.; Sánchez-Correa, B.; Simón-Vázquez, R.; Csaba, N.; Alonso, M. J.; González-Fernández, Á. Polymeric Nanocapsules for Vaccine Delivery: Influence of the Polymeric Shell on the Interaction With the Immune System. *Front. Immunol.* **2018**, *9*, 791, doi:10.3389/fimmu.2018.00791.
28. Calvo, P.; Remuñán-López, C.; Vila-Jato, J. L.; Alonso, M. J. Development of positively charged colloidal drug carriers: Chitosan-coated polyester nanocapsules and submicron-emulsions. *Colloid Polym. Sci.* **1997**, *275*, 46–53, doi:10.1007/s003960050050.
29. Gallardo, M.; Couarraze, G.; Denizot, B.; Treupel, L.; Couvreur, P.; Puisieux, F. Study of the mechanisms of formation of nanoparticles and nanocapsules of polyisobutyl-2-cyanoacrylate. *Int. J. Pharm.* **1993**, *100*,

- 55–64, doi:10.1016/0378-5173(93)90075-Q.
30. Berney, C.; Danuser, G. FRET or no FRET: a quantitative comparison. *Biophys. J.* **2003**, *84*, 3992–4010, doi:10.1016/S0006-3495(03)75126-1.
31. Klopman, G.; Li, J. Y.; Wang, S.; Dimayuga, M.; Wang, S.; Dimayuga, M. Computer Automated log P Calculations Based on an Extended Group Contribution Approach. *J. Chem. Inf. Comput. Sci.* **1994**, *34*, 752–781, doi:10.1021/ci00020a009.
32. Iida, T.; Moriyama, T.; Kobata, K.; Morita, A.; Murayama, N.; Hashizume, S.; Fushiki, T.; Yazawa, S.; Watanabe, T.; Tominaga, M. TRPV1 activation and induction of nociceptive response by a non-pungent capsaicin-like compound, capsate. *Neuropharmacology* **2003**, *44*, 958–967, doi:10.1016/S0028-3908(03)00100-X.
33. Hulst, H. C.; Van De Hulst, H. C. *Light Scattering by Small Particles*; John Wiley & Sons, Inc.: New York, 1958; Vol. 84; ISBN 0486642283.
34. Lakowicz, J. R. *Principles of Fluorescence Spectroscopy*; Lakowicz, J. R., Ed.; Springer US: Boston, MA, 2006; ISBN 978-0-387-31278-1.
35. Fahr, A.; Hoogevest, P. van; May, S.; Bergstrand, N.; S. Leigh, M. L. Transfer of lipophilic drugs between liposomal membranes and biological interfaces: Consequences for drug delivery. *Eur. J. Pharm. Sci.* **2005**, *26*, 251–265, doi:10.1016/j.ejps.2005.05.012.
36. Petersen, S.; Fahr, A.; Bunjes, H. Flow Cytometry as a New Approach To Investigate Drug Transfer between Lipid Particles. *Mol. Pharm.* **2010**, *7*, 350–363, doi:10.1021/mp900130s.
37. Mondal, S.; Ghosh, S. Role of curcumin on the determination of the critical micellar concentration by absorbance, fluorescence and fluorescence anisotropy techniques. *J. Photochem. Photobiol. B Biol.* **2012**, *115*, 9–15, doi:10.1016/j.jphotobiol.2012.06.004.
38. Peterson, A. M.; Tan, Z.; Kimbrough, E. M.; Heemstra, J. M. 3,3'-Diocetadecyloxacarbocyanine perchlorate (DiO) as a fluorogenic probe for measurement of critical micelle concentration. *Anal. Methods* **2015**, *7*, 6877–6882, doi:10.1039/C5AY01444A.
39. Fradinger, E. A.; Monien, B. H.; Urbanc, B.; Lomakin, A.; Tan, M.; Li, H.; Spring, S. M.; Condron, M. M.; Cruz, L.; Xie, C.-W.; Benedek, G. B.; Bitan, G. C-terminal peptides coassemble into Abeta42 oligomers and protect neurons against Abeta42-induced neurotoxicity. *Proc. Natl. Acad. Sci. U. S. A.* **2008**, *105*, 14175–80, doi:10.1073/pnas.0807163105.
40. Hinterwirth, H.; Wiedmer, S. K.; Moilanen, M.; Lehner, A.; Allmaier, G.; Waitz, T.; Lindner, W.; Lämmerhofer, M. Comparative method evaluation for size and size-distribution analysis of gold nanoparticles. *J. Sep. Sci.* **2013**, *36*, 2952–2961, doi:10.1002/jssc.201300460.
41. Aggarwal, P.; Hall, J. B.; McLeland, C. B.; Dobrovolskaia, M. A.; McNeil, S. E. Nanoparticle interaction with plasma proteins as it relates to particle biodistribution, biocompatibility and therapeutic efficacy. *Adv. Drug Deliv. Rev.* **2009**, *61*, 428–437.

42. Cedervall, T.; Lynch, I.; Lindman, S.; Berggård, T.; Thulin, E.; Nilsson, H.; Dawson, K. A.; Linse, S. Understanding the nanoparticle-protein corona using methods to quantify exchange rates and affinities of proteins for nanoparticles. *Proc. Natl. Acad. Sci. U. S. A.* **2007**, *104*, 2050–5, doi:10.1073/pnas.0608582104.
43. Dobrovolskaia, M. A.; Aggarwal, P.; Hall, J. B.; McNeil, S. E. Preclinical Studies To Understand Nanoparticle Interaction with the Immune System and Its Potential Effects on Nanoparticle Biodistribution. *Mol. Pharm.* **2008**, *5*, 487–495, doi:10.1021/mp800032f.
44. Naidu, P. S. R.; Norret, M.; Smith, N. M.; Dunlop, S. A.; Taylor, N. L.; Fitzgerald, M.; Iyer, K. S. The Protein Corona of PEGylated PGMA-Based Nanoparticles is Preferentially Enriched with Specific Serum Proteins of Varied Biological Function. *Langmuir* **2017**, *33*, 12926–12933, doi:10.1021/acs.langmuir.7b02568.
45. Stepien, G.; Moros, M.; Pérez-Hernández, M.; Monge, M.; Gutiérrez, L.; Fratila, R. M.; las Heras, M. de; Menao Guillén, S.; Puente Lantarote, J. J.; Solans, C.; Pardo, J.; de la Fuente, J. M. Effect of Surface Chemistry and Associated Protein Corona on the Long-Term Biodegradation of Iron Oxide Nanoparticles In Vivo. *ACS Appl. Mater. Interfaces* **2018**, *10*, 4548–4560, doi:10.1021/acsami.7b18648.
46. Bertrand, N.; Grenier, P.; Mahmoudi, M.; Lima, E. M.; Appel, E. A.; Dormont, F.; Lim, J.-M.; Karnik, R.; Langer, R.; Farokhzad, O. C. Mechanistic understanding of in vivo protein corona formation on polymeric nanoparticles and impact on pharmacokinetics. *Nat. Commun.* **2017**, *8*, 777, doi:10.1038/s41467-017-00600-w.