

Supplementary Material for

New biocompatible polyurethanes: synthesis, structural characterization and cytotoxicity

Barbara S. Gregorí Valdés^{1,3}, Clara S. B. Gomes², Pedro T. Gomes^{2,*}, José R. Ascenso^{2,*},
Hermínio P. Diogo², Lúcia M. Gonçalves³, Rui Galhano dos Santos¹, Helena M. Ribeiro³,
João C. Bordado^{1,*}

¹ CERENA, Departamento de Engenharia Química, Instituto Superior Técnico, Universidade de Lisboa, Av. Rovisco Pais, 1049-001 Lisboa, Portugal


² Centro de Química Estrutural, Departamento de Engenharia Química, Instituto Superior Técnico, Universidade de Lisboa, Av. Rovisco Pais, 1049-001 Lisboa, Portugal

³ Research Institute for Medicine and Pharmaceutical Science (iMed.Ulisboa), Faculty of Pharmacy, Universidade de Lisboa, Av. Prof. Gama Pinto, 1649-003 Lisboa, Portugal


E-mails: pedro.t.gomes@tecnico.ulisboa.pt, jose.ascenso@tecnico.ulisboa.pt, jcbordado@tecnico.ulisboa.pt

Atom numbering in chain fragments of polyurethanes used in NMR assignments


- Fragment with two monomers (Isosorbide and IPDI) of the chain of polyurethanes **PU1–PU3**:

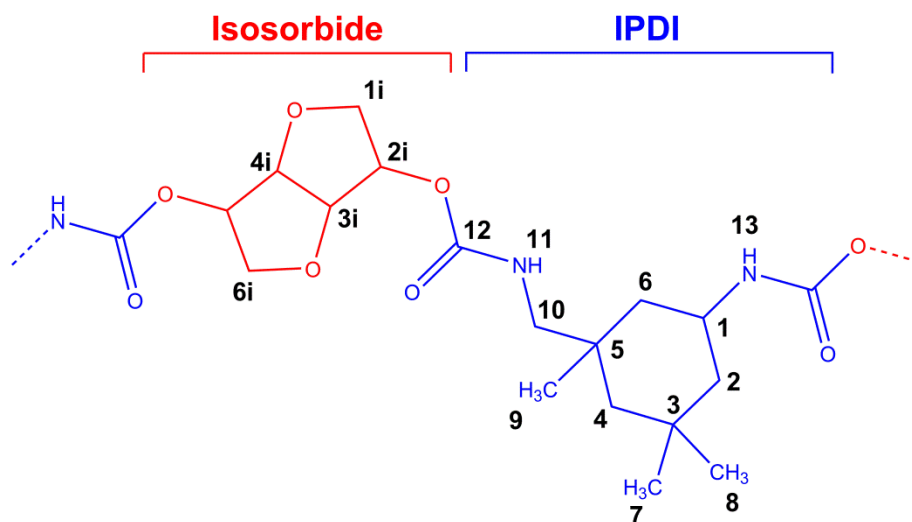

Fragment with two monomers (Isosorbide and HDMI) of the chain of polyurethane **PU4**:

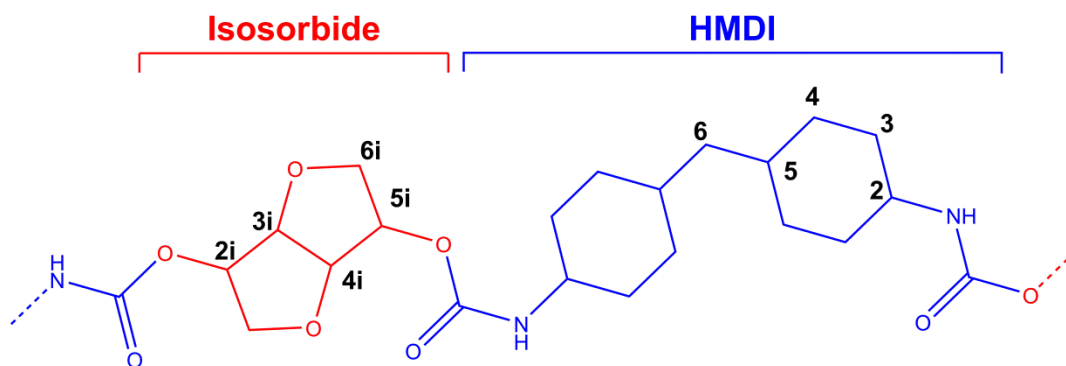

Average polypropyleneglycol (PPG) soft-blocks in **PU1–PU4**:

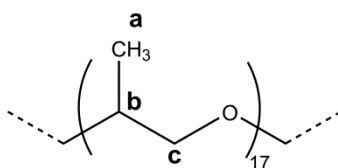

NMR data

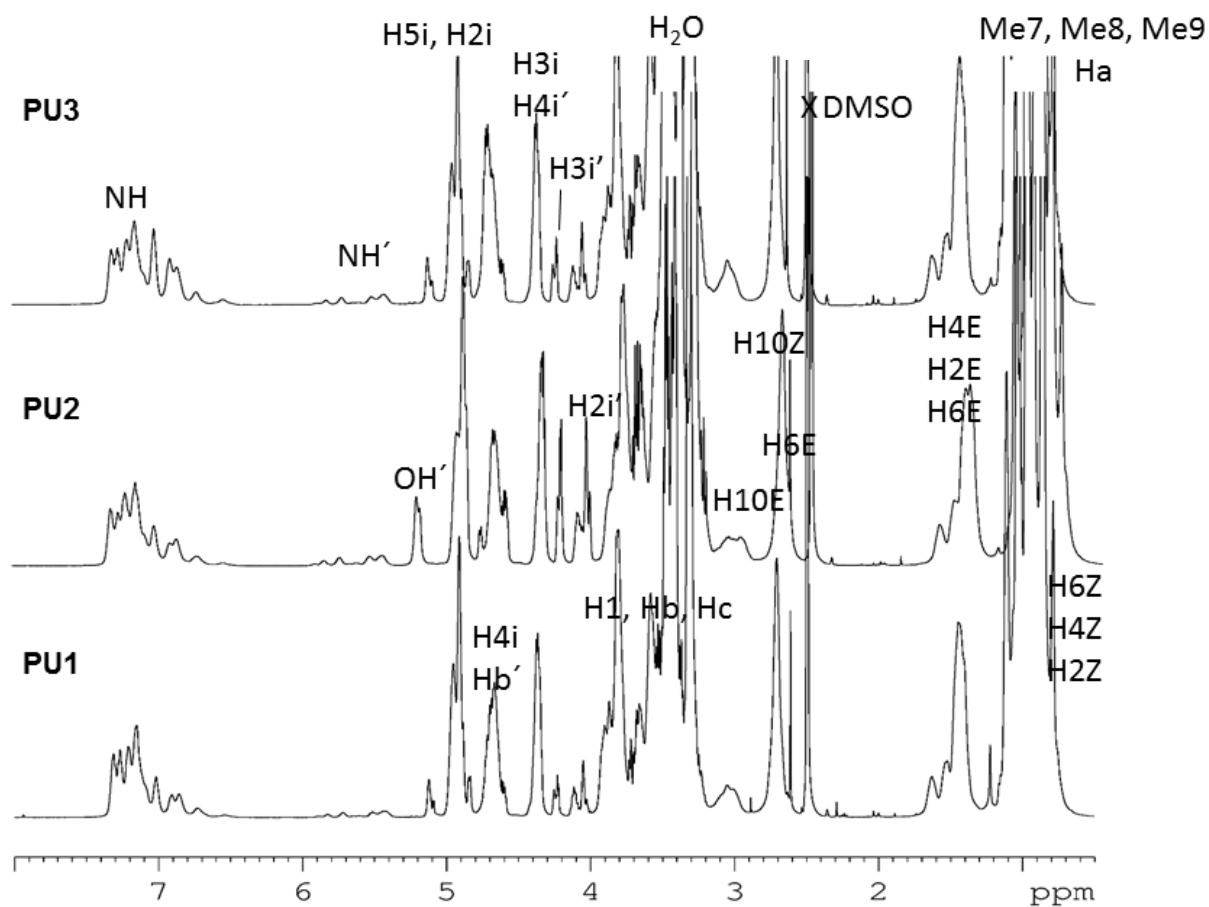


Figure S1. Assignment of the ^1H NMR spectra of polyurethanes **PU1**, **PU2** and **PU3** in $\text{DMSO-}d_6$. Protons of terminal groups are primed. Z and E refer to the *cis* and *trans* isomers of IDPI, respectively.

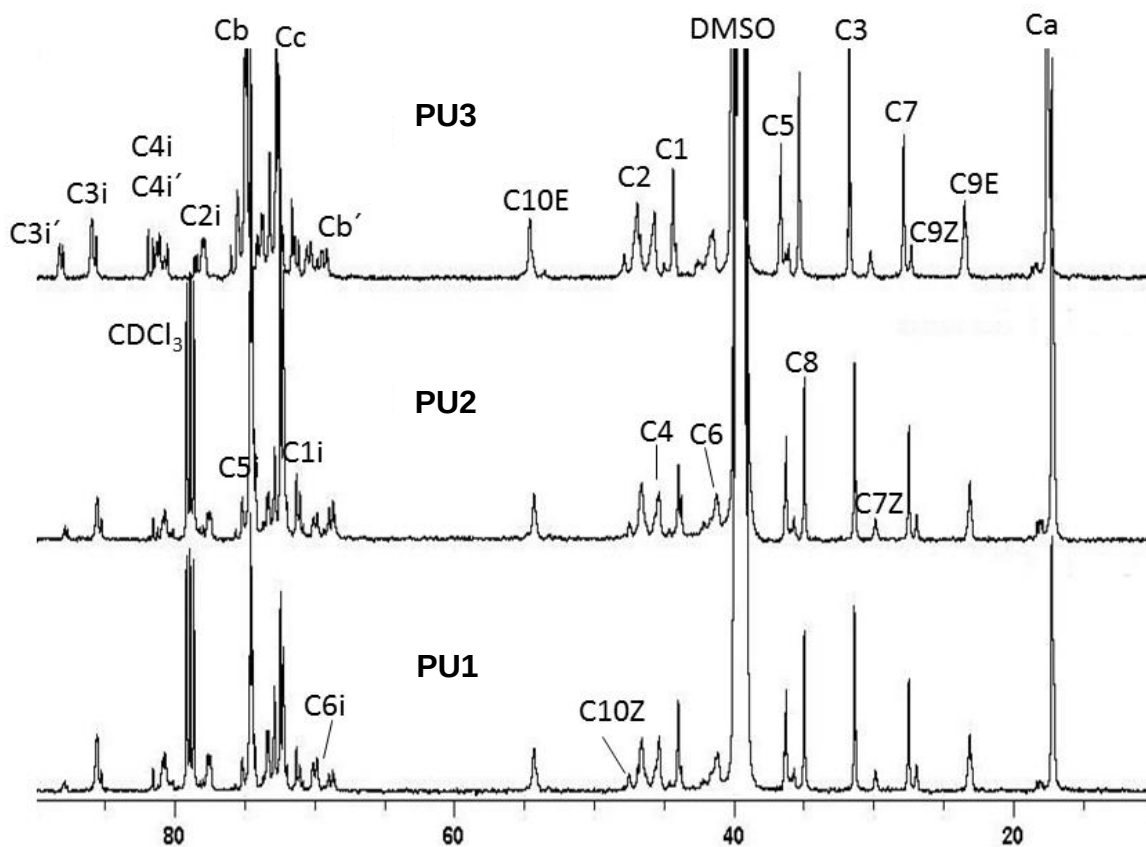


Figure S2. Assignment of the $^{13}\text{C}\{^1\text{H}\}$ NMR spectra of Isosorbide and IPDI repeating units of polyurethanes **PU1**, **PU2** and **PU3** in $\text{DMSO}-d_6$. Carbons of terminal groups are primed. Z and E refer to the *cis* and *trans* isomers of IDPI, respectively.

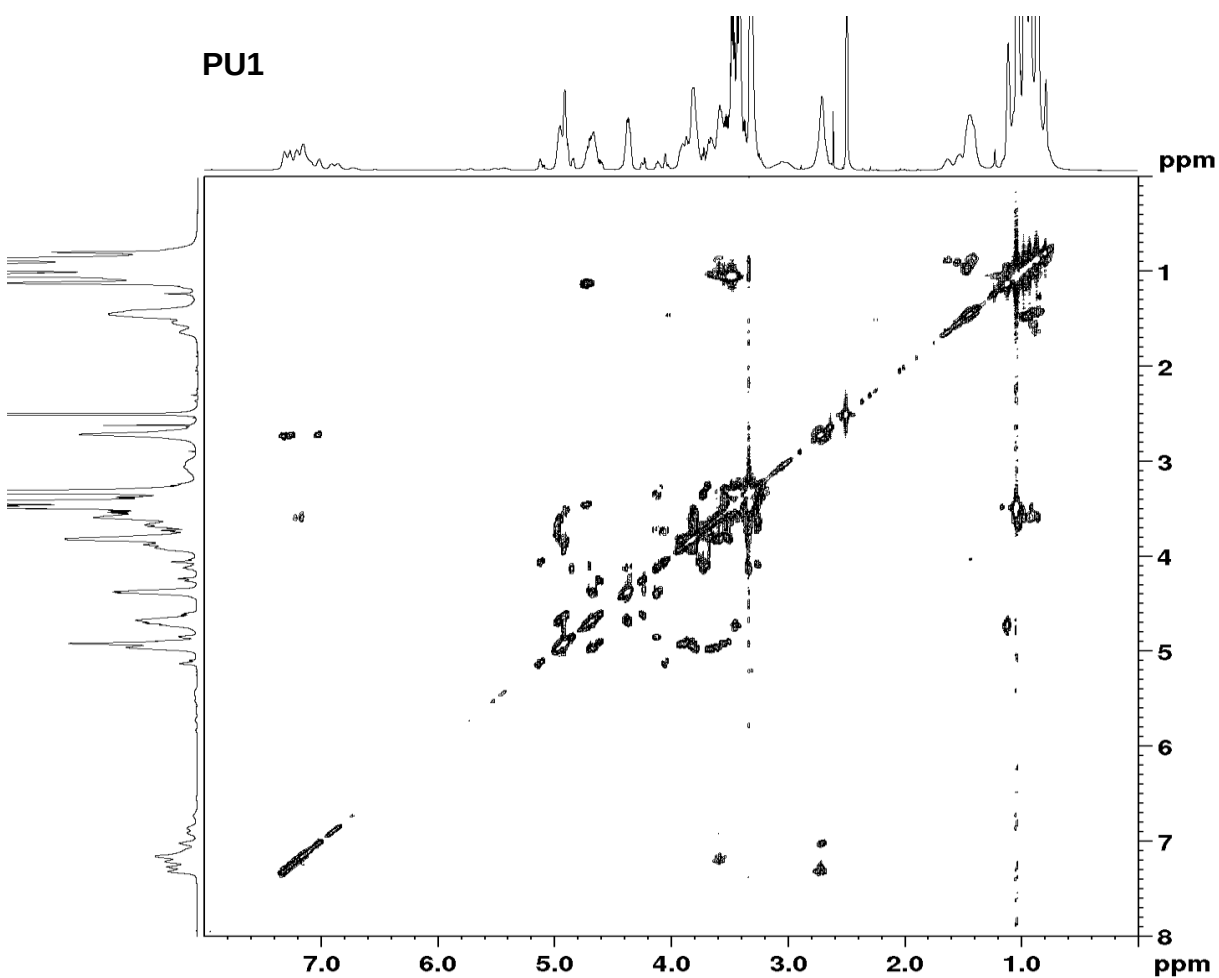


Figure S3. COSY spectrum of **PU1** in DMSO- d_6 .

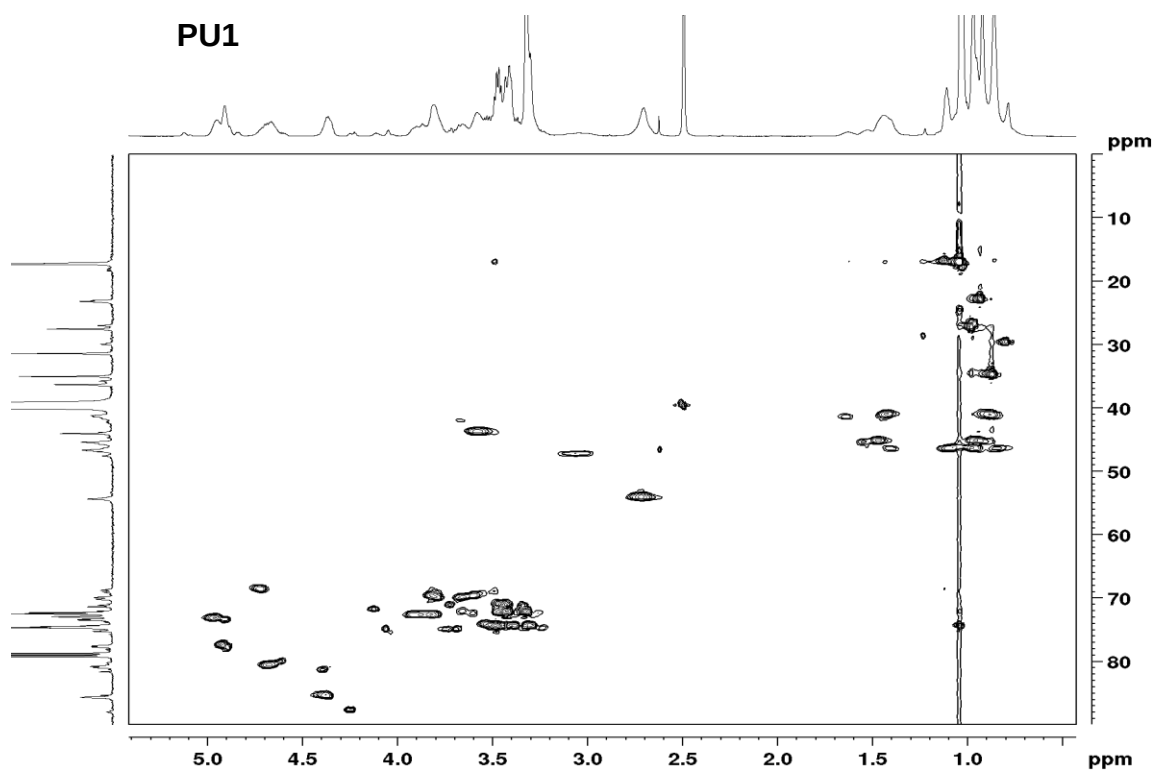


Figure S4. HSQC spectrum of **PU1** in DMSO- d_6 .

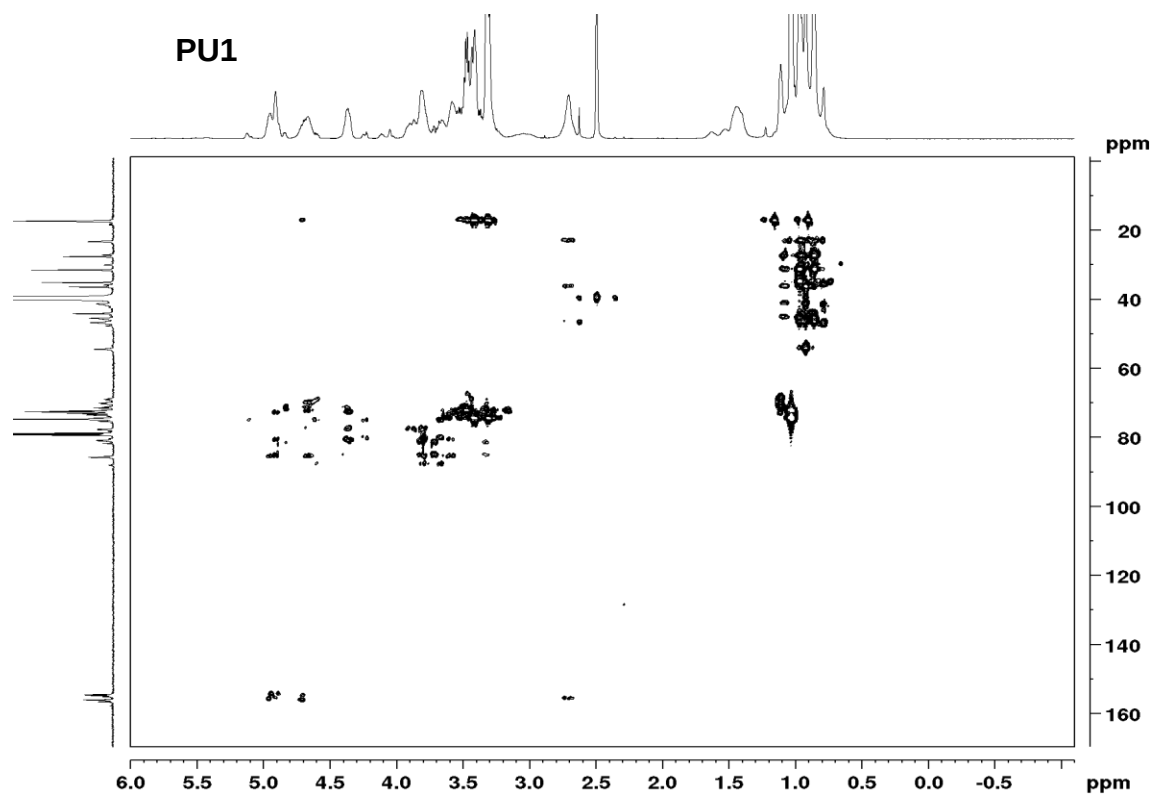


Figure S5. HMBC spectrum of **PU1** in DMSO- d_6 .

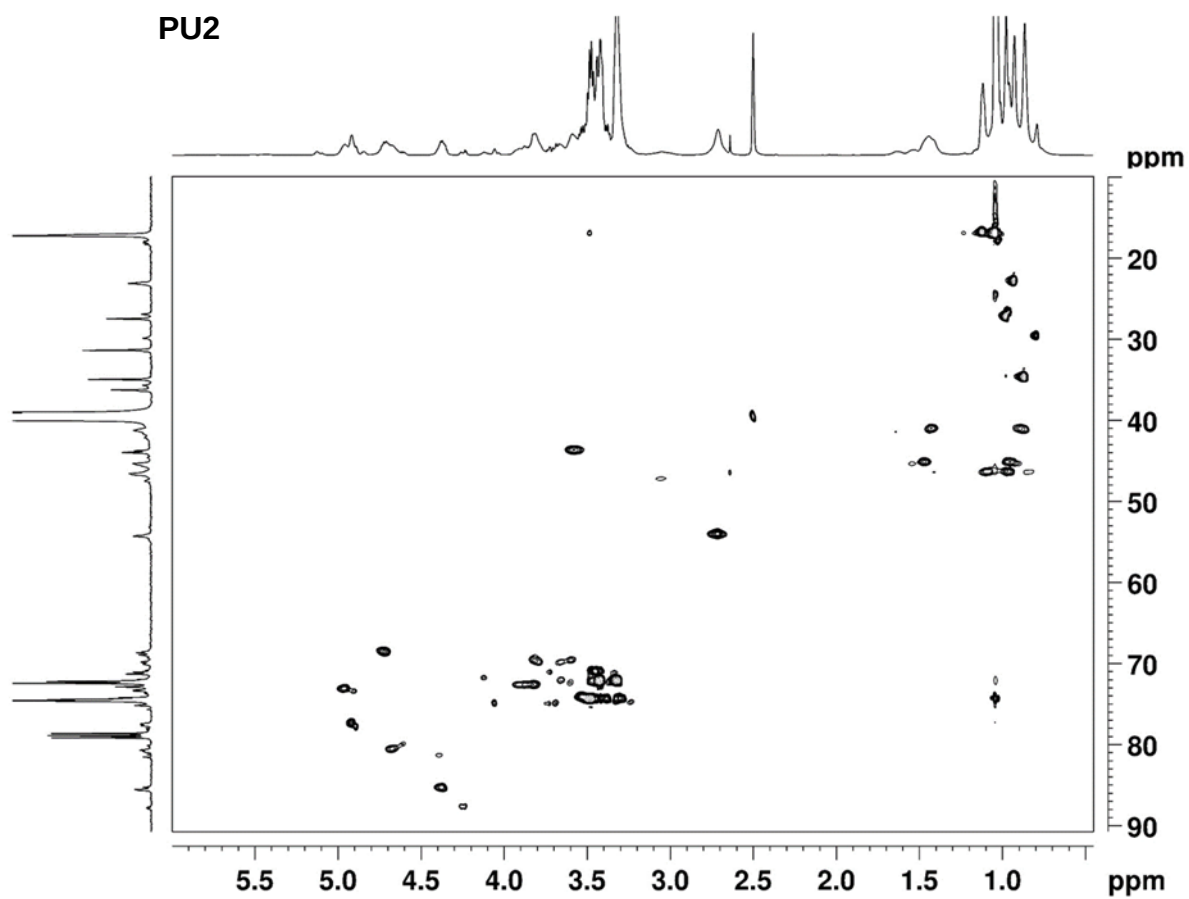


Figure S6. HSQC spectrum of **PU2** in DMSO- d_6 .

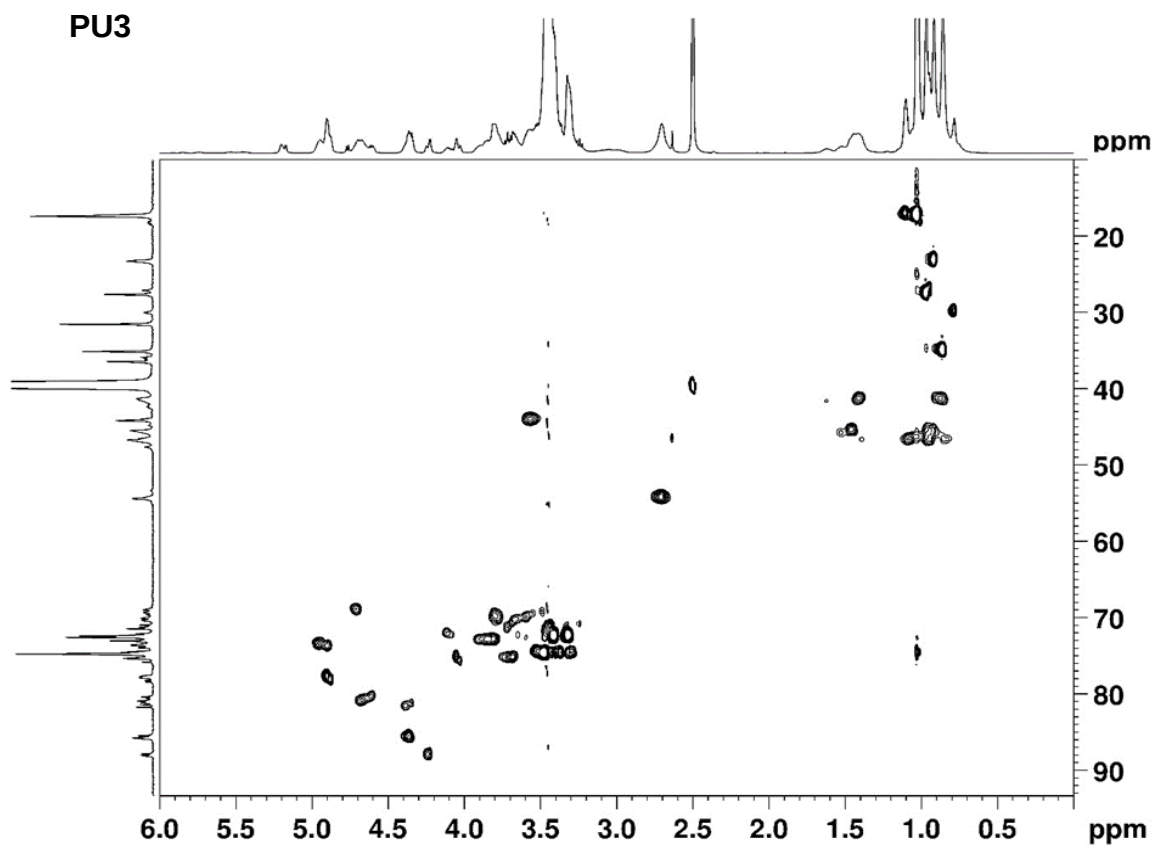


Figure S7. HSQC spectrum of **PU3** in DMSO- d_6 .

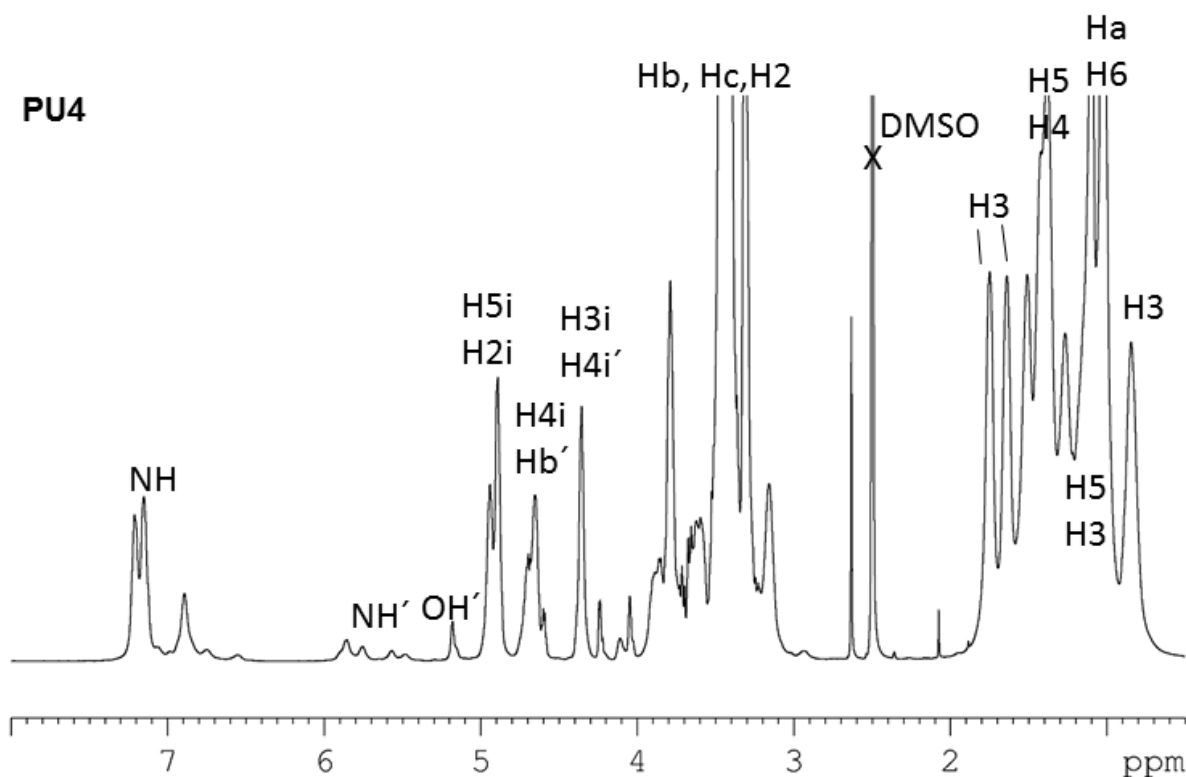


Figure S8. Assignment of the ^1H NMR spectrum of polyurethane **PU4** in $\text{DMSO-}d_6$. Protons of terminal groups are primed.

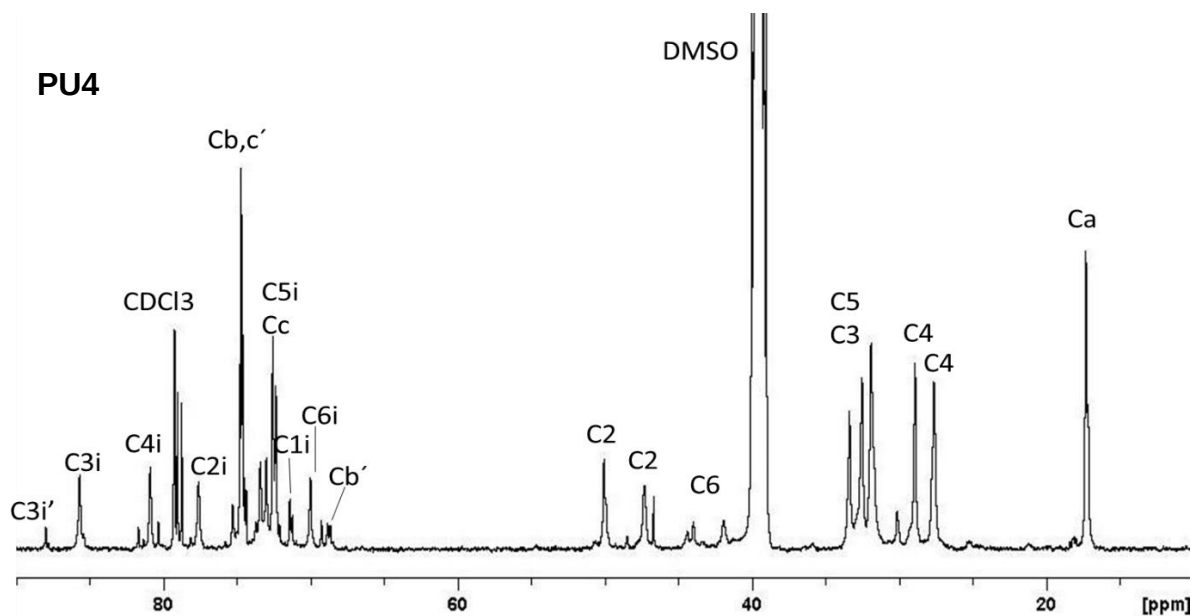


Figure S9. Assignment of the $^{13}\text{C}\{^1\text{H}\}$ NMR spectrum of Isosorbide and HMDI repeating units of polyurethane **PU4** in $\text{DMSO-}d_6$. Carbons of terminal groups are primed.

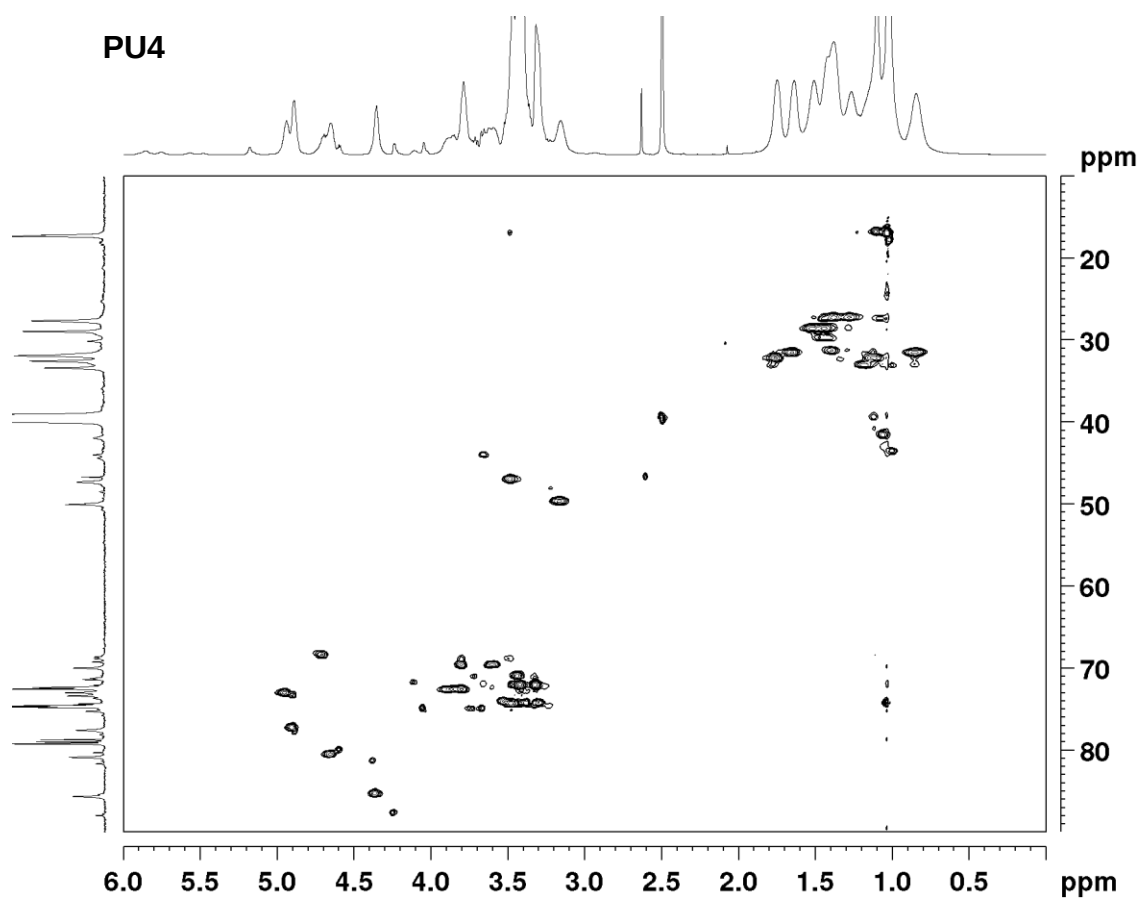


Figure S10. HSQC spectrum of **PU4** in DMSO- d_6 .

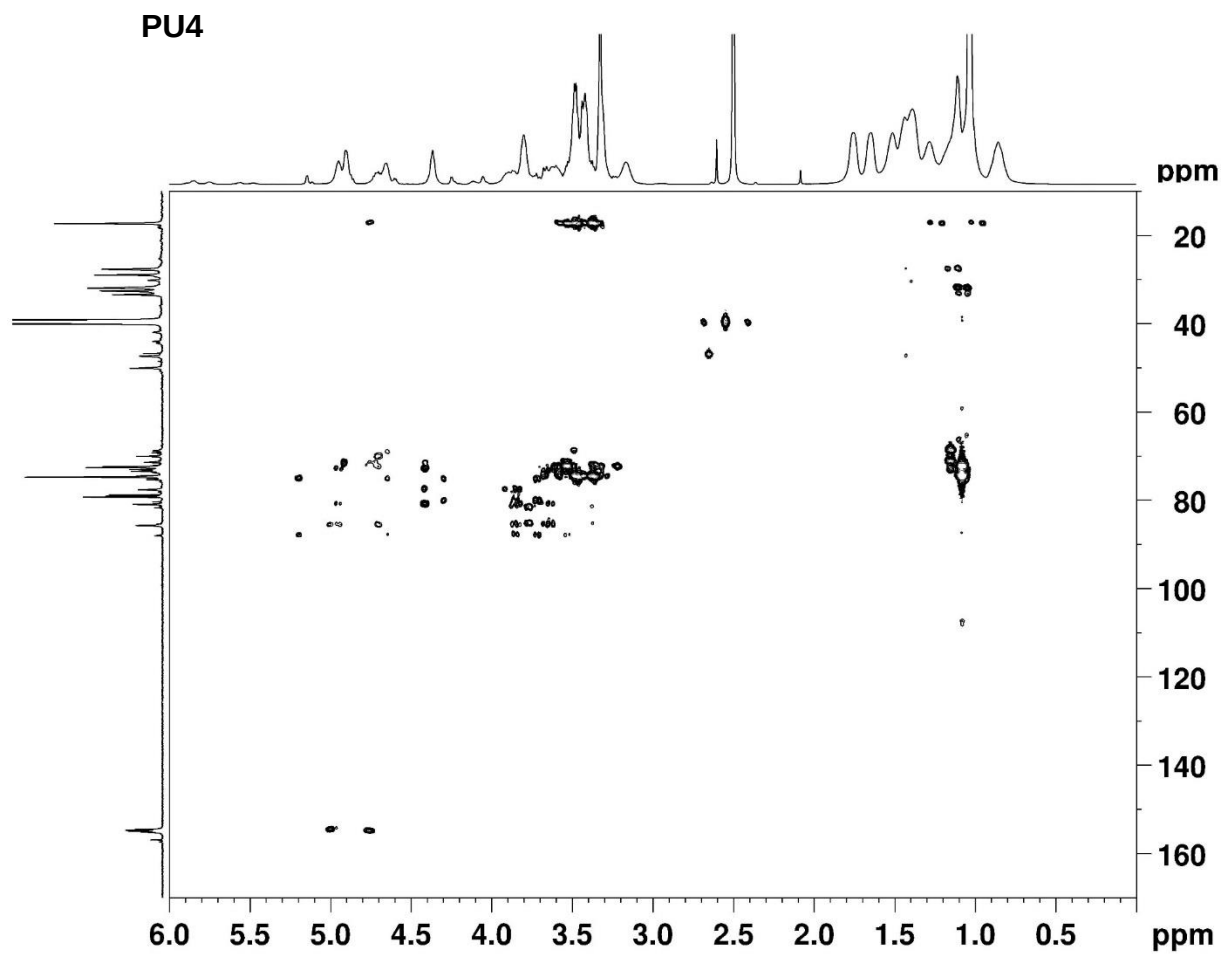


Figure S11. HMBC spectrum of **PU4** in DMSO- d_6 .

Determination of self-diffusion coefficients D_0

The duration of the gradient pulses (δ) and the diffusion time (Δ) were optimized in order to obtain a residual signal of 2-5 % at the maximum gradient strength. The values used were 3.4 ms for the duration of the gradient pulses and 110 to 140 ms for the diffusion time. The gradient strength was incremented from 2% to 98% in a linear ramp with 16 steps. A delay of 15s between echoes was used. The gradients were previously calibrated using 99.9% pure D_2O as a standard. Each diffusion experiment produces a pseudo array of 16 spin echoes that were first FT processed in the t_2 dimension using a LB of 0.2 Hz to generate a series of 1D spectra that were phased and baseline corrected prior to extraction of the diffusion coefficient by Gaussian fittings using the T_1/T_2 relaxation module of Topspin 3.1.

Table S1. Average diffusion coefficient D in relation to the concentration of **PU1**.

[PU1] (g/mL)	$D \times 10^{11} \text{ (m}^2/\text{s}^{-1}\text{)}$
3.42×10^{-4}	7.19
7.46×10^{-4}	7.25
1.74×10^{-3}	6.62
3.42×10^{-3}	6.61
1.14×10^{-2}	6.37

Table S2. Average diffusion coefficient D in relation to the concentration of **PU2**.

[PU2] (g/mL)	$D \times 10^{11} \text{ (m}^2/\text{s}^{-1}\text{)}$
3.66×10^{-4}	4.61
7.56×10^{-4}	4.17
1.62×10^{-3}	4.07
3.24×10^{-3}	4.04
1.22×10^{-2}	3.87

Table S3. Average diffusion coefficient D in relation to the concentration of **PU3**.

[PU3] (g/mL)	$D \times 10^{11} \text{ (m}^2/\text{s}^{-1}\text{)}$
3.24×10^{-4}	6.62
7.56×10^{-4}	6.91
1.62×10^{-3}	6.61
3.24×10^{-3}	6.01
1.08×10^{-2}	6.01

Table S4. Average diffusion coefficient D in relation to the concentration of **PU4**.

[PU4] (g/mL)	$D \times 10^{11} \text{ (m}^2/\text{s}^{-1}\text{)}$
2.94×10^{-4}	4.52
6.84×10^{-4}	4.08
1.47×10^{-3}	4.31
2.94×10^{-3}	4.62
9.80×10^{-3}	3.32

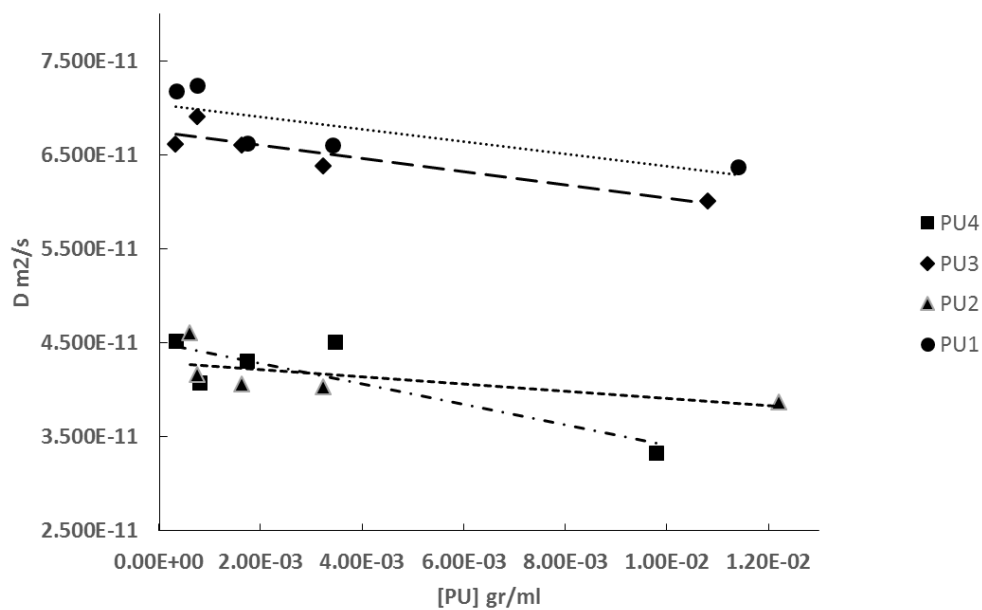


Figure S12. Plots of diffusion coefficients vs. concentrations of PUs.

GPC/SEC chromatograms

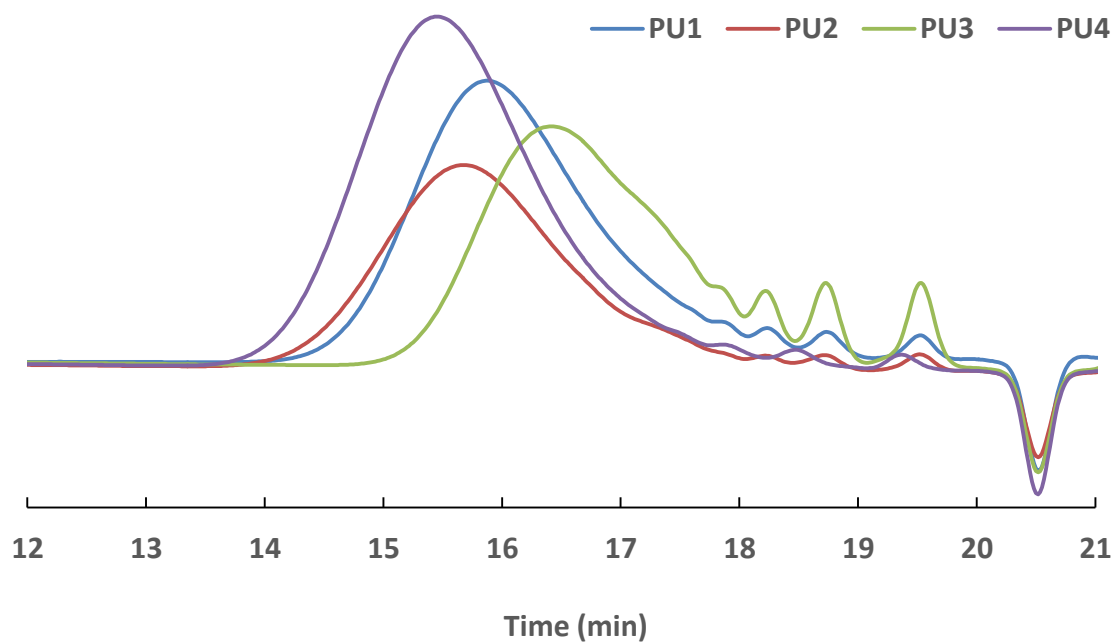


Figure S13. GPC/SEC chromatograms of **PU1-PU4**.

Average PUs compositions from ^{13}C NMR

Table S5. Average monomer composition of **PU1**.

Carbons	Relative area	No. carbons
CO	12.2	11 - 12 carbonyls
C3i'	0.5	1
C4i'	0.8	1 terminal iosorbides
C2i	4.2	4
C6i	4.1	4 main chain isosorbides
C4	5.8	6
C1	5.8	6
C8	6.5	6-7
C3	6.5	6-7
C7	6.3	6
C9	6.4	6 isocyanates
Cb	17.6	17 PPG monomers

Table S6. Average monomer composition of **PU2**.

Carbons	Relative area	No. carbons
CO	12.8	12-13 carbonyls
C3i'	1.9	2 terminal isosorbides
C3i	3.8	4
C4i	3.0	3
C2i	3.3	3
C6i	3.5	3 - 4 main chain isosorbides
C10	6.5	7
C2	8.2	8
C4	6.7	7
C1	6.7	7
C8	6.5	7
C3	6.7	7
C7	6.7	7
C9Z, C9E	6.6	6
Ca	34	34 2 PPG blocks, 17 monomers each

Table S7. Average monomer composition of **PU3**.

Carbons	Relative area	No. carbons
C3i'	1.9	2 terminal isosorbides
CO	10.8	11 carbonyls
C3i	3.9	4
C2i	4.0	4
Cb	17.1	17
C1i	4.1	4
C6i	3.8	4 main chain isosorbides
C4	5.4	5
C1	5.6	6.
C8	6.2	6
C3	6.4	6
C7	6.0	6
C9	6.2	6 isocyanates
Ca	17	17 PPG monomers

Table S8. Average monomer composition of **PU4**.

Carbons	Relative area	No. Carbons
CO	11.8	12 carbonyls
C3i'	0.6	1 terminal isosorbides
C3i	4.3	4
C4i, C4i'	4.6	5
C2i	4.2	4
Cb	17.0	17
C6i	3.7	4 main chain isosorbides
C6	5.2	5
C2	5.3	5
C2	6.1	6
C4	13.6	14
C4	14.2	14 6 isocyanates, one is terminal
Ca	17.0	17 PPG monomers