

Article

Assessment of Thermal Stresses in Asphalt Mixtures at Low Temperatures Using the Tensile Creep Test and the Bending Beam Creep Test

Marek Pszczola ^{1,*}, Mariusz Jaczewski ¹ and Cezary Szydlowski ¹

¹ Faculty of Civil and Environmental Engineering, Gdansk University of Technology, 80-233 Gdansk, Poland; mpszczol@pg.edu.pl; marjacze@pg.edu.pl, cezszydl@pg.edu.pl;

* Correspondence: mpszczol@pg.edu.pl; Tel.: +48 58 347-27-82

Abstract: Thermal stresses belong to the leading factors that influence low-temperature cracking behavior of asphalt pavements. During winter, when temperature drops to significantly low values, tensile thermal stresses develop as a result of pavement contraction. Creep test methods can be suitable for the assessment of low-temperature properties of asphalt mixtures. To evaluate the influence of creep test methods on the obtained low-temperature properties of asphalt mixtures, three point bending and uniaxial tensile creep tests were applied and the master curves of stiffness modulus were analyzed. On the basis of creep test results, rheological parameters describing elastic and viscous properties of the asphalt mixtures were determined. Thermal stresses were calculated and compared to tensile strength of the material to obtain the failure temperature of the analyzed asphalt mixtures. It was noted that lower strain values of creep curves were obtained for the Tensile Creep Test (TCT) than for the Bending Beam Creep Test (BBCT), especially at lower temperatures. Results of thermal stress calculations indicated that higher reliability was obtained for the viscoelastic Monismith method based on the TCT results than for the simple quasi-elastic solution of Hills and Brien. The highest agreement with the TSRST results was also obtained for the Monismith method based on the TCT results. No clear relationships were noted between the predicted failure temperature and different methods of thermal stress calculations.

Keywords: asphalt mixture; low-temperature cracking; Tensile Creep Test (TCT); Bending Beam Creep Test (BBCT); tensile strength; thermal stress

1. Introduction

1.1. Background

Low-temperature cracking of asphalt pavements can be a serious problem in regions where the temperature drops to extremely low values, such as -20°C or lower. When the pavement is cooled to a temperature significantly lower than 0°C, tensile stresses develop in the asphalt layer as a result of the pavement's tendency to contract. During winter, low-temperature cracks develop at the surface of the pavement when tensile thermal stress induced in the asphalt layer during cooling equals and exceeds the tensile strength of the material [1-6]. Under repeated temperature cycles, the crack can penetrate to the full depth of the asphalt layers. As a consequence, the existence of transverse cracks caused by extremely low temperature leads to degradation of the pavement structure by water entering through the cracks. According to the literature, the addition of additives such as sulfur [7], bio-agents [8], rubber-bitumen granulate [9] or composition of polymer-rubber modified bitumen [10] can improve low-temperature performance of asphalt mixtures. Zhao et al. [11] assessed the effect of mineral fiber addition on the bending creep test results at low temperatures. It was concluded that adding mineral fiber increased the creep rate of asphalt mixtures and low-

temperature properties were improved. The problem of thermal stresses is important not only in asphalt layers but also in concrete pavements subjected to seasonal and daily changes of temperature [12, 13].

Tensile thermal stresses that occur in the asphalt layers during cooling are very difficult to measure directly in the pavement structure. Therefore, correct analytical estimation of thermal stresses is of crucial importance for evaluation of asphalt binders and design of asphalt mixtures. Calculation of tensile thermal stresses in asphalt pavements has been a subject of research for over 50 years. Viscoelastic solutions for thermal stresses were developed in the early 1960s by Muki and Sternberg [14], Lee and Rogers [15] and Humphreys and Martin [16]. This approach was dedicated to a specific class of polymers and used the temperature-dependent viscoelastic material parameters. The viscoelastic solution was also adopted in 1965 by Monismith et al. [17]. The basic viscoelastic equation for thermal stress calculation is as follows:

$$\sigma(t) = \int_0^t E(t - \xi) \frac{\delta \varepsilon(\xi)}{\delta \xi} d\xi \quad (1)$$

where: $\sigma(t)$ – thermal stress in a viscoelastic slab at time t , $E(t)$ – relaxation modulus of the viscoelastic slab as a function of time t , ε – thermal strain induced in the viscoelastic slab by change of temperature and calculated as:

$$\varepsilon(\xi) = \alpha_T [T(\xi) - T_0] \quad (2)$$

where: α_T – linear coefficient of thermal expansion, ξ – reduced time associated with time and temperature: $\xi = \frac{t}{a_T}$ and a_T – temperature shift factor, $T(\xi)$ – pavement temperature at reduced time ξ , T_0 – pavement temperature when $\sigma(t) = 0$.

The viscoelastic solution presented in Equations (1) and (2) has been used for calculation of thermal stresses in asphalt layers by several researchers [18-25]. This method has also been incorporated in the new AASHTO mechanistic-empirical method of pavement design [26] as well as the AASHTO PP 42-02 [27] and ASTM D6816-11 [28] standards.

In 1966 Hills and Brien introduced a simple quasi-elastic solution for calculation of thermal stresses [29]. Due to the fact that asphalt mixtures are viscoelastic materials with time-temperature dependent properties, the basic disadvantage of this method is that the viscoelastic nature of bituminous material and stress relaxation behavior is not fully considered. Nevertheless, mainly for its simplicity, the Hills and Brien method of thermal stress calculation has been used in several research papers [30-34]. In this method the thermal stresses are calculated from the following equation:

$$\sigma(T) = \frac{1}{1-\nu} \sum_{i=1}^n S(t, T_i) \cdot \alpha_T \cdot \Delta T \quad (3)$$

where: $\sigma(T)$ – thermal stress induced in an asphalt layer at temperature T , ν – Poisson's ratio of the asphalt layer, $S(t, T)$ – stiffness modulus of the asphalt layer as a function of time of loading t and temperature T_i , α_T – coefficient of thermal expansion of the asphalt layer, ΔT – increment of temperature assumed in calculations, $i = 1, \dots, n$ – steps in calculations, T_i temperature at step i and $T_i = T_{i-1} + \Delta T$.

Thermal stresses can be also assessed in laboratory and the results of thermal stress calculations can be then compared to the laboratory test results. In the research of Qian et al. [35], thermal viscoelasticity theory was applied to simulate the Thermal Stress Restrained Specimen Test (TSRST). Gajewski and Langlois [36] modeled the TSRST results using the finite element method in a frame of thermo-mechanics with a “weak coupling” between thermal and mechanical effects. As an alternative to the TSRST method, the Asphalt Concrete Cracking Device (ACCD) was developed by Akentuna et al. to study thermal stress development in asphalt mixtures [37]. Yavuzturk and Ksaibati [38] developed a computer model using a transient, two-dimensional finite volume approach to mathematically describe the thermal response of asphalt pavements to thermal environmental conditions on an hourly basis. Creep tests belong to the most common tests used to assess low-temperature properties of asphalt mixtures in laboratory conditions [39-43]. Thermal stresses can be also calculated on the basis of test results of asphalt mixture samples cored from existing pavement structures [44].

1.2. Objectives

The main objective of the paper is to assess the influence of creep test methods on the obtained results of low-temperature properties of asphalt mixtures, especially the thermal stresses induced in asphalt pavement by a decrease in temperature during winter. For this purpose, three point bending and uniaxial tensile creep tests were applied and the master curves of stiffness modulus were analyzed. Rheological parameters describing elastic and viscous properties of the asphalt mixtures were determined on the basis of creep test results. Burgers rheological model was used to calculate the rheological parameters. Thermal stresses were calculated and compared to tensile strength of the material to obtain the failure temperature of the analyzed asphalt mixtures.

2. Materials and Methods

2.1. Materials

2.1.1. Bitumens

Three types of neat road bitumen – 35/50, 50/70 and 70/100, produced according to EN 12591 standard [45] – and one polymer Styrene-Butadiene-Styrene modified bitumen 45/80-55, produced according to EN 14023 standard [46], were selected for the assessment of low-temperature creep properties of asphalt mixtures. Standard properties of the bitumens used in this research are shown in Table 1.

Table 1. Properties of bitumens

		Type of bitumen			
Property		35/50	50/70	70/100	45/80-55
Penetration at 25°C, 0.1 mm, acc. to PN-EN 1426	Original	45	54	81	60
	RTFOT	28	40	48	40
R&B Temperature, °C, acc. to PN-EN 1427	Original	53.0	50.8	47.8	68.6
	RTFOT	57.8	57.8	53.4	67.4
Performance Grade, acc. to AASHTO M 320		70-16	64-22	58-22	70-22
Fraass Breaking Point Temperature, °C, acc. to PN-EN 12593	Original	-6	-14	-16	-16
	RTFOT	-3	-12	-10	-15

2.1.2. Asphalt mixtures

Laboratory tests were conducted on three types of asphalt mixtures: two wearing course asphalt concretes – AC 11 S for low traffic (LT) and AC 11 S for medium traffic (MT) – as well as one binder course asphalt concrete AC 11 W for medium traffic (MT). All mixes were designed in compliance with the EN 13108-1 standard [47] and were prepared in the laboratory [48]. The mixture type AC 11 S (MT) was designed in two variants (using the neat 50/70 bitumen and the modified 45/80-55 bitumen), therefore, a total of four different asphalt mixtures was used in the test. The compositions of mixtures and types of bitumen used are presented in Table 2.

Table 2. Properties of asphalt mixtures

Asphalt mixture	Type of mixtures		
	AC 11 S	AC 11 S	AC 11 W
Type of layer	wearing course	wearing course	binder course
Type of traffic	low traffic (LT)	medium traffic (MT)	medium traffic (MT)
Bitumen type	70/100	50/70 45/80-55	35/50
Binder content (% by mass)	5.8	5.6	5.6
Aggregate type	crushed gravel	crushed gneiss	crushed gneiss
Filler type	limestone	limestone	limestone
Sieve size (mm)	% Passing (by mass)		
16	100	100	100
11.2	97	98	98
8	83	77	83
5,6	71	62	65
4	60	52	54
2	40	39	43
0.125	11	11	12
0.063	8.0	7.2	7.4

2.2. Methods

2.2.1. Tensile Creep Test (TCT)

Tensile creep properties of asphalt mixtures at low temperatures were assessed by means of the Tensile Creep Test (TCT) method according to EN 12697-46 standard [49]. In the TCT the specimen is subjected to a constant tensile stress σ at a constant temperature T . The progression of the strain ϵ with time is recorded. According to the standard, it is recommended to maintain the constant load for 8 hours and, after unloading, record the regression for additional 2 hours. The principle of the TCT is shown in Figure 1.

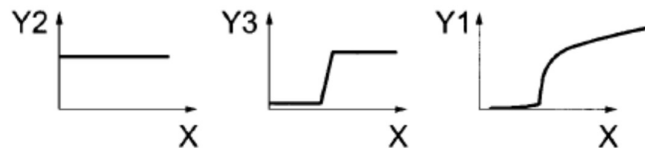


Figure 1. Principle of the Tensile Creep Test (TCT); where: X – time, Y1 – strain, Y2 – temperature, Y3 – stress, [49]

In the TCT method the specimens were loaded in order to achieve a constant tensile stress at a constant temperature. The stress levels were determined in relation to tensile strength results from the Uniaxial Tension Stress Test (UTST). In the UTST a specimen is pulled with a constant strain rate at a constant temperature until failure. Results of the UTST are: the maximum stress (tensile strength) $\beta_t(T)$ and the corresponding tensile failure strain $\epsilon_{failure}(T)$ at the test temperature T . In this research, the Tensile Stress Restrained Specimen Test (TSRST) method was used as well. The results from the TSRST were compared to thermal stresses calculated based on the results from the creep test methods. The results of the TSRST procedure are: the progression of the thermal stress over the temperature $\sigma_{cry}(T)$ and the failure stress $\sigma_{cry, failure}(T)$ at the failure temperature $T_{failure}$. The results from the UTST and TSRST have been published and discussed in a separate paper [6]. In the TCT method the level of the stresses applied was determined as the percentage of the maximum stress $\beta_t(T)$ from the UTST at a given test temperature. Temperatures and stresses applied in the TCT are presented in Table 3 and in Figure 2.

Table 3. Test conditions for the Tensile Creep Test (TCT), [49]

Test temperature T , °C	Percentage of the maximum stress $\beta_i(T)$ obtained from the UTST, %
+ 20	5
+ 5	10
-10	30
-20	50
-30	50

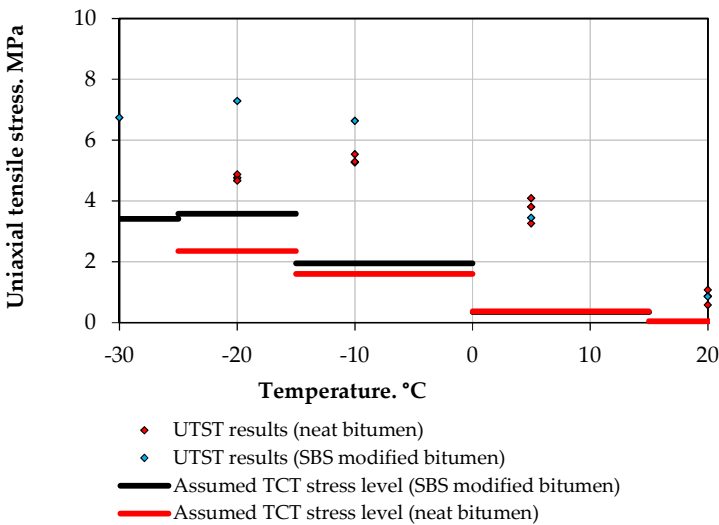


Figure 2. Stress levels at test temperatures applied in the Tensile Creep Test (TCT)

The specimens were tested using a “TSRST-MULTI” Multi Station Thermal Asphalt System (PAVETEST, Italy) device with servo hydraulic equipment. The equipment and test setup used are presented in Figure 3.

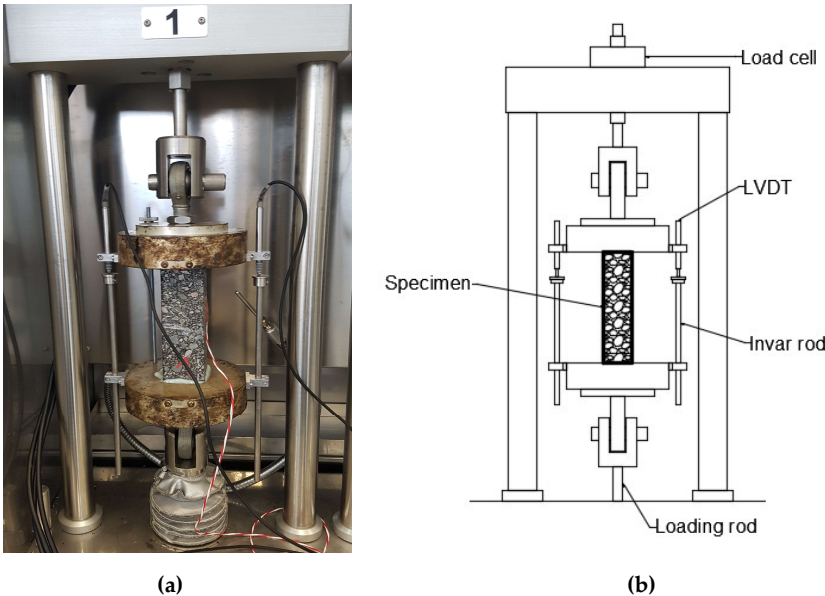


Figure 3. Tensile Creep Test (TCT) and Uniaxial Tension Stress Test (UTST) setup: a) photograph of the specimens during the test, b) schematic view

5. Stress levels and test temperatures in the Bending Beam Creep Test are presented in Figure

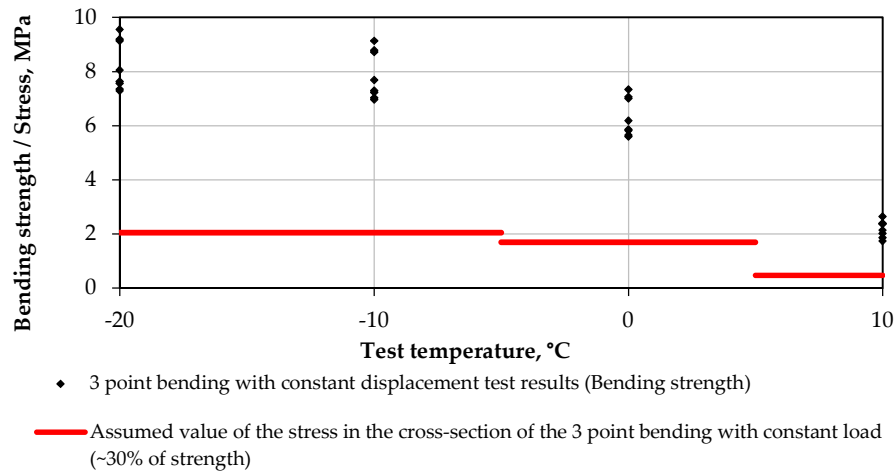


Figure 5. Stress levels at various test temperatures applied in the Bending Beam Creep Test (BBCT)


2.3. Method of calculation of rheological properties

On the basis of TCT and BBCT results, rheological parameters describing elastic and viscous properties of the asphalt mixtures were determined. Burgers rheological model was used to calculate the rheological parameters that were later utilized for calculation of thermal stresses. Burgers model parameters are determined using the least square method. For this purpose, each of the creep curves is described using Equation (6), where Burgers model parameters are treated as fitting parameters.

$$\varepsilon(T, t) = \sigma_0 \cdot \left\{ \frac{1}{E_1} + \frac{t}{\eta_1} + \frac{1}{E_2} \left[1 - e^{(-t/\lambda)} \right] \right\} \quad (6)$$

where: $\lambda = \eta_2/E_2$, E_1 —instantaneous modulus of elasticity, MPa; E_2 —modulus of retarded elasticity, MPa; η_1 —coefficient of viscosity of steady flow, MPa·s; η_2 —coefficient of viscosity of retarded flow, MPa·s; t —time of loading, s, σ_0 —constant stress during load phase, specific for each temperature, MPa.

Exemplary fittings of the test data for the AC 11S KR3-4 50/70 mixture for selected temperatures are presented in Figure 6.

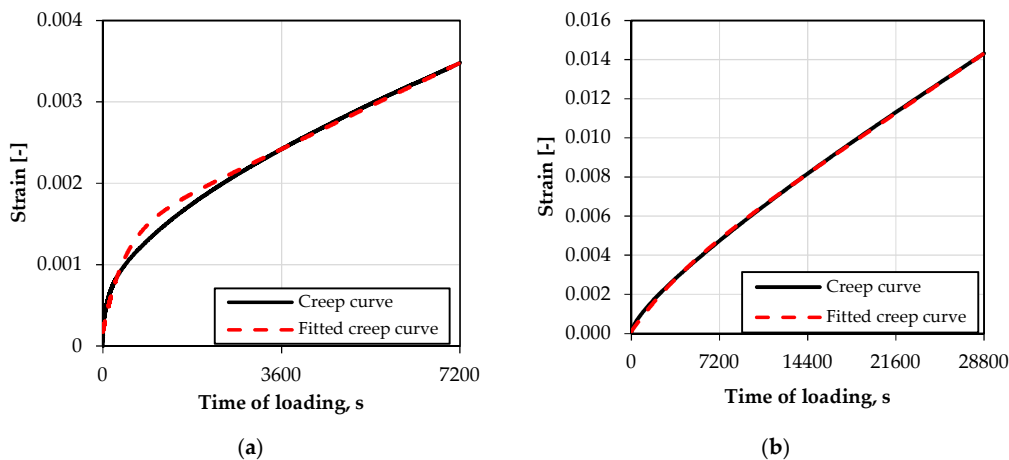

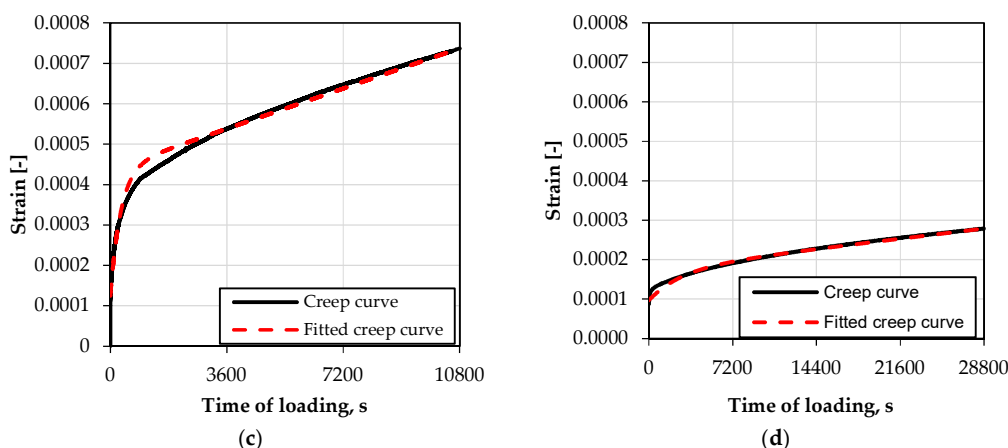


Figure 6. Bending and tensile creep test results—creep curves and fitting of the creep using Burgers model at given test temperatures: BBCT (a) 0 °C; (c) -10 °C; and TCT (b) +5 °C; (d) -10 °C

Under assumption of the time-temperature superposition principle [52], on the basis of TCT and BBCT results obtained for 4 different temperatures (either +20°C, +5°C, -10°C, -20°C or +10°C, 0°C, -10°C, -20°C), the master curves of stiffness modulus were developed. In the first step, stiffness curves (mean values) determined for each temperature were shifted along the time axis to obtain one smooth line. The reference temperature was chosen as -10°C, as it was the highest test temperature shared by both methods. After shifting of the stiffness curves, one equation was used for description of the master curve. Based on previous research works [10, 39, 40], it was assumed that the best fitting is obtained with Richards model [53], which is given by Equation (7):

$$\log|E^*| = \delta + \frac{\alpha - \delta}{[1 + \lambda e^{\beta + \gamma \log f}]^{(1/\lambda)}} \quad (7)$$

where: $\log|E^*|$ – stiffness modulus, psi; f – reduced frequency, Hz; $\alpha, \delta, \beta, \gamma, \lambda$ – master curve fitting parameters. Stiffness modulus is in further steps recalculated into SI units (MPa).

3. Results and discussion

Bending and tensile creep tests conducted in this study posed a base for determination of various rheological properties of the tested asphalt mixtures. Afterward, selected properties were used in calculation of thermal stresses developed in the pavement due to a decrease in temperature. The following characteristics were determined from the conducted laboratory tests: stiffness moduli, Burgers model parameters and master curve equations with appropriate shift factors. All the derived basic properties were assessed taking into assumption linear viscoelasticity and thermo-rheological simplicity. In the case of master curves, the Richards “branching” model modification [54] properties were determined as well.

3.1. Stiffness modulus

Stiffness curves derived from the results of the two creep tests – the Bending Beam Creep Test (BBCT) and the Tensile Creep Test (TCT) – for all the tested materials are presented in Figures 7 through 10. In the case of the Bending Beam Creep Test, the presented results are the mean values from 5 different specimens (coefficient of variation for all test results is in the range from 5 to 25%; mean 10%). In the case of the Tensile Creep Test, the presented results are the mean values from 2 to 4 different specimens (coefficient of variation for all test results is in the range from 1 to 40 %; mean 15%). For the asphalt mixture AC 11W with neat bitumen 35/50, only the Tensile Creep Test was conducted.

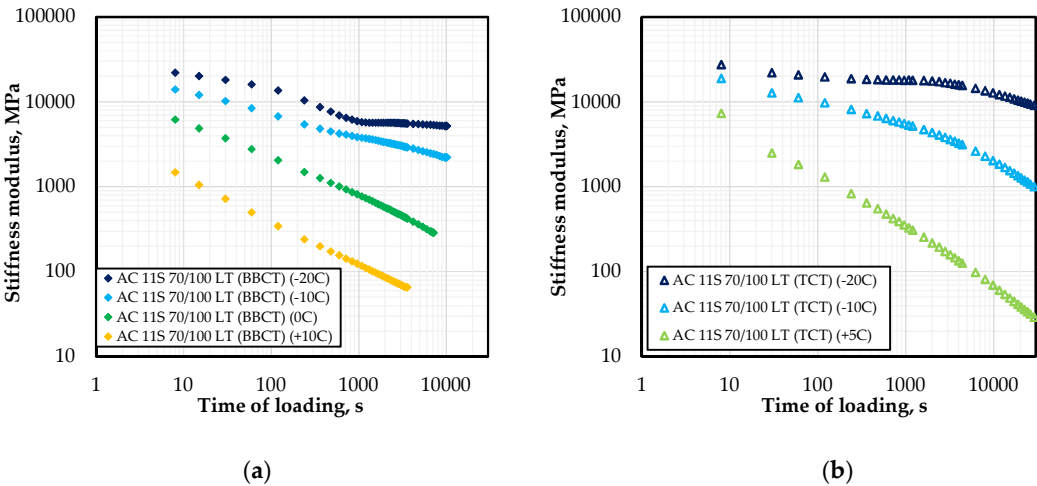


Figure 7. Creep test results—stiffness curves for AC 11S 70/100 LT (a) BBCT; (b) TCT

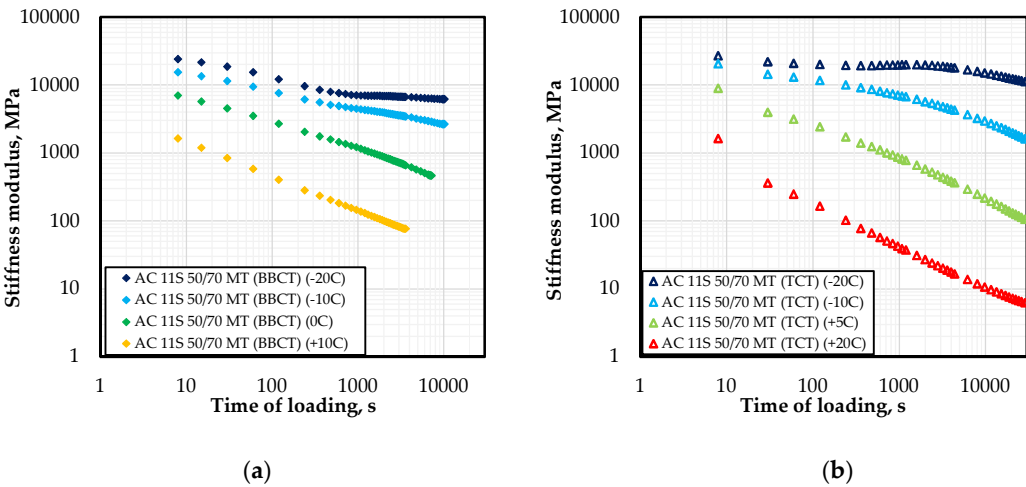


Figure 8. Creep test results—stiffness curves for AC 11S 50/70 MT (a) BBCT; (b) TCT

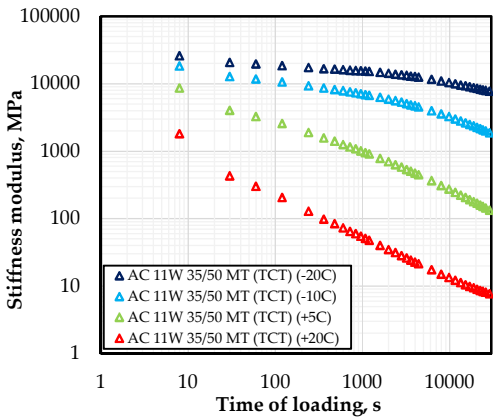


Figure 9. Creep test results—stiffness curves for AC 11W 35/50 MT, only for TCT

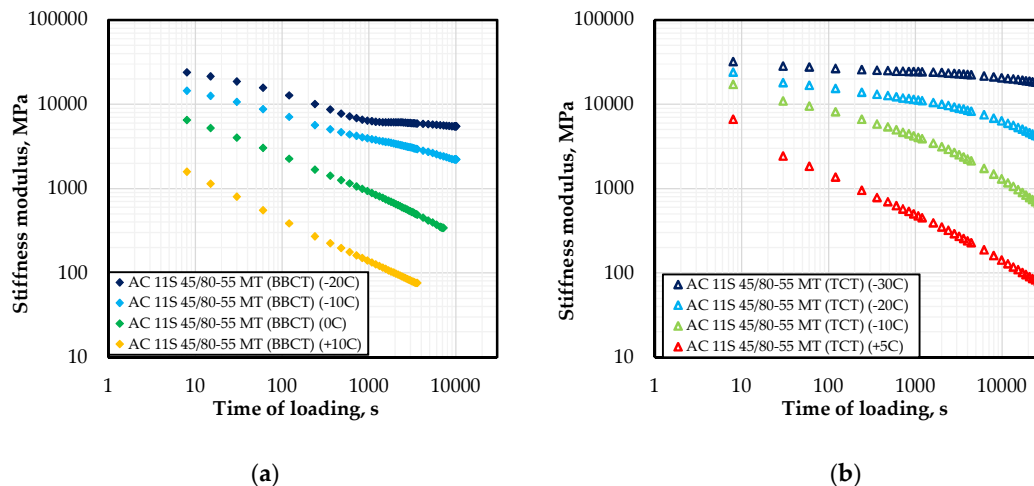


Figure 10. Creep test results—stiffness curves for AC 11S 45/80-55 MT (a) BBCT; (b) TCT

Stiffness curves derived from both creep tests differ at all the tested temperatures – both by shape and by values. For low temperatures (-10°C and lower) results obtained from the TCT present higher values of stiffness modulus. The situation is opposite at temperatures higher than 0°C , where results obtained from the BBCT present higher values. The difference in both cases is around 50% and will be discussed in detail further in the paper.

In terms of shape of the stiffness curves, two main differences are visible between the two tests: the shape of the stiffness curve at the highest temperature as well as the occurrence and shape of deviations from the time-temperature superposition principle. As shown in Figures 7b and 8b, for the temperature of $+20^{\circ}\text{C}$ the stiffness curve derived from the TCT test bends from the straight line for long times of loading. Such shape is beneficial for construction of the master curve – it is easier to develop equation for the typical sigmoidal shape, so “Max” and “ δ ” master curve parameters could have physical meaning of maximum and minimum stiffness modulus. In the case of BBCT test trials in $+20^{\circ}\text{C}$ for the lowest possible stress suggested destruction of the specimen for times of loading longer than 200 seconds (stiffness moduli reached value of ~ 1 MPa). Therefore in the case of BBCT test it is much harder to derive the “ δ ” master curve parameter which corresponds to lowest value. As for the appearance of deviations – previous studies [40, 54] showed that in the case of BBCT test, deviations appeared after around 500 seconds of loading. Their shape was suggesting reaching of the horizontal asymptote. Such results were confirmed in other studies [10, 39]. In the case of TCT test, deviations from time-temperature superposition principle was also observed for most cases (except of AC 11S 45/80-55 MT mixture) in temperatures of -10°C and lower. But first analyses showed that they appearance is faster – around 200-300 seconds – and the shape is different – after the “asymptotical” phase which lasts around 1000-3000 seconds, modulus starts to decrease again. As further tests will be conducted on other mixtures, deviations will be analysed in details in further studies.

3.2. Burgers model parameters

Burgers model parameters were derived using the procedure presented in Section 2.3. The procedure was the same for creep curves determined in both tests. Results for the TCT are presented in Table 4 and results for the BBCT are presented in Table 5.

Table 4. Burgers model parameters for the Tensile Creep Test (TCT)

Mixture designation	Test temperature T, °C	Burgers model parameters			
		E ₁ , MPa	E ₂ , MPa	η ₁ , MPa·s	η ₂ , MPa·s
AC 11S 70/100 LT	-20	24,601	60,649	620,381,505	83,584,308
	-10	12,516	6,790	38,457,749	14,471,875
	5	2,791	254	991,934	767,794
	20	*	*	*	*
AC 11S 50/70 MT	-20	24,656	115,183	827,458,047	90,290,579
	-10	13,737	7,758	69,265,928	21,096,067
	5	4,070	459	4,086,935	1,888,343
	20	629	14	353,051	62,056
AC 11S 45/80- 55 MT	-30	29,941	98,166	2,381,475,542	91,889,789
	-20	19,307	19,490	195,406,816	28,798,508
	-10	12,257	4,123	21,890,814	10,897,801
	5	2,762	239	3,205,784	1,009,562
AC 11W 35/50 MT	-20	21,772	28,228	600,059,352	75,959,661
	-10	13,004	8,210	87,034,368	23,417,485
	5	4,031	601	5,187,255	2,240,592
	20	749	16	453,536	85,500

* - specimen failure during the test

Table 5. Burgers model parameters for the Bending Beam Creep Test (BBCT)

Mixture designation	Test temperature T, °C	Burgers model parameters			
		E ₁ , MPa	E ₂ , MPa	η ₁ , MPa·s	η ₂ , MPa·s
AC 11S 70/100 LT	-20	38,503	4,517	588,962,264	2,007,996
	-10	34,090	2,948	60,779,274	624,963
	0	18,572	801	3,152,349	271,364
	10	6,168	151	397,640	41,598
AC 11S 50/70 MT	-20	46,106	5,024	595,720,702	470,341
	-10	34,208	3,350	79,945,328	490,828
	0	18,582	1,153	5,340,236	303,322
	10	5,129	175	467,638	49,697
AC 11S 45/80- 55 MT	-20	45,953	4,676	487,685,841	588,195
	-10	30,444	3,149	53,177,748	437,444
	0	17,695	876	3,849,752	319,700
	10	5,134	167	478,026	47,128

Burgers model parameters differ in all cases, apart from the η₁ coefficient of viscosity steady flow, in whose case values are comparable. Secondary parameters E₂ and η₂ present higher values for the TCT and show better consistency with the results determined from dynamic tests [55]. In the case of the E₁ modulus the situation is more complicated. While the values obtained from the TCT are almost two times lower than those derived from the BBCT and seem more realistic, a reduction in values obtained from the TCT could have been caused to some extent by the less accurate record of the creep curve in the unloading part. The first record is made after 25 seconds. Nevertheless, the results of the E₁ Burgers model parameter derived from the TCT show more consistency with the stiffness curves presented in Section 3.1. The highest values of stiffness modulus for the temperatures of -10°C and -20°C are similar for both tests.

3.3. Master curve parameters

On the basis of previous studies and literature review [10, 39, 40, 52, 53, 57], Richards model was selected as the basic equation of master curves. “Branching” model modification [54] was also applied for all the tested mixtures, to take into account the deviations from the time-temperature superposition principle. Parameters for asphalt mixtures derived from the TCT are presented in Table 6. Parameters for asphalt mixtures derived from the BBCT are presented in Table 7. Shift factors used in the study are presented in Figure 11.

Basic parameters of the master curve described by the Richards model in which deviations are completely omitted are presented in the first row of results for each mixture (for $T > -20^{\circ}\text{C}$ or $T > -10^{\circ}\text{C}$, depending on the mixture and test procedure). It is visible that in the case of higher temperatures for the TCT, the “ δ ” parameter shows consistency between all the tested mixtures, and it is always higher than 0. Determination of the same parameter for the BBCT sometimes requires setting of the minimum value of “ δ ” as 0, as the SOLVER unit of EXCEL used in the analysis sometimes suggests values lower than 0 [40], which is in contradiction to the physical meaning of the parameter. Additional “branches”, deviating from the master curves due to shifting of stiffness curves obtained at lower test temperatures, are presented in further rows of the tables, according to their corresponding temperature ranges. Since the shape of the deviations in the TCT is different than in the BBCT, the values of the “ δ ” parameter for the TCT are equal across all temperatures. The “asymptotical” phase is not correctly described, which suggests that for the TCT a new model needs to be developed. Results presented in this study for the BBCT show full consistency with the “branching” modification of Richards model [54], and deviations are correctly described.

Table 6. Master curve parameters for the Tensile Creep Test (TCT)

Mixture designation	Test temperature T, $^{\circ}\text{C}$	Richards model parameters (“branching” modification)				
		Max	β	γ	δ	λ
AC 11S 70/100 LT	> -20	4.712	-10.075	-0.462	0.367	0.000615
	< -20	4.712	-17.217	-0.279	0.367	0.0000005
AC 11S 50/70 MT	> -20	4.789	-9.735	-0.451	0.441	0.000898
	< -20	4.789	-16.478	-0.196	0.441	0.000001
AC 11S 45/80- 55 MT	> -20	4.823	-9.584	-0.421	1.175	0.000566
	$-20 \div -30$	4.823	-10.698	-0.366	0.823	0.000226
	< -30	4.823	-10.424	-0.212	3.786	0.000066
AC 11W 35/50 MT	> -10	4.935	-9.703	-0.369	0.284	0.00055
	$-10 \div -20$	4.935	-6.737	-0.302	0.284	0.01074
	< -20	4.935	-11.818	-0.213	0.284	0.00006

Table 7. Master curve parameters for the Bending Beam Creep Test (BBCT)

Mixture designation	Test temperature T, $^{\circ}\text{C}$	Richards model parameters (“branching” modification)				
		Max	β	γ	δ	λ
AC 11S 70/100 LT	> -10	4.766	-9.066	-0.428	1.327	0.000864
	$-10 \div -20$	4.766	-9.560	-0.498	3.246	0.000206
	< -20	4.766	-10.471	-0.848	3.713	0.000066
AC 11S 50/70 MT	> -10	5.118	-11.162	-0.295	0.146	0.000090
	$-10 \div -20$	5.118	-11.835	-0.368	3.234	0.000014
	< -20	5.118	-12.737	-0.703	3.815	0.000004
	> -10	4.764	-10.941	-0.429	1.358	0.000132

AC 11S 45/80-55 MT	-10÷ -20	4.764	-11.643	-0.482	3.209	0.000026
55 MT	< -20	4.764	-11.381	-0.852	3.741	0.000025

Two models of shift factors commonly used for binders and asphalt mixtures were used in the study – WLF and Arrhenius [52]. The reference temperature for which the master curves and shift factors were determined was assumed as -10°C – the highest common temperature for both tests. Arrhenius model parameters are similar for both tests, but results obtained from the BBCT presented higher homogeneity. In both cases the results were similar, both in shape and in values, to the WLF function determined for the TCT (Figure 11b). The WLF function proved more reliable when applied to the TCT results than to the BBCT results. For the BBCT test, in the case of higher temperatures, the WLF function (Figure 11a) presents a significantly different shape. While in the case of temperatures of up to 0°C the course of the line is similar to the TCT test, in the case of $+10^{\circ}\text{C}$ the values decrease strongly, probably due to limitation of the BBCT test. It was impossible to obtain reliable results at temperatures higher than $+15^{\circ}\text{C}$.

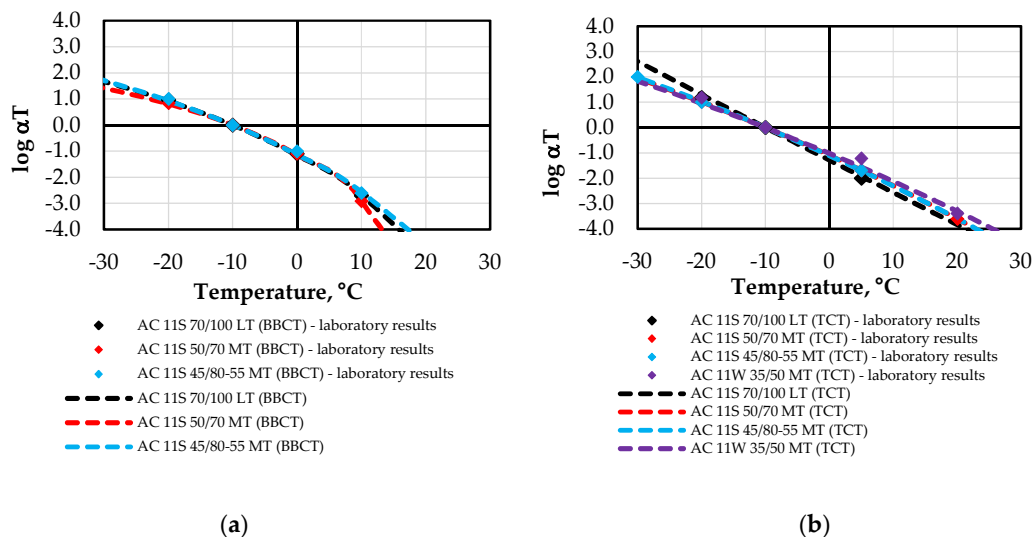


Figure 11. Shift factor – WLF function: (a) BBCT; (b) TCT

Analysis of the master curve and shift factor models suggests that more reliable results should be obtained for the TCT, regardless of the model used. Some difficulties occurred for the “branching” modification of the Richards model, but further works should eliminate this problem. In the case of the BBCT, reliable results should be obtained using only Arrhenius shift factor model. The WLF model can influence analyses conducted at higher temperatures.

3.4. Comparison of the TCT and BBCT results

Relationships between different test modes are commonly used in analyses of solid materials such as cement concrete. While the Young modulus should have the same value regardless of the test mode, the relationship between strength determined in simple tension and flexural test is approximately 1:2. While asphalt mixture strength relationships between different test modes were the subject of other studies [6, 56], in this study the authors focused on relationships between stiffness moduli. In Figures 12 through 15, the results obtained from both tests are compared in various forms: stiffness curves for chosen temperatures, shifted stiffness curves as well as master curves.

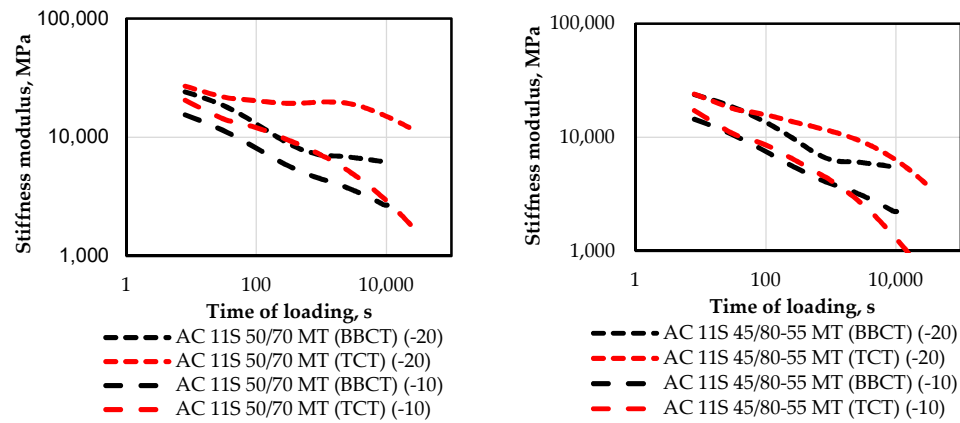


Figure 12. Comparison of stiffness curves at temperatures of -10°C and -20°C

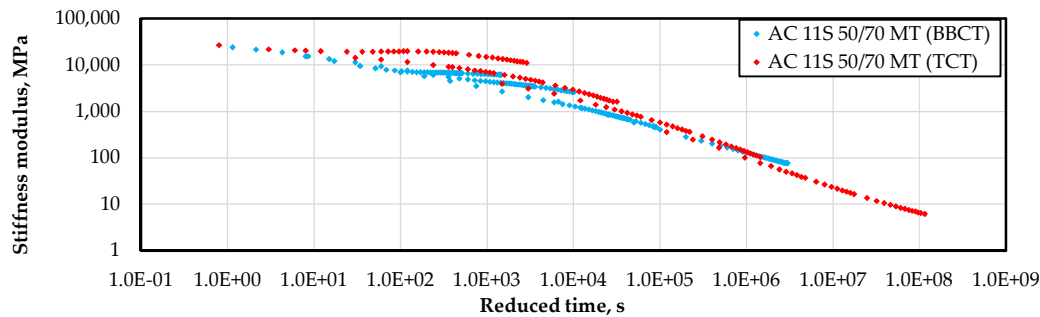


Figure 13. Comparison of shifted stiffness curves for AC 11S 50/70 MT, reference temperature: -10°C

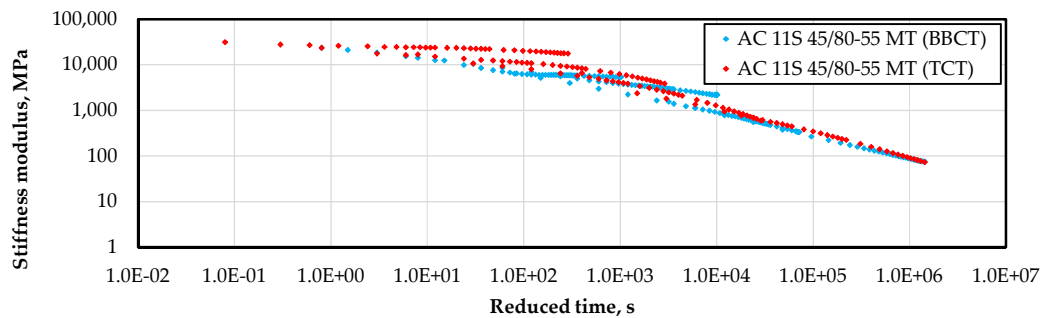
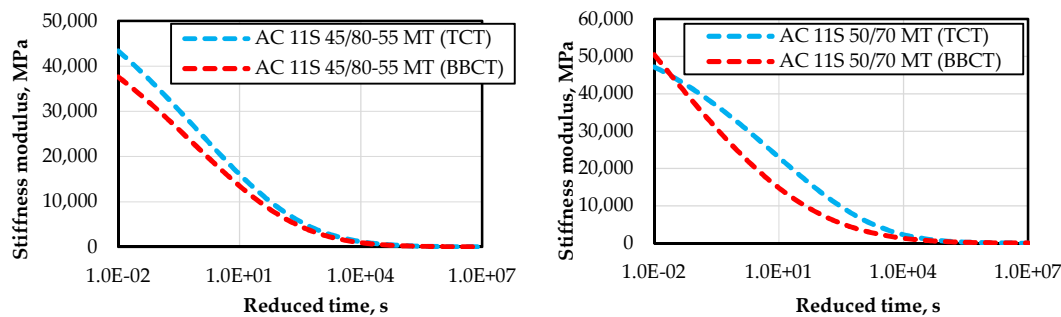


Figure 14. Comparison of shifted stiffness curves for AC 11S 45/80-55 MT, reference temperature: -10°C



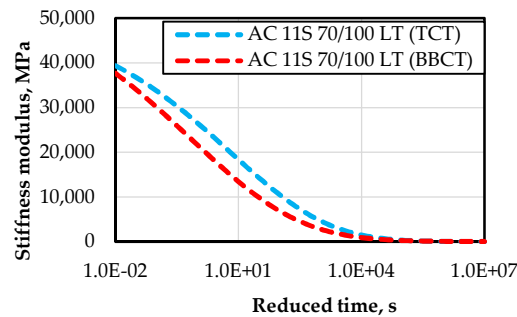


Figure 15. Comparison of master curves for all tested mixtures, reference temperature -10°C

As shown in Figure 12, for the first 100 seconds the results obtained from both tests are similar, with higher values of stiffness modulus obtained from the TCT. For longer times of loading the results differ strongly, both in values and the shape of the curve. Stiffness ratio between the TCT and the BBCT for the first 100 seconds is around 1.5 (Figure 16b). In the case of longer times of loading, the relationship is in the range from 1.1 to 4.0, with no visible tendencies for specific types of bitumen. Comparison of the shifted stiffness curves (Figures 13 and 14) shows that for lower temperatures ($<0^{\circ}\text{C}$) higher stiffness values are obtained for the TCT. The relationship changes at temperatures higher than 0°C , for which the values of stiffness modulus obtained in the BBCT are higher. The same is visible in the developed master curves (Figure 15), where the master curve derived from the BBCT has a “flatter” shape than the one from the TCT. Stiffness ratio between master curves is presented in Figure 16a. While the range of variability is lower (between 0.5 and 2.0), no direct relationships are visible in this case, as opposed to the case of stiffness curves for shorter times of loading. For the majority of the reduced time, higher values are obtained for the TCT.

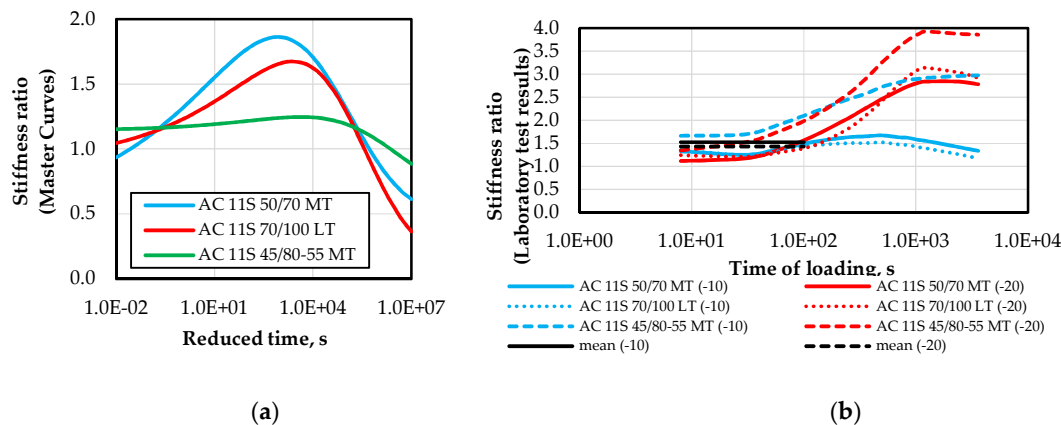


Figure 16. Stiffness ratio (TCT versus BBCT): (a) master curves (b) stiffness curves at temperatures of -10°C and -20°C

4. Thermal stress analysis

Thermal stresses developed due to a decrease in temperature were calculated using procedures presented in Section 1.1. For comparison with the TSRST [49], the gradient of temperature was assumed as 10°C/h . For the Hills and Brien method, values of stiffness moduli were derived from stiffness curves as described in [5]. For the Monismith method, “branching” modification of Richards model was used (shift factor – according to the Arrhenius model). In the case of AC 11W 35/50 MT, only results from the TCT were used. Calculated values of thermal stresses are presented in Figure 17. The predicted failure temperatures determined from Figure 17 are presented in Table 8.

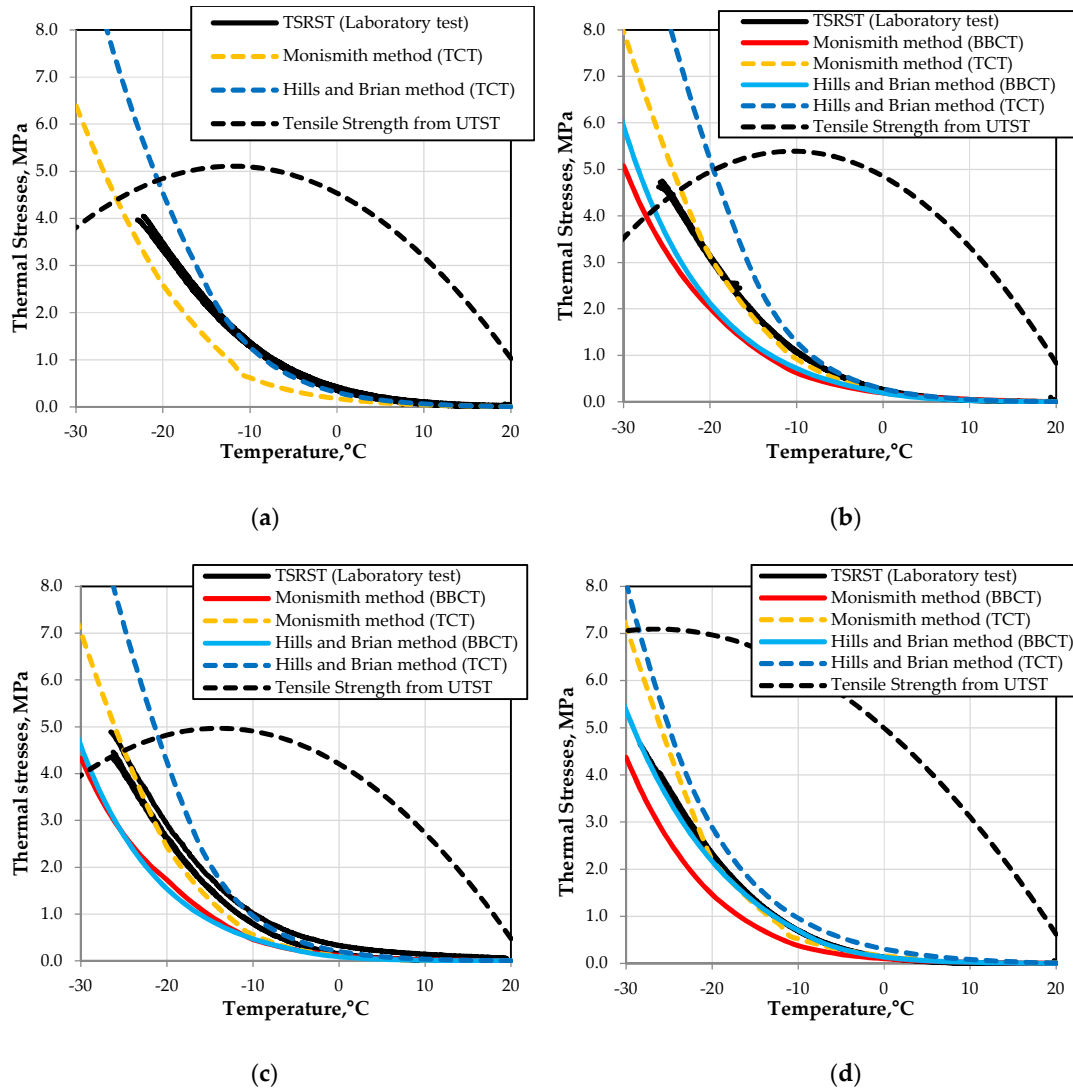


Figure 17. Results of calculation of thermal stresses for all the tested mixtures in comparison to the TSRST and UTST results, temperature gradient of 10°C/h: (a) AC 11W 35/50 MT (b) AC 11S 50/70 MT (c) AC 11S 70/100 LT (d) AC 11S 45/80-55 MT

Table 8. Comparison of predicted failure temperatures (mean values)

Mixture designation	TSRST	Thermal stress calculation method (data source)			
		Hills & Brien (BBCT)	Hills & Brien (TCT)	Monismith (BBCT)	Monismith (TCT)
AC 11S 70/100 LT	-26.4	-29.0	-21.0	-29.5	-25.0
AC 11S 50/70 MT	-25.7	-26.5	-19.5	-27.5	-23.5
AC 11S 45/80-55 MT	-29.5	<-30.0	-28.5	<-30.0	-29.5
AC 11W 35/50 MT	-22.3	-	-20.5	-	-25.5

As shown in Figure 17, the highest agreement with the TSRST results was obtained for the Monismith method based on the TCT results. In most cases, the TSRST results (black line) are almost

the same. Lower values were often obtained for both thermal stress calculation methods (Hills & Brien as well as Monismith) when the BBCT results were used. In the case of the Hills & Brien method based on the TCT results, almost in all cases the values of stress were higher than those obtained from the TSRST, which could result from the fact that stress relaxation is not fully considered in this method.

In the course of assessment of failure temperatures presented in Table 8, no clear relationships were noted. The highest agreement was obtained for the Monismith method calculated based on the TCT results, for which in 2 of 4 cases the determined values of failure temperature were in good agreement with the TSRST results.

The conducted analysis suggests that the highest reliability in calculations of thermal stresses was obtained for the Monismith method based on the TCT results. For the results of calculations based on the BBCT, a “method constant” should be determined in order to shift the results calculated from the BBCT into those calculated from the TCT, similarly to the BBR methodology [27]. In this standard, to obtain values of thermal stresses for asphalt mixtures, one should multiply the thermal stresses calculated according to the AASHTO PP42-02 standard by a factor of 18. The presented study showed that such a factor for the BBCT results is in the range from 1.5 to 1.7, but it should be verified in more detailed studies encompassing other types of mixtures and bitumens.

5. Summary and conclusions

This paper presents the study of low-temperature creep properties of asphalt mixtures and the methods of thermal stress assessment. Three point bending and uniaxial tensile creep tests were applied to calculate thermal stresses at low temperatures. Based on the test results and analysis, the following conclusions can be drawn:

1. According to different creep test methods applied in the study, lower strain values of creep curves were obtained for the Tensile Creep Test (TCT) than for the Bending Beam Creep Test (BBCT), especially at lower temperatures.
2. Stiffness curves derived from both creep tests (BBCT and TCT) differ at all the tested temperatures – both in terms of shape and values. For low temperatures (-10°C and lower) results obtained from the TCT presented higher values of stiffness modulus. The situation is opposite at temperatures higher than 0°C , where the results obtained from the BBCT present higher values.
3. Master curves determined on the basis of the TCT results showed higher values of stiffness modulus for temperatures $< 0^{\circ}\text{C}$ and lower for temperatures $> 0^{\circ}\text{C}$ in comparison to those determined from the BBCT.
4. “Branching” modification of the Richards model correctly described the master curves determined from the BBCT results. In the case of the TCT results, master curves presented some discrepancies and a new model should be determined.
5. Arrhenius shift factor function presented reliable results for both tests (BBCT and TCT). In the case of WLF shift factor function, the BBCT results showed significantly decreased values at temperatures higher than 0°C .
6. Results of thermal stress calculations indicated that higher reliability was obtained for the viscoelastic Monismith method based on the TCT results. The highest agreement with the TSRST results was also obtained for the Monismith method based on the TCT results.
7. No clear relationships were obtained between the failure temperatures predicted from different methods of thermal stress calculation. The highest agreement was obtained for the viscoelastic Monismith method calculated based on the TCT results, for which in 2 of 4 cases the determined values of failure temperature were in good agreement with the TSRST results.
8. The main limitation of the study was related to the methodology of the TCT method. The test method was applied and conducted according to the European standard EN 12697-46. In the TCT the time of loading is long (8 hours) and an additional measurement period of 2 hours is

also recommended after unloading. The authors have come to the opinion that the time of loading can be shortened, but this issue requires further research.

Acknowledgment: The research was partly supported by the project RID-1B, financed by the National Center for Research and Development and the General Directorate for National Roads and Motorways under the program "Development of Road Innovations".

Author Contributions: Marek Pszczola conceived and designed the experiments; Cezary Szydlowski and Marek Pszczola coordinated the experiments; Marek Pszczola and Mariusz Jaczewski analyzed the TCT and BBCT data; Marek Pszczola, Mariusz Jaczewski and Cezary Szydlowski wrote the paper; Marek Pszczola coordinated and edited the paper.

Conflicts of Interest: The authors declare no conflict of interest. The founding sponsors had no role in the design of the study; in the collection, analyses, or interpretation of data; in the writing of the manuscript, and in the decision to publish the results.

References

1. Jung, D.; Vinson, T.S., Thermal Stress Restrained Specimen Test to Evaluate Low-Temperature Cracking of Asphalt-Aggregate Mixtures, Transportation Research Record No. 1417, **1993**, Transportation Research Board, National Academy Press, Washington D.C., 12-20.
2. Judycki, J., A new viscoelastic method of calculation of low-temperature thermal stresses in asphalt layers of pavements, *International Journal of Pavement Engineering*, **19**(1), **2016**, 24-36, DOI: 10.1080/10298436.2016.1149840
3. Vinson, T.S.; Janoo V.C., Low Temperature and Thermal Fatigue Cracking, **1989**, Summary Report No SR-OSU-A-003A-89-1.
4. Pucci, T.; Dumont, A.-G.; Di Benedetto H., Thermomechanical and Mechanical Behaviour of Asphalt Mixtures at Cold Temperature: Road and Laboratory Investigations, Road Materials and Pavement Design, **2004**, Volume 5, Issue 1, pp. 45-72, DOI: 10.1080/14680629.2004.9689962.
5. Pszczola, M.; Judycki J., Comparison of calculated and measured thermal stresses in asphalt concrete, *Baltic Journal of Road and Bridge Engineering*, **10**(1), **2015**, pp. 39-45. <https://doi.org/10.3846/bjrbe.2015.05>.
6. Pszczola, M.; Szydlowski C., Influence of Bitumen Type and Asphalt Mixture Composition on Low-Temperature Strength Properties According to Various test Methods, *Materials – MDPI*, **2018**, **11**, 2118, doi:10.3390/ma11112118.
7. Bai, M., Investigation of low-temperature properties of recycling of SBS modified asphalt binder, *Construction and Building Materials*, **150**, **2017**, 766-773, <https://doi.org/10.1016/j.conbuildmat.2017.05.206>.
8. Kowalski, K.J.; Król, J.B.; Bańkowski, W.; Radziszewski, P.; Sarnowski, M., Thermal and Fatigue Evaluation of Asphalt Mixtures Containing RAP Treated with a Bio-Agent, *Applied Sciences - MDPI*, **2017**, **7**(3), 216, <https://doi.org/10.3390/app7030216>
9. Sybilski, D.; Bańkowski, W.; Mirski, K.; Hododecka, R.; Wróbel, A., Rubber-bitumen granulate for asphalt pavements – laboratory comparative analysis, *5th International Conference on Bituminous Mixtures and Pavements*, Thessaloniki, **2011**, 1413-1421.
10. Pszczola, M.; Jaczewski, M.; Szydlowski, C.; Judycki, J.; Dołycki, B., Evaluation of low temperature properties of rubberized asphalt mixtures, *Procedia Engineering*, **172**, **2017**, 897-904, <https://doi.org/10.1016/j.proeng.2017.02.098>.
11. Zhao, L.; Xu, G.; Zhang, M., Low-temperature creep properties for fibre-asphalt mixtures, *Proceedings of the Institution of Civil Engineers – Transport*, **170**(3), **2017**, 152-157, <https://doi.org/10.1680/jtran.14.00076>.
12. Mackiewicz, P., Thermal stress analysis of joined plane in concrete pavements, *Applied Thermal Engineering*, **2014**, **73**, 1169-1176, <https://doi.org/10.1016/j.applthermaleng.2014.09.006>.
13. Chaubane, B.; Tia, M., Analysis and verification of thermal-gradient effects on concrete pavement, *Journal of Transportation Engineering*, **1995**, **121**(1), 75-81.
14. Muki, R.; Sternberg, E., On transient thermal stresses in viscoelastic materials with temperature-dependent properties, *Journal of Applied Mechanics*, **1961**, 193-207.
15. Lee, E.H.; Rogers, T.G., Solution of viscoelastic stress analysis problems using measured creep or relaxation functions, *Journal of Applied Mechanics*, **1963**, 127-133.
16. Humphreys, J.S.; Martin, C.J., Determination of transient thermal stresses in a slab with temperature-dependent viscoelastic properties, *Transaction of the Society of Rheology*, **1963**, **VII**, 155-169.

17. Monismith, C.L.; Secor, G.A.; Secor, K.E., Temperature Induced Stresses and Deformations in Asphalt Concrete, *Journal of the Association of Asphalt Paving Technologists*, **34**, **1965**, 248 – 285.
18. Wittmann, F.H.; Knappe, O.W.; Schuhbauer, A., Temperature induced stresses in concrete, *Cement and Concrete Research*, **8**, **1978**, 703-710.
19. Wittmann, F.H.; Schwanke, H., Influence of composition on temperature induced stresses in asphalt concrete mixtures, *Cement and Concrete Research*, **9**, **1979**, 497-500.
20. Marasteanu, M.; Zofka, A.; Turos, M.; Li, X.; Velasquez, R.; Xue, L.; Buttlar, W.G.; Paulino, G.; Braham, A.; Dave, E.; et al. Investigation of Low Temperature Cracking in Asphalt Pavements. A Transportation Pooled Fund Study; Report No MN/RC 2007-43; University of Minnesota: Minneapolis, MN, USA, October **2007**.
21. Apeagyei, A.K.; Dave, E.V.; Buttlar, W.G., Effect of cooling rate of thermal cracking of asphalt concrete pavements, *Journal of the Association of Asphalt Paving Technologists*, **77**, **2008**, 709–738.
22. Marasteanu, M.; Buttlar, W.; Bahia, H.; Williams, C. Investigation of Low Temperature Cracking in Asphalt Pavements, National Pooled Fund Study—Phase II; Report No MN/RC 2012-23; University of Minnesota: Minneapolis, MN, USA, August **2012**.
23. Tabatabaee, H.; Velasquez R.; Bahia, H.U., Modeling thermal stress in asphalt mixtures undergoing glass transition and physical hardening, *Transportation Research Record: Journal of the Transportation Research Board*, **2296**, **2012**, 106-114, <https://doi.org/10.3141/2296-11>.
24. Hajj, E.Y.; Souliman, M.; Alavi, M.Z.; Salazar, L.L., Influence of hydrogreen bioasphalt on viscoelastic properties of reclaimed asphalt mixtures, , *Transportation Research Record: Journal of the Transportation Research Board*, **2371**, **2013**, 13-22, <https://doi.org/10.3141/2371-02>.
25. Farrar, M.J.; Hajj, E.Y.; Planche, J-P.; Alavi, M.Z., A method to estimate the thermal stress build-up in an asphalt mixture from a single-cooling event, *Road Materials and Pavement Design*, **14** (sup1), **2013**, 201-2011, <https://doi.org/10.1080/14680629.2013.774756>.
26. AASHTO, Guide for mechanistic – empirical design of new and rehabilitated pavement structures MEPDG, Final Report, **2004**, Part 3, Design Analysis, p. 3.3.93, Part 2, design Inputs, 2.2.32.
27. AASHTO PP 42-02, Standard practice for determination of low-temperature performance grade (PG) of asphalt binders, AASHTO Provisional Standards, **2005**.
28. ASTM D6816-11, Standard practice for determining low-temperature performance grade of asphalt binders, **2011**.
29. Hills, J.F.; Brien D., The fracture of bitumen and asphalt mixes by temperature induced stresses, *Journal of the Association of Asphalt Paving Technologists*, Symposium on Pavement Cracking, **35**, **1966**, 294–309.
30. Burgers, B.A.; Kopvillem, O.; Young, F.D., Ste. Anne Test – relationships between predicted fracture temperatures and low temperature field performance, *Journal of the Association of Asphalt Paving Technologists*, **40**, **1971**, 148-193.
31. Christianson, J.T.; Murray, D.W.; Anderson, K.O., Stress prediction and low temperature fracture susceptibility of asphalt concrete pavements, *Journal of the Association of Asphalt Paving Technologists*, **41**, **1972**, 494-523.
32. Haas, R.C.G., A method for designing asphalt pavements to minimize low-temperature shrinkage cracking, Asphalt Institute Research Report 73-1, **1973**, College Park, MD: The Asphalt Institute.
33. Janoo, V.; Bayer, J.; Walsh, M, Thermal stress measurements in asphalt concrete, *US Army Corps of Engineers, Cold Regions Research and Engineering Laboratory*, **1993**, CRREL Report 93-10.
34. Kliewer, J.E.; Zeng, H.; Vinson, T.S., Aging and low-temperature cracking of asphalt concrete mixture, *Journal of Cold Regions Engineering*, **1996**, **10**(3), 134-148.
35. Qian, G.; Zheng, J.; Wang, Q., Calculating Thermal Stresses of Asphalt Pavement in Environmental Conditions, *Symposium on Pavement Mechanics and Materials, Geotechnical Special Publication*, **2007**, 78-87, doi: 10.1061/40986(326)8.
36. Gajewski, M.; Langlois, P-A., Prediction of Asphalt Concrete Low-Temperature Cracking Resistance on the Basis of Different Constitutive Models, *Procedia Engineering*, **91**, **2014**, 81-86, <https://doi.org/10.1016/j.proeng.2014.12.016>.
37. Akentuna, M.; Kim, S.S.; Nazzal, M.; Abbas, A.R.; Arefin M.S., Study of the thermal stress development of asphalt mixtures using the Asphalt Concrete Cracking Device (ACCD), *Construction and Building Materials*, **114**, **2016**, 416-422, <https://doi.org/10.1016/j.conbuildmat.2016.03.207>.
38. Yavuzturk, C.; Ksaibati, K., Assessment of Thermal Stresses in Asphalt Pavements Due to Environmental Conditions, Report, University of Wyoming, **2006**.

39. Pszczola, M.; Jaczewski, M.; Rys, D.; Jaskula, P.; Szydlowski, C., Evaluation of Asphalt Mixture Low-Temperature Performance in Bending Beam Creep Test, *Materials - MDPI*, **2018**, vol. 11, 100, <https://doi.org/10.3390/ma11010100>.
40. Jaczewski, M.; Judycki, J.; Jaskula, P., Asphalt concrete subjected to long-time loading at low temperatures – Deviations from the time-temperature superposition principle, *Construction and Building Materials*, **202**, **2019**, 426–439, <https://doi.org/10.1016/j.conbuildmat.2019.01.049>.
41. Pszczola M.; Judycki J., Testing of low temperature behaviour of asphalt mixtures in bending creep test, *7th International RILEM Symposium on Advanced Testing and Characterization of Bituminous Materials: Advanced Testing and Characterization of Bituminous Materials*, Rhodes, Greece, **2009**, 303–312.
42. Zofka, A.; Marasteanu, M.O.; Turos, M., Determination of asphalt mixture creep compliance at low temperatures using thin beam specimens, *Transportation Research Record: Journal of the Transportation Research Board*, **2057**, **2008**, 134–139, <https://doi.org/10.3141/2057-16>.
43. Zofka, A.; Marasteanu, M.O.; Turos, M., Investigation of asphalt mixture creep compliance at low temperatures, *Road Materials and Pavement Design*, **9** (sup1), **2011**, 269–285, <https://doi.org/10.1080/14680629.2008.9690169>.
44. Judycki, J.; Jaskula, P.; Dolzycki, B.; Pszczola, M.; Jaczewski, M.; Rys, D.; Stienss, M., Investigation of low-temperature cracking in newly constructed high-modulus asphalt concrete base course of a motorway pavement, *Road Materials and Pavement Design*, **16**(sup1), **2015**, 362–388, <https://doi.org/10.1080/14680629.2015.1029674>.
45. CEN - EN 12591: Bitumen and bituminous binders - Specifications for paving grade bitumens, **2009**, European Committee for Standardization CEN.
46. CEN - EN 14023: Bitumen and bituminous binders - Specifications framework for polymer modified bitumens, **2010**, European Committee for Standardization CEN.
47. CEN - EN 13108-1: Bituminous mixtures - Material specifications - Part 1: Asphalt Concrete, **2016**, European Committee for Standardization CEN.
48. Szymanski D., Assessment of the low-temperature properties of asphalt mixtures based on the TSRST, UTST and TCT test results, MSc thesis, **2018**, Gdansk University of Technology (in Polish).
49. CEN - EN 12697-46: Bituminous mixtures – Test methods for hot mix asphalt – Part: 46: Low temperature cracking and properties by uniaxial tension tests, **2012**, European Committee for Standardization CEN.
50. CEN - EN 12697-33: Bituminous mixtures - Test methods for hot mix asphalt - Part 33: Specimen prepared by roller compactor, **2007**, European Committee for Standardization CEN.
51. Judycki, J., Bending Test of Asphaltic Mixtures under Statical Loading. In Design and Quality Control of Bituminous Mixes, Proceedings of the 4th International Symposium on the Role of Mechanical Tests for the Characterization, Budapest, Hungary, 23–25 October 1990; Book Series: RILEM Proceedings; Taylor & Francis: Oxfordshire, UK, **1990**; Volume 8, pp. 207–227.
52. Ferry, J.D. Viscoelastic Properties of Polymers, 3rd ed.; John Wiley & Sons: New York, NY, USA, **1980**.
53. Rowe, G.M.; Sharrock, M.J., Alternate shift factor relationship for describing the temperature dependency of the visco-elastic behaviour of asphalt materials, *Transportation Research Record*, **2207**, **2011**, 125–135.
54. Jaczewski, M.; Judycki, J.; Jaskula, P., Modelling of Asphalt Mixes under Long Time Creep at Low Temperatures, *Transportation Research Procedia*, **14**, **2016**, 3527–3535.
55. Mejłun Ł., Judycki J., Dołzycki B., Comparison of Elastic and Viscoelastic Analysis of Asphalt Pavement at High Temperature, *Procedia Engineering*, **172**, **2017**, 746–753, <http://dx.doi.org/10.1016/j.proeng.2017.02.095>.
56. Judycki, J., Non-linear viscoelastic behaviour of conventional and modified asphaltic concrete under creep, *Materials and Structures*, **25**, **1992**, 95–101.
57. Cholewińska, M.; Iwański, M.; Mazurek, G., The impact of ageing on the bitumen stiffness modulus using the cam model, *Baltic Journal of Road and Bridge Engineering*, **13**(1), **2018**, 34–39.