

The effect of chemical character of ionic liquids on biomass pre-treatment and posterior enzymatic hydrolysis

Joana R. Bernardo, Francisco. M. Gírio, Rafał M. Łukasik*

Unidade de Bioenergia, Laboratório Nacional de Energia e Geologia, I.P., Estrada do Paço do Lumiar 22, 1649-038 Lisboa, Portugal

*e-mail: rafal.lukasik@lneg.pt

Abstract

Ionic liquids have been recognised as interesting solvents applicable in the efficient lignocellulosic biomass valorisation, especially in the biomass fractionation into individual polymeric components or direct hydrolysis some of biomass fractions. Considering the chemical character of ionic liquids, two different approaches, paved the way for a fractionation of biomass. The first strategy integrated a pre-treatment, hydrolysis and conversion of biomass through the employment of hydrogen-bond acidic 1-ethyl-3-methylimidazolium hydrogen sulfate ionic liquid. The second one relied on the use of a three-step fractionation process with hydrogen-bond basic 1-ethyl-3-methylimidazolium acetate to produce high purity cellulose, hemicellulose and lignin fractions. The proposed approaches were scrutinised for wheat straw and eucalyptus residues. Those different biomasses allowed understanding that enzymatic hydrolysis yields are dependent on the crystallinity of pre-treated biomass. The use of acetate based ionic liquid allowed to change crystalline cellulose I to cellulose II and consequently enhanced glucan to glucose yield to 93.1 ± 4.1 mol% and 82.9 ± 1.2 mol% for wheat straw and eucalyptus, respectively. Whereas for hydrogen sulfate ionic liquid, the same enzymatic hydrolysis yields were 61.6 ± 0.2 mol% for wheat straw and only 7.9 ± 0.3 mol% for eucalyptus residues. These results demonstrate the importance of either ionic liquid character or biomass type on the efficient biomass processing.

Keywords

Biomass, valorisation, ionic liquid, crystallinity, enzymatic hydrolysis, pre-treatment

1. Introduction

Lignocellulosic biomass is a renewable, sustainable, abundant, CO₂ neutral and alternative to fossil feedstock for a portfolio of fuels, chemicals and materials. Composed of crystalline cellulose nanofibrils embedded in an amorphous matrix of cross-linked lignin and hemicelluloses, lignocellulose shows the natural recalcitrance that impedes enzyme and microbial accessibility, resulting in a relatively low digestibility of raw lignocellulosic materials [1]. Thus, an efficient pre-treatment and consequently a deconstruction of the lignocellulosic biomass makes these fractions susceptible for more favourable transformation to value-added products [2,3]. However, many pre-treatment methods require harsh conditions, especially temperature and/or pressure that result often in undesired by-products, which decrease the sugar yields and inhibit enzymatic hydrolysis and further bioconversion [2].

In the last years, ionic liquids (ILs) have gained increasing interest for biomass processing due to their capacity to dissolve lignocellulosic biomass by an effective disruption of the complex network of noncovalent interactions between carbohydrates and lignin [4-6]. A main function of IL in the lignocellulosic biomass pre-treatment is the modification the fibrillary structure of cell walls in order to (i) decrease cellulose crystallinity, (ii) increase cellulose surface accessibility by the removal of lignin and/or hemicellulose and (iii) promotion of a swelling effect of biomass [7]. Imidazolium-based ILs are among the most extensively studied ILs and have demonstrated that either a cation or an anion is considerably important in the biomass processing [8,9]. Swatloski *et al.* showed that high concentration of chloride anion is effective in breaking down the hydrogen-bond network of cellulose [10]. Similar effect was reported for acetate ([OAc]) anion, which demonstrated to be efficient in a dissolution of lignocellulosic biomass [11]. It was reported that a key reason for this is a high hydrogen bond acceptor capacity (β) of the [OAc] anion ($\beta = 1.201$) in comparison to previously mentioned chloride anion ($\beta = 0.83$) [12]. Due to that, 1-ethyl-3-methylimidazolium acetate IL confirmed to be one of the best and most commonly used [13] ILs able to dissolve a large variety of lignocellulosic biomass and to fractionate it into cellulose- and hemicellulose-rich fractions as well as to produce high pure lignin [9,14,15].

Alternative approach of the biomass processing with IL is the employment of ILs as both solvent and catalyst. In these processes, ILs hydrolyse mainly polysaccharide fraction without the presence of other catalyst [5,16,17]. Therefore, ILs with acidic character demonstrated ability to selectively hydrolyse hemicellulose [18,19], both cellulose and hemicellulose [20], or lignin [21]. One of the most commonly used IL in such approaches are those based on hydrogen sulfate ([HSO₄]). They are able to catalyse a selective hemicellulose hydrolysis [17-19]. Furthermore,

[HSO₄]-based ILs have been increasingly used because of their acidic properties and due to their low cost when compared to other ILs [22]. The use of acidic IL, e.g. 1-butyl-3-methylimidazolium hydrogen sulfate, [bmim][HSO₄], allowed achieving up to 90% fermentable glucose after enzymatic saccharification of the cellulose-rich *Miscanthus* pulp [18]. The same IL was also reported as able to hydrolyse and to convert hemicellulose fraction of wheat straw with no additional catalyst used [17]. The pre-treatment with this IL produced a liquor rich in hemicellulosic sugars, furans and organic acids, and a solid fraction constituted mainly of cellulose and lignin. Furthermore, water was confirmed to have an influence on the equilibrium of the hemicellulose hydrolysis. The increase of the water content close to 10% (w/w) in the reaction system disfavoured xylose dehydration and thus allowed increasing significantly the production of hemicellulose-derived monosaccharides [19].

Learnt on previous works about processing of biomass with hydrogen-bond basic ([emim][OAc]) [11] and hydrogen-bond acidic ([emim][HSO₄]) [17,19] ILs, this work aims to demonstrate the importance of biomass type on the efficiency of the biomass pre-treatment as well as on the efficiency of subsequent enzymatic hydrolysis. This was examined using two very distinct types of biomasses, namely herbaceous (wheat straw) and hardwood such as *Eucalyptus globulus* and allowed elucidating change observed in a chemical structure of the biomass, cellulose crystallinity and consequently their effects on the cellulose-rich pulp hydrolysability.

2. Results and Discussion

2.1. Hydrogen-bond acidic IL

2.1.1. Biomass pre-treatment with [emim][HSO₄]

The first methodology used was focused on the biomass pre-treatment with [emim][HSO₄]. As stated above, this approach allowed the integration of biomass pre-treatment, hydrolysis and conversion in a single step process. The acidic character of [HSO₄] anion of IL, promoted a selective hydrolysis of hemicellulose fraction and the resulting products (mainly pentoses and furfural) were kept in the liquid phase. Both biomasses, wheat straw and eucalyptus residues were subject to processing with [emim][HSO₄] IL at 140 °C during 90 min at varied [emim][HSO₄]/H₂O mass ratio and with fixed 10 wt.% of dry biomass in the reaction mixture. The pentose and furfural yields obtained in these trials are depicted in Figure 1.

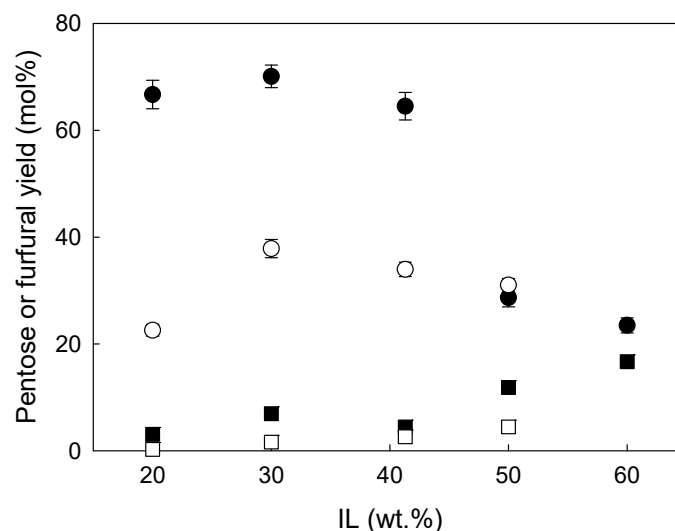


Figure 1. The yields of (●○) pentose (sum of arabinose and xylose) or (■□) furfural as a function of IL concentration (wt.%) obtained from pre-treatment of wheat straw (full symbols) and eucalyptus residues (open symbols) performed at 140°C and 90 min.

As it can be seen, at IL concentration of 30 wt.%, the pentose yields peaked for both biomasses. For eucalyptus residues or wheat straw, further increase in the IL concentration demonstrated to have a negative effect on the pentose yield as was counterbalanced by predominant production of furfural. These results are not surprising since a high performance of acidic ILs towards furfural was often reported in literature [23-25]. One of the reason for this is that pentose conversion to furfural is a dehydration reaction therefore, a higher concentration of IL or in other words, a lower concentration of water may disturb the equilibrium existing in the system promoting the dehydration of pentoses towards furfural production. On the other hand, the presence of water in the system allowed protection of pentoses from dehydration and consequently, high pentose yield was possible to be obtained for IL concentration below 30 wt.%. Although this observation is valid for either wheat straw or eucalyptus residues, the yield of hemicellulose hydrolysis as well as pentose and furfural yields seem to be strongly dependent on the biomass nature. As it can be seen in Figure 1, at the best conditions, i.e. 30 wt.% IL, pre-treatment of the eucalyptus residues with [emim][HSO₄] allowed achieving only 37.9±1.7 mol% pentoses, while for a wheat straw a maximum pentose concentration was almost double i.e. 70.1±0.5 mol%. This difference is also reflected in the composition of pre-treated solids and the solid yields. The last for eucalyptus residues was very high and varied between 81 and 85 wt.% while for pre-treated wheat straw it oscillated between 68 to 75 wt.%. For both

biomasses, the lowest solid yields were observed for solids obtained in pre-treated with IL concentration of 30 wt.%. It is a direct consequence of the most pronounced hydrolysis of hemicellulose. Further increase in the IL concentration has increased a solid yield for wheat straw up to 74.9 ± 3.0 wt.%. This unexpected increase of the solid yield with an increase in the pre-treatment severity might be justified by a formation of pseudo-lignin called also humins [26]. As pseudo-lignin are quantified gravimetrically [27], they contribute to an increase in the lignin content detected, which is clearly visible in Figure 2. For two the highest IL concentration tested, the lignin recovered were superior than 100 wt.% of lignin present in native biomass. This, in turn may confirm this hypothesis.

Similar effect was not observed for eucalyptus residues for which either solid yield appeared to be constant or lignin content in the solids pre-treated at various IL concentrations did not change as demonstrated in Figure 3.

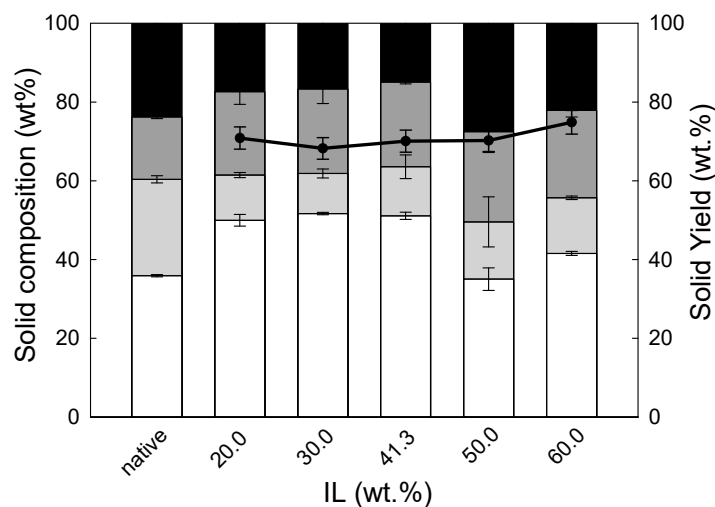


Figure 2. The solid phase composition (white bar - cellulose; light grey bar - hemicellulose; dark grey bar – Klason lignin; black bar – others) of wheat straw pre-treatment at 140°C and 90 min with [emim][HSO₄] at various % IL. Solid line represents the solid yield (wt.%) of pre-treated solids recovered after pre-treatment.

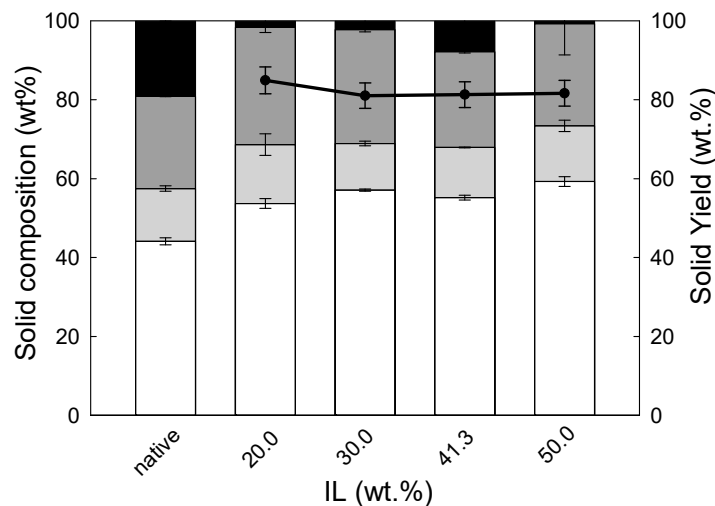


Figure 3. The solid phase composition (white bar - cellulose; light grey bar - hemicellulose; dark grey bar – Klason lignin; black bar – others) of eucalyptus residues pre-treatment at 140°C and 90 min with [emim][HSO₄] at various % IL. Solid line represents the solid yield (wt.%) of pre-treated solids recovered after pre-treatment.

The aforementioned analysis of the hemicellulose hydrolysis reflects also the macromolecular composition of pre-treated leftovers of both biomasses. It is clearly visible that the IL pre-treatment induced the reduction of hemicellulose fraction in comparison to native biomasses as xylan was found in amount not exceeding 15 wt.% of the pre-treated biomasses. Consequently, the major components of the produced solids were glucan, followed by already discussed lignin. It indicates that contrary to a great performance of aqueous [emim][HSO₄] solution in processing hemicellulose, a cellulose hydrolysis in this catalytic system seems to be very inefficient. For IL concentration up to studied 41.3 wt.%, the cellulose yield was kept constant but in case of wheat straw for higher IL concentrations (>50 wt.%), the cellulose content started to diminish. It demonstrates that only at these conditions, the cellulose fraction of wheat straw is also susceptible for hydrolysis and for pre-treatment with IL concentration of 60 wt.% as much as 20 wt.% of cellulose in comparison to native biomass was removed. In case of eucalyptus residues, in the range of studied IL concentrations, already 20 wt.% of IL allowed to remove about 1/3 of hemicellulose and further increase in the IL concentration in the reaction mixture has no further significant changes in the composition of the pre-treated solids as it can be seen in Figure 3. These results confirm again that although ILs are capable of processing various types of herbaceous and woody biomass as a single feedstock, the conditions for efficient pre-treatment are dependent upon the biomass type, with softwoods or hardwoods are

recognised as the most difficult to process when compared to herbaceous biomass [6]. Indeed, Xu *et al.* found that the eucalyptus residues treatment catalysed by 0.5 % (v·v⁻¹) [bmim][HSO₄] gave only ≈ 25 mol% of pentose yield at 190 °C [28]. Other literature reports depict the use of the acidic ILs in the pre-treatment of biomass as well. For example, Li *et al.* observed that acidic IL demonstrated to be as an efficient system for hydrolysis of lignocellulosic materials. They obtained a total reducing sugars (TRS) yields of 23% and 15% from corn stalk after only 5 min of the reaction at 100 °C in [bmim][HSO₄] and [C₄SO₃Hmim][HSO₄], respectively. On the other hand longer reaction times provided lower TRS yields suggesting that these strongly acidic ILs resulted in the promotion more advanced degradation of polysaccharide fraction at the pre-treatment step [20]. Other work showed that in case of Miscanthus pre-treatment at higher temperature (120 °C) and during 4 h with [bmim][HSO₄] and 20 vol.% (17 wt.%) of H₂O content, close to 16% of hemicellulose sugar monomers were obtained [18]. In a different study, Carvalho *et al.* showed that the same IL with 9.22 wt.% H₂O content in pre-treatment of wheat straw (125 °C and 82.1 min) allowed to obtain 40.1 mol% pentose yield [19]. Thus, comparing the literature data to these presented in this work, it can be stated that higher yield of pentoses was selectively achieved without excessive amounts of IL present in the system.

2.1.2. Enzymatic hydrolysis of pre-treated solids

The efficiency of pre-treatment of wheat straw and eucalyptus residues by [emim][HSO₄] was evaluated by enzymatic hydrolysis. The enzymatic hydrolysis yield of pre-treated wheat straw is presented in Figure 4.

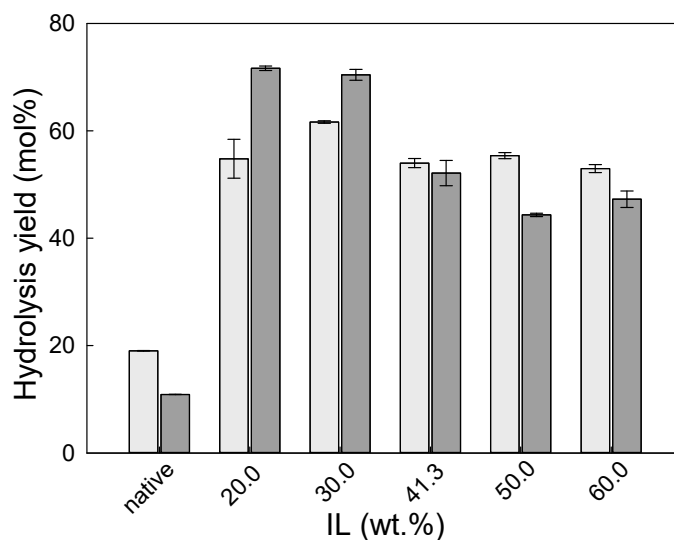


Figure 4. The enzymatic hydrolysis yield (glucan to glucose (light grey bar) and xylan to xylose (dark grey bar)) of wheat straw pre-treated solids as a function of IL concentration used in the pre-treatment. The enzymatic hydrolysis yield for native wheat straw presented for comparison.

As it can be observed in Figure 4, the pre-treatment of wheat straw with [emim][HSO₄] allowed to increase by 3-fold the enzymatic hydrolysis of cellulose to glucose in comparison to native biomass. Interestingly, the enzymatic hydrolysis yield of cellulose (light grey bars) changed slightly with the IL concentration used in pre-treatment and varied from 53.0±0.7 mol.% to 61.6±0.2 mol% for 60 and 30 wt.% of IL, respectively. On the other hand, xylan hydrolysis yield decreased more pronouncedly with an increase of IL concentration from 71.7±0.4 mol% to 47.3±1.5 mol% for 20 and 60 wt.% of IL concentration. The reason for this might be that with an increase in the reaction severity, more hemicellulose was extracted from biomass consequently less hemicellulose accessible for enzymatic attack was present in the pre-treated solid. In addition, the formation of pseudo-humins may interfere with the accessibility of enzymes to hemicellulose and lignin presence affects an enzymatic hydrolysis because of unproductive and irreversible cellulase enzyme adsorption on lignin [29].

Similarly to wheat straw, pre-treatment of eucalyptus residues with [emim][HSO₄] improved the enzymatic hydrolysability in comparison to native biomass as it can be seen in Figure 5.

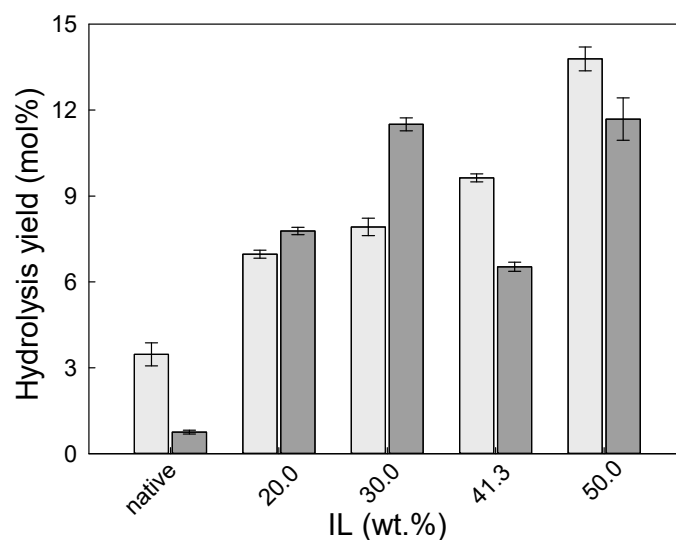


Figure 5. The enzymatic hydrolysis yield (glucan to glucose (light grey bar) and xylan to xylose (dark grey bar)) of eucalyptus residues pre-treated solids as a function of IL concentration used

in the pre-treatment. The enzymatic hydrolysis yield for native eucalyptus residues presented for comparison.

Furthermore, for eucalyptus residues pre-treated solids, an increase of IL concentration has generally a positive effect on the yield of enzymatic hydrolysis. For example, an enhancement of glucan to glucose yield was found with an increase of IL concentration, however, the hydrolysis yields detected were very low and did not exceed 14 mol%, i.e. 4.5-fold lower than observed for wheat straw. In previous work, Xu *et al.* verified that the cellulose rich-solids from eucalyptus residues after [bmim][HSO₄]-catalysed hydrothermal microwave pre-treatment allowed achieving greater glucose conversion yield (89.2 %), however, it was only possible to when temperature as high as 200 °C was used in pre-treatment and enzymatic hydrolysis was performed at 2 w/v% of substrate concentrations and 20 FPU/g substrate after 72h [28]. Brand *et al* demonstrated that the pre-treatment time has a significant effect on the enzymatic saccharification [18]. The pre-treatment of Miscanthus with [bmim][HSO₄] at 120 °C and 8 h resulted in solid which produced ~80 % glucose and ~30 % hemicellulose release. It is noteworthy that enzymatic saccharification was performed according to very favourable NREL conditions for enzymatic hydrolysis [30].

These very different results for wheat straw and eucalyptus residues drove to an employ of the approach with hydrogen-bond basic IL, namely [emim][OAc].

2.2. Hydrogen-bond basic IL

3.2.1. Biomass pre-treatment with [emim][OAc]

The biomass pre-treatment with hydrogen-bond basic [emim][OAc] IL allowed biomass dissolution and fractionation into cellulose-, hemicellulose- and lignin-rich fractions. For this purpose, pre-treatment of wheat straw or eucalyptus residues in [emim][OAc] at 120 and 140 °C, during 2 h at biomass/IL ratio of 1/20 (w/w) was examined on the basis of methodology presented in literature [11]. The composition of obtained solids is given in Figures 6 and 7.

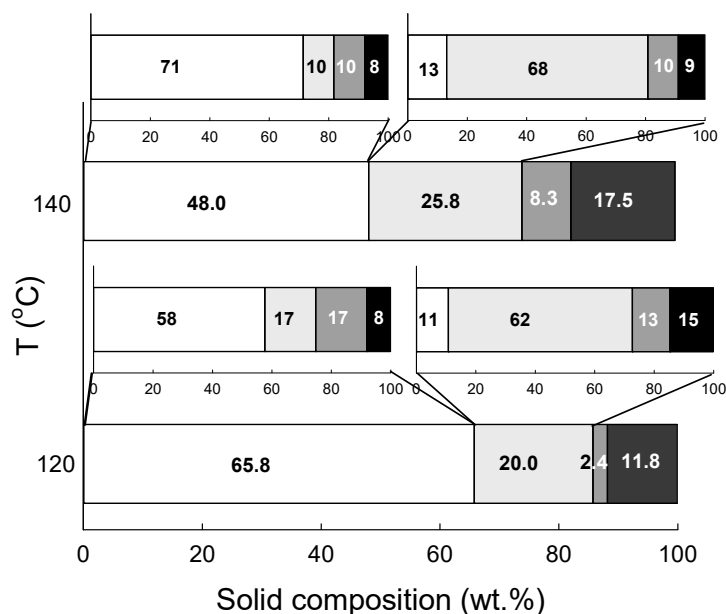


Figure 6. The cellulose- (white bar), hemicellulose- (light grey bar), Klason lignin-rich (dark grey bar) fractions obtained from wheat straw pre-treated with [emim][OAc] at 120 °C and 140 °C and 2 h. Inserts present the composition of cellulose- and hemicellulose-rich fractions (the same colours were used to denominate each individual component). Numbers presented in the figure indicate the composition (expressed in wt.%). For clarity purposes, the composition presented in inserts is given with no decimal cases. For exact values, refer to table S1 in Electronic Supplementary Information (ESI). Black bars correspond to other non-identified components and were calculated as a difference between biomass used for process or characterised fraction and cellulose, hemicellulose and lignin determined.

The obtained results demonstrate that temperature has an effect on the selectivity of the fractionation because although a significantly lower amount of cellulose-rich fraction was obtained at 140 °C in comparison to 120 °C (48.0 wt.% vs. 65.8 wt.% for 140 and 120 °C, respectively), it contained more cellulose, i.e. 57.6 ± 0.3 wt.% vs. 71.4 ± 0.6 wt.% for 120 and 140 °C. However, as it can be seen in Figure 6, a major reason for this was insufficient fractionation of hemicellulose and lignin because cellulose-rich sample obtained at 120 °C contained still 17.1 ± 3.4 and 17.2 ± 1.0 wt.% of hemicellulose and lignin, respectively. The same sample obtained at 140 °C enclosed much lower hemicellulose and lignin contents because it was only 10.3 ± 1.8 wt.% of each. These relevant differences in more selective fractionation of biomass achieved at higher temperature found also confirmation in hemicellulose-rich sample. Contrary to cellulose-rich sample, hemicellulose-rich fraction obtained at 140 °C contained

more solid, i.e. 25.8 wt.% in comparison to 20.0 wt.% for 120 °C and this solid was enriched in hemicellulose as it encompassed 67.8±1.6 wt.% of hemicellulose while at 120 °C it was only 61.9±1.5 wt.%. Consequently, it was predominantly counterbalanced by a difference in lignin and other component contents found in both hemicellulose-rich solids. Interestingly, the lignin-rich fraction obtained at 120 °C was negligible (2.4 wt.%), while this produced at 140 °C was more than 3 times higher and equalled 8.3 wt.%. This again clearly indicates that a higher temperature was more effective in the fractionation of wheat straw and allowed producing cellulose-, hemicellulose- and lignin-rich fraction characterised by higher purity.

Labbé *et al.* also concluded that at high temperatures, [emim][OAc] is capable to cleave the acetyl groups covalently attached mostly to the hemicellulose component of yellow poplar [31]. Therefore, at higher temperature this IL can effectively disrupt the carbohydrate – lignin linkages favouring hemicellulose release.

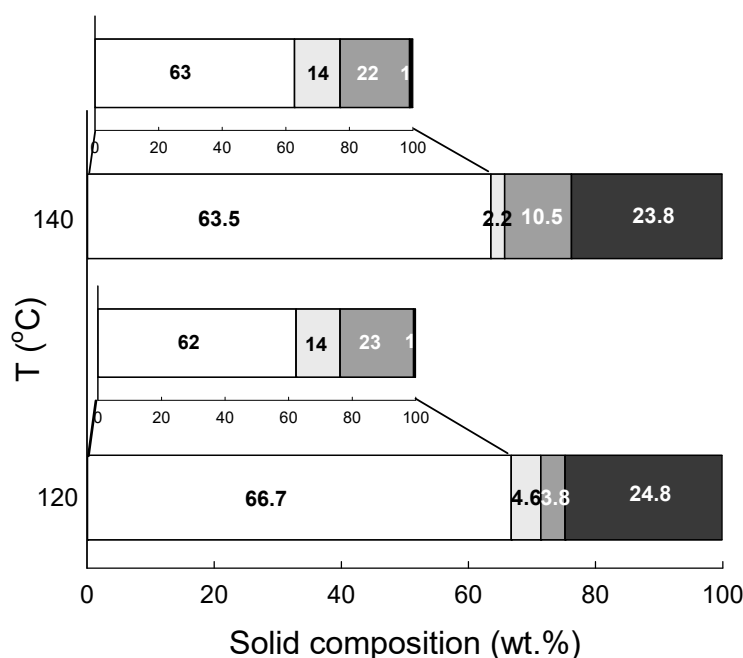


Figure 7. The cellulose- (white bar), hemicellulose- (light grey bar), Klason lignin-rich (dark grey bar) fractions obtained from eucalyptus residues pre-treated with [emim][OAc] at 120 °C and 140 °C and 2 h. Inserts present the composition of cellulose- and hemicellulose-rich fractions (the same colours were used to denominate each individual component). Numbers presented in the figure indicate the composition (expressed in wt.%). For clarity purposes, the composition presented in inserts is given with no decimal cases. For exact values, refer to table S2 in ESI. Black bars correspond to other non-identified components and were calculated as a

difference between biomass used for process or characterised fraction and cellulose, hemicellulose and lignin.

As demonstrated in Figure 7, eucalyptus residues processing with [emim][OAc] at different temperature has almost no effect on the selectivity of biomass fractionation. An increase of temperature by 20 °C from 120 to 140 °C, similarly to wheat straw reduced the amount of cellulose-rich sample recovered from 66.7 wt.% to 63.5 wt.% and enhanced its purity by less than 1 wt.%. Although the trends are the same as observed for wheat straw, but the changes are negligible when compared to those presented in Figure 6. Hemicellulose-rich fractions were recovered in very small quantities, which made their characterisation impossible. Consequently, it can be concluded that although biomass fractionation to cellulose-, hemicellulose- and lignin-rich fraction occurred however the eucalyptus residues turn the process with hydrogen-bond basic IL less efficient than in case of herbaceous biomass and others presented in literature [9,11,32,33].

3.2.2. Enzymatic hydrolysis of pre-treated solids

Regardless the efficiency of both biomass fractionation processes, cellulose-rich samples were subject to the enzymatic hydrolysis according to method presented in the experimental section. The obtained results are presented in Figure 8 and are compared to those achieved for hydrogen-bond acidic IL.

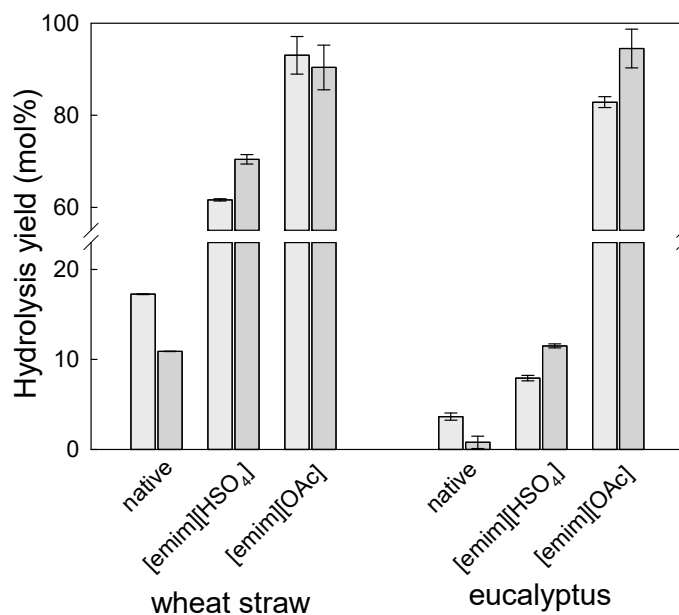


Figure 8. The enzymatic hydrolysis yield (glucan to glucose (light grey bar) and xylan to xylose (dark grey bar)) of pre-treated wheat straw and eucalyptus residues solids produced in processes at 140 °C with aqueous [emim][HSO₄] (30 wt.%, 90 min) and [emim][OAc] (2 h). The enzymatic hydrolysis yield for native biomasses presented for comparison.

The obtained results demonstrate clearly that pre-treatment of either wheat straw or eucalyptus residues with [emim][OAc] enhanced dramatically the enzymatic hydrolysis yields. For example, for cellulose-rich sample of wheat straw obtained from pre-treatment with [emim][OAc], the glucan to glucose yield was as high as 93.1±4.1 mol%, while for the same biomass pre-treated with [emim][HSO₄] a maximum hydrolysis yield of 61.6±0.2 mol% was achieved. Although this 50% enhancement is remarkable however, the same process for eucalyptus residues demonstrated even more astonishing improvement of glucan to glucose hydrolysis yield. As it was shown above, the pre-treated solids obtained after reaction with [emim][HSO₄] allowed achieving very modest enzymatic hydrolysis yield of 7.9±0.3 mol% but the enzymatic hydrolysis yield of cellulose-rich solid obtained from the pre-treatment of eucalyptus residues with [emim][OAc] was as high as 82.9±1.2 mol%. In terms of potential valorisation of cellulose present in the native biomass, a switch from [emim][HSO₄] to [emim][OAc] also demonstrated to be better choice for both biomasses. The yield of glucose released after both steps (pre-treatment with [emim][OAc] and posterior enzymatic hydrolysis) was as high as 91.4 mol% and 74.9 mol% for wheat straw and eucalyptus residues, respectively. The same yield for both biomasses pre-treated with [emim][HSO₄] with 30 wt.% of IL was only 62.3 mol% and 7.9 mol% for wheat straw and eucalyptus, correspondingly.

These results indicate that a change of the IL used from hydrogen-bond acidic to hydrogen-bond basic IL promoted a significant changes in the pre-treated solids as the enzymatic hydrolysis yield increased more than 1000%. The literature results also confirm similar although not so pronounced differences. For example, Bian *et al.* studied the effect of IL pre-treatment on enzymatic hydrolysis of cellulose as a function of chemical and physical structure changes [34]. In a case of cellulose isolated from sugarcane bagasse subjected to IL ([emim][OAc]) dissolution at a mild temperature (90 °C) followed by a solid regeneration in water, an increase in glucose content from 80.0–83.3 wt.% to 91.6–92.8 wt.%, a decrease in the degree of polymerisation from 974–1039 unit to 511–521 unit, a transformation from cellulose I to cellulose II, and an increase of surface area during the pre-treatment was found. Such cellulose was subsequently hydrolysed by commercial cellulases with 2 w/v% cellulose

substrate and enzyme loadings of 35 FPU/g (cellulase) and 40 CbU (β -glucosidase) in relation to the dry weight of cellulose substrates) allowed achieving a high glucose conversion yield of 95.2 mol%. These results suggest that pre-treatment led to an effective disruption of cellulose favouring enzyme hydrolysis. Torr *et al.* also observed an improvement of the glucan to glucose after saccharification for 72 h performed at biomass loading of 1.5% (w/v) and Celluclast 1.5L and Novozymes 188 with 40 FPU/g glucan and β -glucosidases of 50 IU/g glucan, from 5 mol% in the untreated pine wood to 84 mol% in wood pre-treated with [emim][OAc]. The analysis of the substrates revealed that the most important change brought by the pre-treatment was an increase in accessible surface area. In this case the delignification was not observed and loss of cellulose crystallinity only occurred for the most severe pre-treatments [35]. Therefore, to verify this, changes in morphology of pre-treated solid materials was studied using X-ray diffraction.

3.3. Morphological analysis of pre-treated solids

Crystalline cellulose is the most organised form of cellulose in the biomass [36]. Also, crystallinity of cellulose has been reported as one of the most relevant factors influencing the efficiency of enzymatic hydrolysis [37]. X-ray diffraction permits to measure the crystallinity of the material as a whole because demonstrate either crystalline (organised) or disordered components of biomass namely, amorphous cellulose, hemicellulose and lignin [38]. ILs have shown to affect cellulose crystallinity during pre-treatment and consequently enhances the enzymatic hydrolysis [39]. Therefore, the effect of different pre-treatment approaches on the crystallinity, which could justify the efficiency of enzymatic hydrolysis, was tested in this work as well. The obtained results for wheat straw and eucalyptus residues are depicted in Figure 9 and 10, respectively.

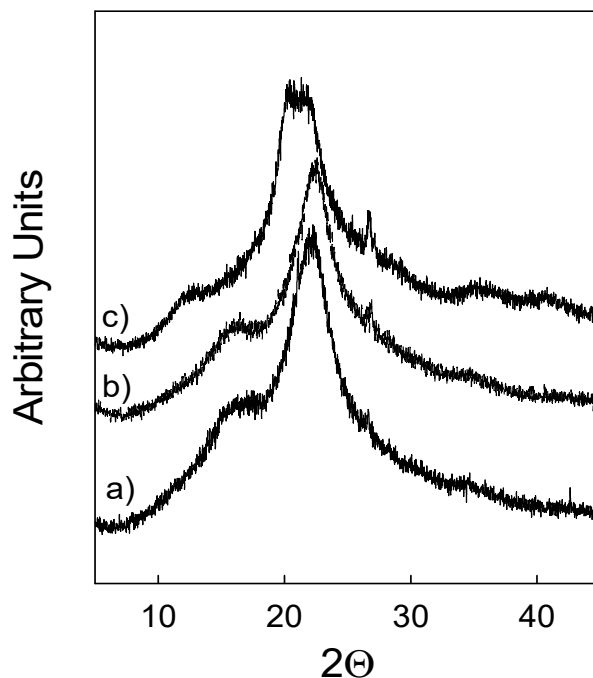


Figure 9. Powder XRD patterns of a) native wheat straw, b) pre-treated by [emim][HSO₄] and c) pre-treated by [emim][OAc] IL.

Figures 9 a) and 10 a) show the diffraction patterns of untreated wheat straw and eucalyptus residues. The main signal can be observed at 22.3° for wheat straw and 22.5° for eucalyptus residues samples. This signal indicates the distance between hydrogen-bonded sheets in cellulose I and corresponds to (200) lattice plane. For both biomasses, the 2nd main band observed is a broad signal registered at $2\theta = 16.7^\circ$ and corresponds to overlapping signals of (101) and (10-1) planes. The “valley” at 18.1° is associated to amorphous region in the biomass and includes disordered cellulose, hemicellulose and lignin. The third barely noticeable signal at 34.5° corresponds to $\frac{1}{4}$ of the length of one cellobiose unit and arises from ordering along the fibre direction.

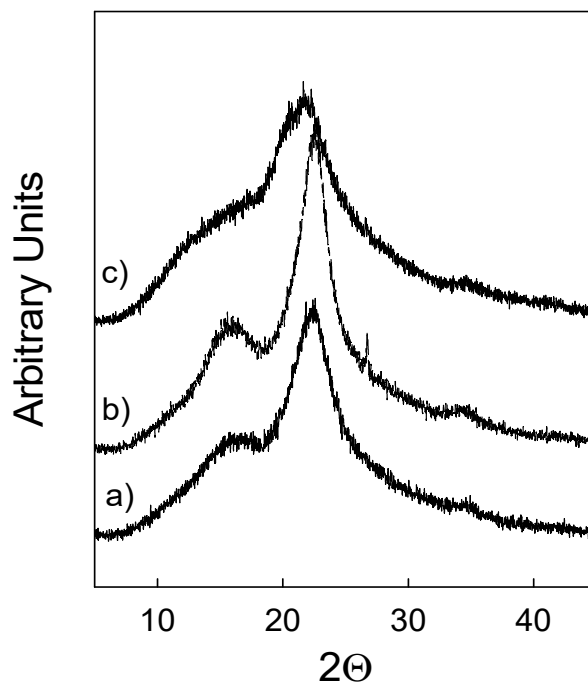


Figure 10. Powder XRD patterns of a) native eucalyptus residues, b) pre-treated by [emim][HSO₄] and c) pre-treated by [emim][OAc] IL.

The XRD patterns of wheat straw and eucalyptus residues pre-treated by [emim][HSO₄] indicated in Figures 9 and 10 as diffractograms b) mirror the diffractograms observed for native biomasses (Figures 9 a) and 10 a)). This confirms that hydrogen-bond acidic IL such as [emim][HSO₄] tested in this work does not induce any qualitative changes in the pre-treated samples. The same cannot be said about the cellulose-rich solids produced in the [emim][OAc] pre-treatment. The most dominant change is a disappearance of signal at 22.5°, and presence a broad asymmetric signal consisting of a doublet at 20° and 21.7° as demonstrated in Figure 9 c). Similarly, the broad signal at 16° disappeared and was substituted by a new signal emerged at 12.1° as can be seen in the same. These changes are characteristics for a transformation of cellulose I to cellulose II and they are the most visible for wheat straw pre-treated samples. For cellulose-rich sample of eucalyptus residues, similar changes in the diffractogram are visible although they are less notorious. For example, as shown in Figure 10 c), a broad signal at 20-22° can be found. Additionally, a signal at 16° turned to be a very wide and was transformed into the arm of the main signal. These changes in signals confirm the alteration in the cellulose organisation similarly to what was observed for wheat straw. At the same time as these signals are still not complete defined contrary to what was observed for wheat straw cellulose-rich sample, it may indicate that in case of eucalyptus residues, a transformation of crystalline

cellulose is less effective and may require longer pre-treatment time. Regardless the reasons, the observed changes in the XRD patterns justify the fact that even partial alteration of biomass crystallinity is sufficient to promote more efficient enzymatic hydrolysis as demonstrated in this work. Similar results were presented in literature where it was confirmed that cellulose II is more readily digested than cellulose I. It has been argued that the van der Waals interactions between hydrogen-bonded sheets in cellulose I are stronger than in cellulose II and they act as a main factor to resist the cellulose hydrolysis [40]. Li *et al.* compared the pre-treatment of the switchgrass with [emim][OAc] and with a 1.2 % (w/w) dilute sulphuric acid [41]. For both untreated and a dilute acid pre-treated switchgrass samples little or no changes in cellulose crystallinity were observed, but for the sample obtained after pre-treatment with [emim][OAc] the crystallinity was altered significantly, observing a structural transformation from cellulose I to cellulose II. This, in turn promoted a better performances of enzymatic hydrolysis.

3. Materials and methods

3.1. Materials

The wheat straw sample was delivered by ECN (Energy Research Centre of the Netherlands), from The Netherlands. The eucalyptus residues were kindly provided by The Navigator Company from their paper mill in Cacia, Portugal. The wheat straw and eucalyptus residues moisture content were found to be 9.8 and 8.4 % (w/w), respectively and was determined using an AMB-50 moisture analyser.

Both feedstocks were grounded with a knife mill IKA® WERKE, MF 10 basic (Germany) to particles smaller than 0.5 mm, homogenised in a defined lot, and stored in plastic containers at room temperature prior to further use.

The [emim][HSO₄] IL (99 wt.% of purity) was purchased from Iolitec GmbH (Heilbronn, Germany) and was used in reactions without any previous purification. The water content in IL was determined by a volumetric Karl-Fischer titration and was 3796 ppm. The [emim][OAc] with stated purity >95% was purchased from Iolitec GmbH – Heilbronn, Germany. Prior to use in the pre-treatment, this IL was subject to drying under vacuum (0.1 Pa) at room temperature for at least 24 h. The water content in this IL was 2800 ppm determined by a volumetric Karl-Fischer titration as for the other IL.

In pre-treatment experiments, the following reagents were used: 0.1 M and 3% (w/w) NaOH aqueous solutions prepared from NaOH pellets (99% purity) supplied by Eka chemicals/Akzonobel–Bohus, Sweden. The aqueous solutions of 1 M and 4 M HCl were

prepared from fuming HCl 37% (w/w) with a purity grade for analysis (Merck – Darmstadt, Germany). Ethanol 96% (v/v) and acetonitrile of HPLC-gradient purity for analysis (Carlo Erba Group – Arese, Italy) and acetone (98% purity) were supplied by Valente & Ribeiro, Lda – Belas, Portugal. For the preparation of NaOH and HCl solutions distilled water ($17 \text{ M } \Omega \text{ cm}^{-1}$) and ultrapure water ($18.2 \text{ M } \Omega \text{ cm}^{-1}$) both produced by the PURELAB Classic of Elga system were used.

For filtration, paper and glass microfiber filters (Whatman GE Healthcare Bio-Sciences Corp. – Piscataway, NJ, USA) and nylon filters, 0.45 μm HNPW (Merck Millipore – Billerica, MA, USA) were used.

Glucose (≥ 98 wt.%, Merck, Germany), xylose (≥ 98 wt.%, Merck, Germany), arabinose (≥ 98 wt.%, Merck, Germany), furfural (furan-2-carbaldehyde) (99 wt.%, Sigma-Aldrich, Germany), 5-hydroxymethylfurfural (5-(hydroxymethyl)-2-furaldehyde) (99 wt.%, Sigma-Aldrich, Germany) and acetic acid (glacial, 99.8 wt.% Merck, Germany) were used for the qualitative and quantitative HPLC analyses of the obtained liquids and solids. Sulfuric acid (96 wt.%, Panreac, Spain) was used to prepare mobile phase for HPLC analyses (5 mM sulphuric acid). For the enzymatic hydrolysis assays 0.1 M sodium citrate buffer (pH 4.8) prepared from citric acid monohydrate (99.7% purity) and tris-sodium citrate ($>99\%$ purity) both from VWR International Ltd. – Leicester, England and a 2 wt.% sodium azide solution were used. Celli@CTec2 enzyme solution kindly provided by Novozymes Europe, Denmark was employed in the enzymatic reaction.

3.2. Biomass and pre-treated solid characterisation

Both biomasses and pre-treated solids were characterised to determine the total moisture, total lignin and polysaccharide contents according to NREL methods [27]. Acid-insoluble lignin was determined gravimetrically, while acid-soluble lignin was established using UV spectrophotometry. The content of glucan and hemicelluloses (xylan, arabinan, and acetyl groups) was determined using high performance liquid chromatography (HPLC) equipment. Furthermore, for native biomasses, total extractives, ash and protein contents were determined according to standard methods, namely: NREL/TP-510-42619 [42], NREL/TP-510-42622 [43] and ISO 8968-1:2014 [44], respectively.

The composition of both biomasses is presented in Table 1.

Table 1. Wheat straw and eucalyptus residues macromolecular composition.

Components (dry weight %)	wheat straw	eucalyptus residues
Glucan	35.9±0.3	44.1±0.9
Hemicellulose	26.7	19.6
Xylan	22.1±0.6	15.7±0.2
Arabinosyl group	2.0±0.7	0.5±0.1
Acetyl group	2.6±0.9	3.4±0.9
Lignin	16.7	33.8
Acid-insoluble	15.5±0.4	26.4±0.1
Acid-soluble	1.2±0.1	7.4±0.1
Ash	11.4±0.1	1.0±0.1
Extractives		
Water	9.4±1.3	3.3±0.4
Water (not ash)	5.1±0.5	0.2±0.0
Ethanol	1.4±0.1	1.5±0.1

3.3. Biomass processing

3.3.1. Pre-treatment of biomass with [emim][HSO₄]

All reactions were performed with a 10 wt.% of dry biomass in the reaction mixture. For this purpose, 0.5 g of dry biomass and 4.5 g of aqueous IL solution with different [emim][HSO₄]/H₂O ratio, were placed into a 15 mL glass vial (Supelco/Sigma-Aldrich, USA). Next, a vial was placed into the oil bath pre-heated to a desired temperature (140 °C), and reactions were carried out for 90 min, under continuous magnetic stirring. The reaction condition was selected on the basis of the previous work published elsewhere [17]. After reaction, the mixture was cooled down to room temperature and approximately 5.0 mL of ultrapure H₂O was added to precipitate non-hydrolysed fractions. The resulting mixture was filtered under vacuum using 0.45 µm nylon membrane filters. The liquid phase was collected and stored in a freezer for posterior analysis by HPLC, while recovered solid biomass was washed with 100 mL of ultrapure H₂O (in 10 mL portions) to guarantee removal of IL from the precipitated solid. Next, the obtained solid was placed in the oven at 60 °C for 24 hours and afterwards was stored at room temperature for 1 hour to analyse the dry mass content. The composition of the solid was analysed as presented in section 2.2.

3.3.2. Pre-treatment of biomass with [emim][OAc]

The pre-treatment was performed according to method presented in literature [11]. Reactions were performed at two different temperatures (120 or 140 °C) during 2 h with a 5% (w/w) biomass/IL ratio in a 15 mL vial. Following the aforementioned procedure presented in literature, three solid fractions, rich in cellulose, hemicellulose and lignin were obtained. All of them were characterised according to methods presented in section 2.2.

3.4. Enzymatic hydrolysis of solids

The digestibility of pre-treated solids obtained with [emim][HSO₄] or [emim][OAc] was evaluated by enzymatic hydrolysis. The assays were performed using 5% (w/v) solids (dry weight basis) concentration in 50 mL vials with 5 mL of 0.05 M sodium citrate buffer (pH 5), prepared from citric acid monohydrate and tris-sodium citrate and 100 µL of a 2 wt.% sodium azide solution to prevent undesired growth of microorganisms. Distilled water was added to reach 5.0 mL taking into account the volume of enzyme added as the last. The enzyme dosage used was 10% (w/w cellulose) of Celli®CTec2 (199.9 FPU·mL⁻¹). The enzymatic hydrolyses were performed in a shaking incubator (Opticivymen®system – Spain) at 180 rpm and 50 °C for 72 h. After hydrolysis, enzymes were inactivated by freezing the samples. To measure monosaccharide content, the hydrolysates were filtered under vacuum using nylon filters (pore size of 0.45 µm) and analysed by HPLC. The glucose and xylose yields were calculated considering the glucan and xylan contents and factors of (162/180) and (132/150) for dehydration, respectively.

3.5. Chemical analysis

3.5.1. HPLC analysis

The liquid phases obtained from the pre-treatment of biomass with [emim][HSO₄] and enzymatic hydrolyses as well as from native or pre-treated biomass characterisation were analysed using an Agilent 110 series equipment with Bio-Rad Aminex HPX-87H column (Hercules, CA, USA). Analyses were performed at 65 °C with 5 mmol·L⁻¹ H₂SO₄ used as the mobile phase at a flow rate of 0.6 mL·min⁻¹. The detection was performed using RID (refractive index detector) for monosaccharides (glucose, xylose and arabinose) and acetic acid and DAD (diode array detector) at 280nm wavelength for furans (furfural and 5-HMF ≡ 5-hydroxymethylfurfural). The quantitative analyses were performed by external calibration using standard solutions.

3.5.2. XRD Measurements

The crystallinity analyses of untreated biomasses and pre-treated materials was performed by X-Ray powder diffraction (XRD). For this purpose, a Rigaku Geigerflex D/MAX-III C X-ray powder diffractometer with vertical goniometer, Bragg-Brentano geometry and graphite monochromator. The $\text{CuK}\alpha$ radiation ($\lambda = 1.5418 \text{ \AA}$) at 45 kV and 20 mA was used. The samples were analysed in the range of 2θ from 5° to 50° with increments of 0.02° .

3.6. Experimental uncertainty

Each weighing was made with a standard uncertainty (u) $u(m)$ of 0.1 mg. All pretreatment experiments were performed with a $u(T)$ of 2°C . All enzymatic hydrolysis experiments were performed with a $u(T)$ of 0.1°C . All other experimental errors related to measurements depended on the calibration technique used to quantify the concentrations of products. All reactions (pre-treatments and enzymatic hydrolyses) and analyses were performed in duplicate are results are given as mean values with corresponding standard deviation.

4. Conclusions

The present work takes a major step toward providing a comparative framework between two IL-type pre-treatments coupled with enzymatic saccharification in terms of their performance of converting wheat straw and eucalyptus residues to fermentable sugars. The first strategy relied on the processing of biomass with hydrogen-bond acidic IL. This approach allowed integration of biomass pre-treatment, hydrolysis and conversion of biomass in a single step process. The acidic character of $[\text{HSO}_4]$ anion of IL promoted a selective processing of hemicellulose fraction and the resulting products (mainly pentoses and furfural) were kept in a liquid phase. The solids produced were mainly constituted by cellulose and lignin. The 2nd approach with hydrogen-bond basic IL allowed biomass dissolution and fractionation into cellulose-, hemicellulose- and lignin-rich fractions. In this case, the recalcitrance of the lignocellulosic matrix was overcome by alteration of strong network of intra- and intermolecular bonds existing in biomass. Consequently a loss of native cellulose crystalline I structure was observed and cellulose II form was obtained, which was not observed for solids produced by $[\text{emim}][\text{HSO}_4]$. This, in turn allowed getting a significant improvement in the enzymatic hydrolysis yields.

Electronic Supplementary Information

Table S1. Composition of cellulose- and hemicellulose-rich fractions obtained from wheat straw pre-treated with $[\text{emim}][\text{OAc}]$ at 120 and 140 $^\circ\text{C}$ and 2 h

Table S2. Composition of cellulose-rich fractions obtained from eucalyptus pre-treated with [emim][OAc] at 120 and 140 °C and 2 h.

Acknowledgments

This research was funded AMBITION (Advanced biofuel production with energy system integration Work) project funded by the European H2020-programme under LCE-33 2016 European Common Research and Innovation Agendas (ECRIAs) in support of the implementation of the SET Action Plan., Grant Agreement 731263. This work was supported by the Fundação para a Ciência e a Tecnologia (FCT, Portugal) through BBRI - Biomass and Bioenergy Research Infrastructure (ROTEIRO/0189/2013) and grant IF/00471/2015 (RML). Authors also wish to thank Dr. Teresa Diamantino and Dr. Isabel Figueira (LRM, UER, LNEG) for XRD measurements. In addition, authors wish to thank also Dr. Susana Marques (UB, LNEG) for conceptualization of the enzymatic hydrolysis assays as well as Mrs. Maria do Céu Penedo (UB, LNEG) for assistance in the HPLC analyses.

Author contributions

Conceptualization and methodology J.R.B. and R.M.L.; Writing – Original Draft Preparation, J.R.B.; Writing – Review & Editing, R.M.L. Funding Acquisition, F.M.G and R.M.L.

Conflicts of Interest

The authors declare no conflict of interest.

References

1. Sun, S.; Sun, S.; Cao, X.; Sun, R. The role of pretreatment in improving the enzymatic hydrolysis of lignocellulosic materials. *Bioresour. Technol.* **2016**, *199*, 49-58.
2. Silveira, M.H.L.; Morais, A.R.C.; da Costa Lopes, A.M.; Oleksyszyn, D.N.; Bogel-Lukasik, R.; Andraus, J.; Ramos, L.P. Current Pretreatment Technologies for the Development of Cellulosic Ethanol and Biorefineries. *ChemSusChem* **2015**, *8*, 3366-3390.
3. Girio, F.M.; Fonseca, C.; Carvalheiro, F.; Duarte, L.C.; Marques, S.; Bogel-Lukasik, R. Hemicelluloses for fuel ethanol: A review. *Bioresour. Technol.* **2010**, *101*, 4775-4800.
4. Anugwom, I.; Eta, V.; Virtanen, P.; Maki-Arvela, P.; Hedenstrom, M.; Hummel, M.; Sixta, H.; Mikkola, J.P. Switchable ionic liquids as delignification solvents for lignocellulosic materials. *ChemSusChem* **2014**, *7*, 1170-1176.
5. da Costa Lopes, A.M.; Bogel-Lukasik, R. Acidic Ionic Liquids as Sustainable Approach of Cellulose and Lignocellulosic Biomass Conversion without Additional Catalysts. *ChemSusChem* **2015**, *8*, 947-965.
6. Brandt, A.; Grasvik, J.; Hallett, J.P.; Welton, T. Deconstruction of lignocellulosic biomass with ionic liquids. *Green Chem.* **2013**, *15*, 550-583.

7. Putro, J.N.; Soetaredjo, F.E.; Lin, S.-Y.; Ju, Y.-H.; Ismadji, S. Pretreatment and conversion of lignocellulose biomass into valuable chemicals. *RSC Adv.* **2016**, *6*, 46834-46852.
8. Janesko, B.G. Modeling interactions between lignocellulose and ionic liquids using DFT-D. *Phys. Chem. Chem. Phys.* **2011**, *13*, 11393-11401.
9. da Costa Lopes, A.M.; João, K.G.; Bogel-Lukasik, E.; Roseiro, L.B.; Bogel-Lukasik, R. Pretreatment and Fractionation of Wheat Straw Using Various Ionic Liquids. *J. Agric. Food Chem.* **2013**, *61*, 7874-7882.
10. Swatloski, R.P.; Spear, S.K.; Holbrey, J.D.; Rogers, R.D. Dissolution of cellulose [correction of cellose] with ionic liquids. *J. Am. Chem. Soc.* **2002**, *124*, 4974-4975.
11. Magalhães da Silva, S.P.; da Costa Lopes, A.M.; Roseiro, L.B.; Bogel-Lukasik, R. Novel pre-treatment and fractionation method for lignocellulosic biomass using ionic liquids. *RSC Adv.* **2013**, *3*, 16040-16050.
12. Brandt, A.; Hallett, J.P.; Leak, D.J.; Murphy, R.J.; Welton, T. The effect of the ionic liquid anion in the pretreatment of pine wood chips. *Green Chem.* **2010**, *12*, 672-679.
13. Zakrzewska, M.E.; Bogel-Lukasik, E.; Bogel-Lukasik, R. Solubility of Carbohydrates in Ionic Liquids. *Energ. Fuel.* **2010**, *24*, 737-745.
14. Gillet, S.; Aguedo, M.; Petitjean, L.; Morais, A.; da Costa Lopes, A.; Łukasik, R.; Anastas, P. Lignin transformations for high value applications: towards targeted modifications using green chemistry. *Green Chem.* **2017**, *19*, 4200-4233.
15. Anugwom, I.; Maki-Arvela, P.; Virtanen, P.; Willfor, S.; Sjöholm, R.; Mikkola, J.P. Selective extraction of hemicelluloses from spruce using switchable ionic liquids. *Carbohydr. Polym.* **2012**, *87*, 2005-2011.
16. Verdia, P.; Brandt, A.; Hallett, J.P.; Ray, M.J.; Welton, T. Fractionation of lignocellulosic biomass with the ionic liquid 1-butylimidazolium hydrogen sulfate. *Green Chem.* **2014**, *16*, 1617-1627.
17. da Costa Lopes, A.M.; Lins, R.M.G.; Rebelo, R.A.; Lukasik, R.M. Biorefinery approach for lignocellulosic biomass valorisation with acidic ionic liquid. *Green Chem.* **2018**, *20*, 4043-4057.
18. Brandt, A.; Ray, M.J.; To, T.Q.; Leak, D.J.; Murphy, R.J.; Welton, T. Ionic liquid pretreatment of lignocellulosic biomass with ionic liquid–water mixtures. *Green Chem.* **2011**, *13*, 2489-2499.
19. Carvalho, A.V.; da Costa Lopes, A.M.; Bogel-Lukasik, R. Relevance of the acidic 1-butyl-3-methylimidazolium hydrogen sulphate ionic liquid in the selective catalysis of biomass hemicellulose fraction. *RSC Adv.* **2015**, *5*, 47153-47164.
20. Li, C.Z.; Wang, Q.; Zhao, Z.K. Acid in ionic liquid: An efficient system for hydrolysis of lignocellulose. *Green Chem.* **2008**, *10*, 177-182.
21. Cox, B.J.; Ekerdt, J.G. Depolymerization of oak wood lignin under mild conditions using the acidic ionic liquid 1-H-3-methylimidazolium chloride as both solvent and catalyst. *Bioresour. Technol.* **2012**, *118*, 584-588.
22. Chen, L.; Sharifzadeh, M.; Mac Dowell, N.; Welton, T.; Shah, N.; Hallett, J.P. Inexpensive ionic liquids:[HSO₄]⁻-based solvent production at bulk scale. *Green Chem.* **2014**, *16*, 3098-3106.
23. Peleteiro, S.; Garrote, G.; Santos, V.; Parajó, J.C. Conversion of hexoses and pentoses into furans in an ionic liquid. *Afinidad* **2014**, *71*.
24. Peleteiro, S.; Rivas, S.; Alonso, J.L.; Santos, V.; Parajó, J.C. Furfural production using ionic liquids: A review. *Bioresour. Technol.* **2016**, *202*, 181-191.
25. Peleteiro, S.; da Costa Lopes, A.M.; Garrote, G.; Parajó, J.C.; Bogel-Lukasik, R. Simple and Efficient Furfural Production from Xylose in Media Containing 1-Butyl-3-Methylimidazolium Hydrogen Sulfate. *Ind. Eng. Chem. Res.* **2015**, *54*, 8368-8373.

26. Patil, S.K.; Lund, C.R. Formation and growth of humins via aldol addition and condensation during acid-catalyzed conversion of 5-hydroxymethylfurfural. *Energ. Fuel.* **2011**, *25*, 4745-4755.
27. Sluiter, A.; Hames, B.; Ruiz, R.; Scarlata, C.; Sluiter, J.; Templeton, D.; Crocker, D. *Determination of structural carbohydrates and lignin in biomass - Laboratory Analytical Procedure (LAP)*; NREL/TP-510-42618; National Renewable Energy Laboratory: Golden, Colorado, USA, 2011.
28. Xu, J.-K.; Chen, J.-H.; Sun, R.-C. Hydrothermal microwave valorization of eucalyptus using acidic ionic liquid as catalyst toward a green biorefinery scenario. *Bioresour. Technol.* **2015**, *193*, 119-127.
29. Rahikainen, J.L.; Evans, J.D.; Mikander, S.; Kalliola, A.; Puranen, T.; Tamminen, T.; Marjamaa, K.; Kruus, K. Cellulase–lignin interactions—The role of carbohydrate-binding module and pH in non-productive binding. *Enzyme Microb. Technol.* **2013**, *53*, 315-321.
30. Selig, M.; Weiss, N.; Ji, Y. *Enzymatic Saccharification of Lignocellulosic Biomass: Laboratory Analytical Procedure (LAP): Issue Date, 3/21/2008*; National Renewable Energy Laboratory - NREL: Colorado 80401-3393, 2008.
31. Labbe, N.; Kline, L.M.; Moens, L.; Kim, K.; Kim, P.C.; Hayes, D.G. Activation of lignocellulosic biomass by ionic liquid for biorefinery fractionation. *Bioresour. Technol.* **2012**, *104*, 701-707.
32. da Costa Lopes, A.M.; Joao, K.G.; Rubik, D.F.; Bogel-Lukasik, E.; Duarte, L.C.; Andreaus, J.; Bogel-Lukasik, R. Pre-treatment of lignocellulosic biomass using ionic liquids: wheat straw fractionation. *Bioresour. Technol.* **2013**, *142*, 198-208.
33. Sun, N.; Rahman, M.; Qin, Y.; Maxim, M.L.; Rodriguez, H.; Rogers, R.D. Complete dissolution and partial delignification of wood in the ionic liquid 1-ethyl-3-methylimidazolium acetate. *Green Chem.* **2009**, *11*, 646-655.
34. Bian, J.; Peng, F.; Peng, X.P.; Xiao, X.; Peng, P.; Xu, F.; Sun, R.C. Effect of [Emim]Ac pretreatment on the structure and enzymatic hydrolysis of sugarcane bagasse cellulose. *Carbohydr. Polym.* **2014**, *100*, 211-217.
35. Torr, K.M.; Love, K.T.; Simmons, B.A.; Hill, S.J. Structural features affecting the enzymatic digestibility of pine wood pretreated with ionic liquids. *Biotechnol. Bioeng.* **2016**, *113*, 540-549.
36. Atalla, R.H.; VanderHart, D.L. Native cellulose: a composite of two distinct crystalline forms. *Science* **1984**, *223*, 283-286.
37. Karimi, K.; Taherzadeh, M.J. A critical review of analytical methods in pretreatment of lignocelluloses: composition, imaging, and crystallinity. *Bioresour. Technol.* **2016**, *200*, 1008-1018.
38. Morais, A.R.C.; Vaz Pinto, J.; Nunes, D.; Roseiro, L.B.; Oliveira, M.C.; Fortunato, E.; Bogel-Lukasik, R. Imidazole: Prospect Solvent for Lignocellulosic Biomass Fractionation and Delignification. *ACS Sustain. Chem. Eng.* **2016**, *4*, 1643-1652.
39. Cheng, G.; Varanasi, P.; Arora, R.; Stavila, V.; Simmons, B.A.; Kent, M.S.; Singh, S. Impact of Ionic Liquid Pretreatment Conditions on Cellulose Crystalline Structure Using 1-Ethyl-3-methylimidazolium Acetate. *J. Phys. Chem. B* **2012**, *116*, 10049-10054.
40. Wada, M.; Ike, M.; Tokuyasu, K. Enzymatic hydrolysis of cellulose I is greatly accelerated via its conversion to the cellulose II hydrate form. *Polym. Degrad. Stab.* **2010**, *95*, 543-548.
41. Li, C.; Knierim, B.; Manisseri, C.; Arora, R.; Scheller, H.V.; Auer, M.; Vogel, K.P.; Simmons, B.A.; Singh, S. Comparison of dilute acid and ionic liquid pretreatment of

- switchgrass: Biomass recalcitrance, delignification and enzymatic saccharification. *Bioresour. Technol.* **2010**, *101*, 4900-4906.
42. Sluiter, A.; Ruiz, R.; Scarlata, C.; Sluiter, J.; Templeton, D. *Determination of extractives in biomass*; NREL/TP-510-42619; National Renewable Energy Laboratory: Golden, Colorado, USA, 2008.
 43. Sluiter, A.; Hames, B.; Ruiz, R.; Scarlata, C.; Sluiter, J.; Templeton, D. *Determination of ash in biomass*; NREL/TP-510-42622; National Renewable Energy Laboratory: Golden, Colorado, USA, 2008.
 44. *Milk and milk products - Determination of nitrogen content - Part 1: Kjeldahl principle and crude protein calculation*; ISO 8968-1:2014; International Organization for Standardization: 2014.