

Article

Miscanthus X Giganteus Stem Versus Leaf-Derived Lignins Differing in Monolignol Ratio and Linkage

Michel Bergs ^{1,2}, Georg Völkerling ², Thorsten Kraska ³, Ralf Pude ^{2,3}, Xuan Tung Do ¹, Peter Kusch ¹, Yulia Monakhova ^{4,5}, Christopher Konow ⁶, Margit Schulze ^{1,*}

¹ Department of Natural Sciences, Bonn-Rhein-Sieg University of Applied Sciences, von-Liebig-Strasse 20, D-53359 Rheinbach, Germany; michel.bergs@h-brs.de (M.B.); xuan-tung.do@h-brs.de (X.T.D.); peter.kusch@h-brs.de (P.K.); ckonow@brandeis.edu (C.K.)

² Institute of Crop Science and Resource Conservation, Faculty of Agriculture, University of Bonn, Klein-Altendorf 2, D-53359 Rheinbach, Germany; g.voelkerling@uni-bonn.de (G.V.); kraska@uni-bonn.de (T.K.); r.pude@uni-bonn.de (R.P.)

³ Field Lab Campus Klein-Altendorf, Faculty of Agriculture, University of Bonn, Campus Klein-Altendorf 1, D-53359 Rheinbach, Germany

⁴ Spectral Service AG, Emil-Hoffmann-Strasse 33, D-50996 Köln, Germany; monakhova@spectral-service.de (Y.M.)

⁵ Institute of Chemistry, Saratov State University, Astrakhanskaya Street 83, 410012 Saratov, Russia

⁶ Department of Chemistry, MS 015, Brandeis University, 415 South Street, Waltham, Massachusetts, U.S.

* Correspondence: margit.schulze@h-brs.de (M.S.); Tel.: +49-2241-865566

Abstract: As a renewable c, *Miscanthus* offers numerous advantages, namely high photosynthesis activity (as a C4 plant) and exceptional CO₂ fixation rate. These properties make *Miscanthus* very attractive for industrial exploitation, such as lignin generation. Here, we present a systematic study analyzing the correlation of the lignin structure with *Miscanthus* genotype and plant portion (stem versus leaf). Specifically, the ratio of the three monolignols and corresponding building blocks as well as the linkages formed between the units have been studied. The lignin amount has been determined for *M. x giganteus* (Gig17, Gig34, Gig35), *M. nagara* (NagG10), *M. sinensis* (Sin2) and *M. robustus* (Rob4) harvested at different time (September, December, April). The influence of the *Miscanthus* genotype and plant component (leaf versus stem) has been studied to develop corresponding structure-property relationships (i.e., correlations in molecular weight, polydispersity and decomposition temperature). Lignin isolation was performed using non-catalyzed organosolv pulping and the structure analysis includes compositional analysis, FTIR, UV-Vis, HSQC-NMR, TGA, pyrolysis GC/MS. Structural differences were found for stem and leaf-derived lignins. Compared to beech wood lignins, *Miscanthus* lignins possess lower molecular weight and narrow polydispersities (< 1.5 *Miscanthus* vs. > 2.5 beech) corresponding to improved homogeneity. In addition to conventional univariate analysis of FTIR spectra, multivariate chemometrics revealed distinct differences for aromatic in-plane deformations of stem versus leaf-derived lignins. These results emphasize the potential of *Miscanthus* as low-input resource and *Miscanthus*-derived lignin as promising agricultural feedstock.

Keywords: biomass; chemometrics; genotype; HSQC NMR; lignin; *Miscanthus X giganteus*; monolignol ratio; principal component analysis

1. Introduction

Miscanthus, a perennial rhizome-forming sweet grass (*Poaceae*), is originally cultivated in subtropical regions in Asia. Currently, there are approximately 17 species investigated in Europe for energy and material development including *Miscanthus tinctorius*, *M. sinensis*, *M. sacchariflorus* and the triploid genotype *M. x giganteus*, an allotriploid hybrid of the diploid *M. sinensis* and the tetraploid *M. sacchariflorus*. *Miscanthus* field trials have been performed in Europe over the past 25 years

confirming that *M. x giganteus* hybrids show high yields over a wide range of environmental conditions [1-3]. As a C₄ plant, Miscanthus is effective in carbon sequestration due to the formation of oxaloacetate, as opposed to D-3-phosphoglycerate for C₃ plants [4-6]. Thus, Miscanthus is one of the very few crops that is studied to serve as a CO₂ sink [7-13]. In addition, this sterile genotype does not generate fertile seeds, which avoids uncontrolled spreading [14]. After planting, the production of the perennial crop lasts for about 20 years. In the production phase the plant needs much less fertilizer than other crops, even at arid conditions, due to an effective nitrogen metabolism. Plant protection is in general not required except for weed control in the first year of establishment [2,15,16]. *M. x giganteus* reaches a height of about four meters and an annual production up to 25 t/ha, thereby saving production costs which decreases environmental impact due to reduced tillage and less soil compaction and erosion [17]. Within the last five years, the upscaling of Miscanthus biomass production in Europe could significantly be improved particularly using seed-based hybrids. Consequently, *Miscanthus* hybrids are expected to play an increasing role in the provision of perennial lingo-cellulosic feedstock in Europe, thereby contributing to a lower carbon economy [1,18,19].

The use of Miscanthus as source for raw materials would significantly improve the environmental performance of lignocellulose-based biorefineries [20-22]. Miscanthus is already used for direct combustion in sustainable and CO₂ neutral manner. In addition to the exploitation of Miscanthus as an energy plant, there is urgent need to exploit the potential of Miscanthus for chemical production. Recent work by Kraska et al. has shown Miscanthus' potential for chemical production through a cascade utilization [23,24]. Other studies focus the production of bioethanol [25], hydrogen [26] and the utilization of the plant fibers for fiber-based composites [27-31].

So far, only a few systematic studies have been published focusing on the structure-property relationships for Miscanthus-derived lignins. El Hage et al. reported the pre-treatment of biomass for ethanol-based organosolv pulping, in which they specify correlations of structural changes with process conditions [32-34]. Catalyzed organosolv pulping was studied to depolymerize lignins using vanadium and nickel-based catalysts, showing correlations between lignin structure and reactivity toward the catalysts [35-37]. Timilsena et al. studied Miscanthus plants and compared different pre-treatment methods (i.e., autohydrolysis, 2-naphthol treatment) [38]. Other authors studied different Miscanthus genotypes regarding their composition (cellulose, hemicellulose, lignin) but did not analyze the lignin structure [39]. Van der Weijde investigated eight *M. sinensis* samples regarding their cell wall constitution [40]. Enzymatic depolymerization of Miscanthus-derived lignin was studied by various groups [41-43].

The most detailed study was reported by Da Costa et al., which investigated the cell tissue type of 25 Miscanthus genotypes (i.e., *M. x giganteus*, *M. sinensis*, and *M. sacchariflorus*) [44]. Cell-wall compositional differences between Miscanthus stem and leaf samples were mainly associated to differences of structural carbohydrates. The authors could proof direct correlations between the lignin content isolated from specific plant portions and the genotype. However, no structural details regarding monolignol ratio and/or corresponding linkages were reported [44].

Iqbal et al. reported a multi-genotype trial performed in south Germany focusing correlations of biomass yield and composition with climatic conditions and harvesting time using multivariate data analysis methods [45]. For example, in *M. sacchariflorus* the harvest date–aging interaction influenced the Mg concentration and ash content. The harvest date–rainfall interaction significantly decreased calcium, silicon and nitrogen concentrations. In addition, these deviations in mineral concentration depend on the Miscanthus genotypes (as studied for *M. x giganteus* and *M. sinensis*). Again, also this study did not include lignin 3D structure analysis [45].

In contrast to the lack of a systematic structural study for Miscanthus-derived lignins, numerous studies are reported regarding the structure of wood-derived kraft lignin obtained from industrial black liquor. Here, heteronuclear single quantum correlation (HSQC) 2D-NMR is one of the most widely used tool for structural characterization of lignins of any origin, comprehensively reviewed by Ralph, Lupoi, and Tarasov et al. [46-48]. Most interestingly, HSQC provides information on the units (G, H, S) and corresponding interunit linkages. Depending on the biomass source (soft and hard wood, grasses) and the pulping process (kraft, steam explosion, organosolv etc.), the monolignol ratio

and their linkages differ significantly [49-60]. Figure 1 shows the most common linkages of lignin formed during biosynthesis, some of them confirmed within the last five years [55,61,62].

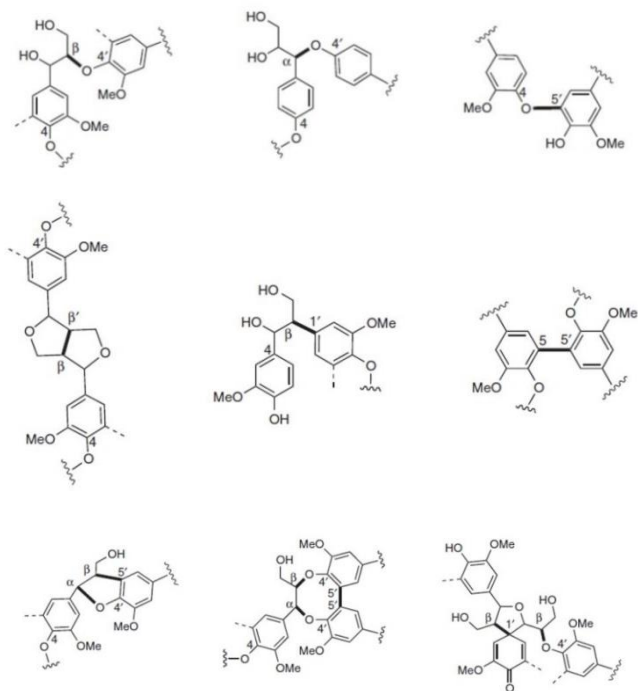


Figure 1. Monolignol linkages. First line: Ether bonds (β -O-4', α -O-4', 4-O-5'); second line: C-C-bonds. (β - β' , β -1', 5-5'), and third line: more complex linkages (β -5'/ α -O-4', 5-5'/ β -O-4'/ α -O-4', β -1'/ β -O-4').

Very recently Lan et al. reported the synthesis of several 4'-O- β -coupling products of triclin with coniferyl and sinapyl alcohol and revealed characteristic new correlations in the HSQC spectrum [63]. Table 1 gives an overview about differences regarding the linkages found for hard and soft wood, and *Miscanthus* grasses [61-63].

Table 1. Abundance of linkages in lignins of soft and hard wood (Wang et al., 2017) and *Miscanthus* grasses (Li et al., 2014) including KOH-extractable and non-KOH-extractable in %.

Linkage	Hard wood	Soft wood	<i>Miscanthus</i>
	H/G/S traces/25-50/50-75	H/G/S 0.5-3.4/90-95/0-1	H/G/S 24/49/27
β ○○○○○	50 - 65	43 - 50	93
α ○○○○○	4 - 8	6 - 8	ns*
β - β'	3 - 7	2 - 4	4
β ○○○	4 - 6	9 - 12	3
β ○○○	5 - 7	3 - 7	traces
4-O-5'	6 - 7	4	ns*
5-5'	4 - 10	10 - 25	ns*

*ns: not specified

In addition, the combination of NMR and chemometrics has been successfully applied in origin analysis of biopolymers including polysaccharides and lignin. For example, Monakhova et al. were recently able to specify porcine and ovine-derived heparins using 2D DOSY NMR and SEC data [64]. In general, chemometric methods can also be used for multivariate FTIR data analysis. Boeriu et al. combined FTIR and principal component analysis (PCA) to be used as a fast and reliable non-destructive technique to classify the botanical origin of lignins. In addition, chemometric models (partial least squares, PLS regression) allowed an accurate determination of phenolic hydroxyl

groups and corresponding antioxidant capacity [65]. Chen et al. used multivariate data analysis to characterize wood samples qualitatively and quantitatively by FTIR spectroscopy. To determine the contents of lignin, cellulose, and hemicellulose, respectively, the authors included a broad variety of input parameters such as wood species obtaining results with the root-mean-square errors of 1.51, 0.96, and 0.62% [66]. Very recently, Christou et al. reported a study examining the combination of FTIR spectroscopy and chemometrics to differentiate carob samples from seven different Mediterranean countries using the first derivatives of the FTIR spectra resulting in confidence level up to 95% [67].

For the first time, this study presents comprehensive analytical data (including NREL, FTIR, UV-Vis, HSQC-NMR, SEC, TGA, Py-GC/MS) for *Miscanthus x giganteus*-derived lignins correlating with plant portions (stem versus leaf). The biomass was separated into stem and leaf portions to be treated separately using the organosolv process for lignin isolation. In addition to conventional analysis of the chemical structure of the obtained lignins, multivariate data analysis of FTIR data is used to specify structural details that allow the discrimination of stem versus leaf-derived lignins.

2. Results and Discussion

2.1. *Miscanthus* Crop Analysis

The seasonal influence on plant constitution was examined. Stem and leaf- samples for lignin analysis were harvested in December 2014 as well as in April and September 2015 to compare across different years and harvest times. Plant constitution analysis showed significant differences regarding the lignin amount with respect to year and harvest date (Fig. 2): in early autumn (September), the leaf content did not reach the maximum (except for *M. sinensis*) compared to the December harvest. Until spring, the plants lose their leaves resulting in an extremely low leaf versus stem ratio. Highest values were found for *M. robustus* (Rob4).

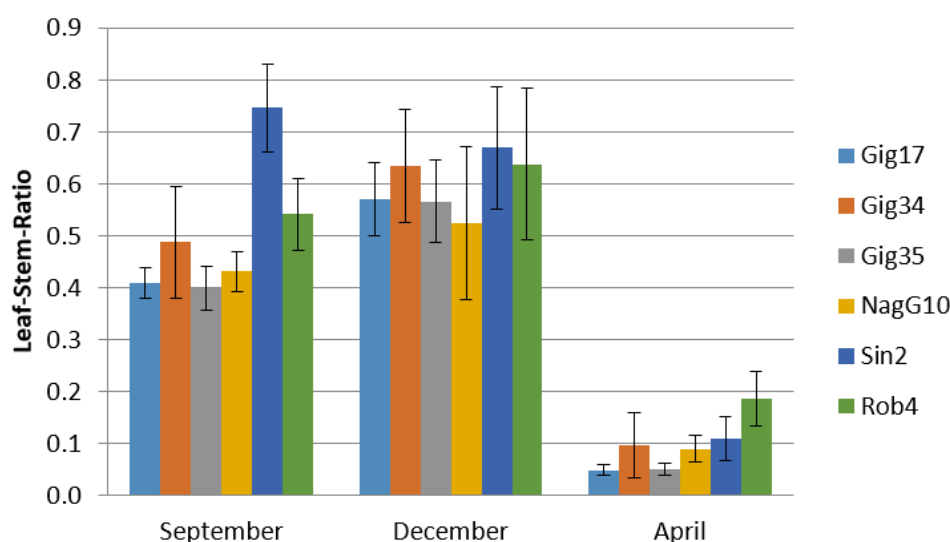


Figure 2. *Miscanthus* crop analysis via NREL measurements. Leaf versus stem content of *Miscanthus* genotypes: *M. x giganteus* (Gig17, Gig34, Gig35), *M. nagara* (NagG10), *M. sinensis* (Sin2) and *M. robustus* (Rob4) harvested in September (09/15), December (12/14) and April (04/15), respectively (arranged to follow the seasonal order from autumn to spring).

In the following, the leaf- and stem-derived lignins will be discussed in detail for two *M. x giganteus* cultivars (Gig17, Gig34). Special focus is given to similarities and differences in lignin content and monolignol constitution depending on plant portion (stem versus leaf).

2.2. NREL Analysis

Four samples were analyzed regarding their element constitution following the NREL protocol. Both *M. x giganteus* samples were harvested in April 2015, then separated into stem and leaf portions to be analyzed separately (Table 2).

Table 2. Compositional analysis data (according to NREL protocol) of *Miscanthus X giganteus* (Gig17, Gig34) and biomasses of leaf versus grasses, harvested in April 2015. AIL: acid-insoluble lignin; ASL: acid-soluble lignin; AIR: acid-insoluble residuals; AISA: acid-insoluble ash.

Genotype Harvest Time Portion	Gig17 April Leaf	Gig34 April Leaf	Gig17 April Stem	Gig34 April Stem
AIL [%]	20.65 ± 0.47	21.06 ± 0.31	21.18 ± 0.01	20.97 ± 0.43
ASL [%]	5.06 ± 0.30	4.13 ± 0.05	4.71 ± 0.26	4.31 ± 0.02
AIR [%]	21.83 ± 0.51	22.14 ± 0.42	22.46 ± 0.22	22.31 ± 0.60
Total lignin [%]	25.52 ± 0.54	25.32 ± 0.48	26.00 ± 0.36	25.25 ± 0.39
AISA [%]	1.18 ± 0.10	1.08 ± 0.22	1.29 ± 0.11	1.01 ± 0.05
Glucan [%]	44.79 ± 1.50	44.98 ± 2.30	50.02 ± 0.63	50.49 ± 0.87
Xylan [%]	28.37 ± 1.77	29.52 ± 0.63	27.41 ± 2.81	26.23 ± 0.49
Galactan [%]	0.00 ± 0.00	0.00 ± 0.00	0.00 ± 0.00	0.00 ± 0.00
Arabinan [%]	3.11 ± 0.05	4.11 ± 1.63	1.89 ± 0.51	2.04 ± 0.34
Mannan [%]	0.00 ± 0.00	0.00 ± 0.00	0.00 ± 0.00	0.00 ± 0.00
Dry matter [%]	92.55	91.25	92.18	92.16
Total ash [%]	4.53	6.82	2.50	3.07

The total ash content between stem- and leaf-derived lignins differs: average values for stem lignins 2.58 % versus 5.71 % for leaf lignins due to a higher mineral content in leaves. Wahid et. al. reported total ash contents for stems of 2.6-4.0 % (*M. x giganteus*) and 1.5-3.4 % (*M. sinensis*). Leaves varied between 3.9-7.2 % (*M. x giganteus*) and 3.3-5.0 % (*M. sinensis*) [68]. Acid-insoluble residuals (AIR) showed very low ash contents (average 0.94 %, calculated for all six genotype samples listed in Figure 2, [69]) due to low mineral impurities in this fraction. Due to a higher cellulose content in stems compared to leaves, higher glucose values were obtained for both *M. x giganteus* samples. In literature, carbohydrate contents vary in the range of 40 to 50 wt.% for *Miscanthus x giganteus* genotypes, mainly consisting of glucan and xylan [70]. Other sugars, i.e., arabinan, mannan and galactan are usually below 2 %, very recently reported by Scaglione-Mellor for different *Miscanthus* genotypes [71]. No significant differences were found for the total lignin content for leaf and stem-derived biomasses. In literature, *Miscanthus*-derived lignin contents vary in the range of 19-25 %, mainly depending on the plant genotype [72,73].

2.3. FTIR Spectroscopy

The results of the FTIR analysis confirmed reported literature data for lignins obtained from *M. x giganteus* plants [74,75]. As an example of the results, Table 3 summarizes the FTIR signals of sample Gig17, a *M. x giganteus* stem/leaf mixture. Signal numbers are given in Figure 3.

Table 3. FTIR signals and corresponding assignment for a lignin isolated from *M. x giganteus* (Gig17, stem/leaf mixture).

Number	Wave number [cm ⁻¹]	Functional Group	Assignment
1	3428±60	O-H	Stretching
2	2926±11	C-H	Stretching
3	2850±6	C-H	Stretching
4	1708±11	C=O	Stretching

5	1655±4	C=O	Stretching
6	1605±12	Aromatic ring	Symmetric Stretching
7	1514±6	Aromatic ring	Antisymmetric Stretching
8	1460±4	C-H	Antisymmetric Deformation
9	1424±4	C-H in O-CH ₃	Antisymmetric Deformation (S mode)
10	1398±4	C-H	Bending C-H in-plane
11	1371±15	Aromatic skeleton	Deformation
12	1331±9	Aromatic skeleton; C-O	Skeleton Stretching (S mode)
13	1267±2	Aromatic skeleton; C-O	Skeleton Stretching (G mode)
14	1225±12	C-C; C-O; C=O	Stretching (G mode)
15	1166±10	C-H (in G)	Stretching
16	1124±2	Aromatic C-H	In-plane Deformation
17	1033±2	Aromatic C-H	In-plane Deformation
18	834±4	Aromatic C-H	Out-of-plane Deformation (S mode)

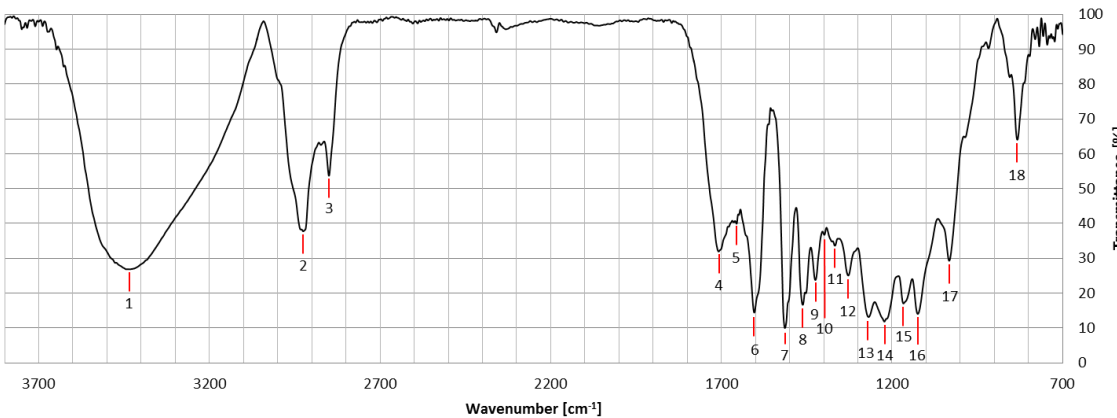


Figure 3. FT-IR spectra of Gig17 (stem, leaf and mixture) with numbered signals listed in Table 4.

Comparing the FTIR data of stem/leaf mixtures (Gig17M) versus separated biomass (Gig17L, Gig17S), similarities were found for mixture and stem-derived lignin (Figure 4 and Figure 5).

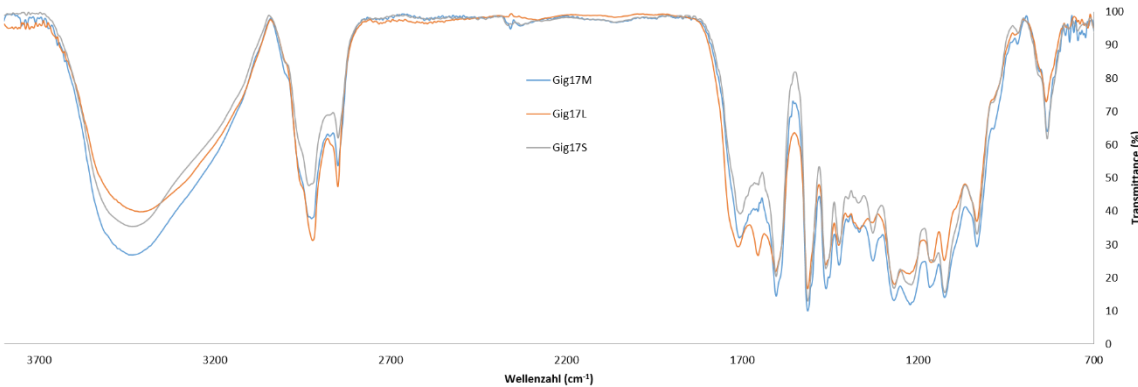


Figure 4. FT-IR spectra of mixture (Gig17M), leaf (Gig17L) and stem-derived (Gig17S) lignins obtained from *M. x giganteus* (Gig17).

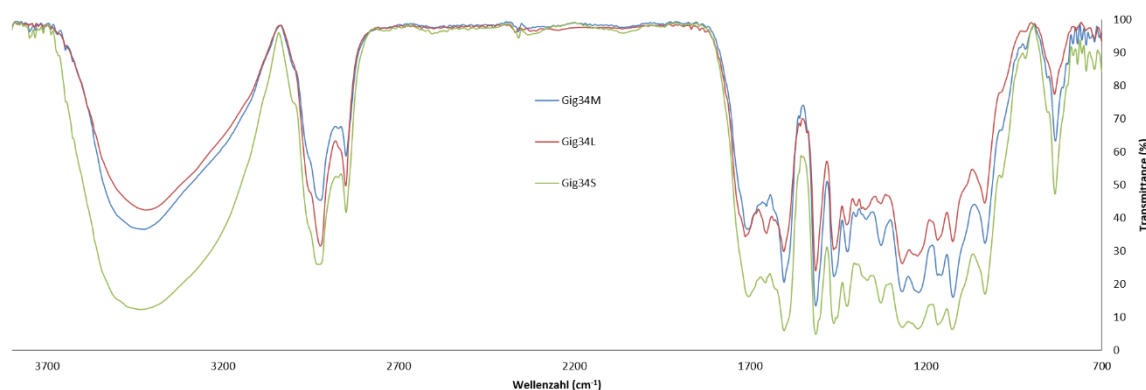


Figure 5. FT-IR spectra of mixture (Gig34M), leaf (Gig34L) and stem-derived (Gig34S) lignins obtained from *M. x giganteus* (Gig34).

This is in good accordance with the low amount of leaves in the plant (< 5 wt.-%). In detail, both leaf samples showed a signal at about 1655 cm⁻¹ (number 5) which is very weak for stem (Gig17S, Gig34S) and the mixtures (Gig17M, Gig34M). Further differences are obtained for signal No. 12 (ca. 1331 cm⁻¹), No. 14 (ca. 1225 cm⁻¹) and 16 (ca. 1124 cm⁻¹); all three are very weak for leaf-derived lignin versus stem and mixture, respectively. The two *M. x giganteus* cultivars (17 and 34) showed no significant differences.

PCA characterization of lignin samples was carried out to evaluate the potential of multivariate data analysis to specify lignin obtained from *Miscanthus x giganteus* plants derived from stem, leaves and their mixtures. The projections of IR spectra of lignin samples on the first three principal components (PCs), which express 82% of variance, are shown in Figure 6.

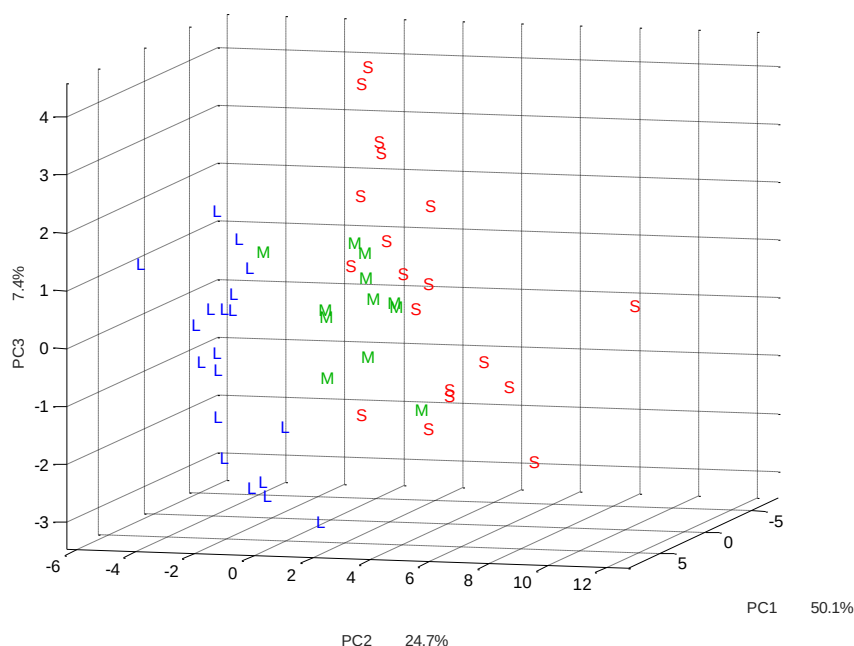


Figure 6. Multivariate data analysis of FT-IR data using the principal component analysis (PCA). L: leaf-derived lignin, M: mixture-derived lignin, S: stem-derived lignin.

The first two PCs are enough to differentiate steam- and leaf-derived materials, whereas PC3 is necessary to highlight the third group of samples (mixtures). The mixture class (M) is completely separated from the leaf class (L), but still shows overlap with the stem class (S). Again, this is most likely due to the low ratio of leaf versus stem lignin in the mixture. Advanced chemometric methods such as discriminant analysis are required to separate all three groups in multivariate space. Loadings plots confirmed our univariate findings described above.

2.4. Size Exclusion Chromatography

Analogous to the FTIR results, SEC studies revealed distinct differences between stem- and leaf-derived lignins and also similarities for stem/leaf mixtures and stem lignins. In detail, the SEC curve profile differs for leaf-derived lignin, showing weak shoulders at molar mass below 1000 Da instead of small but sharp peaks for stem- and mixture-derived lignin (Fig. 7).

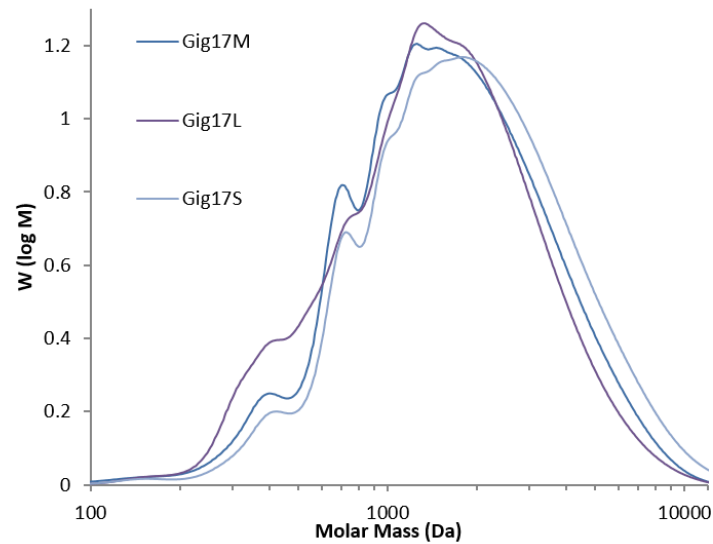


Figure 7. SEC curves of lignins obtained from *Miscanthus x giganteus* (mixture: Gig17M; leaf: Gig17L; stem Gig17S).

All obtained data (number and weight average molar masses (Mn, Mw) and polydispersities (PD) are summarized in Table 4.

Table 4. SEC results including number average (Mn) and weight average (Mw) molecular weight and polydispersity (PD) of lignin obtained from *Miscanthus x giganteus* mixtures (Gig17M, Gig34M), leaves (Gig17L, Gig34L) and stems (Gig17S, Gig34S).

		Gig17M	Gig34M	Gig17L	Gig34L	Gig17S	Gig34S
Mn (g mol ⁻¹)	RI	1138.80	1139.10	967.13	960.96	1314.40	1206.30
	UV	1077.70	1084.40	904.49	931.43	1168.90	1120.00
Mw (g mol ⁻¹)	RI	2041.40	2146.40	1758.70	1800.10	2385.00	2098.70
	UV	1983.40	2050.90	1691.60	1745.00	2216.30	2033.90
PD	RI	1.79	1.88	1.82	1.87	1.81	1.74
	UV	1.84	1.89	1.87	1.87	1.90	1.82

There are weak deviations for Mn and Mw in stem versus leaf lignin. However, these differences did not influence the final polydispersity which is very narrow for all samples. Literature data for organosolv-derived *Miscanthus* lignin vary between 2.0-2.5 kDa (Mw), 1.1-1.6 kDa (Mn) and 1.5-2.0 (PD) [76]. This is a much lower PD than beech wood-derived organosolv lignins, which showed polydispersities of 2.7-2.9 [47,77,78]. Brandt et al. reported SEC data for *M. x giganteus*-derived lignin isolated via ionic solvents showed significantly higher polydispersities of 3.7-7.6 depending on pre-treatment times [79]. In difference, the *M. x giganteus* samples isolated via organosolv treatment showed the narrowest polydispersity and resulting macromolecular homogeneity reported so far for grass-derived lignins.

Structural differences for stem- versus leaf-derived lignins, namely lower molecular weight of the leaf-lignins could also be confirmed by spectroscopic methods (FTIR, UV-Vis, see sections 2.3 and 2.5).

2.5. UV-Vis Spectroscopy

As shown in Figure 8, *M. x giganteus* lignin obtained via organosolv pulping samples showed two distinct signals, which is in accordance to literature data [35].

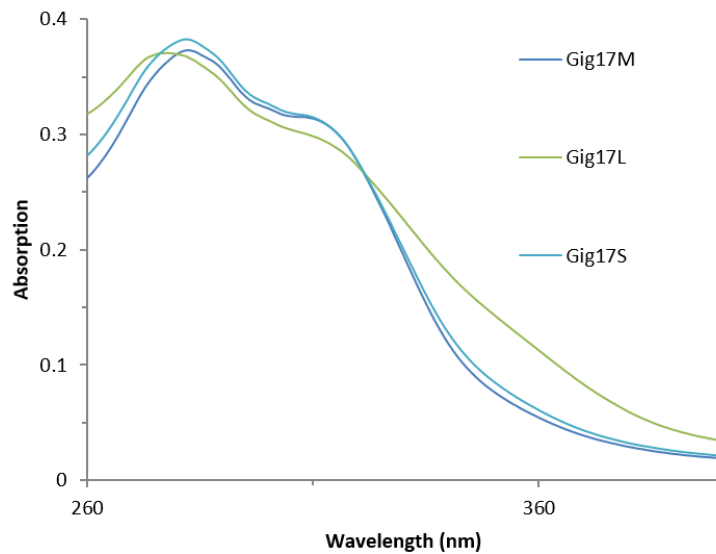


Figure 8. UV/Vis curves for lignins obtained from *Miscanthus x giganteus*. (mixture: Gig17M; leaf: Gig17L; stem Gig17S).

Again (due to the much higher amount of stems in the mixture), mixtures (Gig17M) and stem-derived lignin (Gig17S) are comparable in their UV absorption profile, whereas leaf-derived lignin (Gig17L) differ also in their UV-Vis absorption behavior. In particular, leaf-lignin consists of higher amounts of conjugated fragments resulting in a weak but visible shoulder around 320-350 nm. This is in accordance with the absorption profile of lignin from other biomasses [22,32,47,80]. In difference to this, four distinct absorption maxima were found for kraft lignins obtained from technical black liquor (spruce/pine mixtures) and purified via sequential extraction from organic solvents. Obviously, stepwise purification influenced the intensity of UV/Vis absorption signals (in addition to effects caused by biomass and pulping process) [80].

2.6. Thermogravimetric Analysis

The thermal behavior of the lignins was determined by thermogravimetric analysis (TGA). In Table 5, the TGA data obtained in this study are summarized including time-depending mass loss (in %/min), residual masses and decomposition temperatures for mixtures (Gig17M) and leaf/stem-separated samples (Gig17L, Gig17S).

Table 5. TGA results including first and second mass loss (ML), residual mass (RM) and decomposition temperature (Td) for two *M. x giganteus* lignins. Mixtures (Gig17M, Gig34M), stem-derived lignins (Gig17S, Gig34S) and leaf-derived lignins (Gig17L, Gig34L).

Sample	First ML (120°C)	Second ML (350°C)	RM	Td
Gig17M	0.86%	75.88%	23.26%	358.2°C
Gig17L	0.91%	64.98%	34.11%	354.8°C
Gig17S	0.42%	65.48%	34.10%	381.6°C
Gig34M	0.54%	73.79%	25.67%	360.0°C
Gig34L	0.72%	71.41%	27.87%	336.1°C
Gig34S	4.60%	84.08%	11.32%	379.2°C

The first mass loss at about 120°C (after 5 min) can be assigned to water elimination. Subsequently, lignin was systematically depolymerized between 170-350°C (starting after ca. 8 min). Corresponding decomposition temperatures vary between 335-380°C with lowest values for leaf-derived lignins. However, the data obtained for Td and residual mass differed less than 10 % and thus, no clear correlation could be drawn between the thermal behavior and plant portion and/or Miscanthus genotype. Most likely, differences in sample pre-treatment and preparation are of more significant influence, confirming results reported in literature [81,82].

In general, lignins are thermally degraded in a broad temperature range (100-700°C) due to their rather complex 3D structure consisting of phenolic hydroxyl, carbonyl, and benzylic hydroxyl functionalities resulting in several weight-loss steps during TGA measurements. The first loss (between 100-200°C) can be attributable to moisture and other volatile substances such as carbon monoxide and dioxide, confirming literature data [83]. According to Wittkowski et al., the degradation of propanoid side chains occurs between 230-260°C resulting in the splitting of methyl, ethyl, and vinyl guaiacol derivatives, whereas aryl ether bonds are usually splitted below 310°C [84]. In most lignins, about two third of the monolignol units are connected by β -O-4' linkages resulting in decomposition temperatures varying between 350 and 425°C for lignin for all analyzed sources of biomass (soft and hard wood, grasses, LCF-rich waste) [47]. Glasser and El-Saied reported a correlation of decomposition temperature and monolignol ratio: lignins with higher contents of G units and corresponding high amount of very stable intermolecular C-C bonds show higher decomposition temperatures [85,86].

2.7. Pyrolysis Gas Chromatography/Mass Spectrometry

Pyrolysis GC/MS analysis has indicated significant variations in monolignol ratios between stem, leaf, and mixed samples. Here, the assignment of the Py-GC/MS data was performed in accordance with data reported by Hodgson et al. [87,88]. Figure 9 shows a typical pyrogram (obtained for Gig17M). All aromatic pyrolysis products are numbered and summarized in Table 6.

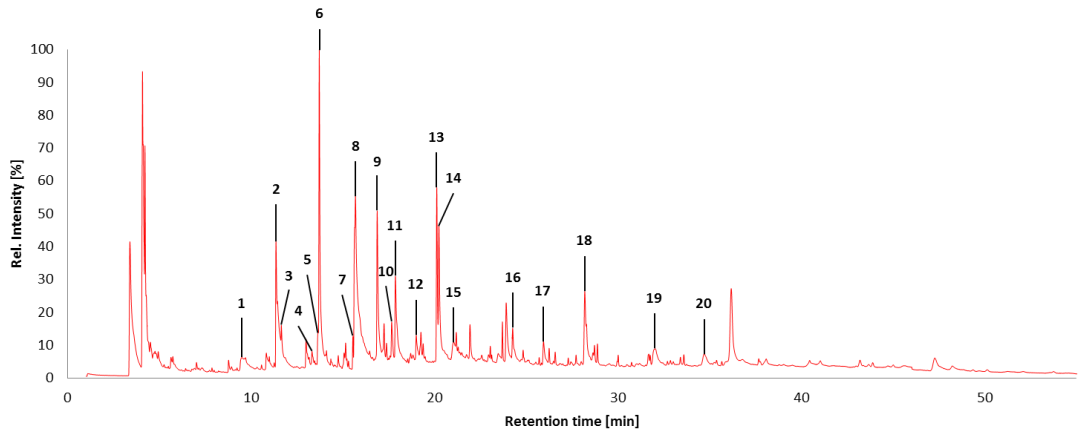


Figure 9. Pyrolysis-GC/MS pyrogram of a lignin obtained from *Miscanthus x giganteus* Gig17M. (stem/leaf mixture) with numbers for all aromatic fragments listed and assigned in Table 6.

Table 6. Pyrolysis-GC/MS fragments of the sample Gig17M and assignment to H, G and S units.

Peak No.	Retention time (min)	Amount (%)	Name	Assignment
1	9.49	3.77	Phenol	H
2	11.36	10.07	Guaiacol	G
3	11.65	1.83	<i>p</i> -Cresol	H
4	13.32	0.70	Creosol	G
5	13.67	1.27	4-Ethylphenol	H

6	13.72	12.92	Creosol	G
7	15.55	0.91	4-Ethylguaiaicol	G
8	15.69	22.08	Coumaran	H
9	16.874	8.17	4-Hydroxy-2-methylacetophenone	H
10	17.66	1.67	Eugenol	G
11	17.87	5.68	Syringol	S
12	19.00	1.55	Eugenol	G
13	20.13	6.80	4-Methylsyringol	S
14	20.24	6.23	(<i>E</i>)-Isoeugenol	G
15	21.05	1.91	Vanillin	G
16	24.26	1.68	4-Allylsyringol	S
17	25.95	1.56	(<i>E</i>)-4-Propenylsyringol	S
18	28.20	6.91	(<i>E</i>)-4-Propenylsyringol	S
19	32.03	2.50	Syringaldehyde	S
20	34.70	1.78	Acetosyringone	S

A few signals could not be attributed to a certain monolignol unit. Based on these data, monolignol ratios were estimated (Figures 10-12).

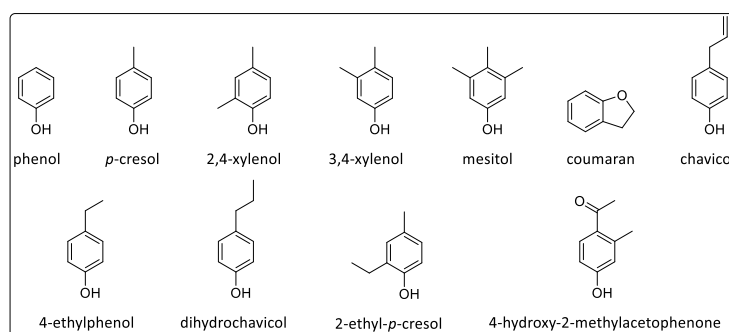


Figure 10. Detected Py-GC/MS fragments attributed to the H-unit.

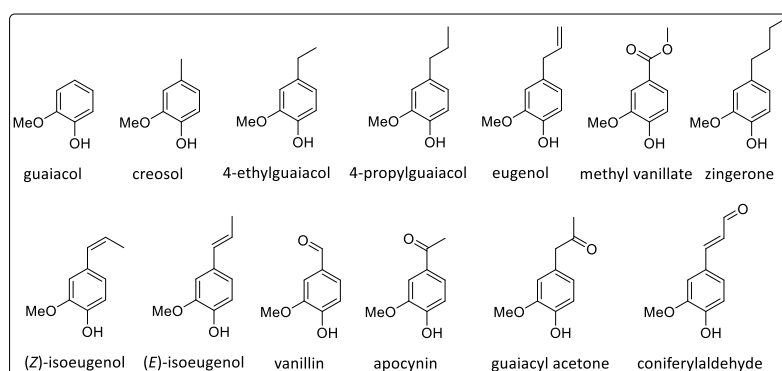


Figure 11. Detected Py-GC/MS fragments attributed to the G-unit.

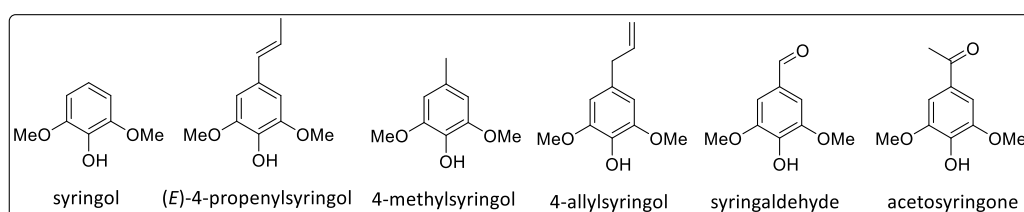


Figure 12. Detected Py-GC/MS fragments attributed to the S-unit.

As summarized in Table 7, Py-GC/MS fragments assigned to the syringyl (S) unit showed lowest values for both leaf-derived lignin samples whereas highest values were found for p-hydroxyphenyl (H) units. However, it should be emphasized that this is just a first estimation since not all Py-GC/MS data could be assigned. In general, all samples investigated in this study showed a high amount of H units (Tab. 7), confirming data reported by Brandt et al. for lignin isolated from *M. x giganteus* using ionic liquids [78].

Table 7. Monolignol ratio of lignins according to pyrolysis GC/MS data of *M. X giganteus* samples (in %) Mixtures (Gig17M, Gig34M), leaves (Gig17L, Gig34L) and stems (Gig17S, Gig34S).

Sample	H (%)	G (%)	S (%)
Gig17M	37.13	35.96	26.91
Gig17L	46.35	45.82	7.83
Gig17S	35.11	32.94	31.95
Gig34M	43.79	29.50	26.71
Gig34L	46.30	39.25	14.45
Gig34S	35.06	38.55	26.39

According to Py-GC-MS analysis, fragments released from untreated *Miscanthus* originated from H/p-coumaric acid, G/ferulic acid and S in roughly equal amounts (32%, 35% and 33%, respectively). For quantification in pyrolysis gas chromatography, FID detectors are used giving nearly the same response as MS detectors once the compounds have been identified [89]. The application of the MS detector for the quantification and determination of monolignol ratio of lignins in our work could be the cause of the discrepancy between the quantitative results obtained from Py-GC/MS and HSQC-NMR methods (see next paragraph).

2.8. Nuclear Magnetic Resonance

Heteronuclear single quantum correlation (HSQC) 2D-NMR was used to characterize the structure of *M. x giganteus* derived lignin with particular focus on monolignol ratio and corresponding linkages. In accordance with literature data, cell wall and lignin HSQC spectra can be divided into the following regions: the aliphatic (side chain) and the aromatic (core) region. The aliphatic region does not provide structural information except for acetyl substituents and/or hemicellulosic component. Tab. 8 summarizes the obtained HSQC data.

Table 8. HSQC 2D NMR data for a *M. X giganteus* stem/leaf mixture (Gig17M).

Number	Integral (rel)	$\delta^1\text{H}$ (ppm)	$\delta^{13}\text{C}$ (ppm)	Name	Assignment
1	0.0190	3.45	52.88	B ⊙	B
2	0.0254	3.06	53.34	C ⊙	C
3	0.7089	3.56	59.66	A ⊙	A
4	0.1322	3.23	59.71	B ⊙	B
5	0.1932	3.68	62.73	A ⊙	A
6	0.0321	3.82	71.00	C ⊙	C
7	0.0441	4.17	70.76	C ⊙	C
8	0.0561	4.74	70.95	A ⊙	A
9	0.1541	4.86	71.37	A ⊙	A
10	0.0435	4.47	79.78	A ⊙	A
11	0.1160	4.31	83.63	A ⊙	A

12	0.0361	4.64	84.75	C ⊙	C
13	0.1106	4.07	85.77	A ⊙	A
14	0.0626	5.45	86.79	B ⊙	B
15	0.7042	6.73	103.42	S 2/6	S
16	0.0411	6.99	103.24	S 2/6	S
17	0.0337	7.33	103.79	S 2/6	S
18	0.4662	6.96	109.88	G 2	G
19	0.1192	6.30	113.46	D ⊙	D
20	1.0000	6.71	114.80	G 5	G
21	0.1827	6.79	118.61	G 6	G
22	0.1588	7.12	127.35	H 2/6	H
23	0.4032	7.48	129.07	H 2/6	H
24	0.1315	7.43	143.84	D ⊙	D

Integral numbers 1-14 found in the non-aromatic region and attributed monolignol linkages (Fig. 13). Integrals 15-24 were obtained in the aromatic region assigned to the monolignol units (H, G, S) (Fig. 14).

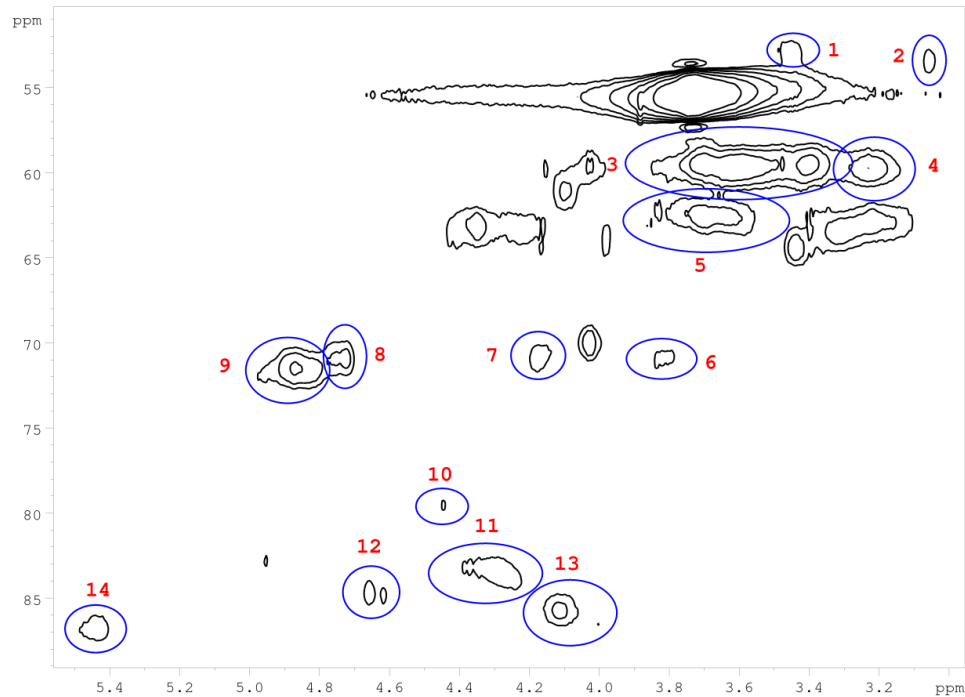


Figure 13. Non-aromatic HSQC region of a lignin obtained from *M. X giganteus* stem/leaf mixture (Gig17M). Numbers are listed and assigned in Table 9.

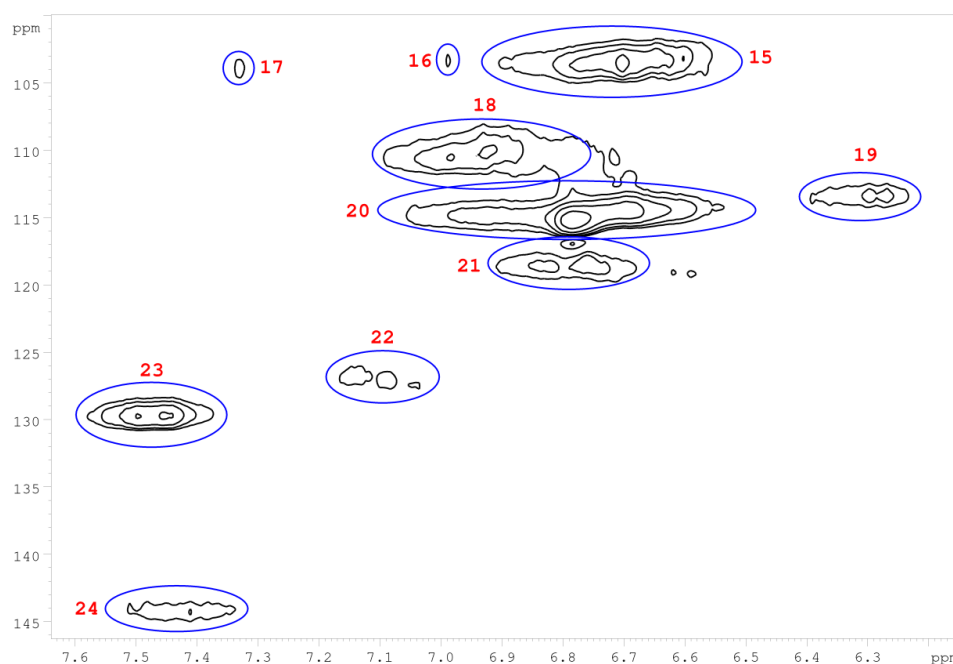


Figure 14. Aromatic HSQC region of a lignin obtained from *M. X giganteus* stem/leaf mixture (Gig17M). Numbers are listed and assigned in Table 9.

Corresponding ratios of monolignols and linkages were estimated. As summarized in Table 9, the data show differences between mixtures and lignin obtained from separated stem versus leaf. In leaves, about two-thirds of the G unit was found, whereas stem and mixture samples showed rather low G content. Instead, H and S units are at a higher ratio in mixtures.

Table 9. Ratio of the monomer units (H, G, S) in lignins obtained from *M. X giganteus*. Stem/leaf mixtures (Gig17M, Gig34M), stems (Gig17S, Gig34S) and leaves (Gig17L, Gig34L).

Sample	H	G	S
Gig17M	23.03	45.05	31.92
Gig17L	13.65	67.24	19.11
Gig17S	15.77	57.67	26.56
Gig34M	21.17	53.54	25.29
Gig34L	14.87	63.43	21.70
Gig34S	19.07	54.80	26.13

However, HSQC NMR only considers signals for free C-H coupling (in case of further aromatic substituents, those fragments would not be recognized) [48,63,90]. So, further detailed analysis is required to explain deviations of the monolignol ratios obtained via pyrolysis GC/MS and HSQC-NMR. Based on the HSQC data, the ratio of most abundant monolignol linkages was estimated (Tab. 10, Fig. 15).

Table 10. Ratio of the most abundant linkages in lignins obtained from *M. x giganteus*. Stem/leaf mixtures (Gig17M, Gig34M), stems (Gig17S, Gig34S) and leaves (Gig17L, Gig34L).

Sample	A (β -aryl ether) %	B (phenylcoumaran) %	C (resinol) %	D (unsaturated ester) %
--------	-------------------------------	-------------------------	------------------	----------------------------

Gig17M	61.84	9.56	6.16	22.43
Gig17L	65.31	9.43	4.35	20.91
Gig17S	58.14	9.37	8.18	24.31
Gig34M	62.62	7.70	8.00	21.68
Gig34L	66.41	10.10	4.92	18.57
Gig34S	54.73	8.22	7.28	29.77

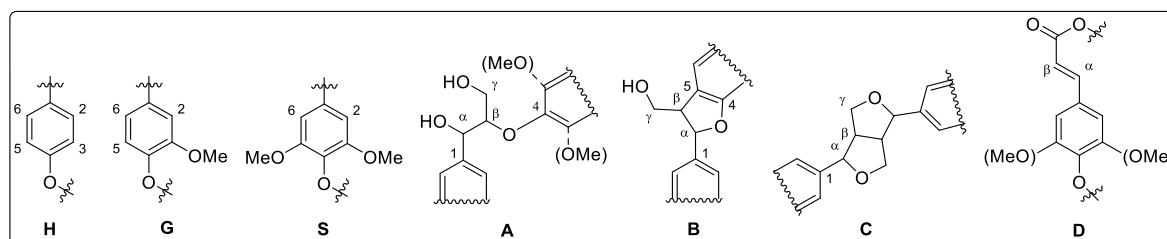


Figure 15. Lignin structure elements for HSQC NMR signal assignment (A: β -O-4 linkage, B: phenylcoumaran, C: resinol, D: β -unsaturated ester).

In accordance with reported data for *Miscanthus*-based lignins, β -arylether were most abundant linkages, varying between 55 to 65 %. About 10 % of the signals could assigned to phenylcoumarane and resinol linkages. Unsaturated esters (D) are most abundant in stem-based lignins (up to 30 %). Contrary to literature data, no signals were found for residual carbohydrates confirming the purity of the lignins obtained via organosolv pulping.

3. Materials and Methods

3.1. *Miscanthus* Field Trial Lignin Isolation via Organosolv Pulping

Miscanthus genotypes used in this study are cultivated at the field lab Campus Klein-Altendorf (University of Bonn, Rheinbach, Germany). The field stand was established in 2012. Genotypes used in this study were *M. x giganteus* (cultivars 17, 34, and 35, named as Gig17, Gig34, Gig35), *M. nagara* (NagG10), *M. sinensis* (cultivar 2, named Sin2), and *M. robustus* (cultivar 4, named Rob4, a hybrid of *M. sacchariflorus* and *M. sinensis*) [15,16]. *Miscanthus* samples were taken from the field stand in December 2014, April 2015, and September 2015.

3.2. Lignin Isolation via Organosolv Pulping

The samples were milled (using a ball mill Pulverisette 6, Fritsch, Germany) and sieved (using a Modell AS 200 basic, Retsch, Germany) to a particle size < 0.5 mm. The organosolv process was performed according to an earlier published procedure [34,91-93]. All samples were prepared without using catalysts. Approx. 50 g *Miscanthus x giganteus* was passed through a 0.5 mm sieve and then mixed with 400 mL Ethanol (80% v/v). The mixture was heated at 170 °C for 90 min under continuous stirring in a Parr reactor with a Parr 4848 Reactor Controller. Afterwards, the *Miscanthus* biomass is vacuum filtrated and washed 5 times with 50 mL Ethanol (80% v/v). Three volumes of water and approx. 10 mL hydrochloric acid was added to the filtrate to precipitate the organosolv lignin, which was collected by centrifugation at 3500 rpm for 5 min and washed 3 times with dist. water. Finally, the samples were freeze-dried for 72 h.

3.3. Lignin Purity, Ash and Sugar Content via NREL Measurements

The chemical composition (% w/w) was determined according to the standard analytical procedures published by National Renewable Energy Laboratory (NREL) (Determination of Structural Carbohydrates and Lignin in Biomass) [94]. NREL measurements were performed by the BIOPOS Research Institute (Teltow-Seehof, Germany). HPLC analysis was conducted using water at a flow rate of 0.4 mL/min in a column (300 x 7.8 mm, Machery-Nagel, Germany) at a constant

temperature of 90°C. Shortly, structural carbohydrates in biomass and lignin samples were determined following NREL/TP-510-42618 [95], biomass extracts in water and ethanol according to NREL/TP-510-42619 [96], dry matter in biomass according to NREL/TP-510-42621 (Sluiter et al., 2008) [97] and ash contents according to NREL/TP-510-42622 [98].

3.4. Size-exclusion Chromatography

To evaluate the depolymerization of the lignins, SEC was performed using the parameters shown in Table 11. Samples with a concentration of 10 mg mL⁻¹ were prepared in tetrahydrofuran (THF) and filtrated through 0.2 µm PTFE filter prior to analysis. For molar weight evaluation polystyrene was used as a calibration standard.

Table 11. SEC set up and parameters.

Component	Description	Parameter
Eluent	THF p.a.	HPLC-grade
Pump	Agilent 1100 Series	Flowrate: 1.000 mL min ⁻¹
Injector	Rheodyne 7725i sample loop	Injection volume: 60 µL
Oven	Agilent 1100 Series	Temperature: 35 °C
Column	1x PSS SDV 8x50 mm pre-column	Particle size: 5 µm
	2x PSS SDV 8x300 mm Linear M 5µ	Particle size: 5 µm Molar weight range: 50-10'000'000 g mol ⁻¹
Detector	Agilent 1100 Series VWD	Wavelength: 280 nm
Calibration	PSS ReadyCal-Kit Polystyren	Calibration range: 376-2'570'000 g mol ⁻¹

Size exclusion chromatography was performed using a PSS SECurity2 GPC System, Mainz, Germany (UV detector, 280 nm) to determine the weight-average (Mw) and number-average (Mn) molecular weights of the lignins, as well as their polydispersity (PD). Tetrahydrofuran (THF) was the mobile phase with a run time of 30 min and an injection volume of 60 µL and polystyrene calibration standards. The lignin sample was completely dissolved in THF (1 mg·mL⁻¹) with gentle stirring at room temperature.

3.5. UV-Vis Spectroscopy

The lignin UV-Vis absorption was measured using a Hewlett-Packard (Waltham, MA, USA) 450 Diode Array spectrometer. Samples of 1 mL containing 0.5 mg mL⁻¹ lignin in THF were measured at room temperature in a range of 260-400 nm.

3.6. Fourier Transform Infrared Spectroscopy

FTIR-spectra were recorded in a wavenumber range of 4'000-700 cm⁻¹ with a resolution of 4 cm⁻¹ and 8 scans per sample (Jasco, Japan). KBr disc containing 2 mg of sample and 300 mg of KBr were prepared using a hydraulic press (10 metric tons).

3.7. Multivariate Data Analysis

Multivariate data analysis was performed using principal component analysis (PCA) in MATLAB 2019a (The Math Works, Natick, MA, USA). SAISIR package for MATLAB was used for statistical calculations [99,100]. The data points from IR spectral regions (800 – 1'800 cm⁻¹ and 2'800-3'700 cm⁻¹) were selected. Autoscaling was used as the pretreatment before PCA. To normalize the intensities in different samples, they were additionally scaled to the total intensity.

3.8. Nuclear Magnetic Resonance Spectroscopy

2D HSQC NMR spectra were recorded using a NMR spectrometer Avance III 600 (Bruker, Karlsruhe, Germany) with 4 scans and 16 prior dummy scans. Deuterated dimethyl sulfoxide (DMSO *d*-6) was used as solvent, tetramethylsilane as standard and 100 mg/mL as sample concentration. A spectral width of 7211 Hz was used, resulting in 4000 points (receiver gain of 2050). A total acquisition time of 0.28 s. O_1 was set to 5 ppm (^1H) and 80 ppm (^{13}C).

3.9. Thermogravimetric Analysis

Approximately 10 mg of lignin were used for thermogravimetric analysis (TGA) using a Netzsch (Selb, Germany) TGA 209 F1 (at a heating rate of 20 °C min⁻¹, nitrogen atmosphere). The temperature ranged from ambient to 900 °C. At 900 °C synthetic air was used for an isothermic combustion.

3.10. Pyrolysis-Gas Chromatography/Mass Spectrometry

Pyrolysis-GC/MS measurements were performed on a combination of two GC 2010 Plus gas chromatographs, a GCMS-QP2010 Ultra mass spectrometer (Shimadzu, Kyoto, Japan) and an EGA/PY-3030D multi-shot pyrolyzer (Frontier Lab, Fukushima, Japan). The two fused silica capillary columns were Ultra Alloy columns (UA5-30M-0.25F and UACW-20M-0.25F) with a length of 30 m each, an inside diameter of 0.25 mm, and a film thickness of 0.25 µm. Shimadzu software MDGC Analysis GC solution 2.41.00.SU1 was used for measurement and Shimadzu GC/MS solution 2.72 for evaluation [73]. A 0.5 mg lignin sample was placed in a pyrolysis crucible made of stainless steel (PY1-EC50F), inserted into the pyrolyzer and pyrolysed at 550 °C. For the first capillary column, the following temperature program was used: 75°C for 1 min, 280°C for 25 min at a heating rate of 7 °C min⁻¹. The column of the second GC instrument was held isothermal at 200 °C. Helium, grade 4.0 (99.990 %, v/v) (Westfalen AG, Münster, Germany) was used as carrier gas. After GC separation of the pyrolysis products, the MS detection was carried out. The ionization of the substances took place via electron impact ionization (EI) at 70 eV. The substances were accelerated in a high vacuum by the electric field of the quadrupole, thereby separated and then detected by their mass/charge ratio (*m/z*) in the electron multiplier. The *m/z* measuring range was 35-740 u.

4. Conclusions

This study presents the first systematic analysis of lignin amount and 3D structure for two different *M. x giganteus* genotypes (Gig17, Gig34) separated into stem and leaf portions. For biomass pulping, the organosolv process was used. Depending on plant component (leaf versus stem), structure-property-relationships have been developed. According to SEC analysis, lignin molecular weights and polydispersities differ for stem and leaf-derived lignins. Spectroscopic data (HSQC-NMR) revealed differences in monolignol ratio and linkages for stem and leaf-based lignins. Further studies are required to explain deviations of pyrolysis GC/MS and HSQC-NMR results. FTIR data discrimination was approved using multivariate data analysis, in particular the principal component analysis (PCA). Here, aromatic in-plane deformation FTIR absorption signals (at about 1160 cm⁻¹) corresponding to the monolignol substitution pattern could be assigned to differentiate between stem and leaf lignins. Due to HSQC NMR results, there are also differences in monolignol composition for the two *M. x giganteus* samples (Gig17, Gig34). In comparison to beech wood-based lignin obtained from organosolv pulping at similar conditions, Miscanthus lignins possess lower molecular weight and a very narrow polydispersity (< 1.5 for *M.* genotypes versus > 2.5 for beech wood lignins) due to a more homogeneous structure of grass versus wood-derived lignins. The obtained results emphasize the potential of Miscanthus crop as low-input resource and agricultural feedstock for sustainable material production.

Author Contributions: M.B. mainly contributed to the manuscript, performed the experiments, analyzed the data and contributed main parts of the manuscript; G.V., R.P. cultivated the crop genotypes and provided the Miscanthus samples of different particle sizes; Y.M. performed the NMR measurements and assisted in data analysis; X.T.D. performed multivariate data analysis (i.e., principal component analysis); P.K. performed Py-GC-MS measurements; T.K. contributed in writing; C.K. performed parts of the lignin FTIR measurements

during his DAAD RISE internship at HBRS and as a native speaker contributed in writing; M.S. conceived and designed the experimental studies and was mainly involved in manuscript writing.

Funding: This project was funded by the BMBF program “IngenieurNachwuchs” project “LignoBau” (03FH013IX4) and BioSC project “Miscanthus Cascade Utilization” (NRW state ministry for research). A PhD scholar ship was given to M.B. by the Graduate Institute of Bonn-Rhein-Sieg University of Applied Sciences. Y.M. acknowledges support from the Russian Science Foundation (project 18-73-10009).

Conflicts of Interest: The authors declare no conflict of interest.

References

- Emmerling, C.; Pude, R. Introducing Miscanthus to the greening measures of the EU Common Agricultural Policy. *GCB Bioenergy* **2017**, *9*, 274–279, DOI:10.1111/gcbb.12409.
- Lewandowski, I.; Clifton-Brown, J.; Trindade, L.M.; van der Linden, G.C.; Schwarz, K.-U.; Müller-Sämann, K.; Anisimov, A.; Chen, C.-L.; Dolstra, O.; Donnison, I.S.; Farrar, K.; Fonteyne, S.; Harding, G.; Hastings, A.; Huxley, L.M.; Iqbal, Y.; Khokhlov, N.; Kiesel, A.; Lootens, P.; Meyer, H.; Mos, M.; Muylle, H.; Nunn, C.; Özgüven, M.; Roldán-Ruiz, I.; Schüle, H.; Tarakanov, I.; van der Weijde, T.; Wagner, M.; Xi, Q.; Kalinina, O. Progress on optimizing miscanthus biomass production for the European bioeconomy: results of the EU FP7 project OPTIMISC. *Front. Plant Sci.* **2016**, *7*, Article 1620, DOI:10.3389/fpls.2016.01620.
- McCalmont, J.P.; Hastings, A.; McNamara, N.P.; Richter, G.M.; Robson, P.; Donnison, I.S.; Clifton-Brown, J. Environmental costs and benefits of growing Miscanthus for bioenergy in the UK. *GCB Bioenergy* **2017**, *9*, 489–507, DOI:10.1111/gcbb.12294.
- Kellogg, E. A. C₄ photosynthesis. *Curr. Biol.* **2013**, *23*, R594–599, DOI: 10.1016/j.cub.2013.04.066.
- Villaverde, J.J.; Ligerio, P.; Vega, A. Miscanthus x giganteus as a Source Of Biobased Products Through Organosolv Fractionation: A Mini Review. *TOAJ* **2010**, *4*, 102–110, DOI:10.2174/1874331501004010102.
- Teese, P. Intraspecific variation for CO₂ compensation point and differential growth among variants in a C₃-C₄ intermediate plant. *Oecologia* **1995**, *102*, 371–376.
- Felten, D.; Frēoba, N.; Fries, J.; Emmerling, C. Energy balances and CO₂-mitigation potentials of bioenergy crops (Miscanthus, rapeseed, maize) based on farming conditions in Western Germany. *Renew. En.* **2013**, *55*, 160–174, DOI: 10.1016/j.renene.2012.12.004.
- Felten, D.; Emmerling, C. Accumulation of Miscanthus-derived carbon in soils in relation to soil depth and duration of land-use under commercial farming conditions. *J. Plant Nutr. Soil Sci.* **2012**, *175*, 661–670, DOI:10.1002/jpln.201100250.
- Kiesel, A.; Nunn, C.; Iqbal, Y.; Van der Weijde, T.; Wagner, M.; Özgüven, M.; Tarakanov, I.; Kalinina, O.; Trindade, L.M.; Clifton-Brown, J.; Lewandowski, I. Site-Specific Management of Miscanthus Genotypes for Combustion and anaerobic digestion: a comparison of energy yields. *Front. Plant Sci.* **2017**, *8*, Article 347, DOI:10.3389/fpls.2017.00347.
- Brosse, N.; Dufour, A.; Meng, X.; Sun, Q.; Ragauskas, A. Miscanthus: a fast growing crop for biofuels and chemicals production. *Biofuels, Bioprod. Bioref.* **2012**, *6*, 580–598, DOI:10.1002/bbb.1353.
- Jørgensen, U. Genotypic variation in dry matter accumulation and content of N, K and Cl in Miscanthus in Denmark. *Biomass Bioenergy* **1997**, *12*, 155–169, DOI: 10.1016/S0961-9534(97)00002-0.
- Clifton-Brown, J.C.; Lewandowski, I. Frosttoleranz der Rhizome verschiedener Miscanthus Genotypen. *Mitt. Ges. Pflanzenbauwiss.* **1998**, *11*, 225–226.
- Eppel-Hotz, A.; Jodl, S.; Kuhn, W.; Marzini, K.; Munzer, W. Miscanthus: new cultivars and results of research experiments for improving the establishment rate. Biomass for Energy. In: Proceedings of the 10th European Biomass Conference. Würzburg, Germany: C.A.R.M.E.N Publishers; 1998. p. 780–786.
- Greef, J. M.; Deuter, M.; Jung, C.; Schondelmaier, J. Genetic diversity of European Miscanthus species revealed by AFLP fingerprinting. *Genet. Resour. Crop Evol.* **1997**, *44*, 185–195.
- Pude, R.; Treseler, C.H.; Noga, G. Morphological, chemical and technical parameters of Miscanthus genotypes. *J. Appl. Botany*, **2004**, *78*, 58–63.
- Pude, R.; Treseler, C.H.; Trettin, R.; Noga, G. Suitability of Miscanthus genotypes for lightweight concrete. *Die Bodenkultur*, **2005**, *56*, 61–69.
- Iqbal, Y.; Lewandowski, I. Inter-annual variation in biomass combustion quality traits over five years in fifteen Miscanthus genotypes in south Germany. *Fuel Process. Technol.* **2014**, *121*, 47–55, DOI:10.1016/j.fuproc.2014.01.003.

18. Clifton-Brown, J.; Breuer, J.; Jones, M.B. Carbon mitigation by the energy crop *Miscanthus*. *Global Change Biol.*, **2007**, *13*, 2296–2307, DOI:10.1111/gcbb.12357.
19. Clifton-Brown, J. C.; Lewandowski, I.; Andersson, B.; Basch, G.; Christian, D.G.; Kjeldsen, J.B.; Jørgensen, U.; Mortensen, J.V.; Riched, A.B.; Schwarz, K.U.; Tayebi, K.; Teixeira, F. Performance of 15 *Miscanthus* Genotypes at Five Sites in Europe. *Agron. J.* **2011**, *93*, 1013–1019, DOI:10.2134/agronj2001.9351013x.
20. Kamm, B.; Kamm, M.; Hirth, T.; Schulze, M. Lignocelluloses Based Chemical Products and Product Family Trees. In *Biorefineries-Industrial Processes and Products*; Kamm, M., Kamm, B., Gruber, P.C., Eds.; Wiley-VCH: Weinheim, Germany, **2006**; pp. 97–150, ISBN 3-527-31027-4.
21. Kamm, B.; Gruber, P.R.; Kamm, M. Biorefineries-Industrial Processes and Products. In *Ullmann's Encyclopedia of Industrial Chemistry*, Wiley-VCH: Weinheim, Germany, **2016**; ISBN 9783527306732.
22. Alzagameem, A.; El Khaldi-Hansen, B.; Kamm, B.; Schulze, M. Lignocellulosic biomass for energy, biofuels, biomaterials, and chemicals. In *Biomass and Green Chemistry*, 1st ed.; Vaz, S., Jr., Ed.; Springer International Publishing: Basel, Switzerland, **2018**; pp. 95–132, ISBN 978-3-319-66736-2, DOI:10.1007/978-3-319-66736-2.
23. Kraska, T.; Kleinschmidt, B.; Weinand, J.; Pude, R. Cascading use of as growing substrate in soilless *Miscanthus* cultivation of vegetables (tomatoes, cucumbers) and subsequent direct combustion. *Scientia Hort.*, **2018**, *235*, 205–213, DOI: 10.1016/j.scienta.2017.11.032.
24. Winzer, F.; Kraska, T.; Elsenberger, C.; Kötter, T.; Pude, R. Biomass from fruit trees for combined energy and food production. *Biomass Bioen.* **2017**, *107*, 279–286, DOI: 10.1016/j.biombioe.2017.10.027.
25. Sørensen, A.; Teller, P. J.; Hilstrøm, T.; Ahring, B. K. Hydrolysis of *Miscanthus* for bioethanol production using dilute acid presoaking combined with wet explosion pre-treatment and enzymatic treatment. *Bioresour. Technol.* **2008**, *99*, 6602–6607, DOI: 10.1016/j.biortech.2007.09.091.
26. Vrije, T. de; Haas, G.G. de; Tan, G.B.; Keijsers, E.R.P.; Claassen, P.A.M. Pretreatment of *Miscanthus* for hydrogen production by Thermotoga elfii. *Int. J. Hydrog. Energy* **2002**, *27*, 1381–1390, DOI:10.1016/S0360-3199(02)00124-6.
27. Kjeldsen, J. B.; Joergensen, U.; Kristensen, E. F. Thatching: use of *Miscanthus*. *DJF Rapport. Markbrug (Denmark)* **1999**.
28. Wagenaar, B. M.; van den Heuvel, E. Co-combustion of *Miscanthus* in a pulverised coal combustor: Experiments in a droptube furnace. *Biomass Bioenergy* **1997**, *12*, 185–197.
29. Khelfa, A.; Sharypov, V.; Finqueneisel, G.; Weber, J. V. Catalytic pyrolysis and gasification of *Miscanthus Giganteus*: Haematite (Fe₂O₃) a versatile catalyst. *J. Anal. Appl. Pyrolysis* **2009**, *84*, 84–88, DOI: 10.1016/j.jaap.2008.11.009.
30. Velasquez, J.A.; Ferrando, F.; Farriol, X.; Salvado, J. Binderless fiberboard from steam exploded *Miscanthus sinensis*. *Wood Sci. Technol.* **2003**, *37*, 269–278, DOI:10.1007/s00226-003-0182-8.
31. Vega, A.; Bao, M.; Lamas, J. Application of factorial design to the modelling of organosolv delignification of *Miscanthus sinensis* (elephant grass) with phenol and dilute acid solutions. *Bioresour. Technol.* **1997**, *61*, 1–7, DOI:10.1016/S0960-8524(96)00056-9.
32. El Hage, R.; Brosse, N.; Chrusciel, L.; Sanchez, C.; Sannigrahi, P.; Ragauskas, A. Characterization of milled wood lignin and ethanol organosolv lignin from miscanthus. *Polym. Degrad. Stab.* **2009**, *94*, 1632–1638, DOI: 10.1016/j.polymdegradstab.2009.07.007.
33. El Hage, R.; Perrin, D.; Brosse, N. Effect of the pre-treatment severity on the antioxidant properties of ethanol organosolv *Miscanthus x giganteus* lignin. *Nat. Resour.* **2012**, *3*, 29, DOI:10.4236/nr.2012.32005.
34. El Hage, R.; Brosse, N.; Sannigrahi, P.; Ragauskas, A. Effects of process severity on the chemical structure of *Miscanthus* ethanol organosolv lignin. *Polym. Degrad. Stab.* **2010**, *95*, 997–1003, DOI:10.1016/j.polymdegradstab.2010.03.012.
35. Chan, J.M.W.; Bauer, S.; Sorek, H.; Sreekumar, S.; Wang, K.; Toste, F.D. Studies on the vanadium-catalyzed nonoxidative depolymerization of *Miscanthus giganteus*-derived lignin. *ACS Catal.* **2013**, *3*, 1369–1377, DOI:10.1021/cs400333q.
36. Luo, H.; Klein, I.M.; Jiang, Y.; Zhu, H.; Liu, B.; Kenttämää, H.I.; Abu-Omar, M.M. Total Utilization of *Miscanthus* Biomass, Lignin and Carbohydrates, Using Earth Abundant Nickel Catalyst. *ACS Sustain. Chem. Eng.* **2016**, *4*, 2316–2322, DOI: 10.1021/acssuschemeng.5b01776.
37. Vanderghem, C.; Richel, A.; Jacquet, N.; Blecker, C.; Paquot, M. Impact of formic/acetic acid and ammonia pre-treatments on chemical structure and physico-chemical properties of *Miscanthus x giganteus* lignins. *Polym. Degrad. Stab.* **2011**, *96*, 1761–1770, DOI:10.1016/j.polymdegradstab.2011.07.022.

38. Timilsena, Y. P.; Abeywickrama, C. J.; Rakshit, S. K.; Brosse, N. Effect of different pretreatments on delignification pattern and enzymatic hydrolysability of miscanthus, oil palm biomass and typha grass. *Bioresour. Technol.* **2013**, *135*, 82–88, DOI:10.1016/j.biortech.2012.09.010.
39. Jin, X.; Chen, X.; Shi, C.; Li, M.; Guan, Y.; Yeon, C.; Yamada, Y.T. Sacks, E.J.; Peng, J. Determination of hemicellulose, cellulose and lignin content using visible and near infrared spectroscopy in *Miscanthus sinensis*. *Biores. Technol.* **2017**, *241*, 603–609, DOI:10.1016/j.biortech.2017.05.047.
40. van der Weijde, T.; Kiesel, A.; Iqbal, Y.; Muylle, H.; Dolstra, O.; Visser, R. G. F.; Lewandowski, I.; Trindade, L. M. Evaluation of *Miscanthus sinensis* biomass quality as feedstock for conversion into different bioenergy products. *GCB Bioenergy* **2016**, *9* (1), 176–190, DOI:10.1111/gcbb.12355.
41. Baker, P.W.; Winters, A.; Hale, M.D.C. Biodegradation of Different Genotypes of *Miscanthus* by Wood Rot Fungi. *BioResources* **2016**, *11*, 4379–4391, DOI:10.1016/j.ibiod.2010.12.009.
42. Ion, S.; Opris, C.; Cojocaru, B.; Tudorache, M.; Zgura, I.; Galca, A.C.; Bodescu, A.M.; Enache, M.; G.-M.; Parvulescu, V.I. One-Pot Enzymatic Production of Lignin-Composites. *Front. Chem.* **2018**, *6*, Article 124, DOI:10.3389/fchem.2018.00124.
43. Sonnenberg, A.M.; Baars, J.J.P.; Visser, M.H.M.; Lavrijssen, B.; Hendrickx, P. M. *Evaluation of shiitake strains (Lentinula edodes) on selective lignin degradation in Miscanthus x giganteus*, **2016**. DOI: 10.18174/401882.
44. da Costa, R.M.F.; Lee, S.J.; Allison, G.G.; Hazen, S.P.; Winters, A.; Bosch, M. Genotype, development and tissue-derived variation of cell-wall properties in the lignocellulosic energy crop *Miscanthus*. *Ann. Bot.* **2014**, *114*, 1265–1277, DOI:10.1093/aob/mcu054.
45. Iqbal, Y.; Lewandowski, I. Inter-annual variation in biomass combustion quality traits over five years in fifteen *Miscanthus* genotypes in south Germany. *Fuel Process. Technol.* **2014**, *121*, 47–55, DOI:10.1016/j.fuproc.2014.01.003.
46. Ralph, J.; Landucci, L. NMR of lignins. In *Lignin and lignans: advances in chemistry*, Editor, Boca Raton: Taylor & Francis, Location, Country, 2010, pp. 137–244, ISBN
47. Lupoi, J.S.; Singh, S.; Parthasarathi, R.; Simmons, B.A.; Henry, R.J. Recent innovations in analytical methods for the qualitative and quantitative assessment of lignin. *Renew. Sustain. Energy. Rev.* **2015**, *49*, 871–906, DOI:10.1016/j.rser.2015.04.091.
48. Tarasov, D.; Leitch, M.; Fatehi, P. Lignin–carbohydrate complexes: properties, applications, analyses, and methods of extraction: a review. *Biotechnol Biofuels* **2018**, *11*, 269, DOI:10.1186/s13068-018-1262-1.
49. Li, M.; Pu, Y.; Ragauskas, A.J. Current Understanding of the Correlation of Lignin Structure with Biomass Recalcitrance. *Front. Chem.* **2016**, *4*, Article 45, DOI:10.3389/fchem.2016.00045.
50. Lang, J.M.; Shrestha, U.M.; Dadmun, M. The Effect of Plant Source on the Properties of lignin-Based Polyurethanes. *Front. Energy Res.* **2018**, *6*, Article 4, DOI:10.3389/fenrg.2018.00004.
51. Klein, S.E.; Rumpf, J.; Kusch, P.; Albach, R.; Rehahn, M.; Witzleben, S.; Schulze, M. Utilization of Unmodified Kraft Lignin for the Preparation of Highly Flexible and Transparent Polyurethane Coatings. *RSC Adv.* **2018**, *8*, 40765, DOI:10.1039/c8ra08579j.
52. Klein, S.E.; Rumpf, J.; Rehahn, M.; Witzleben, S.; Schulze, M. Biobased Flexible Polyurethane Coatings Prepared from Kraft Lignin: One-Pot Synthesis and Antioxidant Activity. Submitted to *J. Coat. Technol. Res.*, Manuscript ID: JCTR-D-18-00729.
53. Witzler, M.; Alzagameem, A.; Bergs, M.; El Khaldi-Hansen, B.; Klein, S.E.; Hielscher, D.; Kamm, B.; Kreyenschmidt, J.; Tobiasch, E.; Schulze, M. Lignin-Derived Biomaterials for Drug Release and Tissue Engineering. *Molecules* **2018**, *23*, 1885, doi:10.3390/molecules23081885.
54. Groenewold, G.S.; Johnson, K.M.; Fox, S.C.; Rae, C.; Zarzana, C.A.; Kersten, B.R.; Rowe, S.M.; Westover, T.L.; Gresham, G.L.; Emerson, R.M. Pyrolysis Two-Dimensional GC-MS of *Miscanthus* Biomass: Quantitative Measurement using an Internal Standard Method. *Energy Fuels* **2017**, *31*(2), 1620–1630, DOI:10.1021/acs.energyfuels.6b02645.
55. Bottcher, A.; Cesarino, I.; dos Santos, A.B.; Vicentini, R.; Mayer, J.L.S.; Vanholme, R.; Morreel, K.; Goeminne, G.; Moura, J.C.M.S.; Nobile, P.M.; et al. Lignification in sugarcane: Biochemical characterization gene discovery, and expression analysis in two genotypes contrasting for lignin content. *Plant Physiol.* **2013**, *163*, 1539–1557, DOI:10.1104/pp.113.225250.
56. Del Río, J.C.; Rencoret, J.; Prinsen, P.; Martinez, A.T.; Ralph, J.; Gutierrez, A. Structural characterization of wheat straw lignin as revealed by analytical pyrolysis, 2D-NMR, and reductive cleavage methods. *J. Agric. Food Chem.* **2012**, *60*, 5922–5935, DOI:10.1021/jf301002n.

57. Villaverde, J.J.; Li, J.; Ek, M.; Ligerio, P.; Vega, A. d. Native lignin structure of *Miscanthus x giganteus* and its changes during acetic and formic acid fractionation. *J. Agric. Food Chem.* **2009**, *57*, 6262–6270, DOI:10.1021/jf900483t.
58. Boerjan, W.; Ralph, J.; Baucher, M. Lignin biosynthesis. *Annu. Rev. Plant Biol.* **2003**, *54*, 519–546, DOI:10.1146/annurev.arplant.54.031902.134938.
59. Kukkola, E.M.; Koutaniemi, S.; Pollanen, E.; Gustafsson, M.; Karhunen, P.; Lundell, T.K.; Saranpää, P.; Kilpeläinen, I.; Teeri, T.H.; Fagerstedt, K.V. The dibenzodioxocin lignin substructure is abundant in the inner part of the secondary wall in Norway spruce and silver birch xylem. *Planta* **2004**, *218*, 497–500, DOI:10.1007/s00425-003-1107-3.
60. Argyropoulos, D.S.; Jurasek, L.; Kristofova, L.; Xia, Z.; Sun, Y.; Palus, E. Abundance and reactivity of dibenzodioxocins in softwood lignin. *J. Agric. Food Chem.* **2002**, *50*, 658–666, DOI:10.1021/jf010909g.
61. Li, Z.; Zhao, C.; Zha, Y.; Wan, C.; Si, S.; Liu, F.; Zhang, R.; Li, F.; Yu, B.; Yi, Z. et al. The minor wall-networks between monolignols and interlinked-phenolics predominantly affect biomass enzymatic digestibility in *Miscanthus*. *PLoS one* **2014**, *9*, e105115, DOI:10.1371/journal.pone.0105115.
62. Wang, S.; Dai, G.; Yang, H.; Luo, Z. Lignocellulosic biomass pyrolysis mechanism: A state-of-the-art review. *Prog. Energy Combust. Sci.* **2017**, *62*, 33–86, DOI:10.1016/j.pecs.2017.05.004.
63. Lan, W.; Yue, F.; Rencoret, J.; Carlos del Río, J.; Boerjan, W.; Lu, F.; Ralph, J. Elucidating Tricin-Lignin Structures: Assigning Correlations in HSQC Spectra of Monocot Lignins. *Polymers* **2018**, *10*, 916–922, DOI:10.3390/polym10080916.
64. Monakhova, Y.; Diehl, B.W.K.; Do, X.T.; Witzleben, S.; Schulze, M. Novel method for the determination of average molecular weight of natural polymers based on 2D DOSY NMR and chemometrics: Example of heparin. *J. Pharm. Biomed. Anal.* **2018**, *149*, 128–132, DOI:10.1016/j.jpba.2017.11.016.
65. Boeriu, C.G.; Bravo, D.; Gosselink, R.J.A.; van Dam, J.E.G. Characterisation of structure-dependent functional properties of Lignin with infrared spectroscopy. *Ind. Crops Prod.* **2004**, *20*, 205–218, DOI:10.1016/j.indcrop.2004.04.022.
66. Chen, H.; Ferrari, C.; Angiuli, M.; Yao, J.; Raspi, C.; Bramanti, E. () Qualitative and quantitative analysis of wood samples by Fourier transform infrared spectroscopy and multivariate analysis. *Carbohydrate Polymers* **2010**, *82*, 772–778, DOI:10.1016/j.carbpol.2010.05.052.
67. Christou, C.; Agapiou, A.; Kokkinofa, R. Use of FTIR spectroscopy and chemometrics for the classification of carobs origin. *J. Adv. Res.* **2018**, *10*, 1–8, DOI: 10.1016/j.jare.2017.12.001.
68. Wahid, R.; Nielsen, S. F.; Hernandez, V. M.; Ward, A. J.; Gislum, R.; Jørgensen, U.; Møller, H. B. Methane production potential from *Miscanthus* sp: Effect of harvesting time, genotypes and plant fractions. *Biosyst. Eng.* **2015**, *133*, 71–80, DOI:10.1016/j.biosystemseng.2015.03.005.
69. Bergs, M. Einfluss von *Miscanthus*-Genotyp und Erntezeit auf Gehalt und Struktur von Lignin aus Organosolv-Verfahren. PhD thesis, Rheinische Friedrich-Wilhelms-Universität Bonn, Bonn, December 20, 2018.
70. Hafez, I.; Hassan, E. B. Rapid liquefaction of giant miscanthus feedstock in ethanol–water system for production of biofuels. *Energy Conv. Manag.* **2015**, *91*, 219–224, DOI: 10.1016/j.enconman.2014.12.016.
71. Scagline-Mellor, S.; Griggs, T.; Skousen, J.; Wolfrum, E.; Holásková, I. Switchgrass and Giant *Miscanthus* Biomass and Theoretical Ethanol Production from Reclaimed Mine Lands. *Bioenerg. Res.* **2018**, *11*, 562–573, DOI: 10.1007/s12155-018-9915-2.
72. Sørensen, A.; Teller, P. J.; Hilstrøm, T.; Ahring, B. K. Hydrolysis of *Miscanthus* for bioethanol production using dilute acid presoaking combined with wet explosion pre-treatment and enzymatic treatment. *Bioresour. Technol.* **2008**, *99*, 6602–6607, DOI:10.1016/j.biortech.2007.09.091.
73. Cha, Y.-L.; An, G. H.; Yang, J.; Moon, Y.-H.; Yu, G.-D.; Ahn, J.-W. Bioethanol production from *Miscanthus* using thermotolerant *Saccharomyces cerevisiae* mbc 2 isolated from the respiration-deficient mutants. *Renew. Energ.* **2015**, *80*, 259–265, DOI:10.1016/j.renene.2015.02.016.
74. Yang, H.; Yan, R.; Chen, H.; Lee, D. H.; Zheng, C. Characteristics of hemicellulose, cellulose and lignin pyrolysis. *Fuel* **2007**, *86*, 1781–1788, DOI:10.1016/j.fuel.2006.12.013.
75. Schorr, D.; Diouf, P. N.; Stevanovic, T. Evaluation of industrial lignins for biocomposites production. *Ind. Crops Prod.* **2014**, *52*, 65–73, DOI:10.1016/j.indcrop.2013.10.014.
76. Bauer, S.; Sorek, H.; Mitchell, V.D.; Ibáñez, A.B.; Wemmer, D.E. Characterization of *Miscanthus giganteus* lignin isolated by ethanol organosolv process under reflux condition. *J. Agric. Food Chem.* **2012**, *60*, 8203–8212, DOI:10.1021/jf302409d.

77. Hansen, B.; Kusch, P.; Schulze, M.; Kamm, B. Qualitative and quantitative analysis of lignin produced from beech wood by different conditions of the Organosolv process. *J. Polym. Environ.* **2016**, *24*, 85–97, DOI:10.1007/s10924-015-0746-3.
78. Hansen, B.; Kamm, B.; Schulze, M. Qualitative and quantitative analysis of lignins from different sources and isolation methods for an application as a biobased chemical resource and polymeric material. In *Analytical Techniques and Methods for Biomass Products*; Vaz Jr, S., Seidl, P., Eds., Springer: Berlin, Germany, 2017; pp. 15–44, ISBN 978-3-319-41414-0, DOI:10.1007/978-3-319-41414-0.
79. Brandt, A.; Chen, L.; van Dongen, B. E.; Welton, T.; Hallett, J. P. Structural changes in lignins isolated using an acidic ionic liquid water mixture. *Green Chem.* **2015**, *17*, 5019–5034, DOI:10.1039/c5gc01314c.
80. Alzagameem, A.; El Khadi-Hansen, B.; Büchner, D.; Larkins, M.; Kamm, B.; Witzleben, S.; Schulze, M. Environmentally Benign Lignin-based Antioxidants isolated from Lignocellulose Feedstock. *Molecules* **2018**, *23*, 2664, DOI:10.3390/molecules23102664.
81. Fenner, R.A.; Lephardt, J.O. Examination of the thermal decomposition of kraft pine lignin by Fourier transform infrared evolved gas analysis. *J. Agric. Food Chem.* **1981**, *29*, 846–849.
82. Norambuena, M.; Vidal, C.; Carrasco, L.; Contreras, D.; Mendonça, R.T. Alkaline-catalyzed Modification of Organosolv Lignin: Optimization of Experimental Conditions. 5rd Nordic Wood Biorefinery Conference (NWBC 2015), Helsinki, Finland.
83. Domínguez, C.; Oliet, M.; Gilarranz, M.A.; Rodríguez, F. Thermal stability and pyrolysis kinetics of organosolv lignins obtained from *Eucalyptus globulus*. *Ind. Crops Prod.* **2008**, *27*, 150–156, DOI:10.1016/j.indcrop.2007.07.006.
84. Wittkowski, R.; Ruther, J.; Drinda, H.; Rafiei-Taghanaki, F. Formation of Smoke Flavor Compounds by Thermal Lignin Degradation. *ACS Symposium Series* **1992**, *490*, 232–243.
85. El-Saied, H.; Nada, A.M.A. The thermal behaviour of lignins from wasted black pulping liquors. *Polym. Degrad. Stab.* **1993**, *40*, 417–421, DOI:10.1016/0141-3910(93)90152-9.
86. Glasser, W.G.; Jain, R.K. Lignin derivatives. I. Alkanoates. *Holzforschung* **1993**, *47*, 225–233.
87. Hodgson, E.M.; Nowakowski, D.J.; Shield, I.; Riche, A.; Bridgwater, A.V.; Clifton-Brown, J. C.; Donnison, I. S. Variation in Miscanthus chemical composition and implications for conversion by pyrolysis and thermo-chemical bio-refining for fuels and chemicals. *Bioresour. Technol.* **2011**, *102*, 3411–3418, DOI:10.1016/j.biortech.2010.10.017.
88. Hodgson, E.M.; Lister, S.J.; Bridgwater, A.V.; Clifton-Brown, J.; Donnison, I.S. Genotypic and environmentally derived variation in the cell wall composition of Miscanthus in relation to its use as a biomass feedstock. *Biomass Bioenergy* **2010**, *34*, 652–660, DOI:10.1016/j.biombioe.2010.01.
89. Lourenço, A.; Gominho, J.; Pereira, H. Chemical characterization of lignocellulosic materials by analytical pyrolysis. In *Analytical Pyrolysis*, 1st ed.; Kusch, P. Ed.; IntechOpen, Location/Country, November 5th 2018. DOI: 10.5772/intechopen.80556.
90. Du, X.; Pérez-Boada, M.; Fernández, C.; Rencoret, J.; del Río, J. C.; Jiménez-Barbero, J.; Li, J.; Gutiérrez, A.; Martínez, A. T. Analysis of lignin-carbohydrate and lignin-lignin linkages after hydrolase treatment of xylan-lignin, glucomannan-lignin and glucan-lignin complexes from spruce wood. *Planta* **2014**, *239*, 1079–1090, DOI:10.1007/s00425-014-2037-y.
91. Obama, P.; Ricochon, G.; Muniglia, L.; Brosse, N. Combination of enzymatic hydrolysis and ethanol organosolv pretreatments: effect of lignin structures, delignification yields and cellulose-to-glucose conversion. *Bioresour. Technol.* **2012**, *112*, 156, DOI:10.1016/j.biortech.2012.02.080.
92. Grisel, R.J.H.; van der Waal, J.C.; Jong, E.de; Huijgen, W.J.J. Acid catalysed alcoholysis of wheat straw: Towards second generation furan-derivatives. *Catalysis Today* **2014**, *223*, 3–10, DOI:10.1016/j.cattod.2013.07.008.
93. Toledano, A.; Serrano, L.; Labidi, J. Improving base catalyzed lignin depolymerization by avoiding lignin repolymerization. *Fuel* **2014**, *116*, 617–624, DOI:10.1016/j.fuel.2013.08.071.
94. Determination of Structural Carbohydrates and Lignin in Biomass. Available online: <https://www.nrel.gov/docs/gen/fy13/42618.pdf> (accessed on 10 October 2018).
95. Sluiter, A.; Hames, B.; Ruiz, R.; Scarlata, C.; Sluiter, J.; Templeton, D.; Crocker, D. Determination of structural carbohydrates and lignin in biomass. *Laboratory analytical procedure* **2008**, 1617.
96. Sluiter, A.; Ruiz, R.; Scarlata, C.; Sluiter, J.; Templeton, D. Determination of extractives in biomass (NREL/TP-510-42619). *National Renewable Energy Laboratory, Golden* **2008**.

97. Sluiter, A.; Hames, B.; Hyman, D.; Payne, C.; Ruiz, R.; Scarlata, C.; Sluiter, J.; Templeton, D.; Wolfe, J. Determination of total solids in biomass and total dissolved solids in liquid process samples. *National Renewable Energy Laboratory, Golden, CO, NREL Technical Report No. NREL/TP-510-42621* **2008**, 1–6.
98. Sluiter, A.; Hames, B.; Ruiz, R.; Scarlata, C.; Sluiter, J.; Templeton, D. Determination of ash in biomass (NREL/TP-510-42622). *National Renewable Energy Laboratory, Golden* **2005**.
99. Cordella, C.B.Y.; Bertrand, D.; SAISIR: A new general chemometric toolbox. *Trends Anal. Chem.* **2014**, *54*, 75–82. DOI:10.1016/j.trac.2013.10.009.
100. Martens, H.; Naes, T. Multivariate calibration by data compression. In: William, P., Norris, K. (Eds.), *Near Infrared Technology in the Agriculture and Food Industries*. Amer. Assoc. Cereal Chem., St. Paul, Min. 1987.