

Design and experimental research on sealing structure for a retrievable packer

Yang Liu, Zhanghua Lian *

^aState Key Laboratory of Oil and Gas Reservoir Geology and Exploitation, Southwest Petroleum

University, PR China, 610500

**Correspondence author at: China Tel: +86 15572100275; E-mail: lianzh1964@sina.com*

Abstract In order to reduce the failure accidents of conventional packers, a kind of sealing structure of retrievable packers is designed, which can provide reference for optimizing the sealing performance and pressure capacity of packers. And theoretical calculation and experimental research on its sealing performance and pressure capacity are carries out through the finite element analysis on the contact with large deformation based on Abaqus and experimental. The results show that when the rubber cylinder of retrievable packers in the sealing process, the upper packer is subjected to greater stress and mainly plays a sealing role. In order to improve the sealing performance of packer, the height of upper and lower packer should be preferentially selected about 60 mm, the height of middle rubber cylinders should be about 50 mm, and the thickness of packer should be about 21 mm. The newly designed rubber cylinders can meet 150 °C. Sealing and pressure-bearing function under the condition of 10000 Psi. The rubber cylinder of newly designed can satisfy the function of sealing and pressure-bearing under 140 °C and 10000 Psi. The whole experiment shows that the capacity of bearing pressure and sealing is stable, which can better meet the requirements of field use.

Keywords: retrievable packer; sealing; height; thickness; pressure-bearing

1. Introduction

Packer is an important product used in oil and gas production. It mainly consists of anti-collision part, seating part, locking part, sealing part, anchoring part and unloading part. The seating part is mainly composed of rubber parts. Some scholars have done relevant research on its material and structure. Yi-Feng Chen et al [1] found that high-pressure packer test (HPPT) is an enhanced constant head packer test for characterizing the permeability or coupled hydro mechanical properties of fractured rocks under high-pressure groundwater flow conditions. Dajiang Zhu et al [4, 5] studied that performances of rubber materials have direct relationship with the sealing function of packers. X. Li et al [6, 7] studied that observations and modeling results on the effects packers have on fracture initiation and near wellbore fracture geometry for a set of laboratory hydraulic fracturing experiments. Xiaozhen He et al [8-10] studied that hydrogenated acrylonitrile butadiene rubber (HNBR) was chosen to develop peroxide cured and carbon black N220 reinforced high modulus vulcanizates with possible applications in packers for oil exploration. Joon-Shik Moon et al [11-13] studied that the effect of anisotropic characteristics of the jointed rock mass around a packer interval is also discussed through numerical parametric study using the distinct element method. Gang Hu et al [14] found that the stresses concentrated at the shoulder and inner vertex of the sealing ring have direct impact on the damage of the sealing rings under operational conditions. Dan Dobrotă et al [15-17] found that the duration of the refining process transformation of the rubber waste reclaiming process into a sustainable one by obtaining the new type of reclaimed rubber. Kazuki Komatsu et al [18] reported experimental and analytical results of partial discharge degradation of silicone rubber

sheets in accordance with proposed procedures.

In consideration of the analysis results of the above scholars and experts, the failure reasons of conventional packers is analyzed in this paper, designs a desirable sealing structure of packers, and carries out theoretical calculation and experimental research on its sealing performance and pressure capacity, so as to provide certain data support for the design and safe use of packers.

2. Structure and working principle of retrievable packer

In the oil and gas well, sealing the formation through the packers, provide gas passage way for oil and gas at project formation, as shown in Fig 1.

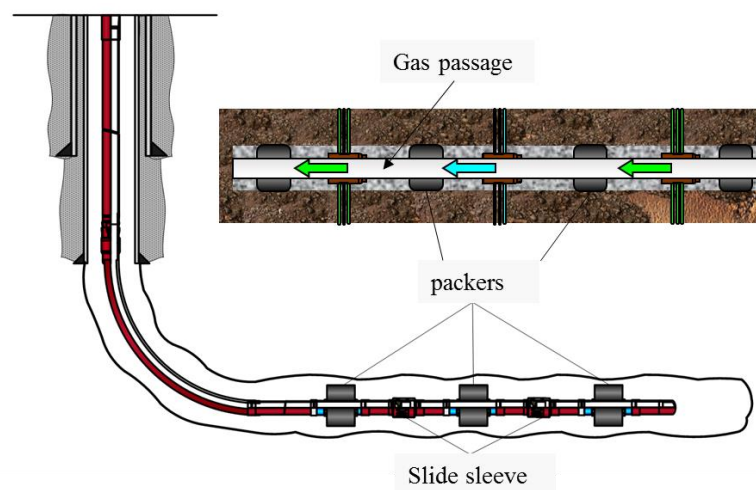


Fig.1 Work mechanical of packer rubber


In the sealing process of conventional packer, the pressure head goes down firstly, the middle support ring moves down, and the rubber ring will be extruded. If the force is too large, plastic deformation will occur, and the elastic deformation will be lost in the process of bottom hole sealing for a long time. The chamfer position of the pressure ring and support ring here will cause the rubber cylinder to protrude, which is more prone to failure and may not necessarily occur in the contact position, but this structure

helps to fix the rubber cylinder. There is a "mutation" area, which is prone to failure or shedding, as shown in Fig.2.




Fig.2 Failure cases of rubber packer

The retrievable packer studied in this paper is a mechanical seating packer. It is a recyclable packer. The packer with two-way slips can be seated in tension, compression or medium state, and can withstand the pressure difference from top to bottom. The design of large bypass holes in packer can reduce swabbing effect during downloading and recycling, and automatically close when tool is seated. When the packer is unpacked, the bypass hole is opened firstly, the upper and lower pressure is balanced, and the upper slip is released. The slip release device on the packer can reduce the resistance of the recovery tool. A schematic diagram of the structure of the preferable packer studied as shown in Fig.3 in this paper.

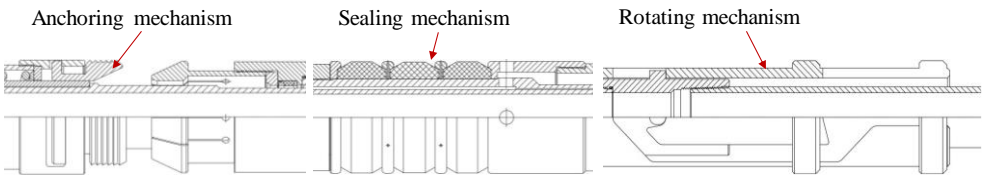

(a) Two-dimensional assembly diagram of retrievable packers

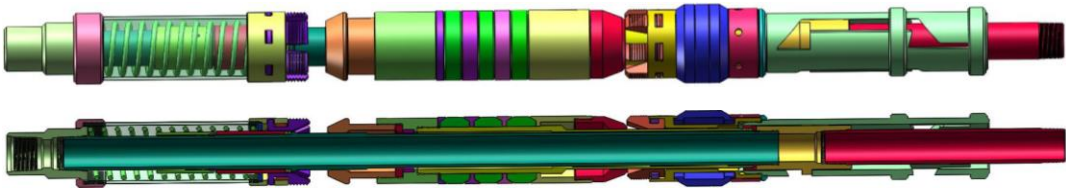

(b) Three-dimensional assembly of retrievable packers

Fig.3 Structural schematic diagram of retrievable packer

of high temperature and high pressure

The retrievable packer needs to be completed by using the sealing element under the external force. The sealing element acts under the action of the axial force to seal the annular clearance and prevent the passage of high-pressure mud. As the key core component of the retrievable packer, the elastic seal body is made into a cylinder shape and also becomes a rubber cylinder.

3. Sealing structure design and finite element calculation

3.1. Force analysis of rubber cylinder

The rubber cylinder does not bear the corresponding axial force and torque during the normal lowering process. When the pressure of rubber cylinder reaches a certain value, the seat shear nails connecting the inner sleeve and the upper jacket of the packer are cut off. The packer begins to realize the seat seal [19]. The outer sleeve starts to slide and compress the rubber cylinder under the gravity of the upper tube pipe itself, so that the rubber cylinder is compressed and expanded, thus the rubber cylinder is compressed and expanded. Contact with external casing can realize the sealing function of outer annulus of tube pipe. The implementation process is shown in Fig. 4.

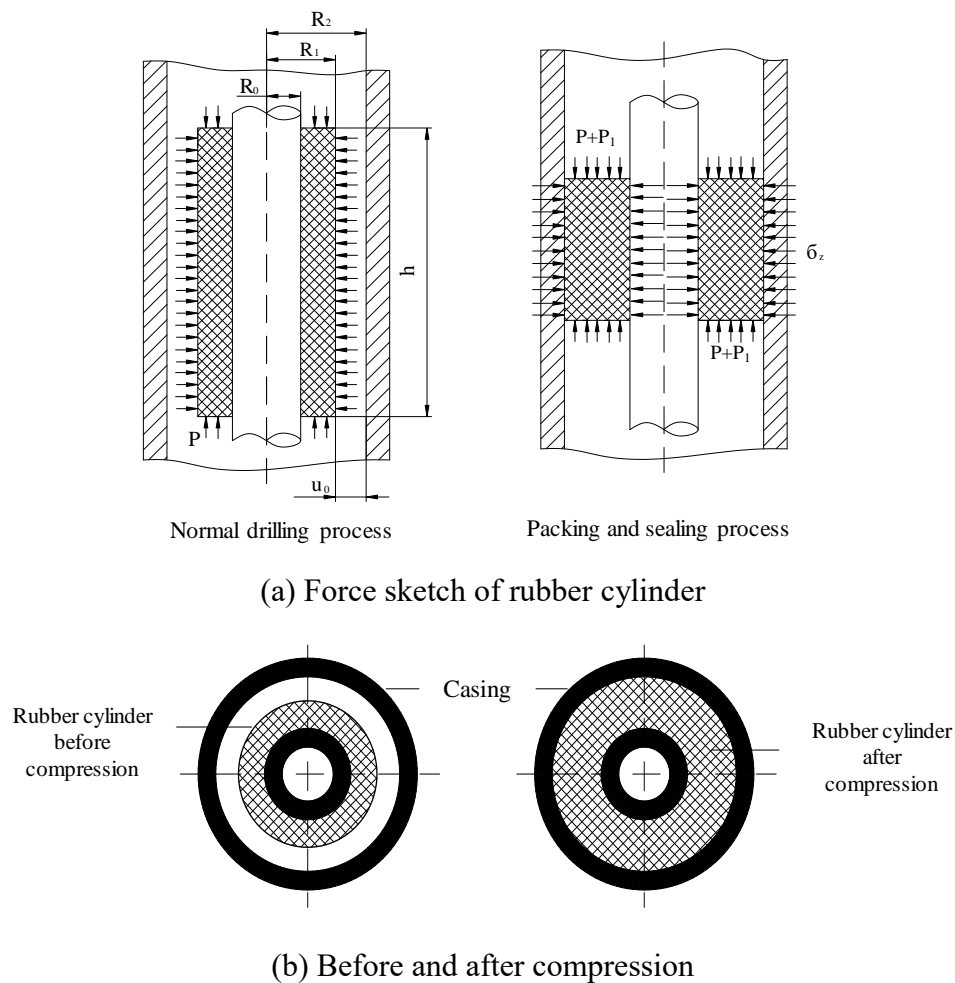


Fig.4 Force sketch and cross-section of rubber cylinder

before and after compression

3.2. Shape and dimension design

The determination of the height of rubber cylinder mainly considers the shear effect of the compression rubber cylinder of the packer. When the compression rubber cylinder is working in the downhole stratum, the shear effect is caused by the sealing pressure difference between the top and bottom of the rubber cylinder. The shear effect diagram is shown in Fig. 5.

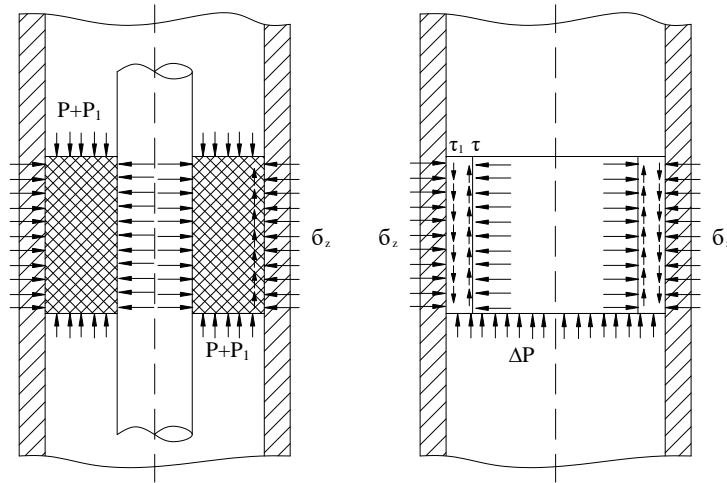


Fig. 5 Shear effect diagram after sealing of rubber cylinder

The shear stress generated after the seating can be calculated according to the following equilibrium equation [19]:

$$2\pi R_2 h \sigma_r \Big|_{r=R_2} f + 2\pi R_1 h \tau = \Delta P \pi (R_2^2 - R_1^2) \quad (1)$$

From formula (1):

$$h = \frac{\Delta P (R_2^2 - R_1^2)}{2R_1 [\tau] + 2R_2 f \frac{P_1 \mu}{1 - \mu}} \quad (2)$$

In the formula: $[\tau]$ —Permissible Shear Stress of Compressed Rubber cylinder Material; f —Friction Coefficient between Rubber Tube and Wellbore.

NBR is used as the material of compression rubber cylinder. Because rubber is a non-linear elastic material, the different formulations of rubber have a great influence on the properties of rubber material.

The properties of standard samples of vulcanized nitrile-butadiene rubber were tested under different temperatures and pressures. Finally, the parameters of rubber material were determined, and the allowable shear stress and shear stress of rubber material were obtained [19,20]. The relevant data are as shown in Table 1.

Table 1 Height of rubber cylinder under different permissible
shear stress and friction coefficient (f)

τ /MPa	f								
	0.1	0.15	0.2	0.25	0.3	0.35	0.4	0.45	0.5
1	152	109	85	70	59	51	45	40	37
2	138	101	80	66	57	49	44	39	36
3	126	95	76	64	55	48	42	38	35
4	116	89	72	61	53	46	41	37	34

According to Table 1, it can be seen that the height of rubber cylinder will change significantly with the difference of allowable shear stress and friction coefficient of rubber. Fig.6 shows that when the allowable shear strength is constant, the height of rubber cylinder decreases gradually with the increase of friction coefficient, and the slowdown trend decreases gradually. Under the same friction coefficient, the higher the allowable shear stress of rubber material, the smaller the height of rubber cylinder. When the friction coefficient is greater than 0.3, the permissible shear strength of the rubber cylinder has little effect on the height.

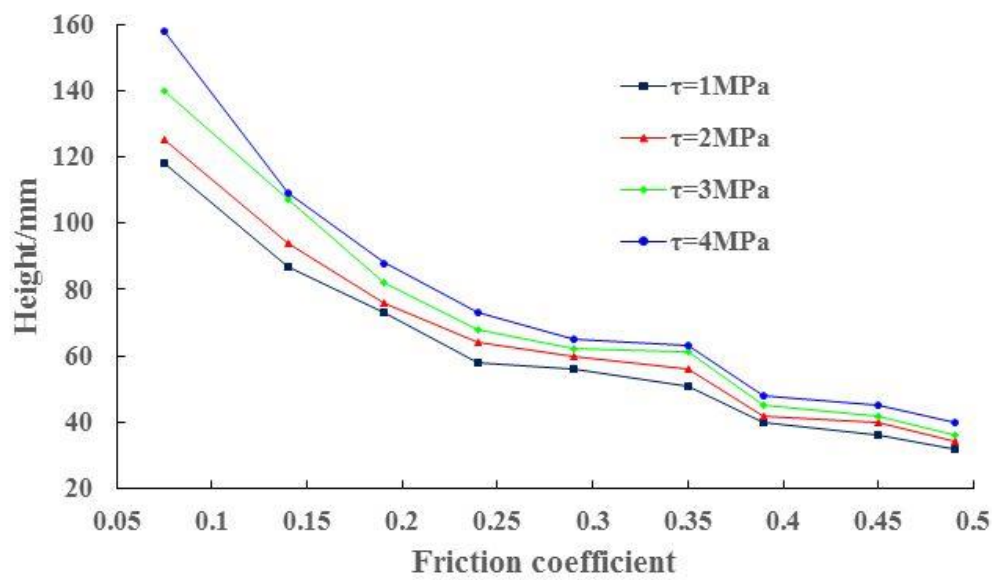


Fig. 6 The height of rubber cylinder varies with shear stress

under different friction coefficients

3.3. Calculation of sealing force of rubber cylinder seat

Compressive rubber cylinder deformation analysis is completed in two stages. The first stage is the process from rubber cylinder deformation to contact wellbore, and the second stage is the process of increasing load after rubber cylinder contact to make it more close to the wellbore. In the first stage, it is assumed that the radial deformation is symmetrically distributed throughout the height, and the volume compression of the rubber cylinder does not exceed the elastic limit of the rubber material. The differential equation can be obtained by removing the higher order differential terms.

$$(1 + \varepsilon_z) \frac{\partial u}{\partial r} + (1 + \varepsilon_z) \frac{u}{r} = -\varepsilon_z \quad (3)$$

The general solution of equation (3) can be obtained:

$$u = \frac{-\varepsilon_z r}{2(1 + \varepsilon_z)} + \frac{\psi_1(z)}{r} \quad (4)$$

$\psi_1(z)$ can be obtained by the following boundary conditions.

$$r = R_0, \quad u = 0; \quad \text{in that way: } \psi_1(z) = \frac{\varepsilon_z R_0^2}{2(1 + \varepsilon_z)}$$

The maximum allowable clearance equation can be obtained by introducing $\psi_1(z)$ in to equation (4):

$$u = \frac{\varepsilon_z}{2(1 + \varepsilon_z)} \left(\frac{R_0^2}{r} - r \right) \quad (5)$$

ε_z can be obtained by the following boundary conditions:

$$r = R_1, \quad u = u_0; \quad \text{in that way: } \varepsilon_z = \frac{2u_0 R_1}{R_0^2 - R_1^2 - 2u_0 R_1} \quad (6)$$

Since the axial deformation of rubber used in rubber cylinder seals must be less than the allowable axial deformation, the following relationship exists:

$$\varepsilon_z = \frac{2u_0 R_1}{R_0^2 - R_1^2 - 2u_0 R_1} < [\varepsilon] \quad (7)$$

In the formula, $[\varepsilon]$ is the relative axial deformation allowed for the rubber cylinder, %; $[\varepsilon]$ can be determined by the test method. Its value mainly depends on the material used in the rubber cylinder and the specific working conditions.

The maximum allowable clearance obtained by formula (7) is:

$$u_{0\max} \leq \frac{[\varepsilon]}{2(100 - [\varepsilon])} \left(R_1 - \frac{R_0^2}{R_1} \right) \quad (8)$$

The corresponding stress values can be obtained according to the generalized Hooke's law.

$$\left. \begin{aligned} -\sigma_r &= \lambda \frac{\varepsilon_z}{1 + \varepsilon_z} - 2G \frac{\varepsilon_z}{2(1 + \varepsilon_z)} \left(1 + \frac{R_0^2}{r^2} \right) \\ -\sigma_\theta &= \lambda \frac{\varepsilon_z}{1 + \varepsilon_z} + 2G \frac{\varepsilon_z}{2(1 + \varepsilon_z)} \left(\frac{R_0^2}{r^2} - 1 \right) \\ -\sigma_z &= \lambda \frac{\varepsilon_z^2}{1 + \varepsilon_z} + 2G \varepsilon_z \end{aligned} \right\} \quad (9)$$

Where, $G = \frac{E}{2(1 + \mu)}$; λ is Lamé coefficient, $\lambda = \frac{E\mu}{(1 + \mu)(1 - 2\mu)}$

In the second stage, the rubber cylinder is close to the wellbore due to the further increase of the load. At this time, the deformation of the rubber cylinder depends on the stiffness of the outer sleeve and the wellbore of the packer. Because the deformation of rubber cylinder does not exceed the yield limit of material, the elastic modulus of three materials (outer sleeve, rubber cylinder and borehole rock) is obviously different, and the radial and circumferential deformation of rubber cylinder after contact with

borehole rock is neglected. Its mathematical expression is as follows:

$$\varepsilon_r = \varepsilon_\theta = 0 \quad (\text{as shown in Fig.5}) \quad (10)$$

According to the generalized Hooke's law, we can find that:

$$\sigma_z = P_1 = \frac{1-\mu}{\mu} \sigma_r \Big|_{r=R_2} \quad (11)$$

In order to ensure the specific pressure (P_1) on the end face of sealing cylinder under the action of pressure difference ΔP , the relationship between radial specific pressure and ΔP , $P_1=f(\Delta P)$, which can effectively seal, can be determined according to the experimental method: $\sigma_r|_{r=R_2} \geq P_1$.

According to the force analysis of the front compressed rubber cylinder, the total specific pressure applied on the sealing rubber cylinder is the sum of the axial force of rubber cylinder of the two stages, that is:

$$P^* = P + P_1 = \frac{\lambda \varepsilon_z^2}{1 + \varepsilon_z} + 2G\varepsilon_z + \frac{1-\mu}{\mu} \sigma_r \Big|_{r=R_2} \quad (12)$$

From the above formula, it can be seen that the axial load affecting the packer is mainly related to the pressure difference of the packer seal, the original clearance between the sealant cylinder and the seat casing, and the size of the rubber cylinder itself.

3.4. Material constants and constitutive relations of NBR

In this paper, the material used in rubber cylinder is NBR. The rubber material used in NBR is suitable for Yeoh model (reduced polynomial hyperelastic model). The stress-strain data of rubber material at all temperatures are brought into ABAQUS finite element analysis software for fitting. In the process of fitting, the Yeoh model is selected

to judge after fitting [21]. The material constants of Yeoh model rubber at five temperatures can be obtained as shown in Table 2.

Tab.2 Material constants of Yeoh model for two rubber materials
at five temperatures

Material Constants	C_{10}/Pa	C_{20}/Pa	C_{30}/Pa
7-30	939840.85	284971.93	79314.0152
7-60	2539782.67	-1816140.36	1246021.2
7-90	1804782.6	-534617.057	560936.07
7-120	1692499.74	-489353.895	918409.019
7-150	1755887.92	-576447.31	897236.305
8-30	1455627.61	131108.146	929565.95
8-60	1438504.43	-342433.01	1202324.23
8-90	1987618.3	-989854.139	2064562.35
8-120	2038447.57	-808712.075	1754438.74
8-150	2001848.94	-526508.69	1453226.66

As a strain energy function, Gregory believes that Mooney-Rivlin model does not take enough high-order terms into account, so the theoretical results of its prediction are quite different from the experimental data [20-22]. Therefore, a third-order expression is proposed:

$$W = C_{10}(I_1 - 3) + C_{01}(I_2 - 3) + C_{20}(I_1 - 3)^2 + C_{11}(I_1 - 3)(I_2 - 3) + C_{30}(I_1 - 3)^3 \quad (13)$$

The research shows that $\frac{\partial W}{\partial I_2}$ is far less than $\frac{\partial W}{\partial I_1}$ and approximately equal to zero.

So Yeoh assumes $\frac{\partial W}{\partial I_2}$ is zero. Formula (13) derives from I_2 by taking partial derivation:

$$W = C_{10}(I_1 - 3) + C_{20}(I_1 - 3)^2 + C_{30}(I_1 - 3)^3 \quad (14)$$

Mooney-Rivlin model can better reflect the stress and strain of rubber under tensile deformation, but it is difficult to describe other deformation, especially compression

deformation. Therefore, this paper intends to use Yeoh model to complete the finite element analysis of rubber cylinder.

3.5. Analysis model of the packer rubber cylinder

In order to verify the seating performance and pressure-bearing capacity of the sealing part of the retrievable packer, theoretical calculation and experimental study are needed. The following are the model of the sealing part of the retrievable packer and the basic size parameters of the packer rubber cylinder.

In this paper, two types of rubber cylinders, 65mm and 92mm, are selected in the analysis process. In the first group, the inner diameter of the rubber cylinder is 104.6 mm, the outer diameter of the rubber cylinder is 146 mm, the length of the single rubber cylinder is 65 mm, the outer diameter of the upper and lower pressure ring is 140 mm, the inner diameter of the upper and lower pressure ring is 102 mm, the seating pressure is 25 MPa, and the inner diameter of the seating casing is 166.5 mm as shown in Fig. 7. In the second group, the inner diameter of the rubber cylinder is 104.6 mm, the outer diameter of the rubber cylinder is 146 mm, the length of the single rubber cylinder is 92 mm, the outer diameter of the upper and lower pressure ring is 140 mm, the inner diameter of the upper and lower pressure ring is 102 mm, the seating pressure is 25 MPa, and the inner diameter of the seating casing is 166.5 mm. Friction coefficient between rubber cylinder and seating section has a great influence on the process of force analysis of rubber cylinder. In this paper, the force and deformation of rubber cylinder with friction coefficient of 0.1, 0.2, 0.3, 0.4 and 0.5 are analyzed respectively.

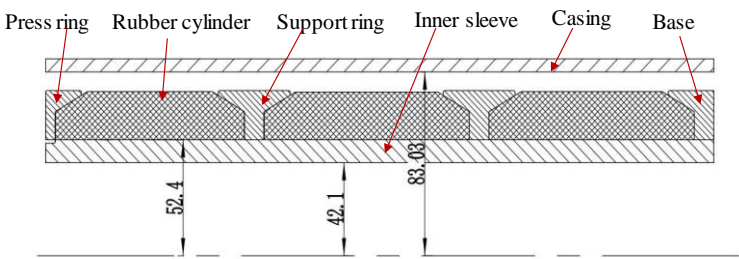


Fig.7 Structure dimensions of sealing parts

Because the main analysis of the deformation of rubber cylinder is that the separating ring and adjusting ring belong to alloy steel and the elastic modulus is relatively large, so this paper sets the separating ring and adjusting ring as rigid body. According to the structure and size of rubber cylinder at assembly state, the contact pair between rubber cylinder and metal parts is established. The outer cylinder and the inner cylinder are fixed equally, and the lower adjusting ring is fixed equally. Fixed, the upper adjusting ring establishes the reference point for loading. The finite element model and loading model of rubber cylinder are shown in Fig.8.

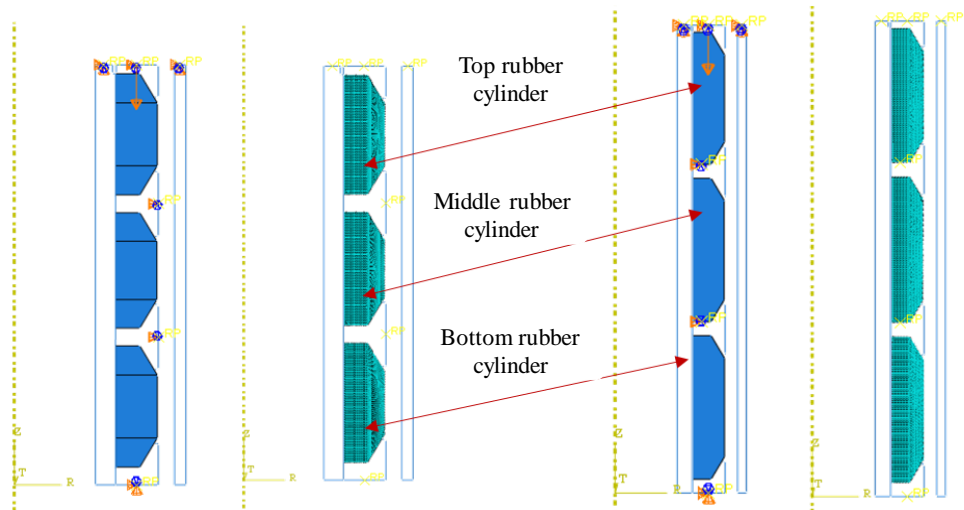


Fig.8 Rubber cylinders and finite element models

3.6. Analysis of results

Assuming that the temperature is 150 °C in the well of 5000m and the

hardness of rubber material is 70, Fig. 9 and Fig. 10 are von Mises stress contours of two length rubber cylinder models with friction coefficient of 0.3 and loading displacement of 40 mm.

When the temperature is 150°C in the downhole and the hardness of rubber material is 70 as shown in Fig. 9, the rubber cylinder gradually decreases and expands with the increase of time. The faster the deformation time of rubber cylinder increases, the faster the deformation of rubber cylinder begins to occur. The first rubber cylinder that contacts seals is the first rubber cylinder. For $t=7\text{s}$, the middle and lower rubber cylinders begin to contact with the casing. It is found that the maximum stress of the three rubber cylinders is in the position where the ring and the rubber cylinder are extruded. It is easy to fail here. When $t=9\text{s}$, the maximum stress is 50.85 MPa. The first rubber cylinder is subjected to the greatest stress and the most serious deformation.

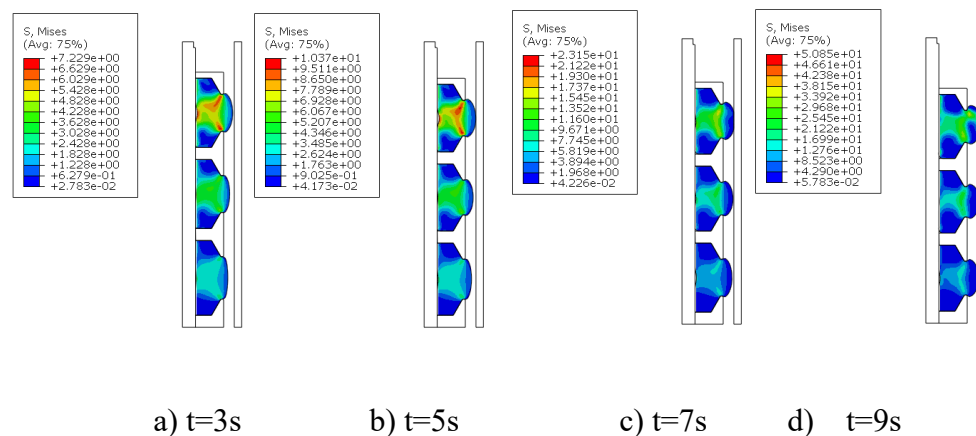


Fig.9 Stress change of short rubber cylinder at different times of seating

Fig.10 shows that the maximum von Mises stress of the rubber cylinder is 162.4 MPa when the length of the rubber cylinder is 92 mm, and it occurs in the upper part of the outer surface of the rubber cylinder, and the phenomenon of stress concentration is obvious. When the pressure is large enough, the region deforms and fails firstly, and

the phenomenon of "protrusion" of the rubber cylinder occurs. In addition, the larger stress area occurs on the inner surface of the rubber cylinder. In the middle area, the stress distribution on the inner surface of the rubber cylinder is "small at both ends and large in the middle". After compression, the deformation presents a "lunar" distribution. The rubber cylinder deforms to the same side, and the middle deformation is the largest. When the displacement is the same, the von Mises stress of the short rubber cylinder is larger than that of the long rubber cylinder. At the same time, it can be found that when the displacement is not large enough, the rubber with the height of 92 mm does not contact the borehole wall.

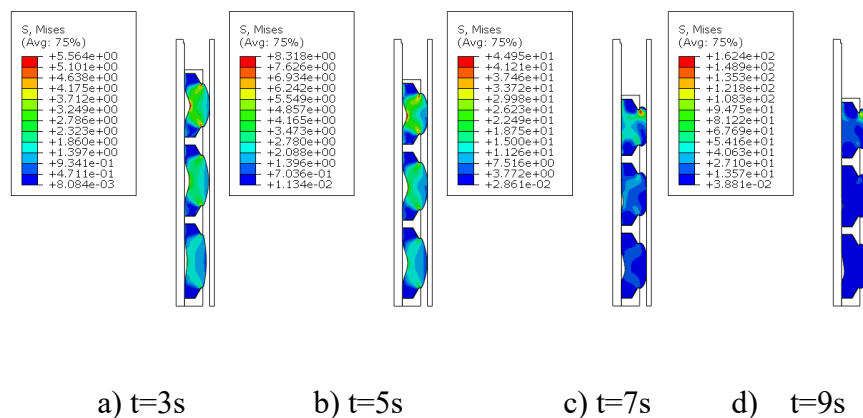


Fig.10 Stress change of long rubber cylinder at different times of seating

From the Fig. 11, it can be seen that there is no linear relationship between the increase of contact pressure and the increase of loading displacement. When the loading displacement is 45 mm, the contact pressure in the upper cylinder sealing area is 4.4-9.4 MPa, the contact pressure in the middle cylinder sealing area is 2.2-3.8 MPa, while the pressure in the lower cylinder sealing area is 0.8-1.7 MPa, and the contact pressure in the upper cylinder sealing area is 4.4-9.4 MPa. The contact pressure is greater than the contact pressure of the middle rubber cylinder, and the contact

pressure of the middle rubber cylinder is greater than the contact pressure of the lower rubber cylinder. The contact pressure difference between the three rubber cylinders increases with the increase of loading displacement. When the loading displacement is small, the contact pressure in the sealing area of the three rubber cylinders does not change much, and the contact pressure of the three rubber cylinders varies from 0.3 to 1.1 MPa.

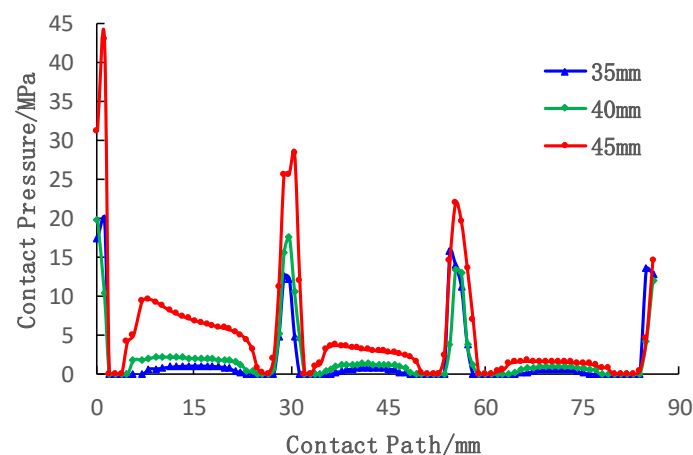


Fig.11 Change curves of contact pressure under different displacements

It can be seen that the greater the friction coefficient is, the greater the maximum contact pressure on the rubber cylinder is as shown in Fig.12. The contact pressure in the sealing area of the upper, middle and lower rubber cylinders increases with the increase of the friction coefficient. The contact pressure of the upper rubber cylinders increases the most, while the contact pressure of the middle rubber cylinders and the lower rubber cylinders increases little with the increase of the friction coefficient. It can be inferred that the top rubber cylinder plays the main role in the sealing process between the wellbore and the rubber cylinder of the removable packer.



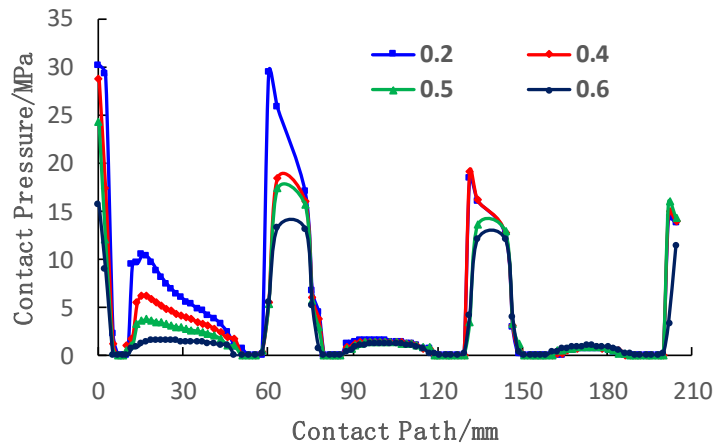


Fig.12 Change curves of contact pressure under different friction coefficients

According to Fig. 13, the contact pressure of the two hardness rubber cylinders is the largest at 60 °C, the smallest at 30 °C, and the contact pressure is little affected by temperature at 90 °C , 120 °C and 150 °C . In high temperature wells with temperature reaching a certain value, the contact pressure is gradually weakened due to the change of mechanical properties of rubber materials caused by temperature change. As the temperature increases with the increase of wellbore structure, it can be considered that the sealing contact pressure of preferable packers is affected by temperature in deep and ultra-deep wells. The effect is small, but the effect of temperature is large when sealing is carried out in shallow wellbore.

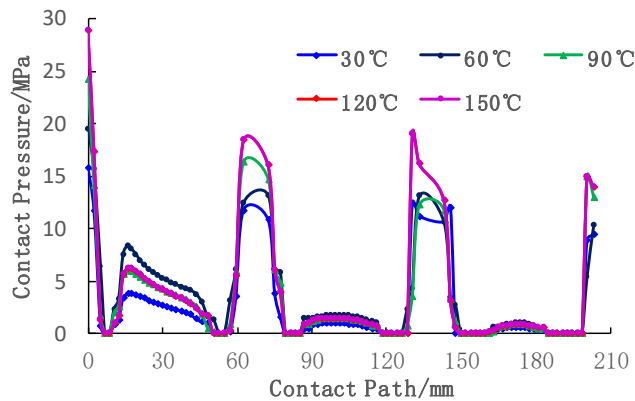

(a) The hardness of the rubber cylinder is 80

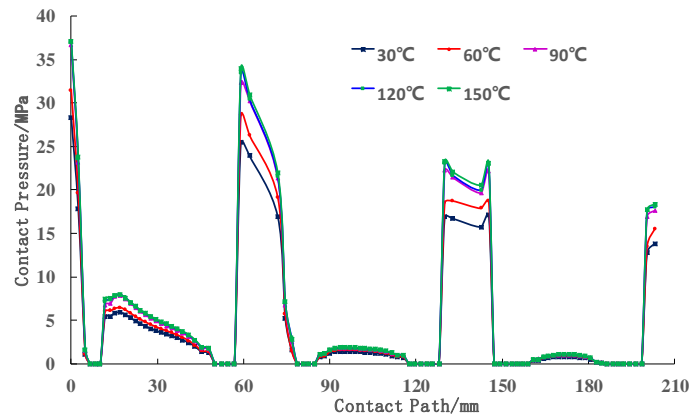

(b) The hardness of the rubber cylinder is 80

Fig.13 Tendency diagram of contact pressure at different temperatures and hardness

In order to verify the sealing performance of the rubber cylinder, the working pressure difference can be withstood. It is necessary to verify the specific pressure of the rubber cylinder. If the specific pressure is too low, the sealing surface will be detached and the sealing performance will be unstable. If the specific pressure of the seal is too high, the contact surface may be damaged because of friction. In the design of sealing structure, there are detailed standards for the specific pressure of rubber. For rubber with medium hardness, the formula for calculating the specific pressure of rubber is [23, 24], as shown in equation (15).

$$Q_{MF} = (0.4 + 0.6PN) / \sqrt{\frac{b_M}{10}} \quad (15)$$

In the formula, Q_{MF} is specific pressure of middle seal; PN is the working pressure difference, MPa; b_M is effective length of seal, mm.

Through the discussion of the factors affecting the contact pressure, it can be seen that the contact pressure at the sealing location is greatly affected by the loading displacement and friction coefficient. In this paper, the length of the rubber tube is 60

mm, the friction coefficient between the borehole wall and the rubber cylinder is 0.3, the temperature at the bottom of the well is 150 °C, and the loading displacement is 45 mm. The effective contact length and average contact pressure are calculated by using the extracted contact pressure. By comparing the contact pressure and sealing specific pressure, it is determined whether the rubber cylinder can seal the pressure difference of 35 MPa. The effective contact length of rubber cylinder is 136 mm, and the average contact pressure is 6.1 MPa. The calculation of sealing specific pressure is as follows:

$$Q_{MF} = (0.4 + 0.6 \times 35) / \sqrt{\frac{136}{10}} = 5.8 \text{ MPa} \quad (16)$$

From the above calculation, it can be seen that the average contact pressure is greater than the sealing specific pressure. Because the friction coefficient between borehole wall and sealing rubber, that is, the friction coefficient between rubber and rock is generally greater than 0.3, the above calculation is safe. When the contact pressure is large enough, the rubber will be destroyed when the allowable specific pressure of NBR is larger than that of NBR. Therefore, when keeping the pressure difference between upper and lower rubber seals safe and effective, the height of rubber tube can be increased appropriately, and the effective sealing length between rubber tube and wellbore can be increased. When the length of rubber tube is too long, the contact pressure will be affected. Because of its size, the length of rubber cylinder is not easy to increase too long on the basis of 60mm.

4. Study on optimization of seal structure size

According to the design theory of packer rubber cylinder, the influence of rubber

cylinder chamfer on the force of rubber cylinder is greater. The existing theory and experimental verification show that when the rubber cylinder chamfer is $30^{\circ}\sim 50^{\circ}$, it is easy to produce "protrusion" phenomenon, which minimizes the stress concentration of rubber cylinder. In this paper, the rubber cylinder chamfer is 45° . In the design of rubber cylinder assembly, the height of upper and lower rubber cylinders is the same, and the height of middle rubber cylinders is less than that of upper and lower rubber cylinders [25]. The design size diagram of rubber cylinder is as shown in Fig. 14.

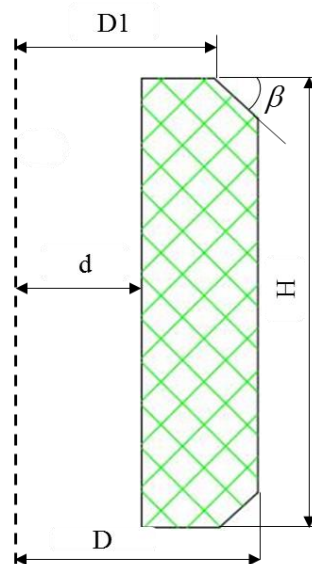


Fig. 14 The design size diagram of rubber cylinder

4.1. Height optimization of rubber cylinder

According to the relevant literature, the height of upper and lower rubber cylinders is the same in the design of rubber cylinder assembly, and the height of middle rubber cylinders is less than that of upper and lower rubber cylinders.

(1) Height optimization of upper and lower rubber cylinders

For upper and lower rubber cylinder materials, the height H of rubber cylinder is taken as design variable under the condition of inclination angle of 45° of rubber

cylinder and seating load of 70 KN. The height of rubber cylinder varies from 20 mm to 170 mm.

The maximum stress on the contact surface between the rubber cylinder and the inner wall of the casing is extracted and the curve of the maximum contact pressure between the rubber cylinder and the casing with the height of the rubber cylinder is obtained. As shown in Fig.15.

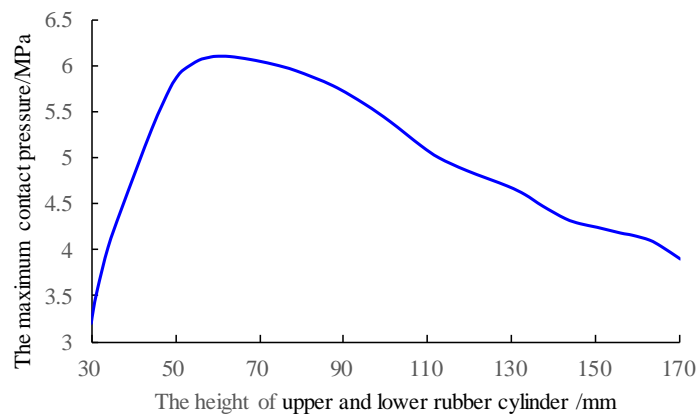


Fig.15 The relationship between the maximum contact stress and the height of rubber cylinder

According to Fig.15, it can be seen that when the height of the rubber cylinder is 20 mm, only one part of the rubber cylinder after deformation contacts with the inner wall of the casing. From height of 30 mm to 60 mm, the maximum contact pressure increases obviously with the increase of height, and the contact length between rubber cylinder and casing also increases, the sealing effect increases significantly, but the shoulder has the trend of outflow; from 60 mm to 170 mm height, with the increase of height, the maximum contact pressure decreases accordingly. Starting from 70 mm, the gap between the inner wall of the rubber cylinder and the central tube is large and not compacted, which reduces the sealing effect and aggravates the shoulder protrusion. In

conclusion, in order to improve the sealing performance of rubber cylinders, the height of upper and lower rubber cylinders should be preferentially selected about 60 mm.

(2) Optimizing the height of middle rubber cylinder

Under the condition of camber angle of 45° and 70 KN seating load, the height of middle rubber cylinder is taken as design variable, and the height H varies from 20 mm to 160 mm.

The maximum stress on the contact surface between the rubber cylinder and the inner wall of the casing is extracted and the curve of the maximum contact pressure between the rubber cylinder and the casing with the height of the rubber cylinder is obtained, as shown in Fig.16.

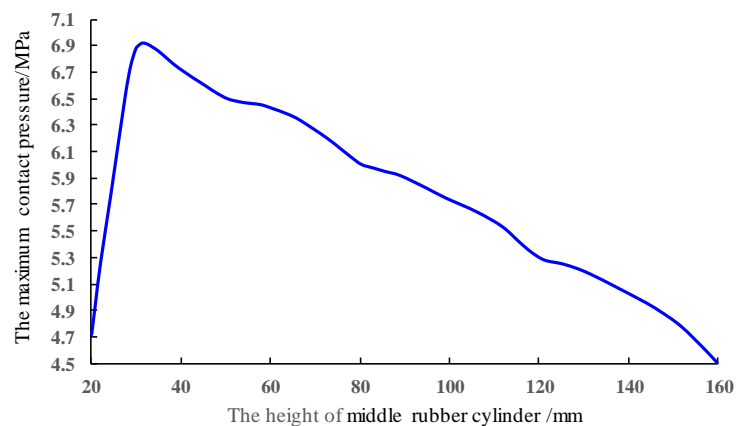


Fig.16 The relationship between the maximum contact stress and the height of rubber cylinder

It can be seen that when the height of the rubber cylinder is 20 mm as shown in Fig.16, the axial compression deformation of the rubber cylinder is relatively small, and the contact length between the rubber cylinder and the casing is relatively small, thus the contact pressure is relatively small; when the height of the rubber cylinder increases to 30 mm, the contact pressure increases significantly, which makes the sealing effect

better. From 30 mm to 160 mm, the maximum contact pressure decreases with the increase of height, the sealing effect decreases, and the rubber cylinder is not compacted from 100 mm. In addition, the shoulder protrusion phenomenon is also serious with the increase of height. Because the heights of 30 mm and 40 mm are relatively short, although the contact pressure is relatively large, it is easy to crush when the load increases. When the rubber cylinder is 50 mm, the rubber cylinder is compacted and the sealing pressure is large, so the sealing effect is better. In summary, the height of the middle rubber cylinder is about 50 mm.

4.2. Thickness optimization of rubber cylinder

Under the condition of camber angle of 45° and 70 KN seating load for single rubber cylinder, the height of rubber cylinder is taken as design variable, and the height H varies from 20 mm to 160 mm.

The maximum contact pressure between the rubber tube and the casing with different thicknesses through analysis is obtained as shown in Fig. 17.

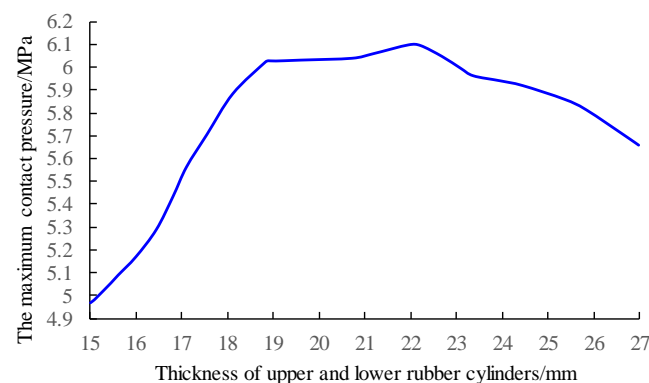


Fig.17 The relationship between the thickness of upper and down rubber cylinders and the maximum contact pressure

From Fig.17, it can be seen that from 15 mm to 21 mm, the maximum contact

pressure increases obviously with the increase of thickness, and the rubber cylinder is compacted, the sealing effect is improved significantly, the shoulder protrusion degree is also increased, but there is little difference, and within a reasonable range; from 21 mm to 25 mm, the maximum contact pressure follows with the increase of thickness. With the decrease of thickness, the sealing effect decreases, and the degree of shoulder protrusion decreases, but the effect is not significant. Generally speaking, the thickness of upper and lower rubber cylinders should be about 21 mm.

4.3. Effect of external conditions on sealing performance of packers

4.3.1. Effect of sealing load on sealing performance of rubber cylinder

For the optimized rubber cylinder seal assembly, the force generated by the contact between rubber cylinder and casing is simulated by numerical simulation software. The upper and lower ends of casing and central pipe (tubing) are fixed, and the lower diaphragm ring is fixed. The seating pressures of 10 kN, 20 kN, 30 kN, 40 kN, 50 kN and 60 kN are applied to the upper diaphragm ring respectively. The variation curves of Fig.18 are obtained by analysis. It can be seen that the maximum contact pressure between the rubber cylinder and the casing increases linearly with the increase of the seating load when the seating force is greater than 30 kN.

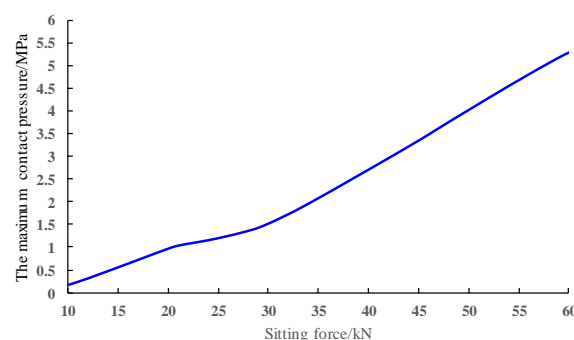


Fig.18 The maximum contact pressure curve of rubber cylinder under different loads

4.3.2. Effect of different Annulus sizes on the sealing performance of rubber cylinders

For the optimized packer, the size of annular space gap is different when the casing type is different. Then the influence of annular gap on the performance of packer is simulated by finite element software. The annular space gap (the space of inner diameter of casing and outer diameter of rubber cylinder) is 1 mm, 2 mm, 3 mm, 4 mm, 5 mm, 6 mm, 7 mm and 8 mm, respectively. Through analysis, the variation curves between the annular space gap of different casing and the maximum axial compression of rubber cylinder are obtained, as shown in Fig. 19

From Fig.19, it can be seen that with the increase of the gap between the inner diameter of casing and the outer diameter of rubber cylinder, the maximum axial compression of rubber cylinder has a significant change. Because the middle rubber cylinder is relatively soft, when the gap is 7 mm, the inner side of the middle rubber cylinder begins to appear larger deformation, which is very disadvantageous and seriously affects the life of rubber cylinder.

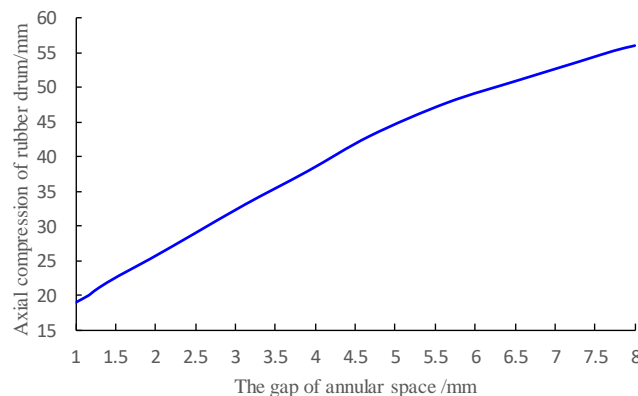


Fig.19 The maximum axial compression curve of rubber cylinder

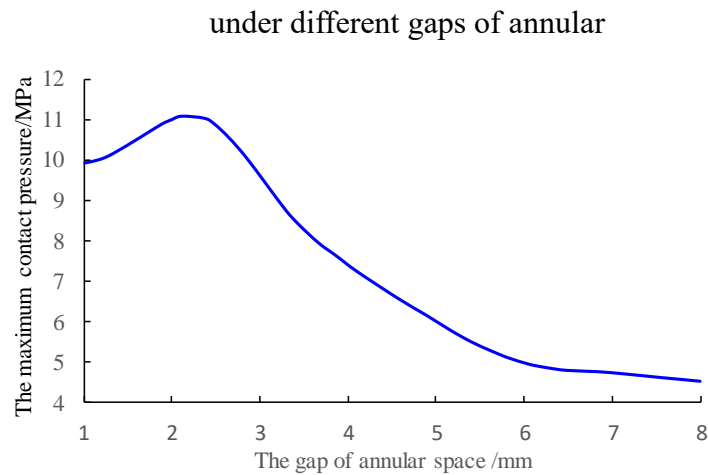


Fig.20 The maximum contact pressure curve of rubber cylinder

under different gaps of annular

It can also be seen from Fig. 20 that when the annular space gap is less than 7 mm, the upper rubber cylinder plays the main role of sealing. When the annular space gap is greater than 7 mm, the contact pressure of the middle rubber cylinder begins to be greater than that of the upper rubber cylinder, and begins to play the sealing role together with the upper rubber cylinder.

In summary, different annular space gap size, in other words, different casing type or different packer outer diameter will affect the sealing performance of packer. Considering the service life of the rubber cylinder, the annular space gap should not exceed 7 mm, so the upper rubber cylinder plays the main sealing role; considering the sealing effect, it is obvious that the contact pressure of the annular space gap is the greatest around 2 mm, so the effect is the best. At the same time, the maximum Mises stress of the rubber cylinder is smaller when the gap is about 2 mm, which can better guarantee the rubber cylinder's performance. Therefore, the optimal annular space gap of this kind of packer is about 2 mm.

The results show that the sealing performance of packer is better when the inclination angle of rubber cylinder is 45 and the height of upper and lower rubber cylinder is 60 mm, the height of middle rubber cylinder is 50 mm, and the thickness of rubber cylinder is 21 mm. With the increase of seating load, the contact pressure between rubber cylinder and casing increases continuously. The maximum contact pressure of rubber cylinder increases with the increase of annular space gap. It shows the trend of first increasing and then decreasing, and reaches the maximum when the gap is about 2 mm.

This provides a theoretical basis for the preliminary seating of the structural dimensions of rubber cylinders by analyzing the stress situation of rubber cylinders. Initially, the inner diameter of the rubber cylinder is 104mm, the outer diameter of the rubber cylinder is 146 mm, and the height of the rubber cylinder is 60 mm. The angle of rubber cylinder is 45 and the height of upper and lower rubber cylinder is 60 mm, the height of middle rubber cylinder is 50 mm, and the thickness of rubber cylinder is 21 mm.

5. Test simulation of new packer rubber

This section mainly aims at the pressure bearing capacity and sealing performance test of the new rubber cylinder, using 7" casing (inner diameter 166.1 mm, central diameter 88.5 mm, guide ring outer diameter 144.3 mm), under 150 C, 10000 Psi conditions of sealing pressure.

Test conditions: Simulated test temperature: $150^{\circ}\text{C} \pm 5^{\circ}\text{C}$; Maximum pressure: 10000 Psi; Simulated casing specification: 20 Pounds

Test equipment: Sealing equipment unit: 160T rubber vulcanizer, maximum

pressure: 160T. Pressure accuracy: 1T; Pressure equipment unit: 27000 Psi pneumatic high pressure pump, pressure display accuracy: 200 Psi;

Simulated working unit: Self-designed test tooling for simulated working conditions. System pressure drop: 200Psi/15min, heating unit: self-designed oil bath heater. Temperature control error: $\pm 5^{\circ}\text{C}$, test medium: ISO/TS 16949, the viscosity of high temperature heat conducting oil is - 30CST at 40°C

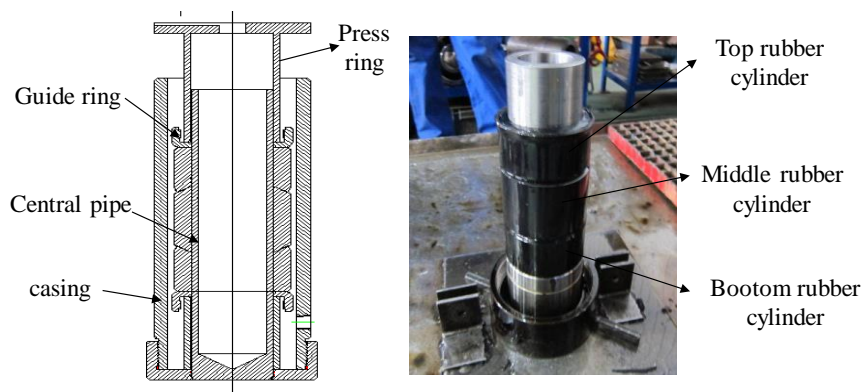


Fig.21 Experimental device of pressure-bearing and physical drawing of rubber sleeve

The whole test process of seal pressure of 7" casing (inner diameter 166.1 mm, central diameter 88.5 mm, guide ring outer diameter 144.3 mm) under 150 and 10000 Psi conditions is as follows:

The assembly parts are tightened everywhere, and then connected with the pressing equipment to test the 1# rubber sleeve as shown in Fig. 21. The seating pressure of 8T is applied slowly, and the pressing test is carried out after 1 minute of pressure stabilization. After 3 minutes of pressure stabilization, the pressure drops to 300 Psi; then the pressure is hit to 4000 Psi, and the pressure drops to 200 Psi after 2 minutes of pressure stabilization. Si; continue to press to 5000 Psi, the pressure drop is 300 Psi after 3 minutes; press to 6000 Psi for 2 minutes, the pressure drop is 200 Psi; continue to press to 7000 Psi for 4 minutes, the pressure drop is 400 Psi, pressure to 8000 Psi for 4 minutes, pressure to 400 Psi, pressure to 900 Psi for 6 minutes, pressure to 400 Psi. I.

After 6 minutes of pressure stabilization to 1000 Psi, the pressure drop was 100 Psi. 2 # rubber sleeve also uses the same experimental process. The curve of two pressing tests is shown in Fig. 22.

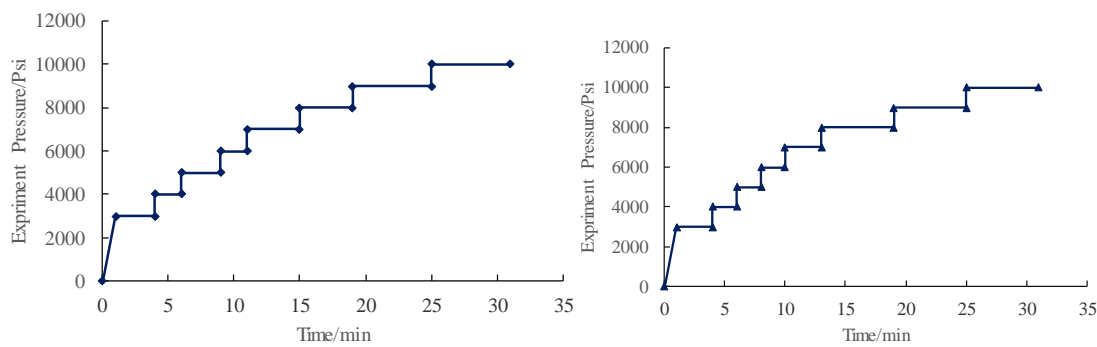


Fig.22 Pressure curves of 1 # and 2 # rubber cylinders

After pressure relief, the elasticity of the rubber sleeve is good, and then the rubber cylinder is taken out. There is a circle of shear marks on the shoulder of the upper rubber sleeve, which is relatively intact as a whole, as shown in Fig. 23.

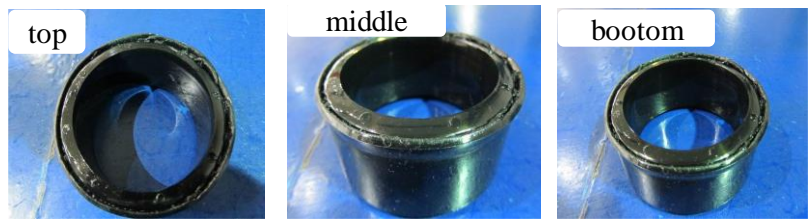


Fig.23 Deformation diagram of 2# rubber sleeve after pressure

6. The whole performance test process of packer

After assembling the removable packer and the pressure testing tooling, the casing is put into the casing as shown in Fig. 25, the pin can be cut by 6 MPa pressure, the seat seal can be started, and then three times of pressure testing are carried out. The pressure is 10 MPa-21 MPa-70 MPa, and the temperature varies between 60 and 140 degrees, respectively. The pressure is stabilized for a certain period of time, and the temperature and seal of the three tests are observed step by step. Pressure, pressure variation law,

seating pressure and pressure are stable in the temperature range. The following is a physical drawing of the assembly equipment and the pressure gauge.

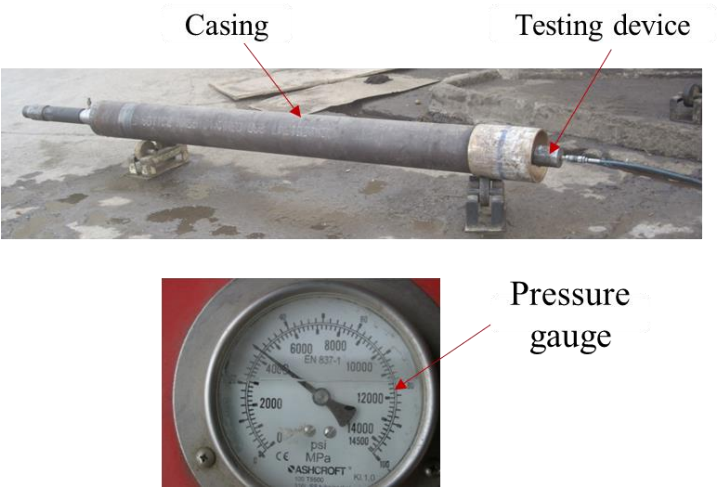


Fig.24 Pressure testing device and pressure gauge

In the first test, it was found from the temperature, seating pressure and bearing pressure curves as shown in Fig. 25. There are bearing pressure stabilization stages in each stage. The temperature drops by about 12 °C, and the temperature drops by about 3 MPa. When the temperature is 112-126 °C, the seating pressure and bearing pressure can be stabilized at about 70-75. MPa, the seating time is 14 minutes, which shows that the sealing performance is stable in this temperature range.

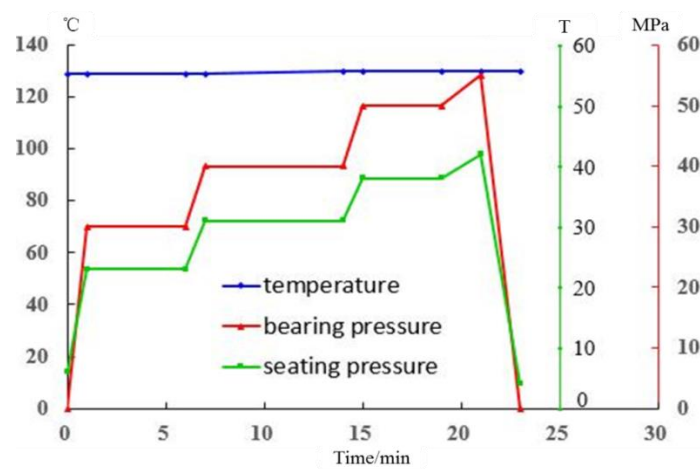


Fig.25 Change curves temperature, seating pressure and bearing pressure

The second test found that the seating pressure and bearing pressure curve found that the seating pressure was lower than the bearing pressure as shown in Fig. 26. The bearing pressure could reach 52.5 MPa when the temperature was 130°C-140°C. The seating pressure was stable at about 18-36 T. The seating pressure was stable, indicating that the sealing performance was stable in this temperature range. There were bearing pressure stabilization stages in all stages, and the temperature was also stable. The bearing pressure can be stabilized at about 52.5 MPa and the seating time is 10 minutes at 132°C. It shows that the sealing performance is stable and the bearing pressure can reach 60 MPa in this temperature range.

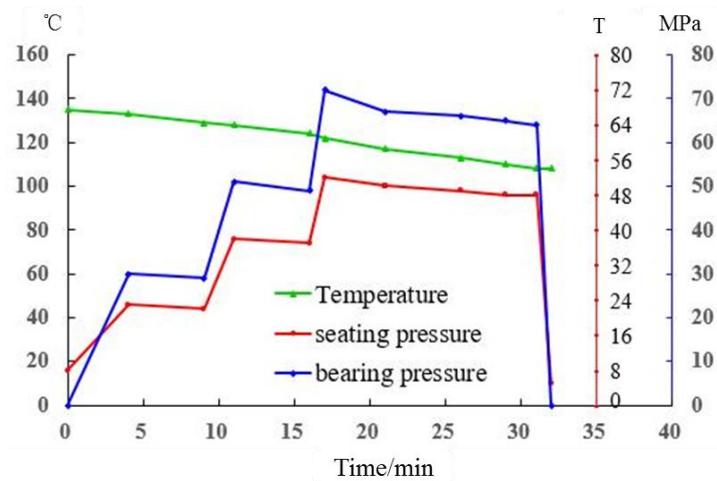


Fig.26 Change curves temperature, seating pressure and bearing pressure

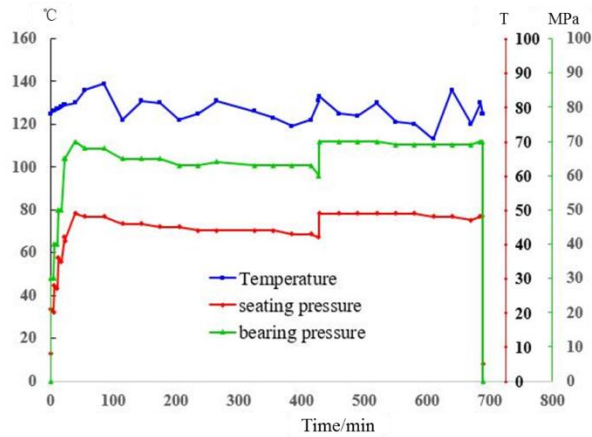


Fig.27 Change curves temperature, seating pressure and bearing pressure

The third test found that the seating pressure and bearing pressure curve found that the seating pressure is lower than the pressure as shown in Fig. 27. The pressure can reach 72 MPa when the temperature is 130-140 °C, the seating pressure is stable at about 15-20 MPa, the seating pressure is stable, the seating and bearing pressure time is 700 minutes, and the temperature varies between 108-140 °C.

7. Conclusions

In this paper, according to the design of the new seal structure, theoretical calculation and experimental research are carried out, and the following conclusions are drawn:

- (1) When the wellbore and the packer are sealed, the upper rubber cylinder is subjected to greater stress under various working conditions, and mainly plays a sealing role.
- (2) Loading displacement, friction coefficient and temperature increase will increase the contact pressure between packer rubber and casing wall, and the average contact pressure is greater than the sealing specific pressure.
- (3) When maintaining the effective pressure difference between the top and bottom of the rubber cylinder, increasing the height of the rubber cylinder appropriately and the effective sealing length between the rubber cylinder and the wellbore.
- (4) Through sealing performance and pressure test, the sealing effect is stable and the elasticity of the rubber sleeve is good, which indicates that the newly designed rubber cylinder can meet the sealing pressure of 150 and 10000 Psi.
- (5) Through three tests, it is found that the bearing pressure can reach 72 MPa, the seating pressure can be stabilized at about 15-20 MPa, the seating pressure and the

holding time can reach 690 minutes, and the sealing performance of the bearing pressure and the bearing pressure can be stable in the temperature range of 108-140 °C.

Acknowledgements

The authors are grateful to financial support from National Natural Science Foundation of China (No. 51974271 and No. 51574198).

Conflicts of Interest: The authors declare no conflict of interest.

References

- [1] Yi-Feng Chen, Ming-Ming Liu, Shao-Hua Hu, et al. Non-Darcy's law-based analytical models for data interpretation of high-pressure packer tests in fractured rocks [J] Engineering Geology 199 (2015) 91–106.
- [2] Patryk Quinn, John A. Cherry, Beth L. Parker Combined use of straddle packer testing and Flute profiling for hydraulic testing in fractured rock boreholes [J] Journal of Hydrology 524 (2015) 439–454.
- [3] Zhi Zhang, Han Wang. Sealed annulus thermal expansion pressure mechanical calculation method and application among multiple packers in HPHT gas wells [J] Journal of Natural Gas Science and Engineering 31 (2016) 692-702.
- [4] Dajiang Zhu, Yuanhua Lin, Huali Zhang, et al. Corrosion evaluation of packer rubber materials in CO₂ injection wells under supercritical conditions [J] Journal of Petroleum Science and Engineering 151 (2017) 311–317.
- [5] Dajiang Zhu, Yuanhua Lin, Huiyun Ma, et al. Experimental studies on CO₂ corrosion of rubber materials for packer under compressive stress in gas wells [J] Engineering Failure Analysis 80 (2017) 11–23.

- [6] X. Li; C. P. Tan; J-C. Roegiers. Effects of Packer on Hydraulic Fractures Initiated from Highly-deviated and Horizontal Boreholes [J] Int. J. Rock Mech. & Min. Sci. Vol. 34, No. 3-4, 1997.
- [7] M. Wanga, P.H.S.W. Kulatilakea, et al. Estimation of REV size and three-dimensional hydraulic conductivity tensor for a fractured rock mass through a single well packer test and discrete fracture fluid flow modeling[J] International Journal of Rock Mechanics & Mining Sciences 39 (2002) 887–904.
- [8] Xiaozhen He, Xinyan Shi, Martin Hoch, et al. Mechanical properties of carbon black filled hydrogenated acrylonitrile butadiene rubber for packer compounds [J] Polymer Testing 53 (2016) 257-266.
- [9] Zheng Tong, Qinyou Ye, Jie Qian, et al. Down-hole isolation towards high-temperature reservoir using packing elements with swellable thermo-plastic vulcanizates [J] Journal of Petroleum Science and Engineering 172 (2019) 964–975.
- [10] Ting Chen, Weiguo Ma, Shaohu Liu, et al. Analysis on mechanical influencing factors of fatigue behavior for the packer on pipe ram in snubbing unit[J] Engineering Failure Analysis 103 (2019) 20–31.
- [11] Joon-Shik Moon. Representativeness of jointed rock mass hydraulic conductivity obtained from packer tests for tunnel inflow rate estimate [J] International Journal of Rock Mechanics & Mining Sciences 48 (2011) 836–844.
- [12] Tang Xin, Qian Bin, Li Bin, et al. Development and application of a packer-type drilling-free liner hanger[J] Natural Gas Industry B 1 (2014) 125-128.
- [13] Zhang Fuxiang, Ding Liangliang, Yang Xiangtong. Prediction of pressure between

packers of staged fracturing pipe strings in high-pressure deep wells and its application

[J] Natural Gas Industry B 2 (2015) 252-256.

[14] Gang Hu, Guorong Wang, Liming Dai, et al. Sealing Failure Analysis on V-Shaped Sealing Rings of an Inserted Sealing Tool Used for Multistage Fracturing Processes [J] energies, 2018,11,1432.

[15] Dan Dobrotă, Gabriela Dobrotă. Reducing of Energy Consumption by Improving the Reclaiming Technology in Autoclave of a Rubber Wastes [J] Energies 2019, 12, 1460.

[16] Kazuki Komatsu, Hao Liu, Mitsuki Shimada, et al. Assessment of Surface Degradation of Silicone Rubber Caused by Partial Discharge [J] Energies 2019, 12, 2756.

[17] Qiao Deng, Hui Zhang, Jun Li, et al. Study of Downhole Shock Loads for Ultra-Deep Well Perforation and Optimization Measures [J] Energies 2019, 12, 2743.

[18] Kazuki Komatsu, Hao Liu, Mitsuki Shimada, et al. Assessment of Surface Degradation of Silicone Rubber Caused by Partial Discharge [J] Energies 2019, 12, 2756.

[19] Wang Hai-lan. Simulating research of working behavior for down-hole packer [D]. Chengdu: Southwest Petroleum University, 2004.

[20]Huang Jian-long, Xie Guang-juan, Liu Zheng-wei. FEA of hyperelastic rubber material based on Mooney-Rivlin model and Yeoh model [J]. China Rubber Industry, 2005, 55(8):467-471.

[21]O H Yeoh. Some forms of the strain energy function for rubber [J]. Rubber

Chemistry and Technology, 1993, 66(5): 754-771.

[22] Jie Zhang, Jingxuan Xie. Investigation of Static and Dynamic Seal Performances of a Rubber O-Ring [J]. Journal of Tribology, 2018, 140(4), 042202.

[23] LONG Lian-chun, DU Jia-zheng, Yang Zhi-gang, et al. Analysis and Optimization of Sealing Rubber of the Packer [J]. Journal of Beijing University of Technology, 2006 (S1):52-57.

[24] Sun Jie, Yang Xianqi. Non-linear Finite Element Analysis on the Factor of Lager Deformation of Assembled Seal Rings with Compound Material [J]. Lubrication Engineering, 2006(4):123-132.

[25] Yang Chunlei, Li Bin, Zheng Xu, et al. The evaluation of sealing and reliability of packer rubber based on working temperature [J]. Chinese Journal of Applied Mechanics, 2017, 34(6):1079-1085.