

Highly Molybdenum-Alloyed Materials Hastelloy BC-1 (2.4708) and B3 (2.4600): Diffusion Bonding Experiments and Evaluation of both Mechanical Behavior and Corrosion Resistance in hot 70 % Sulfuric Acid

Thomas Gietzelt*¹, Mario Walter², Volker Toth¹, Florian Messerschmidt¹, Ralf Dahm²

[*] corresponding author: *Dr. Thomas Gietzelt, KIT, Institute of Micro Process Engineering*

PoBox 3640, 76021 Karlsruhe

thomas.gietzelt@kit.edu

[1] *Institute for Micro Process Engineering*

[2] *Institute for Applied Materials - Solid and Biomechanics*

Abstract: Sulphuric acid is a widely used raw material in the chemical industry. Its corrosive effect on materials varies considerably, depending on impurities, temperature and water content. Accordingly, good corrosion resistance under all conditions is very difficult to achieve. This is especially an issue for micro process apparatus with very thin walls. Furthermore, such devices are often joint by diffusion bonding what may alter materials properties due to high temperatures and long dwell times. In fact, for each new material, the diffusion bonding parameters must be optimized and the impact on mechanical as well as corrosion properties must be investigated. In this paper, two high molybdenum alloys, namely *Hastelloy B3* and *BC-1*, were evaluated.

Diffusion bonding tests were performed using ten layers of sheet material in between round stock. Corrosion tests were performed in 70 % sulphuric acid at 100°C for 1000 h. Tensile tests on both alloys were carried out for different material conditions, to determine the change in mechanical strength and elongation at fracture values.

In general, independent of the condition of the materials, the fracture behavior of both alloys was found to be ductile and the specimens show the typical dimple structure, in the case of diffusion bonded samples, interrupted by weak spots or rather non-bonded areas. These areas are obviously causing the onset of material failure and thus, a degradation of mechanical properties.

Tensile samples, that were aged in 70% sulphuric acid at 100°C for 1000 hours showed local corrosion attacks at the grain boundaries at the circumferential surfaces and especially at the joining

planes – for *Hastelloy B3* much more pronounced than for *Hastelloy BC-1*. Accordingly, a further decrease of both, the stress- and elongation at fracture values is observed. However, the typical material parameters like 0.2 % yield strength used for dimensioning components are found to be sufficient high, even when operating the materials under such harsh conditions. When concluding the results, at least *Hastelloy BC-1* reveals both sufficient good mechanical properties and an excellent corrosion resistance, regardless of the heat treatment, and could be considered for manufacturing micro-process engineering apparatuses operated in a sulphuric acid environment. This is a significant advance compared to the results obtained within a AiF project, previously carried out on four different materials to investigate the corrosion resistance in sulphuric acid.

1 Introduction

In addition to blockages caused by by-products resulting from side reactions, corrosion is one of the main reasons for the failure of micro process devices due to the low material thickness. Furthermore, micro process devices are often manufactured from a large number of thin, microstructured sheets, which are mainly joined by diffusion bonding. During processing, they are exposed to high temperatures and long dwell times, which is often associated with a decrease of materials strength and formation of precipitations at grain boundaries.

Sulphuric acid is widely used in different concentrations in the chemical industry. Depending on the source and ambient condition during manufacturing, it may contain impurities and a water content that varies within certain limits. During chemical conversion, strong heat of reactions may occur. This can be controlled quite well by micro process devices, which have a purely large surface to volume ratio. For this reason, for a number of years now, various investigations at *KIT-IMVT* were performed to identify a robust solution for micro-process engineering apparatus in contact with sulphuric acid.

In this paper, two highly molybdenum-alloyed materials, namely *Hastelloy B3* and *Hastelloy BC-1* were evaluated regarding corrosion resistance in hot 70 % sulfuric acid and eligibility to diffusion bonding.

Molybdenum is known to decrease the surface corrosion in non-oxidizing acids such as sulphuric acid and to improve the pitting corrosion resistance. [1, 2, 3, 4, 5] In an earlier AiF-research project, four different materials were characterized with regard to their corrosion behavior (Tab. 1). [6]

However, the rate of corrosion or material changes were that significant, that the life cycles do not seem to be sufficient enough for micro process devices. In addition, the results were fluctuating and not consistent to different concentrations of sulfuric acid, so that a useful life prediction for micro process devices is not possible.

Even for *Alloy 2120 MoN* (2.4700) produced by *Krupp-VDM*, containing comparable high contents of molybdenum, no good results were obtained, despite it showed the lowest corrosion rate in 70% sulfuric acid at 100°C, especially in the heat-treated condition.

Also coating concepts, such as tantalization, were investigated to improve the corrosion resistance of micro process devices. [7] However, it has to be stated, that any coating solution is susceptible to mechanical damaging in harsh industrial environment at all.

Tab. 1: Results of corrosion tests from [6] on four different materials aged in 70 and 95-97 % sulfuric acid at 100°C for 1000 h.

Material	Concentration Sulfuric Acid [%]	Condition	Initial Weight [g]	Final Weight [g]	Weight Loss [g]	Weight Loss [%]
2.4602	95-97	delivery condion	45.464	43.867	1.597	3.5
2.4605	95-97		38.796	37.823	0.973	2.5
2.4692	95-97		47.094	46.385	0.709	1.5
2.4700	95-97		38.124	37.776	0.348	0.9
2.4602	70		41.444	36.345	5.099	12.3
2.4605	70		35.025	31.586	3.439	9.8
2.4692	70		49.217	48.748	0.469	1
2.4700	70		35.594	35.164	0.43	1.2
2.4602	95-97	heat- treated 1100°C/4h	38.672	37.115	1.557	4
2.4605	95-97		34.652	33.355	1.297	3.7
2.4692	95-97		44.701	44.095	0.606	1.4
2.4700	95-97		37.594	36.489	1.105	2.9
2.4602	70		40.332	36.03	4.302	10.7
2.4605	70		37.42	32.636	4.784	12.8

2.4692	70		46.404	39.763	6.641	14.3
2.4700	70		41.436	38.56	2.876	6.9

2 Materials and Design of Experiments

Hastelloy B3 and *BC-1* are highly molybdenum-alloyed materials. In Tab. 2, physical properties and the composition of these alloys are given, together with values of *Alloy 2120 MoN* for comparison reasons.

It needs to be mentioned, that all materials reveal a cubic face-centered lattice (fcc). But due to the high content of molybdenum and according to *Grüneisens Rule*, in contrast to ordinary austenitic stainless steels, the coefficient of thermal expansion is more comparable to that of ferritic steels. While *Hastelloy BC-1* has a clearly higher chromium content than *Hastelloy B3*, *B3* contains significant more molybdenum.

Tab. 2: *Physical properties and chemical composition of Hastelloy B3, Hastelloy BC-1 and Alloy 2120 MoN. [8, 9, 10]*

Alloy [%]	B3	BC-1	Alloy 2120 MoN
EN	2.4600	2.4708	2.4700
UNS	N10675	N10362	N06058
T _s [°C]	1370–1418	1343–1443	1330-1370
Thermal Conductivity α [W/m*K]	11.2	9.3	9.8
Mean Coefficient of Thermal Expansion λ [*10 ⁻⁶ K ⁻¹] (25-100°C)	10.6	11.5	11.44
Ni	Bal.	Bal.	Bal.
Mo	28.5	22	18.5-21
Cr	1.5	15	20-23
Fe	1.5	<2	<1.5
W	<3		<0.3
Mn	<3	0.25	<0.5

Co	<3	<1	<0.3
Al	<0.5	<0.5	<0.4
Ti	<0.2		
Si	<0.1	<0.08	<0.1
C	<0.01	<0.01	<0.01
Nb	<0.2		
V	<0.2		
Cu	<0.2		<0.5
Ta	<0.2		
Zr	<0.01		
N			0.02-0.15

For *Hastelloy B3*, the yield strength at room temperature in solution annealed condition is ranging from 400 to 421 MPa, depending on form of delivery. The tensile strength is specified with 862-863 MPa, while the elongation at fracture varies between 53 and 58 %. For solution annealing, a temperature of 1066°C is recommended.

For *Hastelloy BC-1*, the yield strength at room temperature in solution annealed condition is ranging from 362 to 405 MPa, depending on the thickness of semi-finished products. The tensile strength varies between 809 and 841 MPa, while the elongation at fracture varies between 61.6 and 70.5 %. For solution annealing, a much higher temperature than for *Hastelloy B3*, namely 1149°C, is recommended.

For the corrosion experiments, coupons of *Hastelloy B3* and *BC-1*, containing a TIG weld and made of 3 mm thick sheet metal, were provided by *HAYNES*. Using a disk cutter from *ATM*, type *Brillant 250*, pieces with a size of approximately 20 x 80 mm² and 40 g in weight were cut. One set of specimens was investigated in condition as delivered. A second set of specimens was placed inside a diffusion bonding furnace during a run to simulate a heat treatment. For this purpose, a temperature of $T = 1100^{\circ}\text{C}$ was applied for $t = 4$ h. Subsequently, the samples were cooled down in diffusion bonding furnace 2. Fig. 1 shows the cooling behavior of three diffusion bonding furnaces of different sizes with 20 kN, 200 kN and 2 MN compressive load, respectively, available at *IMVT*. It can be seen that the cooling rate of furnace 2 at approx. 600°C falls below 5 K/min,

what is half of the heating rate. This facilitates sensitization, especially with nickel-based alloys, which has an impact on corrosion behavior in aggressive media. [11, 12]

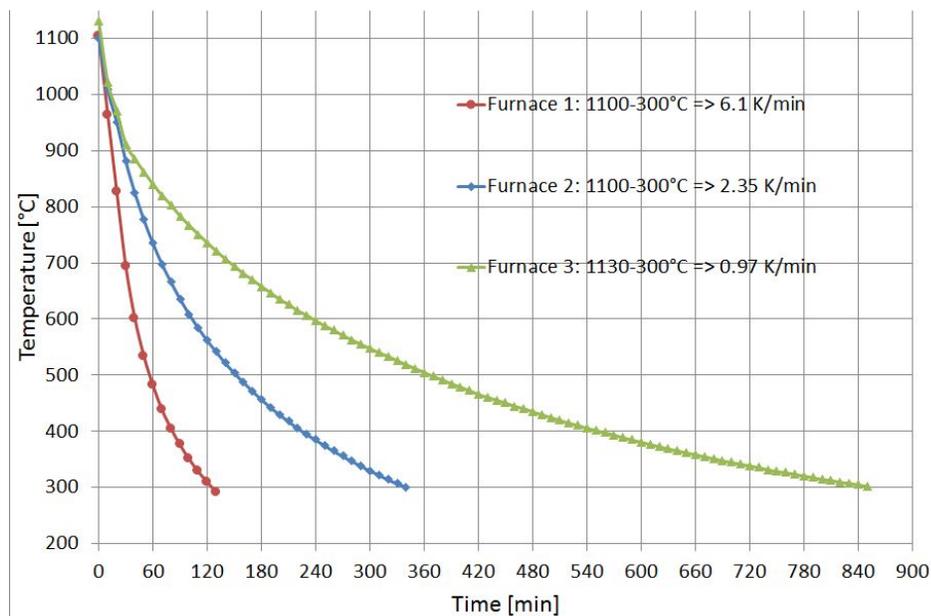


Fig. 1: Temperature profile of the used diffusion bonding furnaces

The main point of criticism of the authors with regard to the investigation of intergranular corrosion according to *ASTM G-28A* for micro process apparatus is the short alloy-specific test duration and the determination of a specific corrosion medium and temperature. [13] If we further realize that the criterion for the derivation of the sensitization diagrams is a corrosion attack depth of 50 μm under the above-mentioned conditions, the test does not provide any helpful information on the suitability of a material in micro-process engineering where dimensions below 1 mm wall thickness need to be realized. Significantly, longer test periods are required to obtain reliable results. For this reason, a test duration of 1000 h was specified.

For initial diffusion bonding experiments, sheet material of *Hastelloy BC-1* and *Hastelloy B3* were supplied by *HAYNES*, 1.0 and 1.6 mm in thickness, respectively. From this sheets, ten pieces each 20 x 20 mm² in size were cut using a *TruLaser Cell 3010*, combined with a 3 kW *TruDisk 3001* from *TRUMPF*.

Round stock of different diameters from both alloys was used to produce the initial material with a diameter of 30 mm by wire erosion. Additional, for both materials, ten disks, 30 mm in diameter, were cut by laser from sheet material. To ensure a reasonable initial height of the diffusion bonding specimens related to the preparation of tensile specimens, two pieces of round stock with a height

of 15 and 17 mm for *Hastelloy B3* and *Hastelloy BC-1*, respectively, were prepared. In between, ten layers of sheet material were stacked, giving an absolute height of 46 and 44 mm, respectively (Fig. 2).

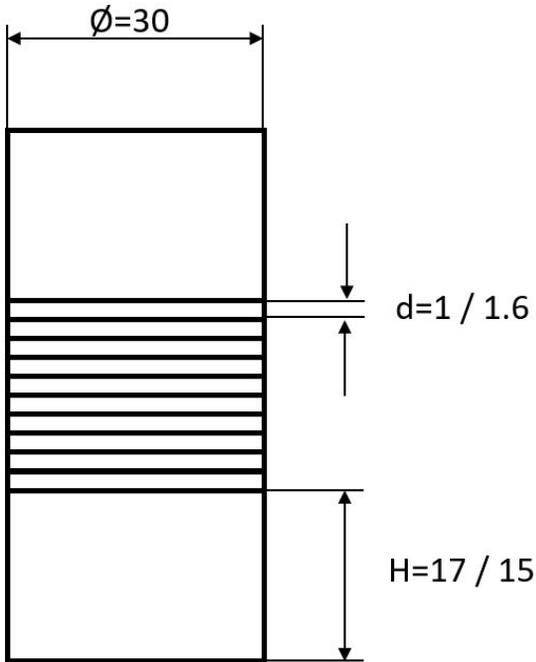


Fig. 2: Diffusion bonding samples used for preparing tensile test specimens.

3 Experiments and Results

3.1 Diffusion Bonding Experiments on Hastelloy B3 and BC-1

3.1.1 Initial Diffusion Bonding Experiments made of ten Sheets

Based on empirical values, initial diffusion bonding tests were carried out for both alloys. The parameters used are listed in Tab. 3. The dwell time was chosen to be $t = 4$ h in all experiments. Diffusion bonding experiments were performed in furnace I (20 kN). Due to different sheet material thickness of 1.0 and 1.6 mm, respectively, the aspect ratio was 0.8 and 0.5 for ten sheets of 20×20 mm². Deformation values are very similar for both materials. Furthermore, the deformation depends on the aspect ratio: Hence, for *Hastelloy B3* with a sheet thickness of 1.6 mm and an aspect ratio of 0.8, a slightly higher deformation was expected than for *Hastelloy BC-1*. [14]

However, due to the low absolute value, the measurement error may be higher than for a larger heights and deformation values.

It turned out, that the deformation decreases with increasing bonding temperature, since the temperature raise of 50 K for subsequent experiments were overcompensated by decreasing the contact pressure as depicted in Tab. 3.

Tab. 3: Diffusion bonding parameters for Hastelloy B3 and BC-1 and resulting deformations.

Temperature [°C]	Surface Pressure [MPa]	Initial Height [mm]	Final Height [mm]	Deformation [mm]	Deformation [%]
Hastelloy B3					
1100	14	16.134	15.904	0.23	1.43
1150	10	16.152	15.998	0.154	0.95
1200	6	16.146	16.036	0.11	0.68
Hastalloy BC-1					
1100	14	10.316	10.176	0.14	1.36
1150	10	10.312	10.218	0.094	0.91
1200	6	10.314	10.232	0.082	0.80

According to Fig. 3, the grain size for *Hastelloy B3* increases with increasing diffusion bonding temperature. At $T = 1100^{\circ}\text{C}$, some pores could be observed. Obviously, the surface pressure of $p = 14$ MPa was not sufficient. Probably due to passivation layers, even at $T = 1200^{\circ}\text{C}$, only the first signs of grain growth over the joining planes were visible.



Fig. 3: Resulting microstructure of Hastelloy B3 after diffusion bonding for $t = 4$ h at $T = 1100^{\circ}\text{C}$ (left), 1150°C (middle) and 1200°C (right).

In contrast, for *Hastelloy BC-1*, even for $T = 1100^{\circ}\text{C}$ grain growth across the bonding plane can be seen (Fig. 4, left). However, the microstructure shows strong discontinuous grain growth with a bimodal grain size distribution. For $T = 1200^{\circ}\text{C}$, strong grain growth was observed.

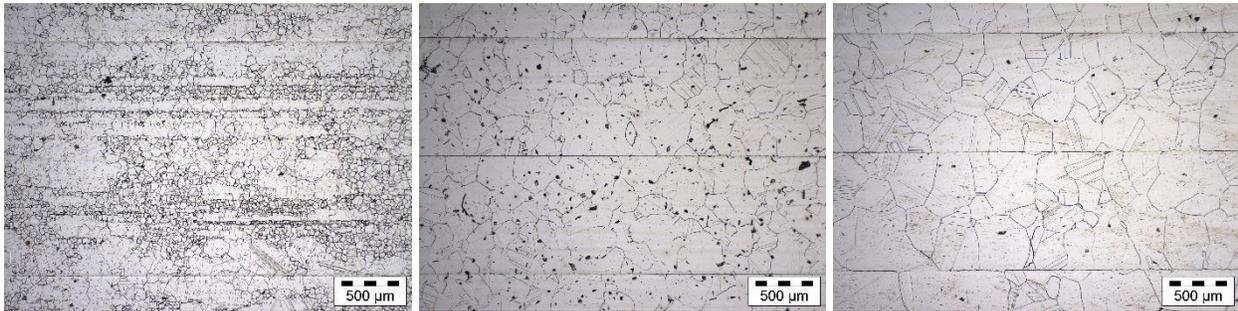


Fig. 4: Resulting microstructure of *Hastelloy BC-1* after diffusion bonding for $t = 4$ h at $T = 1100^{\circ}$ (left), 1150 (middle) and 1200°C (right)

3.1.2 Diffusion Bonding Experiments for Manufacturing Tensile Test Specimens

Based on the results of the initial diffusion bonding tests, the bonding temperature for the diffusion bonding cycle to produce tensile test specimen was set to $T = 1200^{\circ}\text{C}$. The dwell time was kept constant with $t = 4$ h but the contact pressure was increased from $p = 6$ MPa to 10 MPa (bulk samples for comparison were placed next to the diffusion bonding samples in the same batch). Taking into account the different geometry of the diffusion bonding sample for tensile test specimen, featuring an aspect ratio of about 1.5, more deformation and facilitating breakthrough the passivation layer was expected.

However, despite the contact pressure was increased by 66 % compared to initial diffusion bonding experiments, the deformation was found to be only 2.03 % and 2.06 % for *Hastelloy B3* and *Hastelloy BC-1*, respectively. This result shows again the impact of the sample geometry as well as the size of the absolute cross-section of the surfaces to be joined on deformation.

3.2 Corrosion Experiments in Sulfuric Acid at $t = 100^\circ\text{C}$

3.2.1 Corrosion Test at Coupons aged in 70 % Sulfuric Acid

For corrosion tests, the specimens were placed on a bridge made of *PTFE* inside a beaker with a volume of 800 ml, filled with 500 ml of sulfuric acid. 70 % sulfuric acid was diluted from 95-95 % sulfuric acid supplied by *Merck*. The beakers were wrapped with rock wool and a lid made of *PTFE* was used for thermal insulation. A magnetic stirrer was placed under the *PTFE* bridge. A speed of 120 rpm was set for the stirrer. The beakers were controlled every week, however, no green color, due to dissolved nickel ions was observed.



Fig. 5: Test specimens after corrosion tests. Left: Condition as delivered. Right: Heat-treated ($T = 1100^\circ\text{C}$, $t = 4$ h). Top: Hastelloy BC-1. Bottom: Hastelloy B3.

70 % sulphuric acid is considered to be more corrosive than 95-97 % sulphuric acid because of its water content. Compared to the results obtained for the other four materials shown in Tab. 1, especially for the heat-treated condition, for *Hastelloy BC-1*, superior results were obtained. In Fig. 5 it can be seen that the surface of *Hastelloy BC-1* has remained almost unchanged, while the surface of *Hastelloy B3* shows some pitting attack.

Tab. 4: Results of corrosion experiments of coupons aged in 70 % sulfuric acid

Material	UNS	Condition	Initial Weight [g]	Final Weight [g]	Weight Loss [g]	Weight Loss [%]
B3 / 2.4600	N06022	delivery	39.673	39.327	0.346	0.87
BC-1 / 2.4708	N08034	condion	37.278	36.922	0.356	0.95
B3 / 2.4600	N06022	heat-treated	34.713	33.773	0.94	2.71
BC-1 / 2.4708	N08034	1100°C/4h	40.845	40.524	0.321	0.79

3.2.2 Corrosion Test at Coupons aged in 95-97 % Sulfuric Acid

As expected, in concentrated sulfuric acid the corrosion is less pronounced than in 70 % sulfuric acid. Especially in the heat-treated condition, both materials exhibit a very low weight loss that is even lower than in the as delivered condition. However, due to low mass loss, it may be attributed to the error of measurement.

Tab. 5: Results of corrosion experiments in 95-97 % sulfuric acid

Material	UNS	Condition	Initial Weight [g]	Final Weight [g]	Weight Loss [g]	Weight Loss [%]
B3 / 2.4600	N06059	delivery	40.403	40.209	0.194	0.48
BC-1 / 2.4708	N06058	condion	41.139	40.734	0.405	0.98
B3 / 2.4600	N06059	heat-treated	37.692	37.55	0.142	0.38
BC-1 / 2.4708	N06058	1100°C/4h	37.274	37.062	0.212	0.57

3.2.3 Corrosion Test at Tensile Test Samples aged in 70% Sulfuric Acid

In a second series of tests, five diffusion bonded tensile specimens from *Hastelloy B3* and *BC-1*, respectively, were aged in 70 % sulphuric acid at 100°C for 1000 h to investigate the impact of corrosion on the mechanical properties. This is an important aspect in order to assess the integrity of micro process devices as a function of corrosion phenomena over lifetime. The corrosion traces of the SEM-pictures at the circumferential surface of both materials showed no strong differences (Fig. 6). There is some corrosion attack at grain boundaries. Only a few grain growth across the bonding plane could be observed. Instead, pronounced decoration by corrosion of original bonding

planes was observed. Probably, the deformation of approximately 2 % and eleven bonding planes is not sufficiently to level surface roughness and to break passivation layers

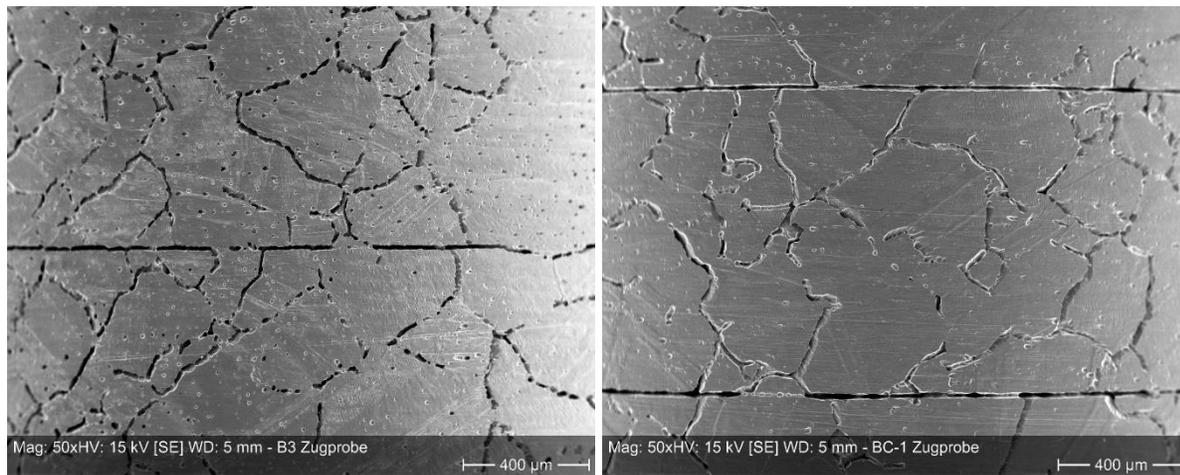


Fig. 6: Surface of tensile specimens from Hastelloy B3 (left) and Hastelloy BC-1 (right) after exposure to 70 % sulfuric acid at 100°C for 1000 h.

3.3 Tensile Tests on both Hastelloy B3 and BC-1

3.3.1 Material Conditions

For tensile tests, four different treated specimen types were prepared for both alloys:

1. Bulk samples in as-delivered condition,
2. bulk samples heat-treated at $T = 1200^{\circ}\text{C}$ for $t = 4$ h and loaded with $p = 10$ MPa in compression,
3. diffusion bonded specimens with ten layers of sheet material processed at $T = 1200^{\circ}\text{C}$ for $t = 4$ h with $p = 10$ MPa in compression,
4. diffusion bonded specimens processed as described in 3., additionally aged in 70 % sulfuric acid at 100°C for 1000 h.

3.3.2 Tensile Specimen Geometry and Test Method

The geometry of tensile test specimens is shown in Fig. 7. Tensile tests were performed displacement controlled ($dl/dt = 2$ mm/min) at RT (room temperature) using an universal testing machine from *Instron* (type 4505), equipped with a controller unit from *Doli*. In order to take into account scatter issues, five tests per treatment condition were carried out.

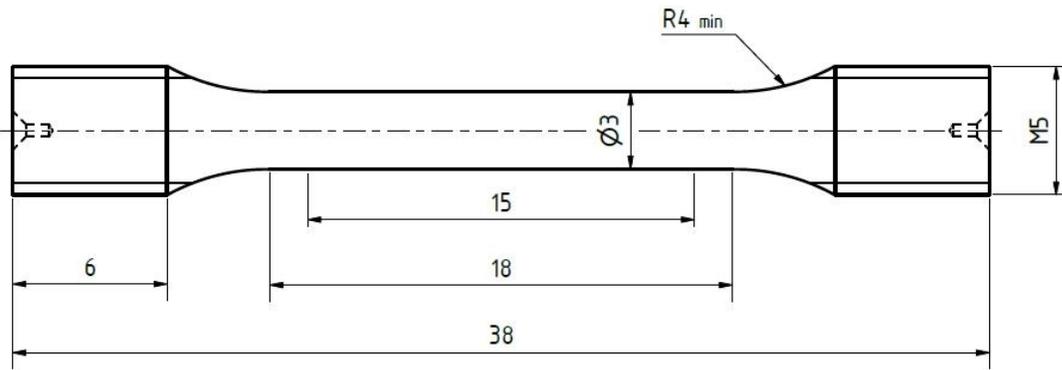


Fig. 7: Geometry of the tensile specimens

3.3.3 Results of Tensile Tests on Hastelloy B3

In Fig. 8, the results of the tests on as delivered-, heat-treated and compressed- and diffusion bonded samples are depicted. When comparing the as delivered condition of bulk material with the heat-treated condition it can be seen, that the annealed samples show a decrease in strength of about 20 to 25 % and an increase in ductility of about 20 %. Accordingly, the annealed material reveals a slightly less pronounced hardening behavior. The change in deformation behavior can be generally traced back on both recovery and recrystallization/grain growth processes (compare Fig. 3 and Fig. 4) occurring during tempering.

Compared to the heat-treated bulk samples, the diffusion bonded samples exhibit a comparable deformation behavior but a significant decrease in elongation at fracture of about 50 % on average. The earlier onset of failure is obviously a result of several weak spots within the bonding planes in the form of non-bonded areas that act as cracks.

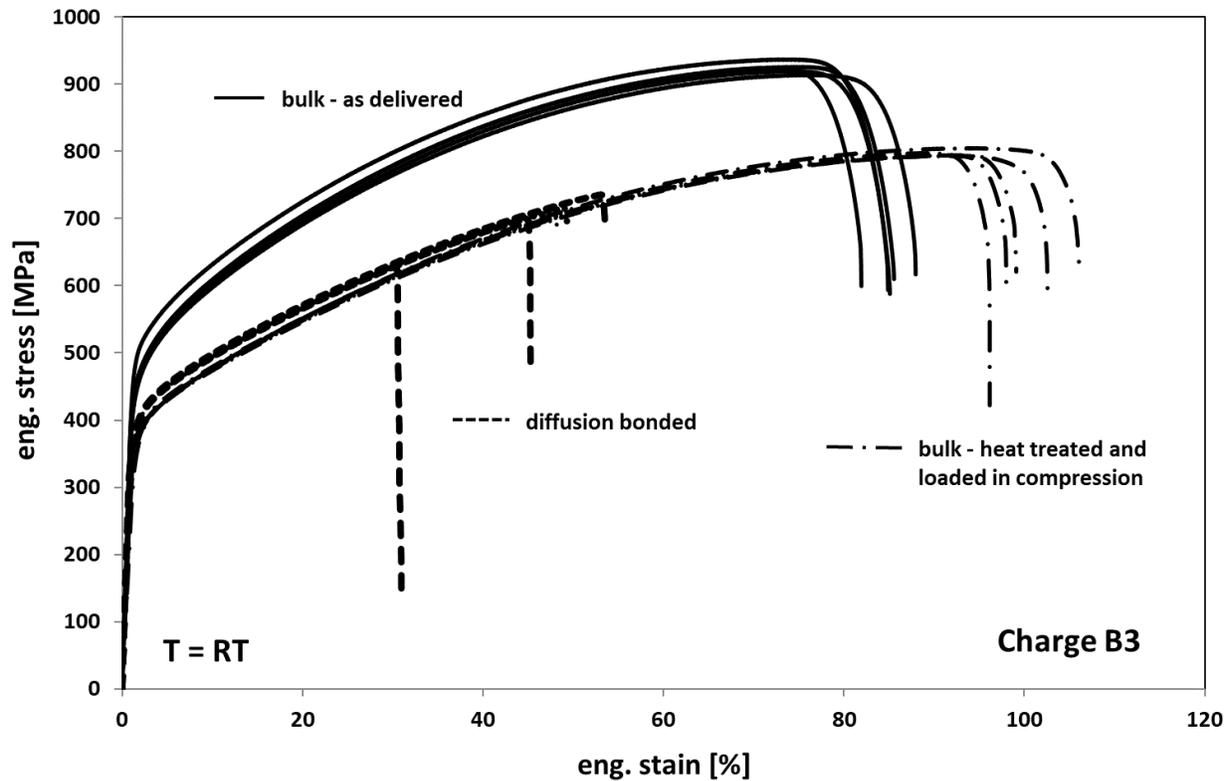


Fig. 8: Tensile response of Hastelloy B3 in different conditions

Examples of such weak spots based on scratches or dents etc. on the individual sheets are shown in Fig. 9. In Fig. 9a and Fig. 9b one can see an overview of fracture surfaces exhibiting a multitude of weak spots. When comparing both micrographs it becomes clear, that the high scatter of the elongation at fracture values is related to the entire size of the non-bonded areas, lowering the real load bearing cross-sections. While sample 5, depicted in Fig. 9b, reveals an elongation at fracture of approximately 30 %, sample 3, depicted in Fig. 9a, reveals an elongation at fracture of almost 50 %. A closer view on a fracture surface (Fig. 9c) is manifesting the general ductile nature of failure within well bonded sections in form of dimples, here, surrounding a weak spot. Non-bonded areas are also located at the surface of a sample. Accordingly, with increasing deformation the occurrence of smaller surface cracks is visible in several bonding planes (Fig. 9d).

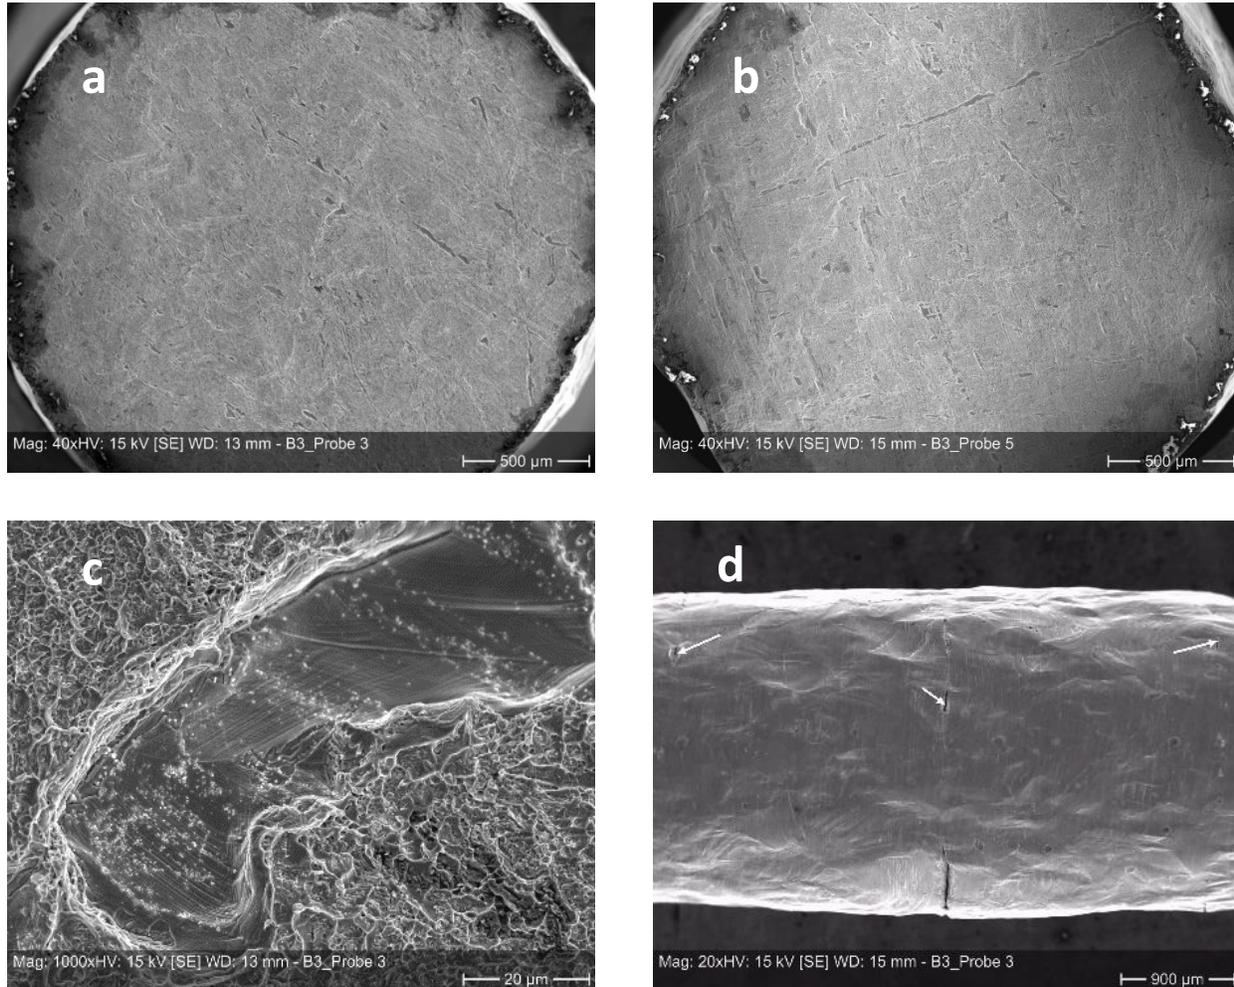


Fig. 9: Micrographs of tensile tested diffusion bonded samples – a and b: overview of fracture surfaces, c: ductile fracture area surrounding a weak spot and d: small surface cracks located at different bonding planes

When comparing the tensile test results obtained from tests on diffusion bonded samples, aged for 1000 h at 100°C in 70 % H₂SO₄ with the results obtained on non-aged bonded samples (Fig. 10), one can see a further strong decrease of the elongation at fracture to an average value of about 20 %. Additionally, the stress level also significantly decreased (Fig. 10, interrupted grey deformation curves). However, this finding is based on the fact, that the stress calculation of the engineering stress is usually related to the nominal initial cross-section. De facto, based on a much stronger corrosive attack into the volume than expected when viewing Fig. 6 left, a real initial cross-section after aging is much smaller as one can see in Fig. 11. Accordingly, by determining the average depth of the corrosion cracks inside the failed bonding planes, the initial cross-sections and

subsequently the stresses were re-calculated. Now, the stress level of aged samples is significantly higher than the one of non-aged samples (Fig. 10, black deformation curves). This might be related to the formation of an inhomogeneous distributed multi-axial stress-strain-field during loading – see Fig. 11c, concave shaped surface between the bonding planes. The pronounced notch effect and the resulting stress concentrations can also explain the decrease of the elongation at fracture values.

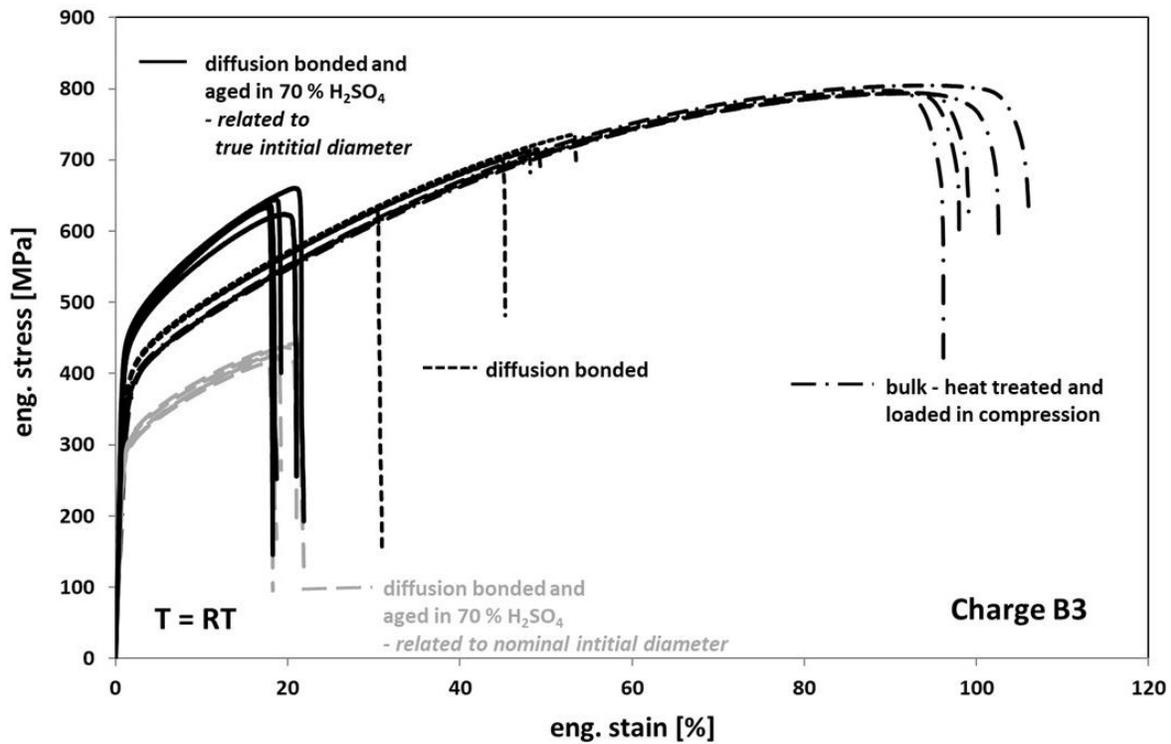


Fig. 10: Tensile response of Hastelloy B3 in different conditions

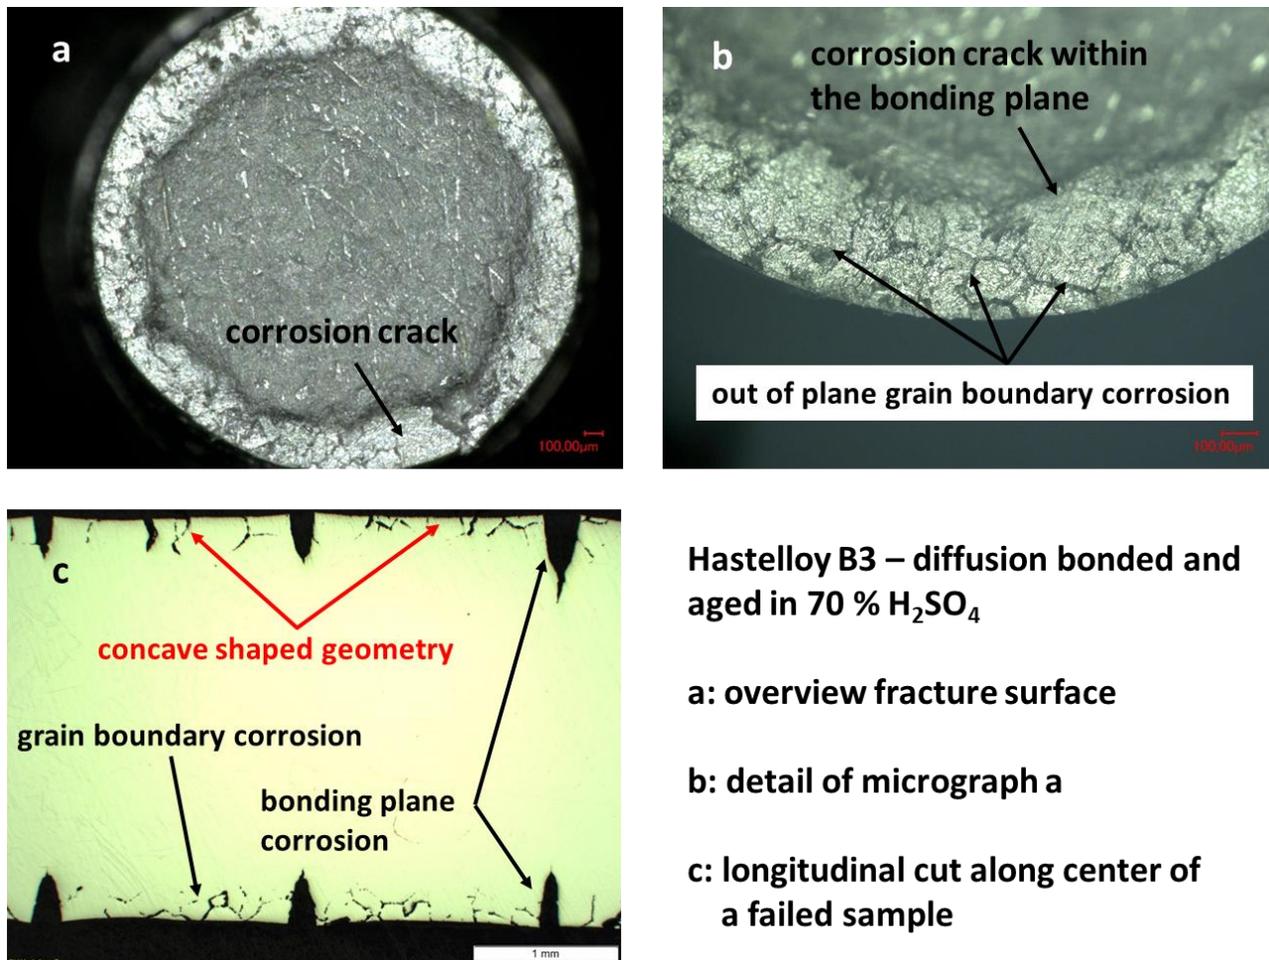


Fig. 11: Micrographs of tensile tested diffusion bonded and aged (1000 h at 100°C in 70 % H₂SO₄) samples

An overview of the obtained mechanical properties of all tested specimens is given in Tab. 6. The obtained stresses are related to the true initial cross-sections.

Tab. 6 Mechanical properties of Hastelloy B3 tested in different conditions.

Yield strength and tensile strength

sample No	Yield strength	Tensile strength						
	R _{p0.2} [MPa]	R _m [MPa]						
1	421	920	344	798	350	736	418	637
2	426	926	338	805	346	700	421	645
3	409	914	340	793	344	712	425	633
4	458	937	341	794	350	716	423	661
5	413	924	332	795	347	631	414	624
Aver.	425	924	339	797	347	699	420	640
Stand. Dev.	19.4	8.5	4.5	4.8	2.6	40.2	4.3	14.0
Min	409	914	332	793	344	631	414	624
Max	458	937	344	805	350	736	425	661

elongation at fracture, (continued)

sample No	as-delivered [%]	heat-treated 1200°C/4h with contact pressure [%]	diffusion bonded 1200°C/4h/10MPa [%]	diffusion bonded 1200°C/4h/10MPa + 1000h 70% H ₂ SO ₄ @ 100°C [%]
1	85.1	96.2	53.5	18.7
2	85.6	106.1	45.3	19.2
3	88	102.6	48.2	18.3
4	84.9	98	49.3	21.9
5	81.9	99.1	30.9	21
Aver.	85	100	45	20
Stand. Dev.	2.2	4.0	8.6	1.6
Min	81.9	96.2	30.9	18.3
Max	88.0	106.1	53.5	21.9

3.3.4 Results of Tensile Tests on Hastelloy BC-1

Generally, it is observed that the mechanical behavior of *Hastelloy BC-1* in tension is comparable to that of *Hastelloy B3*. Only the strength of *Hastelloy B3* is found to be slightly higher in all comparable conditions than the one of *BC-1*. In Fig. 12, the results of the tests on as delivered-, heat-treated- and diffusion bonded samples are presented. When comparing the as delivered condition of bulk material from *Hastelloy BC-1* with the heat-treated condition it can be seen, that the annealed and compressed samples also show a decrease in strength of about 25 % and an increase in ductility of about 20 %. The change in deformation behavior can be again traced back on both recovery and recrystallization/grain growth processes occurring during tempering.

Compared to the heat-treated bulk samples, the diffusion bonded samples also exhibit a comparable deformation behavior and a significant decrease in elongation at fracture of about 45 to 50 %. However, the scatter of the elongation at fracture values is clearly lower, indicating a more homogeneous distribution of weak spots and/or a lower variation of the entire size of non-bonded areas within the different bonding planes.

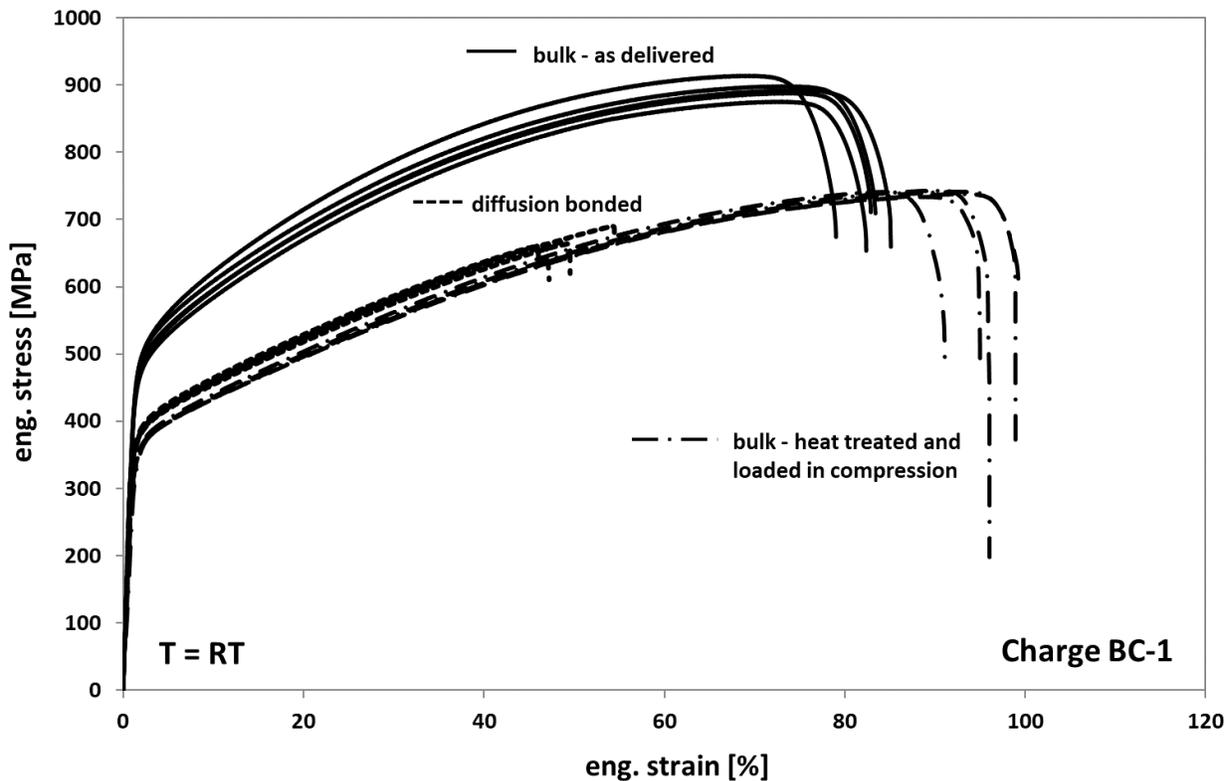


Fig. 12: Tensile response of Hastelloy BC-1 in different conditions

The fracture mode of all samples is also found to be ductile, at least in well bonded areas, but in contrast to *Hastelloy B3*, the dimples reveal a significant smaller size (compare Fig. 9c and Fig. 14b). In addition, identical to *Hastelloy B3*, small surface cracks in several other bonding planes are observed as already shown in Fig. 9d.

When comparing the tensile test results of *Hastelloy BC-1* obtained from tests on diffusion bonded samples, aged for 1000 h at 100°C in 70 % H₂SO₄ to non-aged diffusion bonded samples (Fig. 13), one can see a strong decrease of the elongation at fracture to 30 %. However, this is approximately 10 % more than for *Hastelloy B3* (Fig. 10). For *Hastelloy BC-1*, in contrast to *Hastelloy B3*, the

stress level of the aged samples is comparable to the non-aged samples. This behavior is obviously related to a less pronounced formation of an inhomogeneous distributed multiaxial stress-strain-field during loading, since the size of the corrosion cracks within the bonding planes is significant smaller compared to the sizes observed in *Hastelloy B3* – compare Fig. 11a and c with Fig. 14a and c. The much better corrosion resistance of *Hastelloy BC-1* and the resulting low corrosion crack depths might reduce the effect of stress concentrations around the crack tips on the entire in plane stress distribution. As a result, related to *Hastelloy B3*, the onset of failure is shifted towards higher elongation at fracture values.



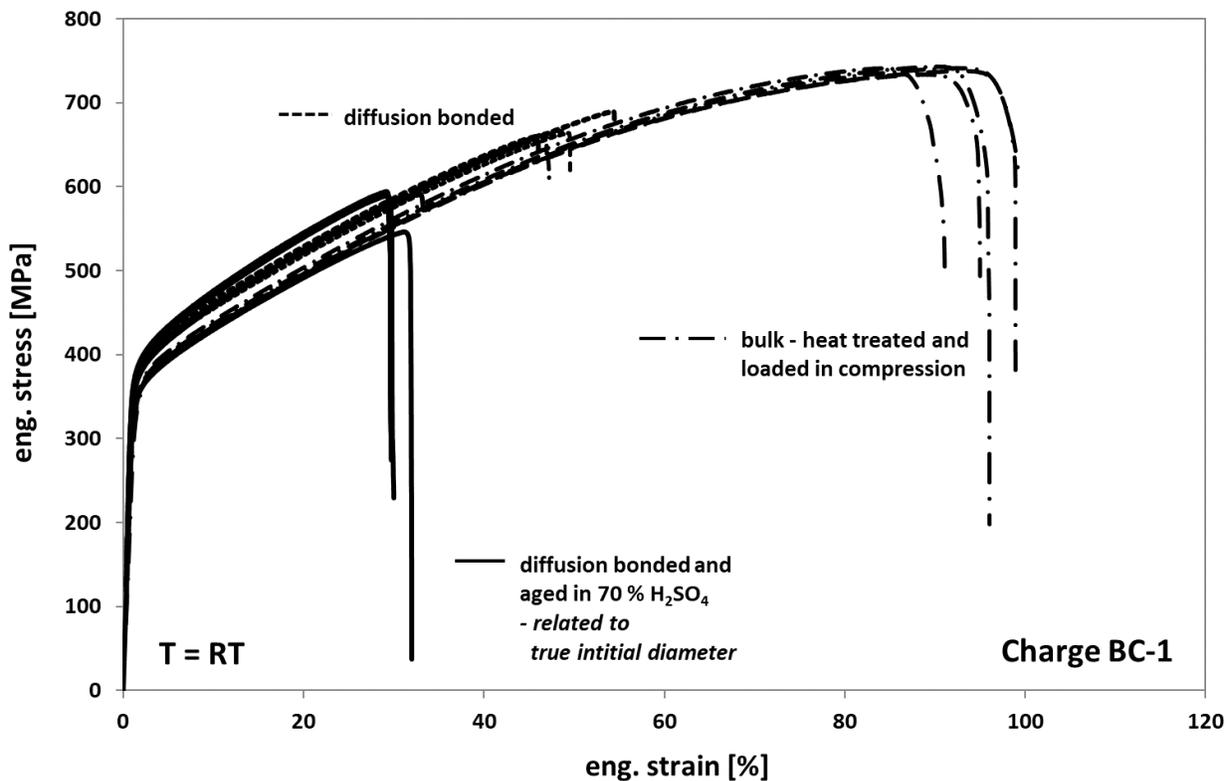


Fig. 13: Tensile response of *Hastelloy BC-1* in different conditions

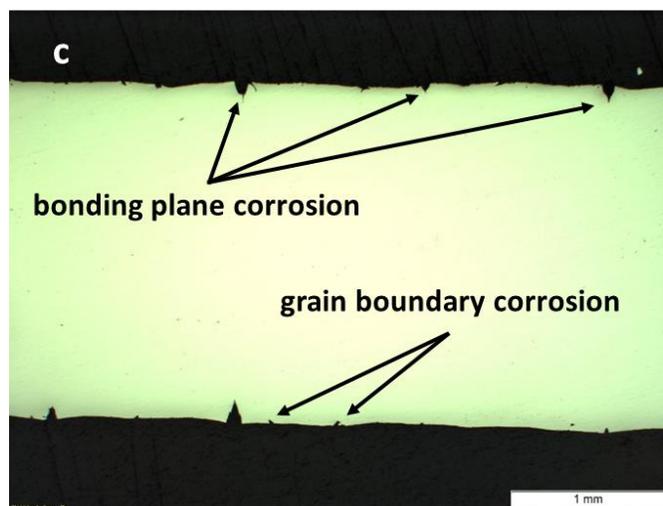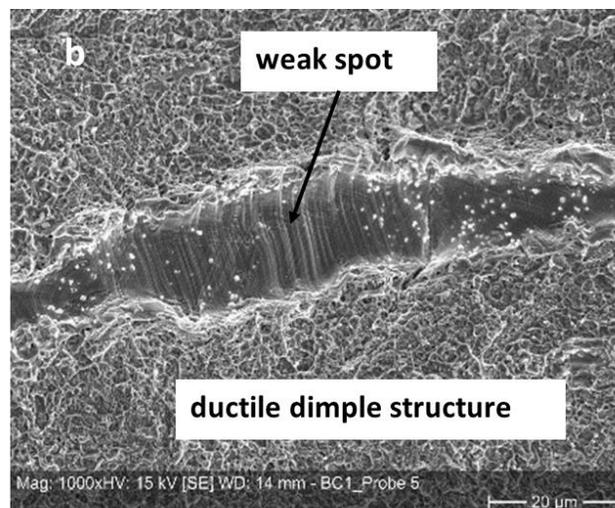

Hastelloy BC-1 – diffusion bonded and aged in 70 % H₂SO₄

a: overview fracture surface

b: fracture surface - ductile fracture area surrounding a weak spot

c: longitudinal cut along center of a failed sample

Fig. 14: Micrographs of tensile tested diffusion bonded and aged (1000 h at 100°C in 70 % H₂SO₄) samples

An overview of the obtained mechanical properties of all tested specimens is given in Tab. 7. The obtained stresses are related to the true initial cross-sections.

Tab. 7 Mechanical properties of Hastelloy BC-1 in different conditions

Yield strength and tensile strength

sample- No	as-delivered [MPa]		heat-treated 1200°C/4h with contact pressure		diffusion bonded 1200°C/4h/10MPa		diffusion bonded 1200°C/4h/10MPa + 1000h 70% H ₂ SO ₄ @ 100°C	
	Yield strength	Tensile strength	Yield strength	Tensile strength	Yield strength	Tensile strength	Yield strength	Tensile strength
	R _{p0.2} [MPa]	R _m [MPa]	R _{p0.2} [MPa]	R _m [MPa]	R _{p0.2} [MPa]	R _m [MPa]	R _{p0.2} [MPa]	R _m [MPa]
1	430	892	325	741	341	660	334	547
2	449	914	326	733	338	690	358	590
3	436	888	318	737	338	664	349	592
4	441	898	317	743	339	663	362	590
5	422	876	325	741	337	667	362	594
Aver.	436	894	322	739	339	669	353	583
Stand. Dev.	10.3	14.0	4.3	4.0	1.5	12.1	11.9	20.0
Min	422	876	317	733	337	660	334	547
Max	449	914	326	743	341	690	362	594

elongation at fracture, (continued)

sample- No	as- delivered [%]	heat-treated 1200°C/4h with contact pressure [%]	diffusion bonded 1200°C/4h/10MPa [%]	diffusion bonded 1200°C/4h/10MPa + 1000h 70% H ₂ SO ₄ @ 100°C [%]
1	85.1	46	99.3	32
2	79	54.4	95	29.2
3	82.9	49.5	98.9	33.2
4	83.4	47.2	96	30
5	82.4	48.7	91.1	29.7
Aver.	83	49	96	31
Stand. Dev.	2.2	3.2	3.3	1.7
Min	79.0	46	91.1	29.2
Max	85.1	54.4	99.3	33.2

4 Conclusions

Within this study, both the effect of diffusion bonding process on the mechanical behavior and the corrosion resistance against hot 70 % sulfuric acid of *Hastelloy B3* and *Hastelloy BC-1* was investigated. It was found, that although the grain growth crossing bonding planes during diffusion

bonding is not fully satisfactory, both materials achieve sufficiently high elongation at fracture values for engineering applications.

The deformation of about 2 % achieved in the diffusion bonding experiments for eleven joining planes is apparently not sufficient for completely leveling out all surface defects. Defects like scratches promote crack formation and propagation. The deformation until fracture decreases accordingly. Here is still potential for optimization.

The tough behavior of nickel-base alloys in combination with their cubic face-centered lattice generally leads to very high elongation at fracture values for both alloys. As delivered and heat-treated, the tensile strength is about twice as high as the yield strength due to cold work hardening effects during tensile tests (Tab. 6, Tab. 7).

Due to the temperature level and duration during diffusion bonding, any pre-work hardening is lost. The values for yield strength and tensile strength drop to 75 - 80% of the values obtained on delivery condition (Tab. 8). The fracture strain values of diffusion bonded samples for both materials are significantly reduced, however, the deformation reserve is sufficient for technical components.

Tab. 8: Decrease of strength properties of Hastelloy B3 and BC-1 related to delivery condition

heat-treated 1200°C/4h with contact pressure				diffusion bonded 1200°C/4h/10MPa			
B3		BC-1		B3		BC-1	
Yield strength R _{p0.2} [%]	Tensile strength R _m [%]	Yield strength R _{p0.2} [%]	Tensile strength R _m [%]	Yield strength R _{p0.2} [%]	Tensile strength R _m [%]	Yield strength R _{p0.2} [%]	Tensile strength R _m [%]
79.7	86.2	74.0	82.7	81.7	75.6	77.7	74.8

Diffusion bonded tensile test samples that were aged in 70 % sulphuric acid at 100°C for 1000 h, show only a low corrosion attack compared to other materials investigated so far, especially *Hastelloy C-22*. However, the corrosion attack on *Hastelloy B3* (2.4600) is much more pronounced than on *Hastelloy BC-1* (2.4708) despite a higher molybdenum content, which is in accordance with the expectations from the beaker tests (Tab. 4).

Obviously, the higher chromium content of *Hastelloy BC-1* results in higher corrosion resistance. It remains incomprehensible why in an earlier research project the material *Alloy 2120 MoN*

(2.4700), which has a very similar composition to *Hastelloy BC-1*, did not perform comparably well, especially after aging in 70% sulphuric acid in heat-treated condition (Tab. 1).

In comparison to solely diffusion bonded condition, the elongation at fracture values of samples aged in 70% sulfuric acid at 100°C for six weeks decreased to 20 % and 30 % for *Hastelloy B3* and *Hastelloy BC-1*, respectively. These values are still sufficient for use of these materials in micro process apparatuses. However, it shows that the impact of corrosion in micro process technology may not be neglected for long-term use. Standardized corrosion tests such as *ASTM G28-A* with special electrolytes and short test duration do not provide any reliable information for micro process devices.

According to [8], the sensitization of the nickel-molybdenum alloy *Hastelloy B3* is shifted to lower temperatures and considerably longer times compared to alloys containing more chromium and less molybdenum like *Hastelloy C-22*.

In contrast to the findings in this study, corrosion data from the data sheets of *Hastelloy B3* and *Hastelloy BC-1* for sulphuric acid of different concentrations suggested that *Hastelloy B3* should be more resistant to corrosion. This is surprising so far as the joining temperature of 1200°C for both materials is above the recommended solution annealing temperature. Sensitization therefore was only expected during the cooling phase in high vacuum.

Both Ni-base materials, due to its high content of molybdenum, have a low coefficient of thermal expansion, which is close to that of ferritic steels. Therefore, they may be considered as an alternative to ferritic stainless steels, in particular for combining with zirconium oxide, used as a diffusion or thermal barrier layer, if improved corrosion resistance of the matrix material is required. However, from both *Hastelloy* materials investigated in this study, only *Hastelloy BC-1* represents an interesting solution for use in micro process devices for hot diluted sulfuric acid. This is particularly important for components made of many microstructured sheets where the wall thicknesses between different passages are very thin.

References

-
- [1] J. R. Hayes, J. Gray, A. W. Szmodis, C. A. Orme, *CORROSION*, **2006**, vol. 62, no. 6, pp. 491-500
 - [2] H.-Y. Ha, T.-H. Lee, J.-H. Bae, D. W. Chun, *metals*, **2018**, vol. 8, 653; doi:10.3390/met8080653

-
- [3] H. Alves, R. Behrens, P. Larry, *Corrosion* 2014, 9.-13.03.2014, San Antonio, Texas, USA; paper No. 4317, NACE International
- [4] U. Heubner, M. Koehler, *Mater. Corros.*, **1992**, vol. 43, pp. 181-190
- [5] D. C. Agarwal, W. R. Herda, *Mater. Corros.*, **1997**, vol. 48, pp. 542-548
- [6] Final report of AiF-Project No. 18034 N, "Untersuchungen zur Verbesserung der Korrosionsbeständigkeit mikroverfahrenstechnischer Bauteile für aggressive chemische Prozessmedien", 01.02.2014 - 30.09.2016, see under http://www.imvt.kit.edu/downloads/AiF_Abschlussbericht_20170117_gie.pdf, last access: 2020-02-14
- [7] T. Gietzelt, M. Kraut, F. Messerschmidt, W. Fürbeth, R. Dittmeyer, *Chem. Ing. Techn.*, **2018**, vol. 90, no. 8, pp. 1037-1046, DOI: 10.1002/cite.201700168
- [8] Data sheet of Hastelloy B3, see under <https://www.haynesintl.com/docs/default-source/pdfs/new-alloy-brochures/corrosion-resistant-alloys/brochures/pdf-alloy-b-3.pdf?sfvrsn=14>, last access: 2020-02-20
- [9] Data sheet of Hastelloy BC-1, see under <https://www.haynesintl.com/docs/default-source/pdfs/new-alloy-brochures/corrosion-resistant-alloys/brochures/hybrid-bc1.pdf?sfvrsn=14>, last access: 2020-02-14
- [10] Data sheet of Nicrofer 5821 hMoN, see under https://www.vdm-metals.com/fileadmin/user_upload/Downloads/Data_Sheets/Datenblatt_VDM_Alloy_2120.pdf, last access: 2020-02-14
- [11] M. Koehler, *MATER CORROS*, **1997**, vol. 48, 528-534
- [12] J. Heinemann, C. Richli, *MATER CORROS*, **2001**, vol. 52, pp. 106-111
- [13] ASTM G28: Standard Test Methods for Detecting Susceptibility to Intergranular Corrosion in Wrought, Nickel-Rich, Chromium-Bearing Alloys, revised **2008**
- [14] T. Gietzelt, V. Toth, A. Huell, R. Dittmeyer, *Adv. Eng. Mater.*, vol. 19, no. 2, **2016**, DOI: 10.1002/adem.201600344