

Article

Effect of residual stresses on the elastoplastic behavior of welded steel plates

José Manuel Gordo¹

¹ CENTEC, Instituto Superior Técnico, University of Lisbon; jose.gordo@centec.tecnico.ulisboa.pt

* Correspondence: jose.gordo@centec.tecnico.ulisboa.pt

Received: date; Accepted: date; Published: date

Abstract: A robust methodology to simulate virtually the residual stresses pattern in welded steel plates is presented. The methodology is applied to the structural analysis of typical welded plates belonging to ship structures, and the effect of residual stresses on the elastoplastic behavior of plates loaded axially is analyzed in comparison to the residual stress free case, both for tension and compression and including initial imperfections. Residual stresses affect in different manner plates with different geometries; thus a parametric study is performed covering the usual range of variation of the most important plate parameters that control the strength of the plates, more precisely the slenderness and the aspect ratio. The results from finite elements analysis are compared with codes and most established formulations and recommendations of applicability in the prediction of load-shortening curves for hull's bending strength evaluation, ultimate strength and ultimate strain of plate elements are made.

Keywords: ultimate strength of plates; residual stresses; initial imperfections

1. Introduction

The study of unstiffened plates under different loading conditions has been object of very deep and extensive analysis along time in relation to the effect of the most important parameters that influence the ultimate strength of such plates.

Plate elements are a fundamental component of stiffened plates that are the basis of structural strength of thin-walled structures evaluation. The hull girder of a ship is subjected to different loadings, like bending moment, shear force and lateral pressure. Plate elements play a very important rule in all cases contributing greatly to the strength to resist to those loadings. In the particular case of the hull girder strength assessment, the structure may be considered to be formed by a set of stiffened plates each of them contributing to resist the applied bending moment and other loads [1–3]. The response of each stiffened element depends greatly from the contributions of the associated plate attached to the stiffeners and frames [4].

The evaluation of the residual stresses distribution along the structure has been concentrated in three main fields: development of non-destructive and destructive techniques [5], use of finite element methods and analytical studies associated with the mechanical characteristics of the different material and welding techniques. Leggatt [6] explains the residual stresses in welded structures, i.e. how the different factors affect the magnitude, direction and distribution of residual stresses in welded joints and structures. There exist today several commercial FE-codes that may be employed for detailed nonlinear simulations of the development of the temperature and stress fields present during welding.

Lindgren [7], Runesson et al [8] and Dong [9] discussed methods for numerical simulation of the welding process taking into consideration actual thermal, mechanical and microstructure developments. The focus is on material modelling, coupling effects between thermal, mechanical fields and microstructure, numerical techniques and modelling aspects.

The evaluation of the residual stresses level in 3-D structures may be done indirectly. It requires the imposition of some hypotheses to establish the residual stress pattern and may be obtained by two methods: the structural tangent modulus method and the total energy dissipation method [10]. The first one considers the variation of the tangent modulus under alternate loading at a point of a cycle corresponding to the maximum loading point in the previous cycle. The variation of the tangent modulus is the result of the variation on the effective inertia of the section due to the development of local plasticity at points where residual stresses are still high. The second method considers the dissipation of energy in a structure with residual stresses when an external load is applied [11].

Tekgoz *et al.* [12] analyzed the effect of residual stress on the ultimate strength assessment of a stiffened panel by a nonlinear finite element method. They develop modified stress strain curves in order to include a model of residual stresses on material properties. An improved approach was proposed by Launert *et al.* [13] by prescribing initial deformations and simplified residual stress pattern manually to the numerical model applied to welded plate girders. The present methodology allows to implement residual stresses in direct way by using the concept of heat affect zone (HAZ) and mechanical and thermal properties of the material.

2. Methodology

This work studies the effect of residual stresses on the behavior of unstiffened rectangular plates subjected to axial compression. In order to achieve this objective, a methodology to implement residual stresses in structural plate elements due to welding process is presented. The internal state of stresses obtained in this first stage is used as initial condition for the evaluation of the unstiffened plate structural performance by finite element analysis.

2.1. Implementation of residual stresses due to welding

The plate elements are divided into different regions according to the thermal process that they are subjected during the welding process. A typical plate element belonging to a ship's panel has a length a and a width b and is welded on its borders to stiffeners and frames, thus there are strips of the plate in the borders that suffer the effect of heating and cooling during the welding process, developing permanent plastic strains that affect the initial internal state of stresses in the whole plate in the end of the welding process.

2.1.1. Theoretical model of residual for perfect plates

It is commonly accepted that these residual stresses pattern may be simply represented by a strip of plate near each border with a width ηt at yield stress (σ_o) in tension and a central region under compression at a stress σ_r with a width of $b-2\eta t$ that equilibrates the plate. η is the factor that relates the width of the heat affected zone with the thickness of the plate t .

The equilibrium equation of loads for the plate quantifies the residual stress as:

$$\sigma_r = -\sigma_o \frac{2\eta t}{b - 2\eta t} \quad (1)$$

In the transverse direction the transversal residual stress in the middle of the plate is:

$$\sigma_{rt} = -\sigma_o \frac{2\eta t}{a - 2\eta t} \quad (2)$$

Figure 1 presents the distribution of residual stresses in the flat plate, after welding, both in longitudinal and transversal directions, for the simplified approach (left) and the one obtained by thermal analysis (right) [14].

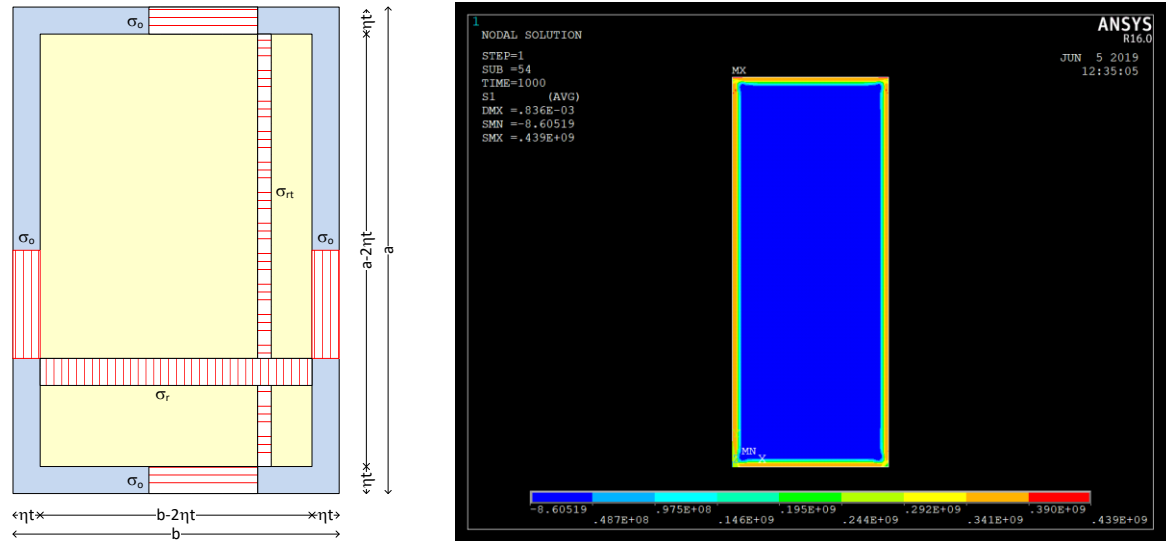


Figure 1. Idealized residual stress model for an unstiffened perfect plate welded in the edges (left) and results by FE thermal analysis (right).

2.1.2. Implementation of residual stresses by FE modelling

The study of plates with initial residual stresses requires, as a first step, the introduction of the residual stresses pattern as described in Figure 1. There are several ways to achieve such objective [15–17], some of them very complex and computationally costly.

The present method allows to perform the thermal analysis to introduce residual stresses, followed by structural analysis without intermediate steps and been computationally very efficient.

The plate model in finite elements (FE) is divided by parts as described in Figure 1 where the lateral strips representing the heat affected zone (HAZ) have a width ηt . The characterization of the material for such analysis requires in general the information about the mechanical properties for different temperatures and the respective coefficient of thermal expansion.

The present method only uses the modulus of elasticity, the yield stress at room temperature and the respective coefficient of thermal expansion, considering an elastic-perfectly plastic deformation without hardening. The thermal loading is inputted by rising the temperature into the HAZ strips to a reference temperature, in this study 500°C, followed by a decrease to room temperature, while the temperature in the rest of the plate is kept at room temperature along the whole process [14].

In the first step, the temperature rises to 500°C in HAZ and it generates plasticity in compression in the lateral strips and some tensile stresses in the central part of the plate. During the second step, cooling of the HAZ strips, the state of internal stresses reverses and, in the end, one has tensile yield stress in the lateral strips and residual compressive stresses in the central part.

This simplified procedure allows to obtain the required residual stress pattern and proceed directly to a structural analysis in a sequential FEA load step. It is recommended to use a mesh size less than half of the HAZ width, preferably $\eta t/3$. The peak temperature needs to be bigger than a reference value given by:

$$\Delta T = \frac{2\sigma_o}{\alpha_T E} \quad (3)$$

which is the minimum difference of temperature required to pass from yield stress in compression to yield stress in tension on HAZ strips. For mild steel, reference values in equation are σ_o of 240 MPa, E is 210 GPa and the coefficient of thermal expansion α_T is $1.1 \times 10^{-5} \text{ } ^\circ\text{C}^{-1}$ resulting in a minimum difference of temperatures ΔT of 208°C.

2.1.3. Implementation of procedure in FE modelling

The complete procedure is composed in four stages: 1. Heating of HAZ strips to 500°C; 2. Cooling of HAZ strips to room temperature (T=20°C); 3. Initial shortening; 4. Compressive displacement in top of plate up to collapse and beyond. The procedure is presented in Figure 2.



Figure 2. FE loading procedure and steps.

The step 3 is very important and it warranties that part of residual stresses are not dissipated in the beginning of step 4. Its value must be bigger than the residual displacement at the top in the final of thermal analysis, step 2. Figure 3 shows the distribution of stresses in the end of steps 1, 2 and at collapse in step 4 for the top layer. As it can be seen, in the end of 1st step the HAZ strips are in compression at yield stress while they are in tension after plasticity in the end of the 2nd step. In the whole process the residual stress pattern varies from point to point due to the presence of initial imperfections and deformations developed during the loading.

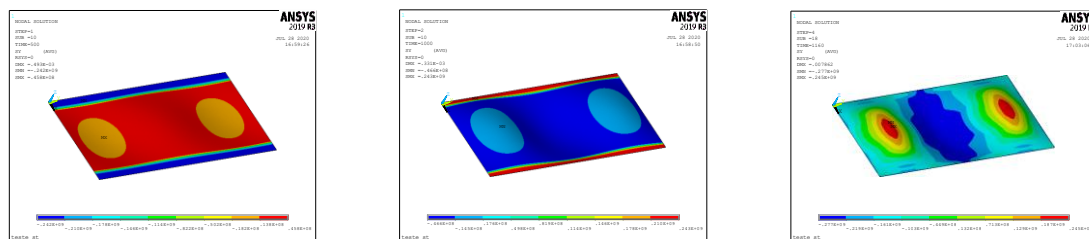


Figure 3. Example of state of stresses of a plate after HAZ heating (left), HAZ cooling (middle) and at collapse (right).

2.2 Parameters affecting the strength of unstiffened plates

The parameters that most affect the structural behavior in compression represented by the load-shortening curves (LSC) and the ultimate strength, are the plate slenderness, initial geometric imperfections, residual stresses, boundary conditions and complexity of loading.

2.2.1. Plate slenderness

The definition of the plate slenderness β results directly from the resolution of rectangular plate's buckling formulation where the elastic critical Euler's stress of a plate under axial compression is:

$$\frac{\sigma_{cr}}{\sigma_0} = k_{cr} \frac{\pi^2}{12(1-\nu^2)\beta^2} \quad (4)$$

β considers both the geometry of the plate and its material properties and is given by eq (5) while k_{cr} accounts for the mode of buckling having as minimum 4 when $m=a/b$.

$$\beta = \frac{b}{t} \sqrt{\frac{\sigma_0}{E}} \quad (5)$$

$$k_{cr} = \left(\frac{mb}{a} + \frac{a}{mb} \right)^2 \quad (6)$$

When the critical stress approaches or overlaps the yield stress, some plasticity is developed in some points of the plate and the ultimate stress of the plate becomes less than the critical one. Several proposals have been presented in the past for estimate the ultimate strength, some of them having the plate slenderness as unique parameter. Two important examples are Faulkner's (eq. (7)) and

Frankland's (eq. (8)) equations that are used as well to introduce the concept of effective width. The former is representative of the strength of simply supported welded plates [18] and the latter is used in IACS formulation in the definition of the effective width of the attached plate in a stiffened structural element [3].

$$\phi_u = \frac{\sigma_u}{\sigma_o} = \frac{2}{\beta} - \frac{1}{\beta^2} \text{ (for } \beta > 1) \quad (7)$$

$$\phi_u = \frac{\sigma_u}{\sigma_o} = \frac{2.25}{\beta} - \frac{1.25}{\beta^2} \text{ (for } \beta > 1.25) \quad (8)$$

Figure 4 compares these formulas showing that IACS equation predict higher strength under in-plane compression than Faulkner's approach which is eventually a consequence of the effect of residual stresses on the strength of the plates used in the database.

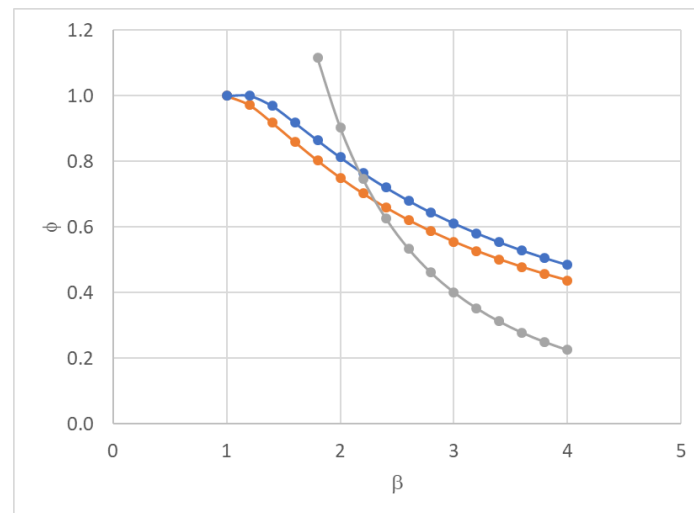


Figure 4. Strength of rectangular plates according to Faulkner, IACS and Euler equations.

2.2.2. Geometric imperfections

Several studies [19–24] proposed different values and formulas to estimate the amplitude of initial imperfections, most of them pointing out for the maximum value without consideration to the mode of imperfections.

In this work a reference value given by eq. (10) is considered and a wide range of amplitude around that value is used to estimate the relevancy of the parameter.

$$\frac{w_i}{t} = 0.1\beta^2 \quad (9)$$

It is considered different amplitudes and modes of imperfections corresponding to the expansion of the shape of imperfections into Fourier series that can be represented by:

$$w(x, y) = \sum \sum w_i \cdot \sin \frac{m\pi x}{a} \cdot \sin \frac{\pi y}{b} \quad (10)$$

The importance of the mode of imperfections is analyzed by considering the fundamental mode ($m=1$) which normally leads to stronger plates, and the critical one corresponding to the weaker plate. Since a/b is 2.5 in the models of this study, the critical mode m is 3.

2.1.2. Boundary conditions

The adoption of appropriate boundary conditions on each type of structure is of vital importance because the differences on structural behavior and strength can be very large between them. A plate element works normally associated with stiffeners and frames and its contribution to strength of the

structure depends on the restraining action of these elements both in terms of displacements and rotations.

One may consider 4 main classes of boundary conditions for plate elements belonging to panels:

- Unrestrained; all edges and tops are supported perpendicularly to the plate's plane, but in-plane movements along the edges are allowed and rotations are free.
- Restrained; all edges and tops are supported perpendicularly to the plate's plane, but in-plane movements along the edges are not allowed, called as fixed condition, and rotations are free.
- Constrained; all edges and tops are supported perpendicularly to the plate plane, in-plane movements of the edges are allowed but kept straight and rotations are free.
- Clamped; displacements and rotations are null.

Each of them leads to differences on the load-elongation curves, ultimate strength and ultimate strain, modes of collapse both in compression and tension. In terms of ultimate strength, the difference may be bigger than 20% in compression leading to completely different modes of collapse due to the development of transversal stresses induced by Poisson effect [25,26].

Unrestrained and constrained conditions warranties that the loading in uniaxial compression do not generate globally transversal loading in the lateral edges. Restrained conditions generate a biaxial state of stresses leading normally to stronger response of plate, with higher ultimate strength and difference collapse mode in certain cases [25]. Clamped conditions can be representative for very rigid framing system in panels which is not usual in ships structures, at least on the hull girder.

Due to the nature of stiffening on ship's panels, it is considered that the constraint condition is the most appropriate to represent the behavior of plate element belonging to ship's structures. Unrestrained are rather conservative and restrained conditions are too optimistic. Figure 5 shows the boundary conditions on the FE model used in this study.

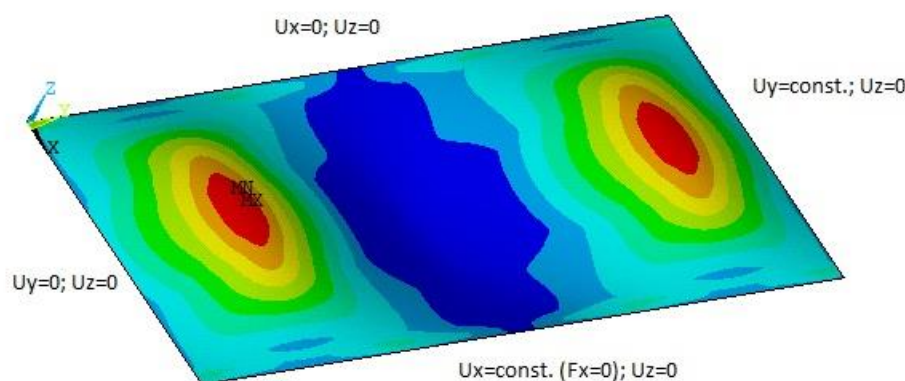


Figure 5. Boundary conditions on a rectangular plate loaded longitudinally (constraint conditions).

3. Results

The analysis of the influence of residual stresses on plate's behavior is performed by FE analysis considering a rectangular plate with length l of 1.5m and a width b of 0.6m resulting in an aspect ratio α of 2.5 as the basic model.

Four different thicknesses of the plate are considered: 20, 15, 10 and 8mm. These thicknesses are representative of different classes of plates in terms of elastoplastic behavior and buckling, respectively stocky, intermediate, slender and very slender plates with increase in the elastic instability in compression. The width to thickness ratio, b/t , is respectively 30, 40, 60 and 75.

At least 2 levels of initial geometric imperfections are considered for each group in order to evaluate its effect on the degradation of the ultimate strength in compression. Since the plate's structural behavior is very sensitive to the mode of initial imperfections, 2 modes are considered and compared, the fundamental ($m=1$) and the critical one ($m=3$).

The material is considered to have an elastic, perfectly plastic behavior with a Young modulus E of 210GPa and yield stress, σ_o , of 240MPa.

The boundary conditions in this study are simply supported in all edges. The edges remain straight during the loading path and the net load in the lateral edges is null which means that the loading is globally uniaxial, and a global transversal movement of lateral edges is allowed (constraint condition).

3.1 Stocky plates

In this group the plates have a slenderness β of 1.014 ($b/t=30$). The reference value for the initial imperfections of these plates, w_i , is 2mm according to equation (9). Three different levels of imperfections are considered: 2, 5 and 10mm, which corresponds to w_i/t ratio of 0.1, 0.25 and 0.5, respectively. Two modes of imperfections are analyzed: the fundamental, $m=1$, and the critical one, $m=3$. The effect of residual stresses for each plate is evaluated for three levels of width of the tensile strip at the edges: $\eta=0, 2$ and 3 to which corresponds a normalized residual stress level of 0.0, 0.15 and 0.25.

The load shortening curves are presented in Figure 6. The results of the ultimate stress normalized by the yield stress and the corresponding strain normalized by yield strain are presented in Table 1 for the different cases.

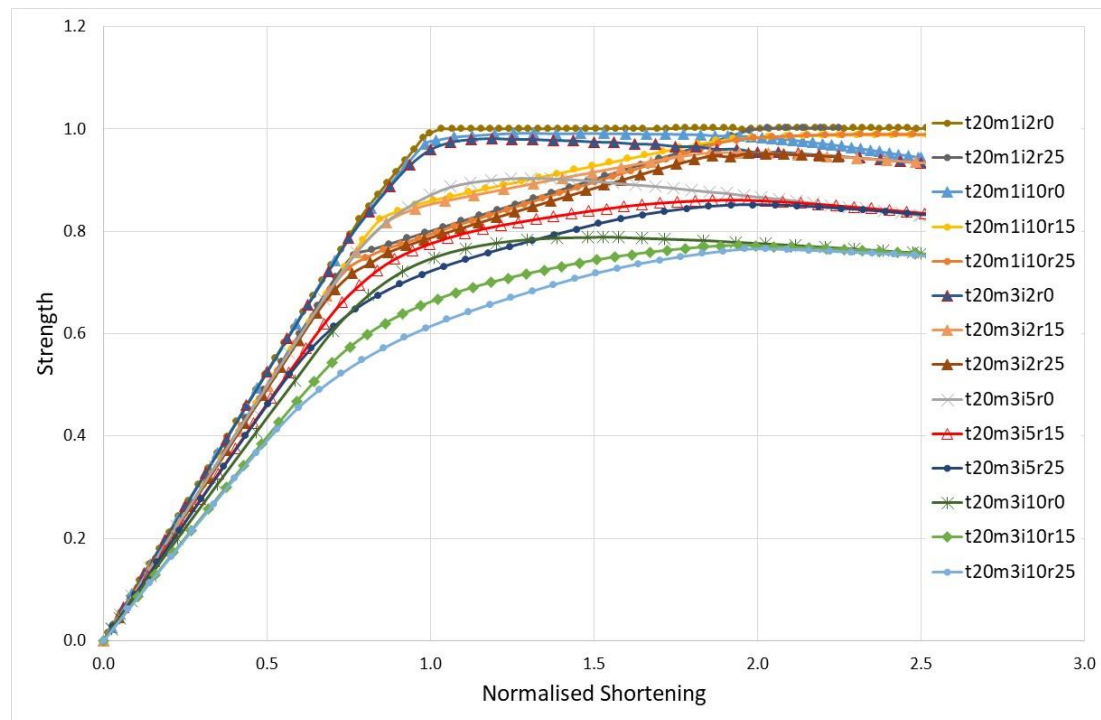


Figure 6. Load shortening curves for stocky plates with different initial imperfections in amplitude ($i=2, 5$ and 10mm) and mode ($m=1, 3$), and several levels of residual stresses ($r=0, 0.15$ and 0.25%)

The analysis of the curves and their maximum values allows to withdraw several conclusions. Plates with fundamental mode ($m=1$) have a behavior very similar to material behavior and do not suffer almost any degradation of strength with the increase of amplitude of imperfection. The ultimate strength maintains constant for large shortening. Residual stresses change the shape of residual stress free LSC in the range of normalized shortening from $1-\sigma_r/\sigma_o$ to 2 by an almost straight cut. The ultimate stress passes to occur at normalized ultimate shortening of 2.

One the other hand, plates with critical mode ($m=3$) suffer a large degradation of strength with the increase of the amplitude of initial imperfections. Nevertheless, the less imperfect one ($w_i=2\text{mm}$) has an ultimate strength close to the values found in plates with fundamental mode of imperfections.

The degradation of the ultimate strength due to increase on amplitude of imperfections is very important for this group of plates ($m=3$) and the ultimate strength can be quantified as:

$$\phi_u(\beta = 1.01; rs = 0\%) = 1.027 - 0.479 \frac{w_i}{t} \tag{11}$$

Table 1. Summary of data and main results for plates with $a=1.5m$, $b=0.6m$ and $t=20mm$

Identification	Mode i	w_i (mm)	w_i/t	η	Ultimate stress	Ultimate strain	Residual Stress %
t20m1i2r0	1	2	0.1	0	1.001	1.00	0
t20m1i2r25	1	2	0.1	3	1.002	2.00	0.25
t20m1i10r0	1	10	0.5	0	0.991	1.46	0
t20m1i10r15	1	10	0.5	2	0.989	2.36	0.15
t20m1i10r25	1	10	0.5	3	0.990	2.37	0.25
t20m3i2r0	3	2	0.1	0	0.982	0.98	0
t20m3i2r25	3	2	0.1	3	0.952	1.97	0.25
t20m3i5r0	3	5	0.25	0	0.904	1.31	0
t20m3i5r15	3	5	0.25	2	0.861	1.92	0.15
t20m3i5r25	3	5	0.25	3	0.851	1.99	0.25
t20m3i10r0	3	10	0.5	0	0.789	1.53	0
t20m3i10r15	3	10	0.5	2	0.772	1.94	0.15

The ultimate strain of the residual stresses free plate also suffers a shift with the increase in the amplitude of initial imperfections towards a normalized strain of 1.5, as shown in Figure 7.

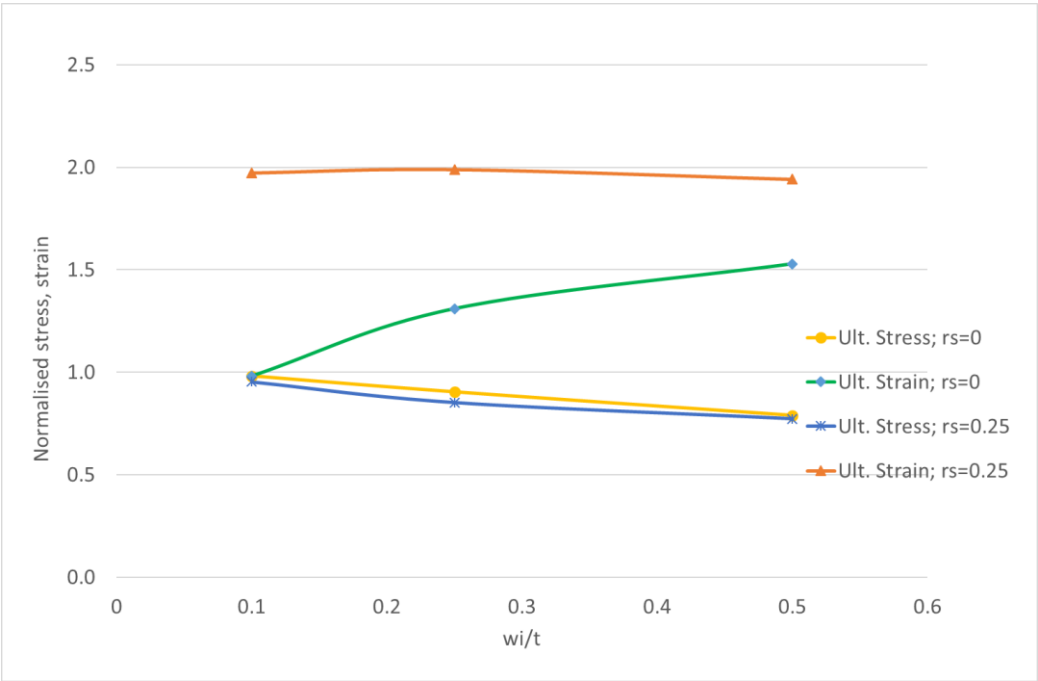


Figure 7. Variation of ultimate strength and corresponding normalized strain for plates with $t=20mm$, $m=3$ and no residual stresses.

Residual stresses have a similar effect to the one described previously for plate with $m=1$ by cutting the LSC to lower values in the same range of shortening. Finally, initial imperfections and residual stress seems to reduce the structural modulus of the plate in elastic range given by the slope

of LSC in Figure 6. The ultimate normalized strain in plates with residual stresses is close to 2, which is the limit of the effect of the tensile strips due to welding.

The load-shedding pattern, after the ultimate load on plates with residual stresses, follows the path of the similar residual stress free plate.

The ultimate strength of plates with residual stresses is given by:

$$\phi_u(\beta = 1.01; rs = 25\%) = 0.983 - 0.438 \frac{w_i}{t} \quad (12)$$

The degradation of ultimate strength due to the level of imperfections is lower by 8.6% in the plates with residual stresses (-0.438) than in plates free of residual stresses (-0.479).

3.2 Intermediate plates

The plates in this group have a slenderness β of 1.352 ($b/t=40$). The reference value for the initial imperfections of these plates w_i is 2.74mm according to equation (9). Three different levels of imperfections are considered: 2, 3 and 5mm, which corresponds to w_i/t ratio of 0.13, 0.2 and 0.33, respectively. The structural analysis concentrates on the critical mode, $m=3$. The effect of residual stresses for each plate is evaluated for three levels of the width of the tensile strip at the edges: $\eta=0, 2$ and 3 to which corresponds a normalized residual stress level of 0, 0.11 and 0.18.

The load shortening curves are presented in Figure 8. The results of the ultimate stress normalized by the yield stress and the corresponding strain normalized by yield strain are presented in Table 2 for the different cases. It is also included the results for a plate with imperfections in the fundamental mode for comparison.

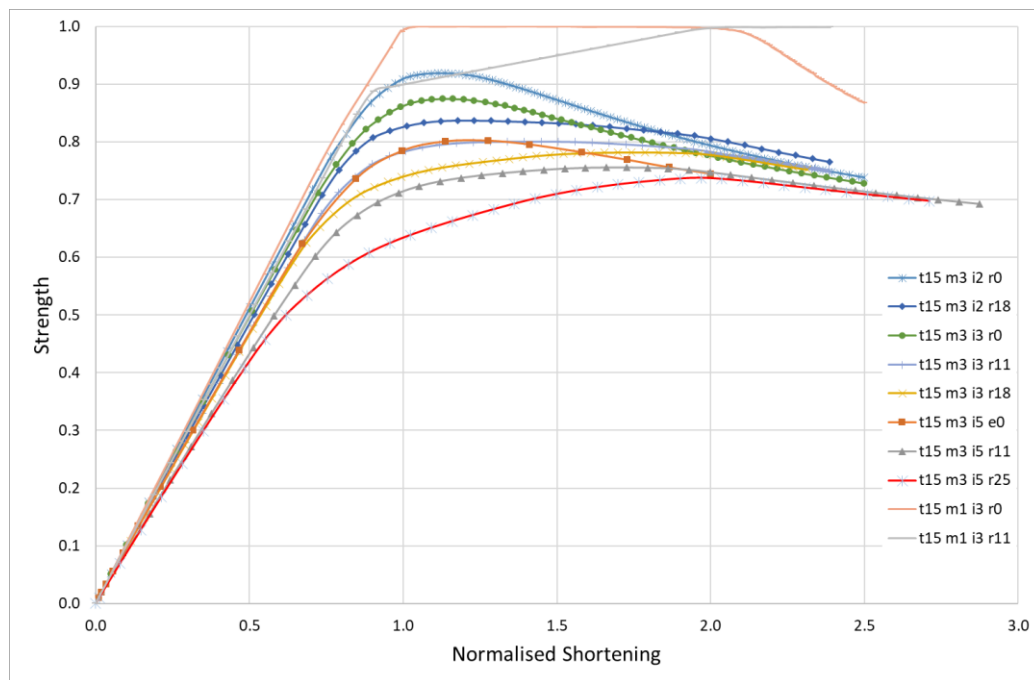


Figure 8. Load shortening curves for intermediate plates ($\beta=1.352$) with different initial imperfections in fundamental and critical mode and residual stresses.

Qualitatively the conclusions are very much in agreement with the ones described for stocky plates in relation to the increase in imperfections and residual stresses: degradation of ultimate strength, reduction of initial structural modulus and increase in ultimate strain, as may be seen in Figure 9.

The degradation of the ultimate strength due to increase on amplitude of imperfections is even bigger than for the stocky ones for this group of plates ($m=3$) and the ultimate strength of the residual stresses free plate can be quantified as:

$$\phi_u(\beta = 1.35; rs = 0\%) = 0.994 - 0.580 \frac{w_i}{t} \quad (13)$$

The equation for the ultimate strength for plates with residual stress of 18% of the yield stress is given by:

$$\phi_u(\beta = 1.35; rs = 18\%) = 0.891 - 0.474 \frac{w_i}{t} \quad (14)$$

One should note that the level of residual stresses does not affect much the ultimate strength of the plate that achieved at a normalized strain close to 2 and after that the LSC follows the residual stresses free plate LSC.

Table 2. Summary of data and main results for plates with $a=1.5m$, $b=0.6m$ and $t=15mm$

Identification	Mode i	w_i (mm)	w_i/t	η	Ultimate stress	Ultimate strain	Residual Stress %
t15m1i3r0	1	3	0.2	0	1.000	1.402	0.00
t15m1i3r11	1	3	0.2	2	0.999	2.114	0.11
t15m3i2r0	3	2	0.13	0	0.919	1.113	0.00
t15m3i2r18	3	2	0.13	3	0.837	1.231	0.18
t15m3i3r0	3	3	0.2	0	0.874	1.129	0.00
t15m3i3r11	3	3	0.2	2	0.801	1.449	0.11
t15m3i3r18	3	3	0.2	3	0.782	1.742	0.18
t15m3i5r0	3	5	0.33	0	0.802	1.276	0.00
t15m3i5r11	3	5	0.33	2	0.755	1.660	0.11
t15m3i5r25	3	5	0.33	4	0.737	1.969	0.25

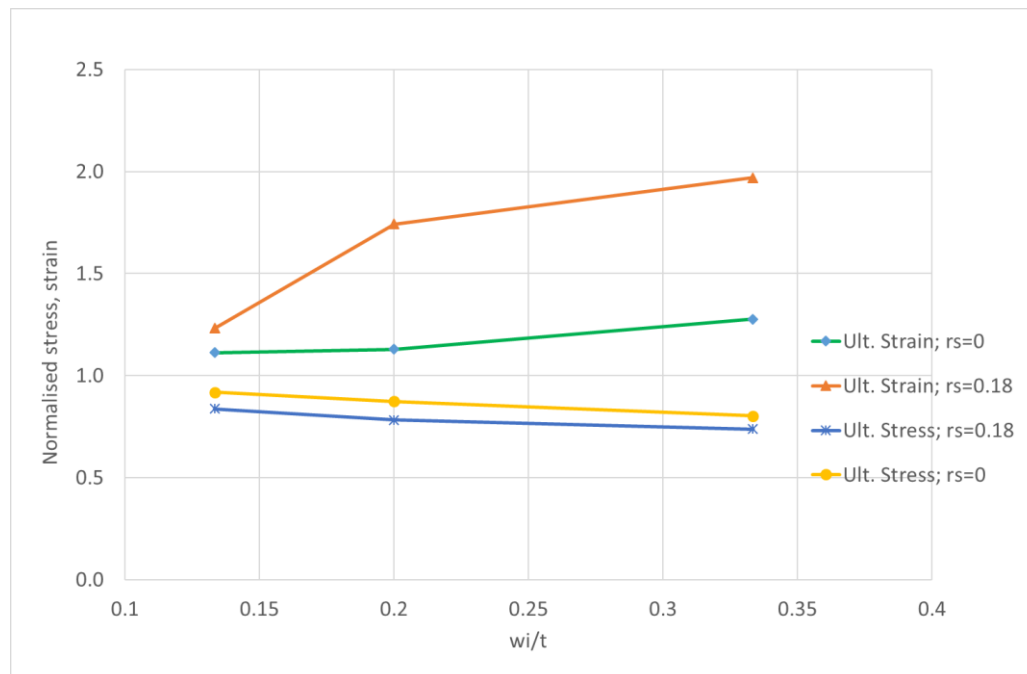


Figure 9. Variation of ultimate strength and corresponding normalized strain for plates with $t=15mm$, $m=3$ and no residual stresses.

3.3 Slender plates

The plates in this group have a slenderness β of 2.03 ($b/t=60$). The reference value for the initial imperfections of these plates w_i is 4.11mm according to equation (9) corresponding to a w_i/t ratio of

0.411. Three levels of imperfections, $w_i=2, 5$ and 6mm and residual stresses of $0, 0.07$ and $0.15\sigma_y$ are considered. The LSC's of this group of plates are shown in Figure 10. Table 3 presents the main results of the ultimate strength and the corresponding normalized shortening for the different cases.

The effects of residual stresses are the reduction the initial structural modulus of the plate, the delay of collapse to normalized shortening in the range of 1.7 to 1.9 , as presented in Figure 11. It is also marked the existence of the almost straight line due to the action of HAZ strips in the range 0.8 - 1.8 of normalized shortening.

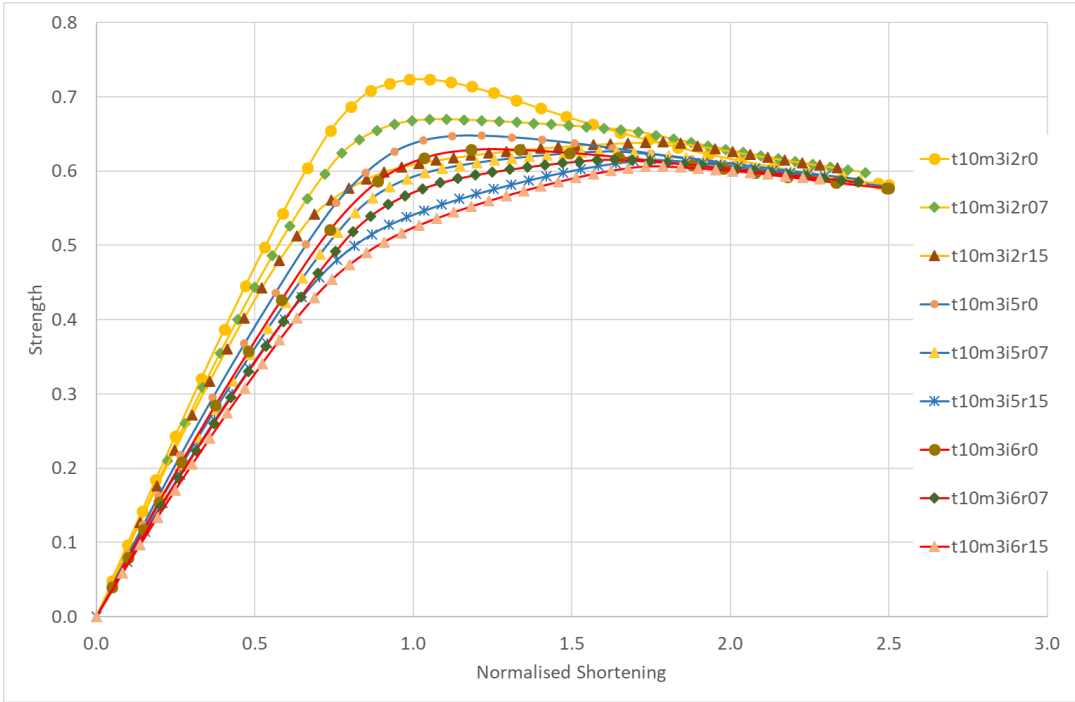


Figure 10. Load shortening curves for intermediate plates ($\beta=2.03$) with different initial imperfections in critical mode and residual stresses.

Table 3. Summary of data and main results for plates with $a=1.5\text{m}$, $b=0.6\text{m}$ and $t=10\text{mm}$

Identification	Mode i	w_i (mm)	w_i/t	η	Ultimate stress	Ultimate strain	Residual Stress %
t10m3i2r0	3	2	0.2	0	0.724	1.052	0.00
t10m3i2r07	3	2	0.2	2	0.670	1.105	0.07
t10m3i2r15	3	2	0.2	4	0.639	1.787	0.15
t10m3i5r0	3	5	0.5	0	0.648	1.215	0.00
t10m3i5r07	3	5	0.5	2	0.626	1.641	0.07
t10m3i5r15	3	5	0.5	4	0.615	1.748	0.15
t10m3i6r0	3	6	0.6	0	0.629	1.183	0.00
t10m3i6r07	3	6	0.6	2	0.615	1.635	0.07
t10m3i6r15	3	6	0.6	4	0.606	1.733	0.15
t10m3i8r0	3	8	0.8	0	0.598	1.432	0.00
t10m3i8r15	3	8	0.8	4	0.588	1.756	0.15

The degradation of the ultimate strength due to increase on amplitude of imperfections is much smaller than in the previous groups, stocky and intermediate ones and the ultimate strength of residual stress free plate can be quantified as:


$$\phi_u(\beta = 2.03; rs = 0\%) = 0.761 - 0.212 \frac{w_i}{t} \quad (15)$$

303 The ultimate strength for plates with residual stress of 15% of the yield stress is given by:

$$\phi_u(\beta = 2.03; rs = 15\%) = 0.657 - 0.084 \frac{w_i}{t} \quad (16)$$

304 Imperfections degrade the ultimate strength by a factor of 0.212 in the case of residual stress free
305 plate while this factor is 0.58 in the same case for intermediate plates which is 2.7 times more.

306 The ultimate strength of the plates with residual stresses is almost constant with the variation of
307 residual stresses and initial imperfections in critical mode.

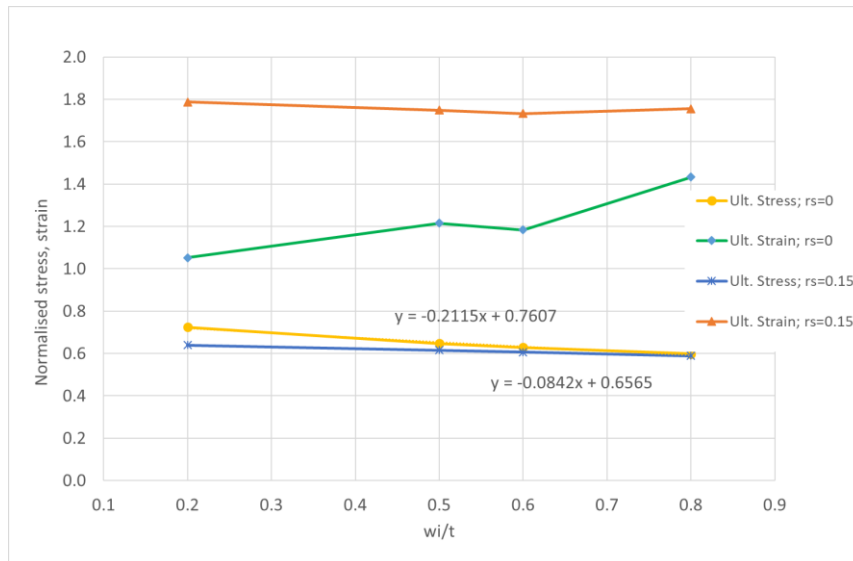

308
309 Figure 11. Variation of ultimate strength and corresponding normalized strain for plates with
310 t=10mm, m=3 and no residual stresses.

311 3.3 Very slender plates

312 The plates in this group have a slenderness β of 2.54 ($b/t=75$). The reference value for the initial
313 imperfections of these plates w_i is 5.14mm according to equation (9) and a w_i/t ratio of 0.643. Three
314 levels of imperfections, $w_i=2, 5$ and 6mm and residual stresses of 0, 0.06 and 0.12 σ_y are considered.

315 The LSC's of this group of plates are shown in Figure 12. Table 4 presents the main results of the
316 ultimate strength and the corresponding normalized shortening for the different cases.

317 Table 4. Summary of data and main results for plates with $a=1.5m$, $b=0.6m$ and $t=8mm$

Identification	Mode i	w_i (mm)	w_i/t	η	Ultimate stress	Ultimate strain	Residual Stress %
t8m3i2r0	3	2	0.25	0	0.627	1.063	0.00
t8m3i2r07	3	2	0.25	2	0.593	1.505	0.06
t8m3i2r15	3	2	0.25	4	0.582	1.654	0.12
t8m3i5r0	3	5	0.63	0	0.575	1.289	0.00
t8m3i5r07	3	5	0.63	2	0.569	1.544	0.06
t8m3i5r15	3	5	0.63	4	0.563	1.668	0.12
t8m3i6r0	3	8	1.00	0	0.542	1.633	0.00
t8m3i6r07	3	8	1.00	4	0.542	1.792	0.12

318 Since the slenderness of this group is very high the ultimate strength of the plates is small but
319 does not degrade much with increase in imperfections and residual stresses, as presented in Figure

13. In fact, the ultimate strength of plates with residual stresses is almost insensitive to imperfections as confirmed by the very low coefficient 0.044 in eq. (18), but the pre-collapse behavior is rather dissimilar for each of them in terms of structural modulus and softening until collapse, Figure 12.

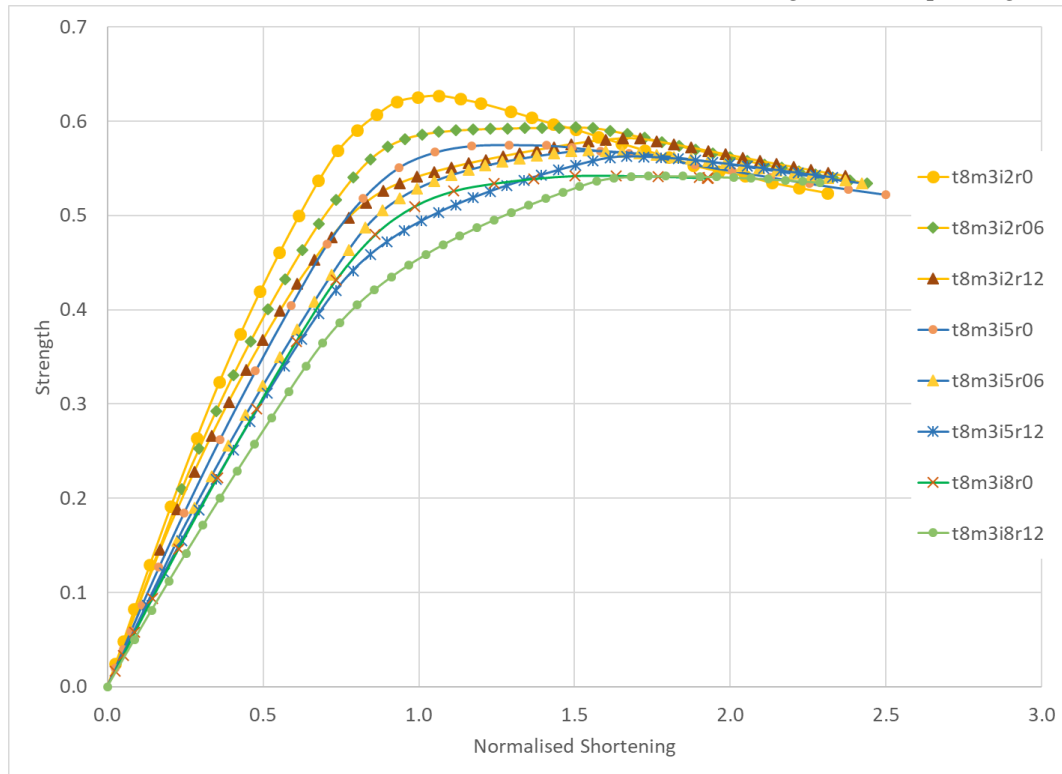


Figure 12. Load shortening curves for very slender plates with different amplitude of initial imperfections in critical mode and residual stresses

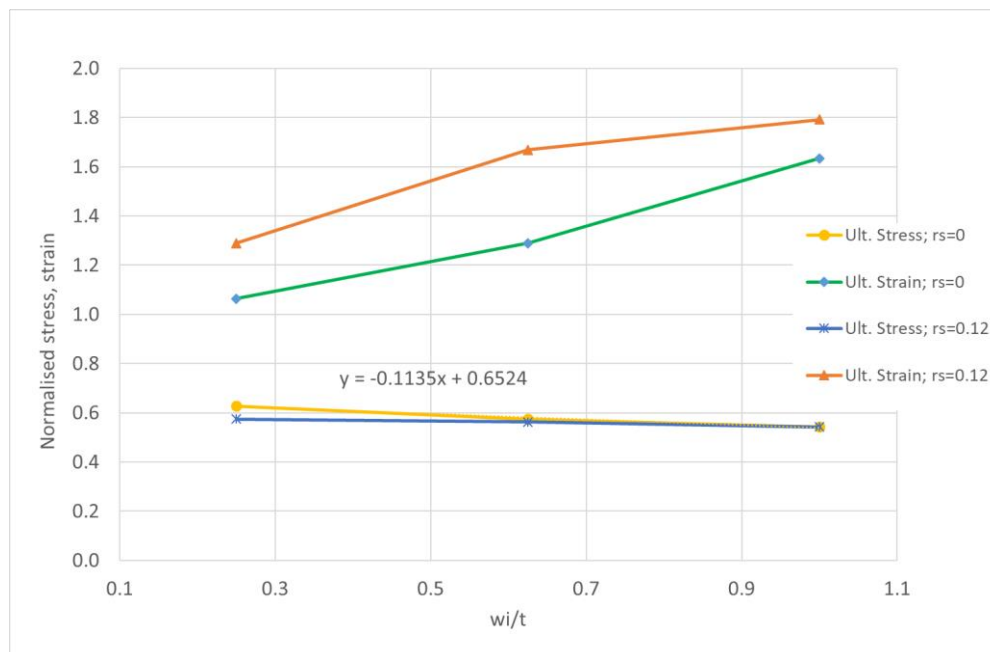


Figure 13. Variation of ultimate strength and corresponding normalized strain for plates with $t=8\text{mm}$, $m=3$ and residual stresses with $\eta=0, 4$.

The ultimate normalized shortening of residual stress free plates tends to be greater than in previous groups and the one for plates with residual stresses is much smaller than the values between

1.8 and 2 found previously. This is result of the very low level of loading carrying capacity of these very slender plates.

The degradation of the ultimate strength due to increase on amplitude of imperfections is the smallest of all groups of plates with critical mode considered in this study and the ultimate strength can be quantified as:

$$\phi_u(\beta = 2.54; rs = 0\%) = 0.652 - 0.114 \frac{w_i}{t} \quad (17)$$

The equation for the ultimate strength for plates with residual stress of 12% of the yield stress is given by:

$$\phi_u(\beta = 2.54; rs = 12\%) = 0.587 - 0.044 \frac{w_i}{t} \quad (18)$$

This results confirm the conclusion of Ueda *et al.* [27] that welding residual stresses reduce the buckling strength remarkably, but have a little effect on the ultimate strength when the plate is thin.

4. Discussion

The present methodology proved to be very efficient on the structural analysis of plate elements with residual stresses. The method is only based on mechanical and thermal properties of the material and allows to obtain the analysis in short time of computation with high accuracy.

The results obtained show how the main parameters already indicated in section 3 affect the load-shortening curves (LSC), the ultimate strength and the corresponding ultimate shortening. The results were partially analyzed for each group of plates and formulas were presented for the ultimate strength of imperfect plates with and without residual stresses. Three main aspects need deeper discussion:

- Effect of slenderness on ultimate strength and correlation with imperfections and residual stresses;
- Dependency of structural tangent modulus from initial conditions of plate, i.e., geometry, imperfections and residual stresses;
- Effect of residual stresses in the LSC's.

The analysis performed for each group of plates indicates that the main parameters may affect the ultimate strength largely, in some cases by more than 20%. Two modes of imperfections ($m=1, 3$) were considered in some groups of plates to demonstrate this variation. For the stocky plates ($t=20\text{mm}$) without residual stresses, one may find a difference of 2% or 20% depending on the amplitude of imperfections, 2mm and 10mm respectively.

4.1 Effect of slenderness on ultimate strength and correlation with imperfections and residual stresses

The dependency of ultimate strength on slenderness may be obtained by treating the strength equations for each group in integrated manner. Each equation has a constant term that represents the strength of virtual 'perfect' plate in terms of imperfections and a term related to the degradation of strength due to amplitude of imperfections. Collecting such information one may present the relationship between strength and slenderness, as plotted on Figure 14 where some usual strength formulation are also plotted for comparison.

The curves for the influence of imperfections (eq. (9): no rs) and for effect of residual stresses alone ('Perfect plate: $rs>10\%$) are very closed which means that the effect of imperfections or residual stresses individually are of the same order in comparison to virtual 'perfect' plate ('Perfect' plate: no rs). Nevertheless, the corresponding ultimate shortening and the LSC for each case are completely different.

The comparison of the plates with average imperfections but no residual stresses (eq. (9): no rs) or with residual stresses (eq. (9): $rs>10\%$) allows to conclude that the degradation of strength due to residual stresses is more marked in intermediate plates in the range of slenderness from 1.2 to 1.7. Thin plates are little affect by residual stresses as mentioned previously.

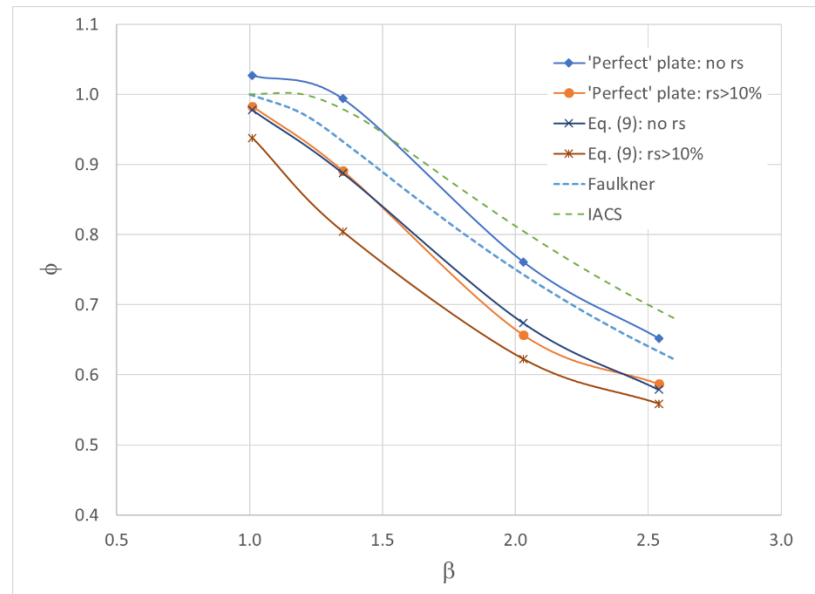


Figure 14. Comparison of results for constraint plates considering residual stress and initial imperfections and standard formulations.

Curve 'eq. (9): rs>10%' is representative of real welded plate and may be given by:

$$\phi_u \left(\beta; \frac{w_i}{t} = 0.1\beta^2; rs > 10\% \right) = 0.309 + \frac{0.645}{\beta} \quad (19)$$

One aspect of concern in relation to structural codes is that all curves with exception for the 'Perfect' plate: no rs' curve, are well below the Faulkner and IACS formulation. This may be result of boundary conditions of the tests that are the database for such formulations, inducing fixed conditions or some degree of rotational restraining.

4.2 Dependency of structural tangent modulus from initial conditions

The comparison of initial stage of LSC for different initial imperfections with the same slenderness leads to the conclusion that plates present different structural tangent modulus in elastic range, where structural tangent modulus is the slope of the LSC, $\delta\sigma/\delta\varepsilon$. This means that the plate suffers a loose of effectiveness in early stages of loading due to out-of-plane of initial imperfections. With the increase in the compressive loading the out-of-plane geometry of plate increases, generating additional loss in effectiveness. The effectiveness depends not only on the level of imperfections but also on the slenderness of the plate. Figure 15 plots the normalized tangent modulus of the plate for different thickness, $t=15\text{mm}$ at left and $t=8\text{mm}$ at right, for different amplitude of initial imperfections and residual stresses.

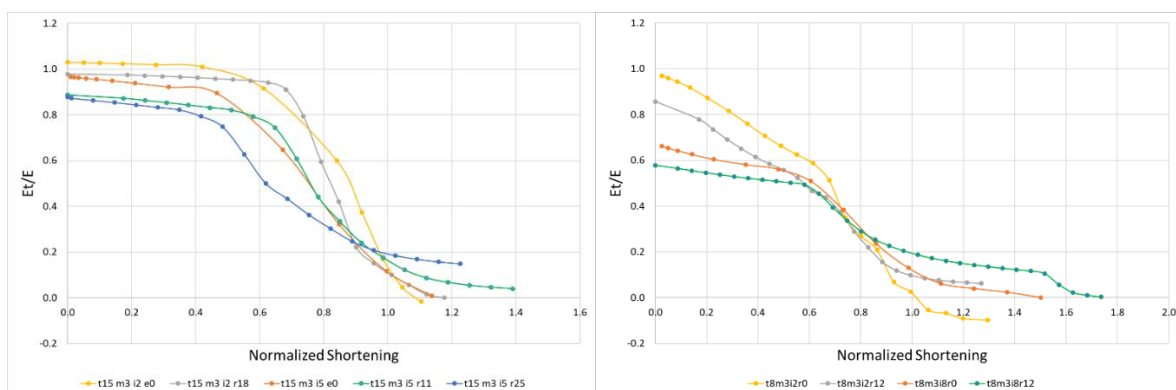


Figure 15. Variation of tangent modulus for intermediate (left) and very slender plates (right).

The reduction in effectiveness at early stage of load is greater in slenderer plates and increases with w_i in both cases, as seen by comparison of yellow and red curves in both graphics. The presence of residual stresses represents a further reduction on initial effectiveness measured as E_i/E . The total reduction can be very high representing a great softening of the structural element in elastic range.

This aspect requires further investigation in the future research because it may have consequences on the response of 3-D structures like the hull girder under longitudinal bending.

4.3 Effect of residual stresses in the LSC's

The results obtained for imperfect plates with residual stresses confirms the hypotheses adopted by Gordo and Guedes Soares [4] to generate predictive LSC's for unstiffened and stiffened plates, $\phi_{pl}(\varepsilon)$. In such work, LSC are obtained by the product of the effective width of the plate without residual stresses at each level of loading, $\phi_{ef}(\varepsilon)$, and a modified material behavior that includes the effect of the tensile strips in HAZ, $\phi_{mat+rs}(\varepsilon)$, reading as:

$$\phi_{pl}(\varepsilon) = \phi_{ef}(\varepsilon) \cdot \phi_{mat+rs}(\varepsilon) \quad (20)$$

Figure 16 shows $\phi_{mat+rs}(\varepsilon)$ for compression and tensile loading. This response is very well reproduced by the stocky plates presented in this study, Figure 6, where the effectiveness $\phi_{ef}(\varepsilon)$ is close to 1. In all other groups of plates, the behavior reproduced by the red dot line is present but curves, in the range of strain affected by residual stresses, are not totally straight due to reduction on $\phi_{ef}(\varepsilon)$.

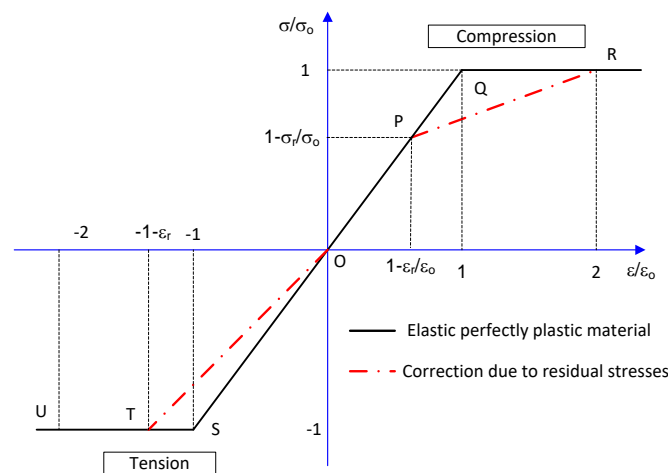


Figure 16. Average stress-strain curve for an unstiffened plate with and without residual stresses

Furthermore, $\phi_{ef}(\varepsilon)$ proposed in [4] was based on Faulkner formulation. For the prediction of LSC of unstiffened plates with average imperfections in critical mode and constrained edges, curves from Figure 14 should be used, in particular the curve 'eq. (9): no rs' representative of plates with average imperfections and no residual stresses.

5. Conclusions

A methodology to evaluate the performance of welded structural element was presented and shows to be efficient and reliable in the study of unstiffened plate elements under compression.

The parameters used in this study, slenderness, residual stresses, mode and amplitude initial imperfections, prove to be of high importance in the prediction of the ultimate strength but also in the response prior to collapse. The variation in ultimate strength of plates due to the change of magnitude of one parameter alone may reach high values.

Residual stresses affect very much the pre-collapse behavior of the plates but the ultimate strength tends to be the same keeping other parameters constant. The corresponding ultimate strain

is much higher than in case of residual stresses free plate, which means that one has a softer response with increase in residual stresses level.

Both residual stresses and initial imperfections affect the initial slope of LSC, structural tangent modulus, and it may affect the performance of 3-D structures, so it should be considered in the future.

Future application of this methodology involves the study of the structural behavior of welded stiffened plates and 3-D structures considering different loading conditions.

Funding: This research received no external funding

Conflicts of Interest: The author declares no conflict of interest.

References

- Gordo, J.; Guedes Soares, C.; Faulkner, D. Approximate assessment of the ultimate longitudinal strength of the hull girder. *Journal of Ship Research* **1996**, *40*, 60–69.
- Yao, T.; Nikolov, P. Progressive Collapse Analysis of a Ship's Hull under Longitudinal Bending. *Journal of the Society of Naval Architects of Japan* **1991**, 449–461, doi:10.2534/jjasnaoe1968.1991.170_449.
- IACS UR S - Strength of Ships Available online: <http://www.iacs.org.uk/publications/unified-requirements/ur-s/>.
- Gordo, J.; Soares, G. Approximate load shortening curves for stiffened plates under uniaxial compression. *Integrity of Offshore Structures-5* **1993**, 189–211.
- Okada, T.; Caprace, J.D.; Estefen, S.F.; Han, Y.; Josefson, L.; Kvasnytsky, V.F.; Papazoglou, V.; Race, J.; Roland, F.; Schipperen, I.; et al. Committee V.3- Materials and Fabrication Technology. In *17th International Ship and Offshore Structures Congress*; 2009; Vol. 2, pp. 137–200.
- Leggatt, R.H. Residual stress in welded structures. *International Journal of Pressure Vessels and Piping* **2008**, *85*, 144–151, doi:10.1016/j.ijpvp.2007.10.004.
- Lindgren, L.-E. Finite element simulation of welding Part 3: Efficiency and integration. *Journal of Thermal Stresses* **2001**, *24*, 305–334, doi:10.1080/01495730151078117.
- Runesson, K.; Skyttebol, A.; Lindgren, L.-E. Nonlinear finite element analysis and applications to welded structures. In *Comprehensive Structural Integrity*; Elsevier: Oxford, UK, 2003; Vol. 3 Numerical and Computational Methods, pp. 255–320.
- Dong, P. Residual stresses and distortions in welded structures: a perspective for engineering applications. *Science and Technology of Welding and Joining* **2005**, *10*, 389–398, doi:10.1179/174329305X29465.
- Gordo, J.M.; Guedes Soares, C. Experimental evaluation of the ultimate bending moment of a box girder. *Marine Systems & Ocean Technology* **2004**, *1*, 33–46, doi:10.1007/BF03449192.
- Gordo, J. Residual stresses relaxation of welded structures under alternate loading. In *Developments in maritime transportation and exploitation of sea resources*; Taylor & Francis, 2013; pp. 321–328.
- Tekgoz, M.; Garbatov, Y.; Soares, C. Finite element modelling of the ultimate strength of stiffened plates with residual stresses. In *Analysis and Design of Marine Structures*; Romanoff, J., Ed.; CRC Press, 2013; pp. 309–317 ISBN 978-1-138-00045-2.
- Launert, B.; Li, Z.; Pasternak, H. Development of a new method for the direct numerical consideration of welding effects in the component design of welded plate girders. In *Proceedings of the Advances in Engineering Materials, Structures and Systems: Innovations, Mechanics and Applications*; Cape Town, 2019.
- Gordo, J.M.; Teixeira, G. A simplified method to simulate residual stresses in plates. In *Proceedings of the Martech2020*; Lisbon, 2020 (in press).
- Chen, B.-Q.; Hashemzadeh, M. Numerical analysis of the effects of weld parameters on distortions and residual stresses in butt welded steel plates. In *Developments in Maritime Transportation and Exploitation of Sea Resources*; Soares, C., Peña, F., Eds.; CRC Press, 2013; pp. 309–320 ISBN 978-1-138-00124-4.
- Pasternak, H.; Launert, B.; Kannengießer, T.; Rhode, M. Advanced Residual Stress Assessment of Plate Girders Through Welding Simulation. *Procedia Engineering* **2017**, *172*, 23–30, doi:10.1016/j.proeng.2017.02.013.
- Hashemzadeh, M.; Garbatov, Y.; Guedes Soares, C. Numerical stress-strain analysis of butt-welded plates during the welding process. In *Developments in the Collision and Grounding of Ships and Offshore Structures*; Guedes Soares, C., Ed.; CRC Press, 2019; pp. 157–162 ISBN 978-1-00-300242-0.

18. Faulkner, D. A Review of Effective Plating for use in the Analysis of Stiffened Plating in Bending and Compression. *Journal of Ship Research* **1975**, *19*, 1–17.
19. Guedes Soares, C. Design equation for the compressive strength of unstiffened plate elements with initial imperfections. *Journal of Constructional Steel Research* **1988**, *9*, 287–310, doi:10.1016/0143-974X(88)90065-X.
20. Bonello, M.A.; Chryssanthopoulos, M.K.; Dowling, P.J. Probabilistic strength modelling of unstiffened plates under axial compression. In Proceedings of the 10th International Conference on Offshore Mechanics and Arctic Engineering (OMAЕ); ASME: Stavanger, Norway, 1991; Vol. 2, pp. 255–264.
21. Carlsen, C.A.; Czujko, J. The specification of tolerances for post welding distortion of stiffened plates in compression. *The Structural Engineer* **1978**, *56*, 133–141.
22. Antoniou, A.C. On the maximum deflection of plating in newly built ships. *Journal of Ship Research* **1980**, *24*, 31–39.
23. Antoniou, A.C.; Lavidas, M.; Karvounis, G. On the shape of post-welding deformations of plate panels in newly built ships. *Journal of Ship Research* **1984**, *28*, 1–10.
24. Kmiecik, M.; Jastrzębski, T.; Kuźniar, J. Statistics of ship plating distortions. *Marine Structures* **1995**, *8*, 119–132, doi:10.1016/0951-8339(94)00014-J.
25. Gordo, J.M. Effect of initial imperfections on the strength of restrained plates. *Journal of Offshore Mechanics and Arctic Engineering* **2015**, *137*, doi:10.1115/1.4030927.
26. Gordo, J.M.; Soares, C.G. Degradation of long plate's ultimate strength due to variation on the shape of initial imperfections. In *Towards Green Marine Technology and Transport*; CRC Press, 2015; pp. 365–374.
27. Ueda, Y.; Yasukawa, W.; Yao, T.; Ikegami, H.; Ohminami, R. Effect of Welding Residual Stresses and Initial Deflection on Rigidity and Strength of Square Plates Subjected to Compression (Report II). *Transactions of JWRI* **1997**, *6*, 33–38.