

Adherence Kinetics of a PDMS Gripper with Inherent Surface Tackiness

Umut D. Çakmak^a, Michael Fischlschweiger^b, Ingrid Graz^c and Zoltán Major^a

^aJohannes Kepler University Linz, Institute of Polymer Product Engineering, Altenbergerstrasse 69, 4040 Linz, Austria

^bClausthal University of Technology, Chair of Technical Thermodynamics and Energy Efficient Material Treatment, Agricolastrasse 4, 38678 Clausthal-Zellerfeld, Germany

^cJohannes Kepler University Linz, School of Education, Altenbergerstrasse 69, 4040 Linz, Austria

umut.cakmak@jku.at

Telephone: +43 732 2468 6596

Fax: +43 732 2468 6593

Abstract

Damage and fibre misalignment of woven fabrics during discontinuous polymer processing remain challenging. To overcome these, a promising switchable elastomeric adherence gripper is introduced here. The inherent surface tackiness is utilized for picking and placing large sheets. Due to the elastomer's viscoelastic material behavior, the surface properties depend on loading speed and temperature. Different peeling speeds result in different adherence strength of an interface between the gripper and the substrate. This feature is mechanically characterized and the viscoelastic behavior of the stamp is examined. Based on this experimental characterization, an empirical model is proposed. Furthermore, a discussion of the applicability and limitation of the elastomeric gripper is given.

Keywords: adherence; adhesion; surface tackiness; PDMS; characterization; organo sheet

1 Introduction

Picking and placing of limp solids (textile, woven fabrics, soft and flexible electronics) during assembling in manufacturing processes remain challenging. The transfer to the desired position has to be achieved without damaging or misaligning the limp solid (i.e., fiber unravel, pull out, contamination by the gripper etc.). A variety of technologies are available to overcome this challenge including vacuum suction, ingressive and adhesive grippers. The first two methods directly interact with the substrate's surface to be transferred and deform it to some extent; vacuum suction results in a local lift up of the limp substrate and ingressive picking in penetrating as well as interlocking with fibers. Adhesive gripper, on the other hand, adhere on the surface and the substrate itself is neither deformed nor misaligned. The adhesive part is usually an elastomer (e.g., copolymers, plasticized elastomers) with permanently tacky surface (Monkman and Shimmin 1991, Taylor 1995). A major drawback is that the adherence cannot be switched off and so the release of a substrate is critical for a textile or soft electronic part. Alternatively, transfer printing is utilized in the assembly of micro-/nanofabrication, where a silicon elastomer stamp with a viscoelastic

surface behavior is used to deliver a part from a donor to a receiver substrate (e.g., Cheng et al. 2012). At the interface of two elastic materials the adhesion force is rather a constant than tunable (Chen et al. 2013). However, the adhesion can depend on the peeling speed (high \rightarrow lifting and low \rightarrow release), the mechanical loading protocol (directional shearing induced delamination), temperature (laser pulse) or could be controlled by the surface relief structure as it was pointed out by Cheng et al. 2012, Li et al. 2012 and Chen et al. 2013. Extensive research efforts were presented to exploit the switchable adhesion in kinetically controlled (Feng et al. 2007, Cheng et al. 2013, Chen et al. 2013), shear assisted (Carlson et al. 2011, Cheng et al. 2012), direction controlled (Yang et al. 2012), laser driven non-contact (Li et al. 2012, Saeidpourazar et al. 2012) and microstructure enabled transfer printing (Bogue 2008, Kim et al. 2010, Wu et al. 2011, Kim et al. 2012). Also in robotics various designs for gripper are presented in order to pick up and handle arbitrary objects (e.g., Brown et al. 2010). This influence of external physical loadings on the elastomeric gripper is exploited in order to achieve a controlled picking and placing of a substrate. Important therefor is a pronounced viscoelastic behavior of the gripper with a high loading rate sensitivity of the mechanical properties.

However, up to now no detailed study on the viscoelastic characteristics of an elastomeric adhesive gripper is presented. A throughout understanding of the interplay between loading rate sensitivity of the gripper's bulk property and the inherent surface tackiness is of particular necessity to optimize the performance of an adhesive gripper. This paper presents an approach to gain insights to the temperature and loading rate dependent storage and dissipative (loss) properties by dynamic thermomechanical analyses of adhesive grippers as well as probe tack tests. The grippers under investigation are made of two different formulations of poly(dimethylsiloxane). Two woven fabrics (limp substrate) and two woven reinforced thermoplastic matrix composites (stiff substrate) are used to examine the gripper capabilities by the probe tack test. In "Material and Specimens" the material selection is briefly discussed and the specimen geometries for the mechanical characterization ("Experimental") presented. The loading rate dependent bulk and interface properties are modeled by simple linear viscoelastic theory assumptions and linear elastic fracture mechanics approach ("Experimental"). Based on the comprehensive experimental characterization the main mechanical features required for a viscoelastic adhesive gripper is summarized and presented in "Results and Discussion".

2 Materials and Specimens

The silicone rubbers (PDMS) under investigation were mixed and cured with two different base polymer:catalyst-ratios (PDMS-soft \rightarrow 20:1 and PDMS-hard \rightarrow 10:1). Critical thereby are the volume fraction of catalyst, curing temperature and time to achieve a solid material, whose surface exhibits tackiness high enough to pick up fabrics from a stack; the higher the tackiness the higher is the risk of contamination in a repetitive assembly process. Details about the fabrication of the material can be found in Cakmak et al. (2014a).

Two categories of specimens were prepared. One category was dedicated for the general mechanical characterization of PDMS by dynamic thermomechanical analysis (DTMA); the other was for component tests under an application-related measurement protocol as well as dynamic mechanical analysis (DMA). DTMA was performed with the "barbell" specimen and the component tests were investigated with a cylindrical stamp. Figure 1 shows the specimen geometries and the respective dimensions.

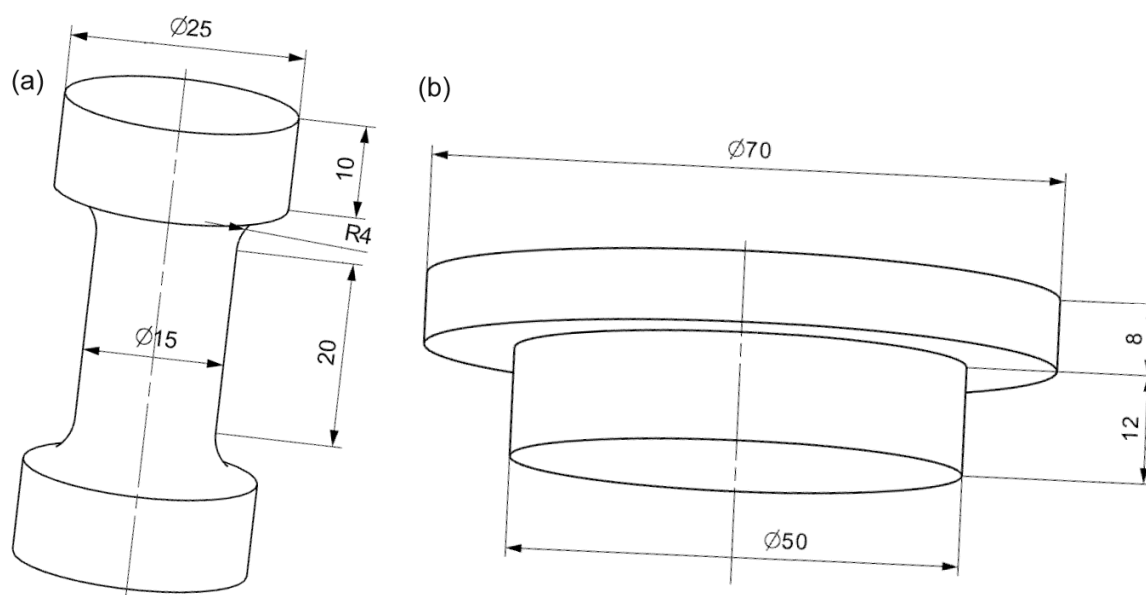


Figure 1 Specimen geometries: (a) barbell specimen and (b) gripper stamp specimen. Dimensions are in mm.

In the following section the experimental procedure (“Experimental”) for the characterization of the employed PDMS is presented. Also the design and the application-related experiments of the gripper stamp are reported there.

3 Experimental

After the initiation of the idea to adopt the rate and delamination loading dependent (switchable) adherence from transfer printing to a large-scale application of limp solids (fabrics). Motivated by these preliminary results, an experimental scheme limited to mechanical characterizations only was defined. All experiments were performed with an electromechanic/-dynamic actuator (TestBench, Bose Corp., ElectroForce Systems Group, MN, US).

3.1 Dynamic (thermo-) mechanical analysis (D(T)MA)

In order to gain more information concerning the viscoelastic nature of the PDMS, DTMA experiments were performed with the barbell specimen as well as the gripper stamp. A classical DTMA test procedure was defined including frequency dependent experiments from 1Hz to 16Hz under isothermal condition at seven different temperatures (-30°C to $+30^{\circ}\text{C}$). The loading mode was uniaxial tensile with a sinusoidal excitation of a mean strain level of 1% and a dynamic amplitude of 0.5%. A similar test procedure was performed with the gripper stamp in order to determine the viscoelastic behavior of the PDMS-soft material under component relevant condition. Component relevant condition means, thereby, a uniaxial compression dynamic mechanical analysis (DMA) just before delamination from the substrate. Compression DMA was examined at room temperature (22°C) with a mean level of -0.5mm and

amplitude of 0.5mm excitation from 0.1Hz to 47Hz. The data of the D(T)MA experiments were analyzed in WinTest DMA software (Bose Corp., ElectroForce Systems Group, MN, US) and the storage (E') as well as the transient (E'' and $\tan\delta=E''/E'$) mechanical material properties were exported for further analyses. The complex modulus E^* is given by Equation (1) and can be modeled by the well-known Prony series in the frequency ($\omega=2\pi f$) domain (Emri and Tschoegl 1995). In the series E_0 refer to the instantaneous modulus, τ_i is the relaxation time and $g_i=(E_{i-1}-E_i)/E_0$ the Prony series coefficient corresponding to the relaxation time.

$$E^*(\omega) = E'(\omega) + j \cdot E''(\omega) = E_0 \cdot \left(1 - \sum_i \frac{g_i}{1+(\tau_i \cdot a_T \omega)^2} + j \cdot \sum_i \frac{g_i \tau_i a_T \omega}{1+(\tau_i \cdot a_T \omega)^2} \right) \quad (1)$$

If the material's thermorheological behavior is simple, then the time-temperature superposition can be applied and resulting in master curve at a reference temperature (Tschoegl et al. 2002, Çakmak et al. 2014a). The temperature dependent shift factor a_T can be given by the well-known WLF-function (Williams et al. 1955):

$$|\log_{10}(a_T)| = 17.44 \cdot \frac{T-T_g}{51.6+T-T_g} \quad (2)$$

By inverse Laplace transformation of E^* into the time-domain, the relaxation modulus in time is obtained:

$$E(t) = E_0 \cdot \left(1 - \sum_i g_i \cdot (1 - e^{-t/\tau_i}) \right) = E_\infty \cdot \frac{1 - \sum_i g_i (1 - e^{-t/\tau_i})}{1 - \sum_i g_i} \quad (3)$$

where $E_\infty = E_0 (1 - \sum_i g_i)$ is the Young's modulus after infinite long time.

For the further analyses of the rate dependent adhesion, Equation (2) will be more convenient. From an experimental point of view, the DMA tests are preferable, as the storage and the transient viscoelastic behaviors are determined at once.

3.2 Probe tack test

The gripper stamp made of PDMS-soft was investigated in order to determine the rate dependent adherence properties for different substrate surfaces. Basically, the adherence test was a tensile delamination test (see Figure 2) at various pulling speeds (0.1mm/s up to 100mm/s) in accordance to the surface tack measurement setup of Çakmak et al. (2011). The stamp was pressed onto the substrate, held for 10s at -10N, followed by the pulling and delamination from the substrate surface, while the force F was measured. In a real application the stamp will lift up the substrate, but here the adherence was of particular interest and therefore the substrate was fixed. The substrates (100x100)mm² were attached to the support by means of double-side adhesive tape. To avoid inertia effects at high pulling speeds, the force was measured at the fixed side of the test setup. The maximum force corresponds to the fully delaminated stamp and is the limiting factor in-service for the considered pulling speed. If components with higher weight-forces are applied, the stamp is not capable to pick them up. Application relevant substrates were investigated and comprised dry carbon and glass fiber woven fabrics as well as poly(amide) based organo sheets reinforced with carbon and glass fiber woven.

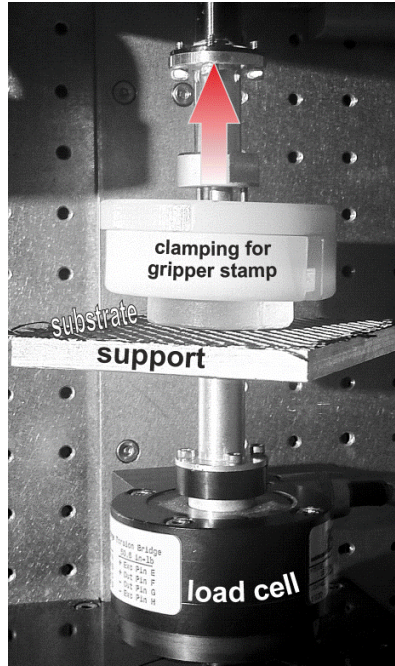


Figure 2 Component test setup

The delamination process is assumed to be driven mainly by the crack propagation from the edge of the stamp when a tractive force F was applied. For the sake of completeness, it should be mentioned, that the other mechanisms would be the crack propagation starting from inside at some interfacial defects and decohesion at theoretical contact strength (Carbone et al. 2011). The real delamination process will be rather a combination of the aforementioned mechanisms. However, visual observations of the experiments revealed that the crack initiation and propagation at the edge was more dominant. From fracture mechanical point of view, the stress singularity at the crack tip can be sufficiently described by the stress intensity factor K_I . When the stamp is fully propagated along the interface, the crack length is equal to the radius R of the stamp and K_I is given by:

$$K_I = \frac{F}{\pi R^2} \cdot \sqrt{\pi \cdot R} \cdot f \quad (4)$$

where F is the tractive force ($F/\pi R^2$ is the tractive stress σ) and f is the geometry coefficient and for a pillar shaped geometry $f = 1/2$. The energy needed to create an area surface during a plain strain loading is connected to the stress intensity factor K_I by:

$$G = \frac{K_I^2 \cdot (1 - \nu^2)}{2 \cdot E} \quad (5)$$

where ν is the Poisson's ratio and E is the Young's modulus. Since the material under investigation can be considered as incompressible ($\nu = 0.5$) and by combining Equation (4) with (5), the following relation can be found:

$$G_c(\nu, t_s(\nu)) = \frac{3 \cdot \sigma(\nu)^2 \cdot \pi \cdot R}{32 \cdot E(t_s)} \quad (6)$$

Equation (6) shows the critical energy release rate per area depending on the pulling speed v and the separation time t_s . The separation time is in turn a function of the pulling speed, meaning that the higher v , the lower t_s . This dependency is mainly driven by the viscoelastic nature of the stamp material and is also examined experimentally. To determine the actual value of the Young's Modulus $E(t_s)$, the knowledge of the separation time is crucial. The pulling velocity dependent tractive stress $\sigma(v)$ has to be obtained by the component tests and is mainly determined by the surface energies of each solid in contact and the surface interaction energy of them in direct contact (cf. Duprè energy of adhesion). It is expected that the investigated substrates have a different trend in terms of measured tractive stresses. However, the velocity dependency of $\sigma(v)$ is a response given by the stamp's viscoelastic nature and can be described by the following square root function sufficiently enough:

$$\sigma(v) = \sigma_0 \cdot \sqrt{1 + \left(\frac{v}{v_0}\right)^n} \quad (7)$$

When the square root function is determined by simply fitting the measured data and combining Equation (3) and (7) with (6) lead to the pulling speed dependent critical energy release rate:

$$G_c(v, t_s(v)) = G_0 \cdot \frac{1 + \left(\frac{v}{v_0}\right)^n \cdot (1 - \sum_i^3 g_i)}{1 - \sum_i^3 g_i \cdot (1 - e^{-t_s/\tau_r})} \quad (8)$$

where G_0 is the critical energy release rate near zero pulling speed v and infinite separation time t_s , v_0 is the reference pulling speed and n is the scaling exponent. Equation (8) is in accordance with the empirical form shown and utilized by Shull (2002) and Feng et al. (2007). The modification is related to the time dependent Young's modulus and so the Prony series is incorporated. Parameter identification of the function in Equation (8) is carried out based on the experimental data of the component tests as well as DMA. The model will be used to predict the critical energy release rate for the desired in-service pulling speed.

4 Results and Discussion

As was mentioned in the "Materials and Specimens" section, two different formulations were considered for the application of the gripper stamp. These two materials will be herein after referred to as PDMS-soft and PDMS-hard. Basically, only the PDMS-soft material was suitable for the use as gripper, however, basic viscoelastic characterization (D(T)MA) was performed for both of the materials in order to show the range of possible mechanical behavior. Only PDMS-soft was investigated with the component testing procedure.

4.1 Dynamic (thermo-)mechanical analysis (D(T)MA)

Figure 3 shows the DTMA results of the investigated materials. Each color corresponds to the results of isothermal testing at various frequencies, which are indicated as single points.

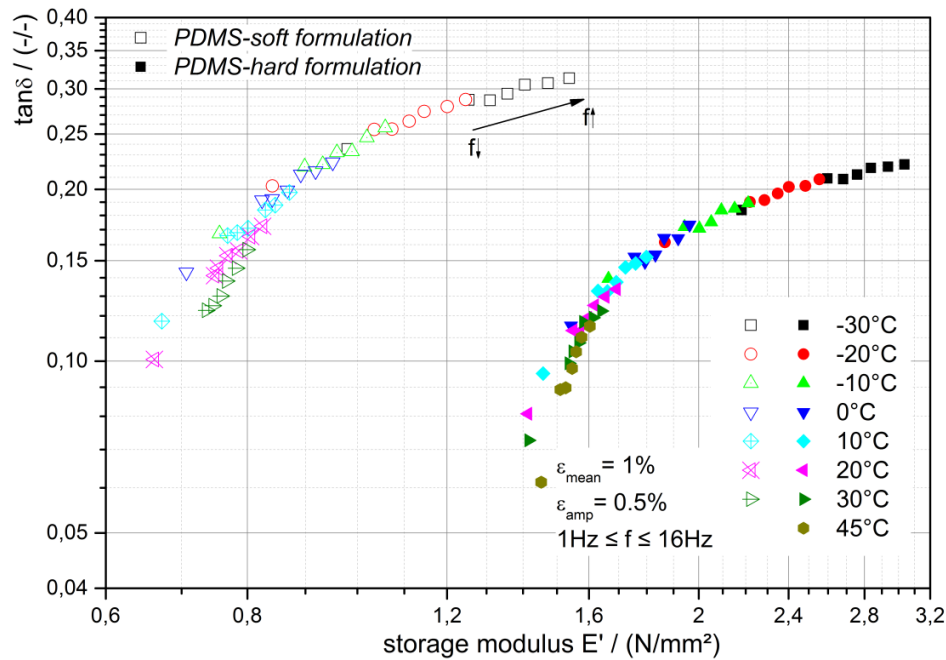


Figure 3 Loss factor $\tan\delta$ over storage modulus E' characteristic of the investigated materials at various temperatures

This diagram is very convenient for analyzing the trend of the inherent response time's temperature dependency as a result of the external mechanical loading. If all examined data reveal that $\tan\delta$ is a unique function of E' , then the response times (here the relaxation times) are equally temperature dependent and time-temperature superposition (TTSP) is applicable (cf. Çakmak and Major 2014b, and Tschoegl et al. 2002). Besides that, PDMS-soft formulation's characteristic is located within the diagram rather at the top right than the trend of PDMS-hard as expected. Important is that for both cases the TTSP can be applied, shift factors determined to construct the master curves at reference temperatures and these factors could be modeled with WLF function, among others. This is illustrated in Figure 4.

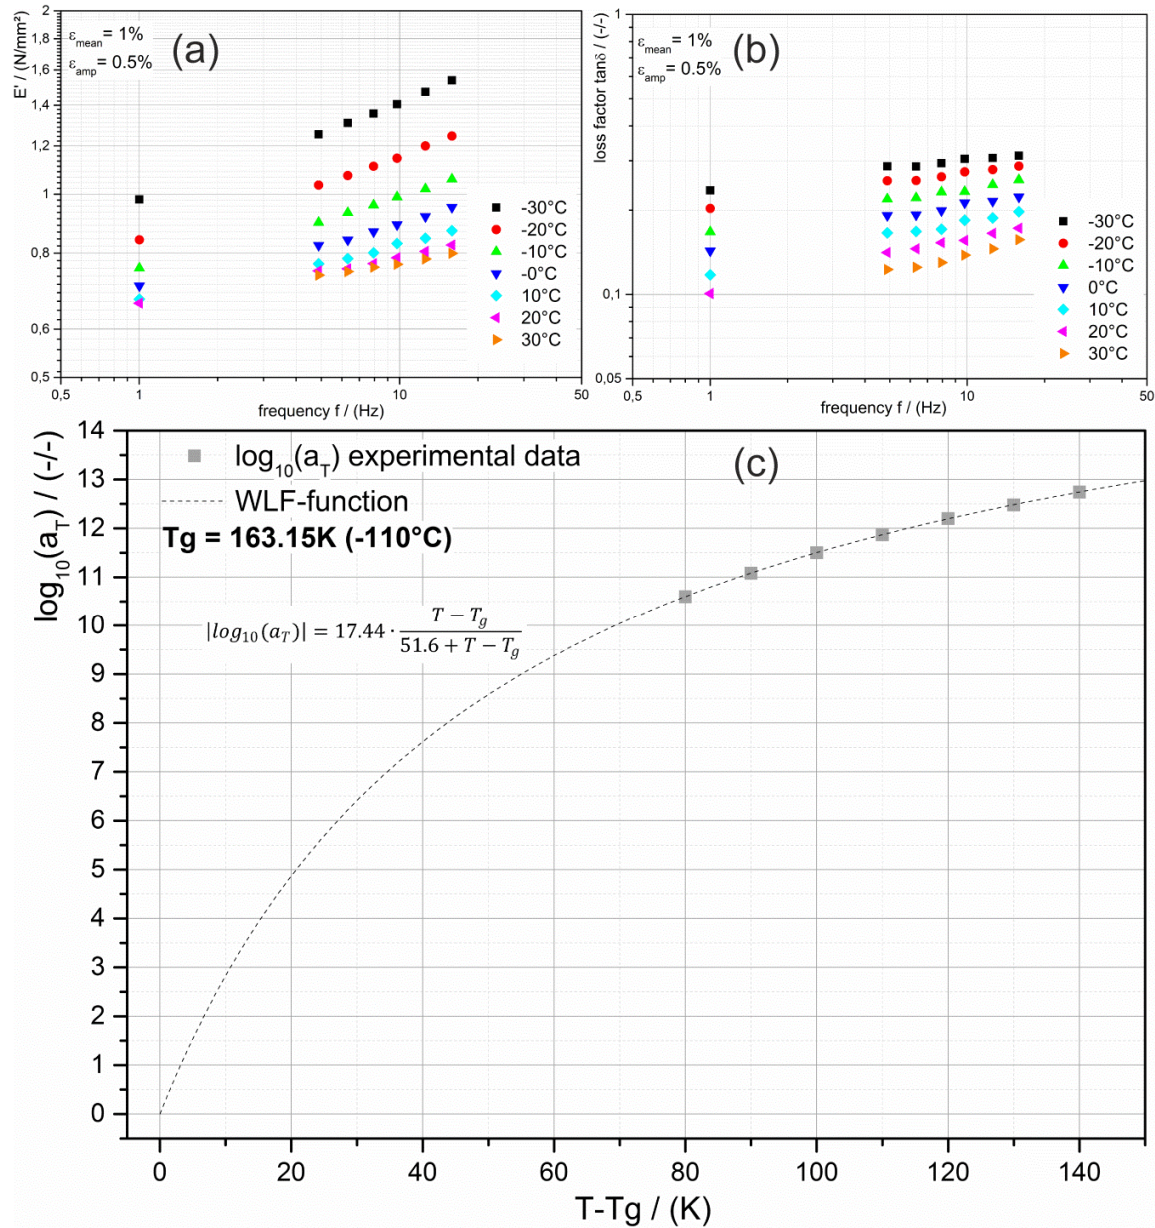


Figure 4 Diagram (a) and (b) shows the temperature and frequency dependent storage modulus and loss factor, respectively. In diagram (c) the obtained time-temperature shift factors a_T are presented as points and the WLF function as dashed line.

If the shift factor function (WLF) is applicable, then the temperature influence on the contact mechanical behavior can be easily predicted (e.g., Feng et al. 2007). This is of particular interest when the environmental conditions in-service of the gripper (i.e., during manufacturing of products) are fluctuating.

Figure 5 demonstrates the compression DMA results as before illustrated for the DTMA results. Now the gripper stamps made of the PDMS-formulations are investigated under contact and mechanically excited before delamination occurs. As mentioned earlier, the surface tackiness is an important prerequisite for the gripper stamp; however, when the viscoelastic behavior is observed, it turns out, that the loss factor is significant as well. It is believed, that a high frequency (loading rate) dependency is essential to exploit the

rate dependent adhesion. If the material has almost no rate dependent $\tan\delta$, which is the case for PDMS-hard formulation, then the material will not be suitable as gripper with rate dependent adhesion. The storage modulus and its rate dependency are of minor importance. It should be low and remain low with increasing loading rate.

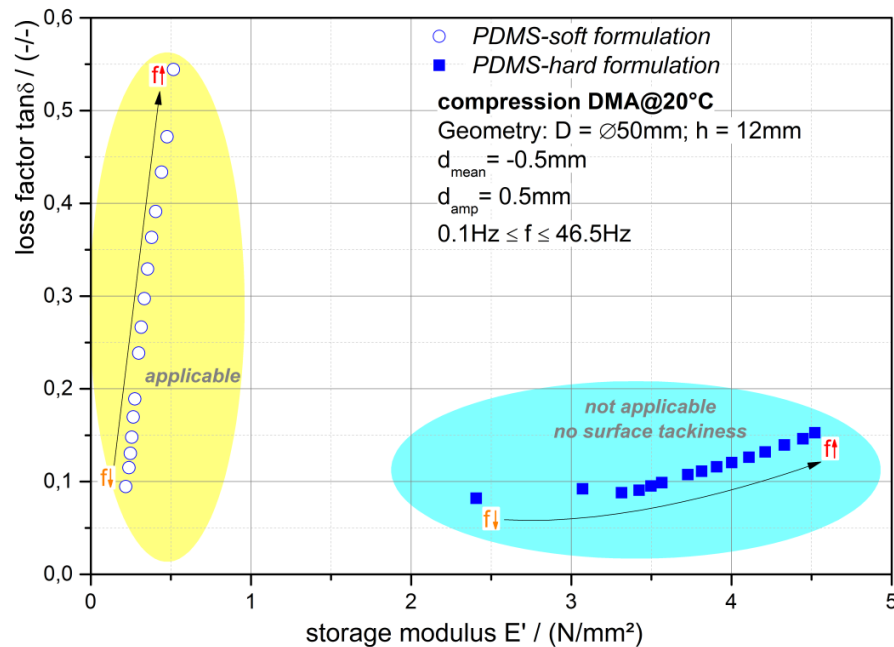


Figure 5 Loss factor $\tan\delta$ over storage modulus E' characteristic of the investigated formulation at 20°C under compression DMA loading procedure

The storage modulus of the PDMS-soft material is modeled with the 3rd order Prony series (cf. Equation (1)) and the respective Prony parameters are listed in Table 1. Figure 6 shows the experimental data of the frequency dependent storage modulus and the mentioned fit curve.

Table 1 Prony parameters of PDMS-soft formulation

gripper stamp	E_0	E_∞	g_i	τ_i
	/ (MPa)	/ (MPa)	-	/ (s)
PDMS-soft	0.517	0.238	8.35e-2	2.50e-1
			1.12e-1	5.23e-2
			3.44e-1	9.22e-3

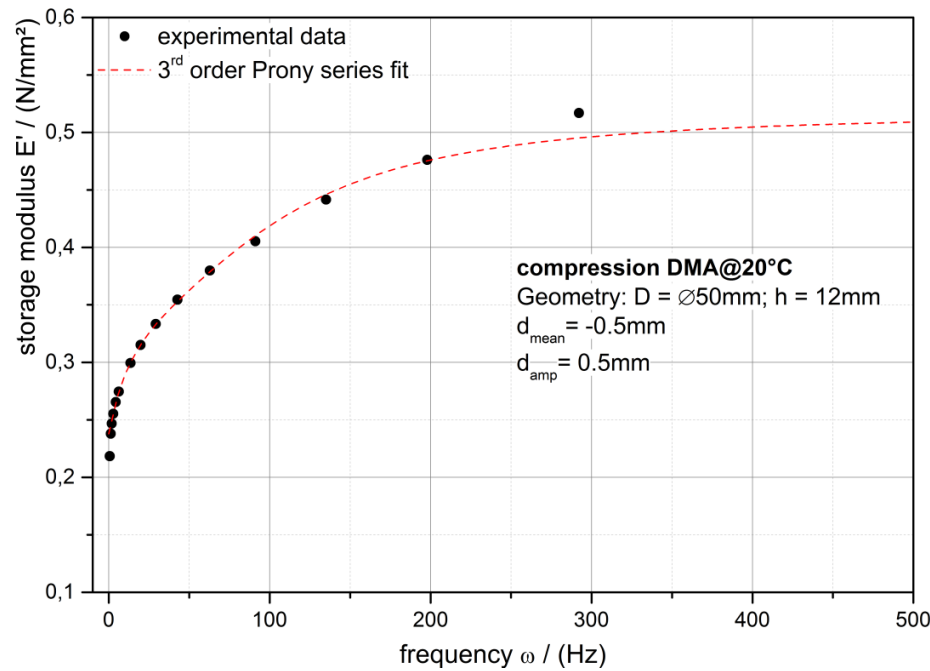


Figure 6 Linear plot of the frequency ($\omega=2\pi$) dependent storage modulus E' of PDMS-soft formulation (black points) with the 3rd order Prony series fit of the data (cf. Table 1)

With the Prony series, the time dependent storage modulus needed for computing and modeling the critical energy release rate is obtained.

4.2 Probe tack test

From the tack tests the tractive stresses are evaluated, which are measured as the maximum stresses before delamination, at various pulling speeds and are shown in Figure 7. The experimental data confirm the assumption of the square root relation between the stresses and the pulling speeds shown in Equation (7). This function's fit parameters for the investigated substrates are given in Table 2.

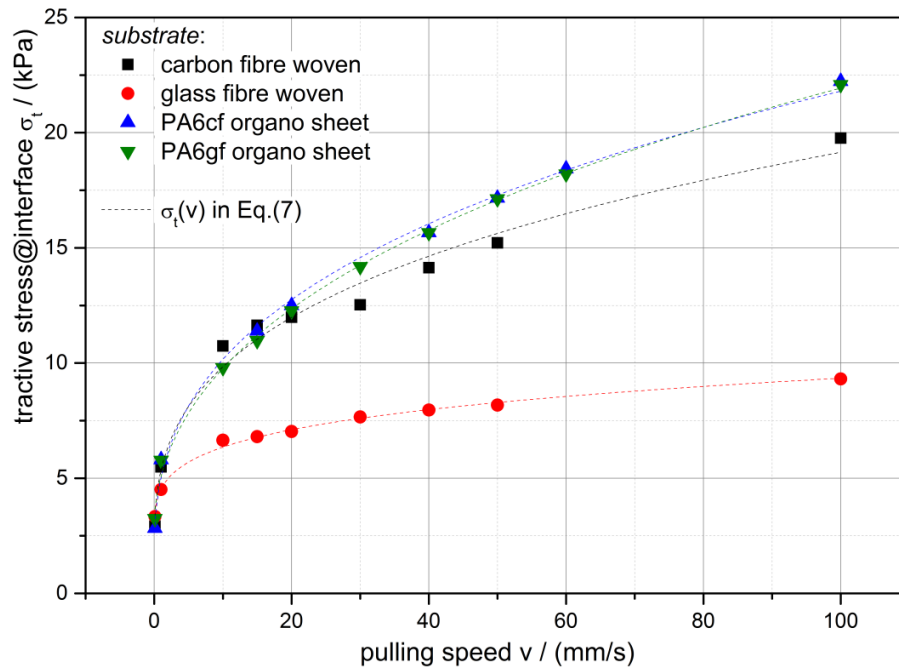


Figure 7 Measured tractive stresses σ_t between the PDMS-soft gripper stamp and the investigated substrates at various pulling speeds (points) with the fit function (Equation (7)) as dashed lines

Table 2 Fit parameter of the tractive stress and the corresponding calculated G_0

substrate	σ_0	n	G_0
	$v_0 = 0.1 \text{ mm/s}$	-	/ (J/m ²)
carbon fiber woven	2.4	0.60	0.36
glass fiber woven	2.5	0.38	0.38
PA6 carbon fiber	2.1	0.68	0.27
PA6 glass fiber	2.0	0.68	0.26

With E_∞ and σ_0 , the critical energy release rate G_0 near zero pulling speed and infinite separation time can be calculated. Table 2 shows the computed values and it can be observed, that the fabrics have a similar G_0 as well as the organo sheets. The surfaces of the fabrics are comprised by the fibers and the empty space in between and so the surface adhesion is determined by this meso-structure; on the other hand, the organo sheets' surfaces are dominated by the thermoplastic PA6.

Moreover, the time to separate the gripper stamp from the fixed substrates is evaluated (see Figure 8) in order to determine the actual storage modulus according to Equation (3). Figure 8 reveal that the separation time is with a good approximation independent of the substrate in contact with the gripper stamp. The red line shows the exponential decay trend over the pulling speed.

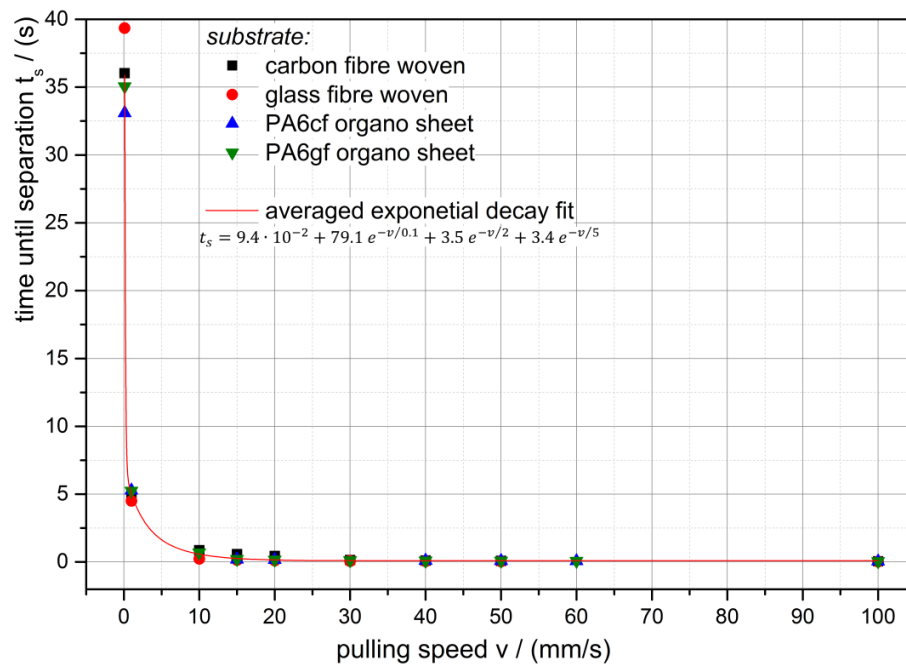


Figure 8 Pulling speed related time to separate the gripper stamp from the substrates; red line shows the trend of all measurement points

From the data presented above, the critical energy release rates G are computed according to Equation (6) and are shown pulling speed dependent in Figure 9. Also the modeled energy release rates are shown with good agreement with the experimental data. The model seems to be appropriate to model and predict the critical energy release rate for in-service use. From this, the pulling speed needed to lift up/release an object with a certain mass could be calculated as well.

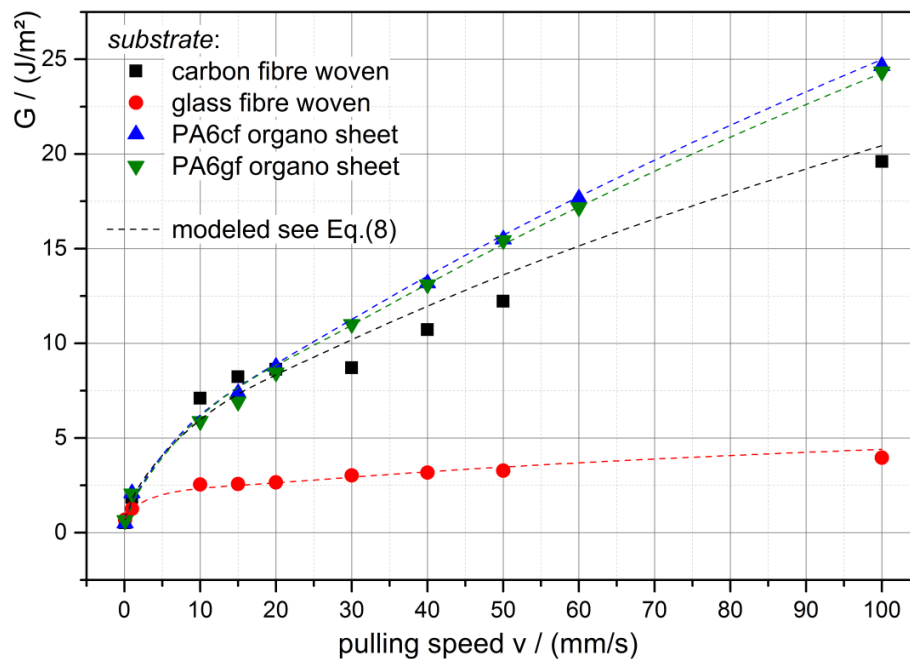


Figure 9 Critical energy release rate G versus the pulling speed v including the model of Equation (8) for each substrate

5 Conclusion

The presented adherence test revealed that the gripper made of PDMS-soft formulation is capable for grasping, holding, transporting and finally assembling (draping) of fabrics as well as semi-finished thermoplastic parts. Grasping and assembling is achieved by the utilization of the rate dependent adhesion. For application the knowledge of the gripper's pulling speed dependent adherence characteristic for the substrate in contact is essential. A model based on Equation (8) describes sufficiently the rate dependency of the gripper. It can be utilized for the prediction of the critical energy release rate and furthermore the maximum mass (weight-force) to handle can be determined. We believe that the presented adherence test as well as the model is of particular interest for the application and a stable operation of the robot handling system. In the presented work the aging and hence the altering of the gripper material's mechanical inherent viscoelastic properties is omitted. It is obvious that this is of crucial importance for the service (replacement) interval time and has to be verified in future.

Acknowledgement

Financial support by the Austrian Research Promotion Agency (FFG) in the framework of the Competence Headquarter Program operated by Engel Austria GmbH is gratefully acknowledged.

References

- Bogue, R. (2014), "Smart materials: a review of capabilities and applications", *Assembly Automation*, Vol. 34 No. 1, pp. 16-22.
- Brown, E., Rodenberg, N., Amend, J., Mozeika, A., Steltz, E., Zakin, M. R., Lipson, H. and Jaeger, H. M. (2010). "Universal robotic gripper based on the jamming of granular material". *Proceedings of the National Academy of Sciences*, Vol. 107 No. 44, 18809-18814.
- Çakmak, U. D., Grestenberger, G. and Major, Z. (2011), "A novel test method for quantifying surface tack of polypropylene compound surfaces". *Express Polymer Letters*, Vol. 5 No. 11, pp. 1009-1016.
- Çakmak, U. D., Hiptmair, F., and Major, Z. (2014a). "Applicability of elastomer time-dependent behavior in dynamic mechanical damping systems". *Mechanics of Time-Dependent Materials*, Vol. 19, pp. 139-151.
- Çakmak, U. D., and Major, Z. (2014b). "Experimental Thermomechanical Analysis of Elastomers Under Uni- and Biaxial Tensile Stress State". *Experimental Mechanics*, Vol. 54, pp. 653-663.
- Carlson, A., Kim-Lee, H. J., Wu, J., Elvikis, P., Cheng, H., Kovalsky, A., Elgan, St., Yu, Q., Ferreira, P. M., Huang, Y., Turner K. and Rogers, J. A. (2011), "Shear-enhanced adhesiveless transfer printing for use in deterministic materials assembly", *Applied Physics Letters*, Vol. 98 No. 26, p. 264104.
- Chen, H., Feng, X., Huang, Y., Huang, Y. and Rogers, J. A. (2013), "Experiments and viscoelastic analysis of peel test with patterned strips for applications to transfer printing". *Journal of the Mechanics and Physics of Solids*, Vol. 61 No. 8, pp. 1737-1752.
- Chen, H., Feng, X., and Chen, Y. (2013), "Directionally controlled transfer printing using micropatterned stamps", *Applied Physics Letters*, Vol. 103 No. 15, p. 151607.
- Cheng, H., Li, M., Wu, J., Carlson, A., Kim, S., Huang, Y., Kang, Z., Hwang, K.-C. and Rogers, J. A. (2012), "A Viscoelastic Model for the Rate Effect in Transfer Printing", *Journal of Applied Mechanics*, Vol. 80 No. 4, pp. 41019-41024.
- Cheng, H., Wu, J., Yu, Q., Kim-Lee, H. J., Carlson, A., Turner, K. T., Hwang, K.-Ch., Huang, Y. and Rogers, J. A. (2012), "An analytical model for shear-enhanced adhesiveless transfer printing", *Mechanics Research Communications*, Vol. 43, pp. 46-49.
- Emri, I., and Tschoegl, N. W. (1995), "Determination of mechanical spectra from experimental responses". *International Journal of Solids and Structures*, Vol. 32 No. 6, pp. 817-826.
- Feng, X., Meitl, M. A., Bowen, A. M., Huang, Y., Nuzzo, R. G. and Rogers, J. A. (2007), "Competing fracture in kinetically controlled transfer printing", *Langmuir*, Vol. 23 No. 25, pp. 12555-12560.
- Kim, S., Wu, J., Carlson, A., Jin, S. H., Kovalsky, A., Glass, P., Liu, Z., Ahmed, N., Elgan, St. L., Chen, W., Ferreira, P. M., Sitti, M., Huang, Y. and Rogers, J. A. (2010), "Microstructured elastomeric surfaces with reversible adhesion and examples of their use in deterministic assembly by transfer printing", *Proceedings of the National Academy of Sciences*, Vol. 107 No. 40, pp. 17095-17100.

Kim, S., Carlson, A., Cheng, H., Lee, S., Park, J. K., Huang, Y. and Rogers, J. A. (2012), “Enhanced adhesion with pedestal-shaped elastomeric stamps for transfer printing”, *Applied Physics Letters*, Vol. 100 No. 17, p. 171909.

Li, R., Li, Y., Lü, C., Song, J., Saeidpouraza, R., Fang, B., Zhong, Y., Ferreira, P. M., Rogers, J. A. and Huang, Y. (2012), “Thermo-mechanical modeling of laser-driven non-contact transfer printing: two-dimensional analysis”, *Soft Matter*, Vol. 8 No. 27, pp. 7122-7127.

Monkman, G. J. and Shimmin, C. (1991), “Permatac adhesives for robot grippers”, *Assembly Automation*, Vol. 11 No. 4, pp. 17-19.

Monkman, G. J., Hesse, S., Steinmann, R., and Schunk, H. (2007), *Robot grippers*, John Wiley & Sons.

Rettenwander, T., Fischlschweiger, M., and Steinbichler, G. (2014), “Computational structural tailoring of continuous fibre reinforced polymer matrix composites by hybridisation of principal stress and thickness optimization”, *Composite Structures*, Vol. 108, pp. 711-719.

Saeidpourazar, R., Li, R., Li, Y., Sangid, M. D., Lü, C., Huang, Y., Rogers, J. A. and Ferreira, P. M. (2012), “Laser-Driven Micro Transfer Placement of Prefabricated Microstructures”, *Journal of Microelectronical Systems*, Vol. 21 No. 5, pp. 1049-1058.

Shull, K. R. (2002), “Contact mechanics and the adhesion of soft solids”. *Materials Science and Engineering: R: Reports*, Vol. 36 No. 1, pp. 1-45.

Taylor, P. M. (1995), “Presentation and gripping of flexible materials”. *Assembly automation*, Vol. 15 No. 3, pp. 33-35.

Tschoegl N.W., Knauss W.G., Emri I. (2002), “The Effect of Temperature and Pressure on the Mechanical Properties of Thermo- and/or Piezorheologically Simple Polymeric Materials in Thermodynamic Equilibrium – A Critical Review”. *Mechanics of Time-Dependent Materials*. Vol. 6, 53-99.

Williams, M. L., Landel, R. F., and Ferry, J. D. (1955), “The temperature dependence of relaxation mechanisms in amorphous polymers and other glass-forming liquids”. *Journal of the American Chemical Society*, Vol. 77 No. 14, pp. 3701-3707.

Wu, J., Kim, S., Chen, W., Carlson, A., Hwang, K. C., Huang, Y. and Rogers, J. A. (2011), “Mechanics of reversible adhesion”, *Soft Matter*, Vol. 7 No. 18, pp. 8657-8662.

Yang, S. Y., Carlson, A., Cheng, H., Yu, Q., Ahmed, N., Wu, J., Kim, S., Sitti, M., Ferreira, P. M., Huang, Y. and Rogers, J. A. (2012), “Elastomer Surfaces with Directionally Dependent Adhesion Strength and Their Use in Transfer Printing with Continuous Roll-to-Roll Applications”, *Advanced Materials*, Vol. 24 No. 16, pp. 2117-2122.