

Design of composites by infiltration process: A case study of liquid Ir-Si alloy/SiC systems

Rada Novakovic^{1*}, Simona Delsante^{1,2}, Donatella Giuranno¹

¹Institute of Condensed Matter Chemistry and Technologies for Energy, National Research Council of Italy (ICMATE-CNR), Via De Marini 6, 16149, Genoa, Italy. rada.novakovic@ge.icmate.cnr.it; donatella.giuranno@ge.icmate.cnr.it

²Department of Chemistry and Industrial Chemistry, Genoa University and Genoa Research Unit of INSTM, Via Dodecaneso 31, 16146, Genoa, Italy. simona.delsante@unige.it

*Correspondence: rada.novakovic@ge.icmate.cnr.it

Abstract

The design of processing routes involving the presence of the liquid phase is mainly associated with the knowledge of its surface and transport properties. Despite this need, due to experimental difficulties related to high temperature measurements of metallic melts, for many alloy systems neither thermodynamic nor thermophysical properties data are available. A good example lacking these datasets represents the Ir-Si system, although over the last fifty years, the structures and properties of its solid phases have been widely investigated. To compensate the missing data, the Gibbs free energy of mixing of the Ir-Si liquid phase was calculated combining the model predicted values for the enthalpy and entropy of mixing using Miedema's model and Free Volume Theory, respectively. Subsequently, in the framework of statistical mechanics and thermodynamics, the surface properties were calculated using the Quasi Chemical Approximation (QCA) for the regular solution, while to obtain the viscosity, the Moelwyn-Hughes (MH) and Terzieff models were applied. Subsequently, the predicted values of the abovementioned thermophysical properties were used to model the non-reactive infiltration isotherm of Ir-Si (eutectic) / SiC system.

Keywords: Ir-Si alloys; Modelling; Surface tension; Viscosity; Molar volume; Infiltration; SiC

1. Introduction

Since the late 1970s iridium silicides became attractive for applications in electronic industry [1-4] and until nowadays, lot of research dedicated to thin film deposition, nucleation and growth of Ir-Si intermetallic phases formed and their stabilities have contributed to optimisation of electronic devices [5,6]. Some of Ir-Si intermetallic compounds, such as *IrSi*, *Ir₃Si₅* [7] and *IrSi₃* [4,7,8] are of interest for microelectronic or thermoelectric applications. Indeed, among Ir-Si intermetallic compounds, *Ir₃Si₅* is a wide-gap semiconductor, while when doped with another transition metal it may be suitable for the use at high temperatures [1,4,7]. Other potential applications of metallic silicides are their use as structural materials in aggressive environments [9] or as infiltrants in the manufacturing of composites via infiltration [10-13]. Binary Ir-X (X = Ti, Ta, Nb, Hf, Zr, and V) and Ir-Nb-Si ternary refractory superalloys provide a wider operating temperature range, i.e. up to 300 K higher with respect to that of Ni-based alloys as well as better mechanical properties and therefore, these alloys can be used for ultra-high-temperature applications [14,15]. Thermodynamic data of the Ir-Si system are scarce, while for its liquid alloys, due to the experimental difficulties related to high temperature measurements, reactivity of alloy melts with container materials, and oxygen as well, the complete lack of data can be observed [16]. Therefore, until nowadays, the Ir-Si phase diagram is not yet well assessed [17]. Concerning the solid-state measurements, several structural investigation of Ir-Si intermetallic phases by X-ray experiments have been carried out [1,5,18-23]. Indeed, *IrSi₃* [1,3,7,19-21,24,25], *IrSi* [1,7,18-20,24-27], *IrSi₅* [20] *Ir₃Si₄* [1,2,20,25], *Ir₄Si₅* [1,20,25] *IrSi_{1.5}* [20] *Ir₃Si₅* [1,7,23,25] and their structures have been investigated. In the case of well-defined stoichiometry, the corresponding structural datasets differ within experimental errors. Most of the work involving iridium silicides deals with deposition, the phase formation, growth and stability of nonequilibrium thin films and their thermophysical properties in the solid state [1,6,7]. Searcy and Finnie have investigated the thermodynamics of platinum metal silicides with carbon and performing the studies on the phase stability of the Ir-Si-C system at T = 1613 K, the heat of formation of seven iridium silicides has been evaluated [24]. SiC and iridium silicides prove to be thermodynamically stable cermet and have good high-temperature oxidation resistance comparable to that of *MoSi₂* [9,24]. Standard enthalpy of formation of *IrSi* has been determined by high-temperature mixing calorimetry [26-28]. The Si-rich side (50-100 at % Si) of the Ir-Si system was investigated by means of density, differential thermal analysis (DTA), X-ray powder diffraction, metallography, microprobe analysis and electrical resistivity [1] and the results obtained were used for the Ir-Si phase diagram assessment [16]. Further investigations of the Ir-Si system were carried out by XRD, EPMA and SEM analyses and are related to the phases and microstructural evolution of Ir-rich alloys (0-50 at % Si) [25]. Based on the abovementioned experimental datasets, the last compilation of Ir-Si thermodynamic data resulting in the most recent Ir-Si phase diagram [17] indicates the presence of *Ir₃Si*, *Ir₂Si*, *Ir₃Si₂*, *IrSi*, *Ir₄Si₅*, *Ir₃Si₄*, *Ir₃Si₅*, β *IrSi₃* and γ *IrSi₃* intermetallic compounds.

The mixing behaviour of Ir-Si melts can be deduced from the Hume-Rothery empirical factors such as the size effect ($V_{Ir}/V_{Si}=0.861$ or its reciprocal value 1.16) [29], valency difference (= 0 or 1) and electronegativity difference according Pauling (= 0.3) [30] estimating the driving force for the formation of intermetallic compounds in this system [31]. To compensate missing thermodynamic data on the liquid Ir-Si phase, Miedema's semi-empirical model [32-35] was combined with the Free Volume Theory [36-39] in order to predict the enthalpy of mixing and the excess entropy of mixing, respectively. The model predicted values of these quantities made possible to evaluate the excess Gibbs free energy and activities of liquid Ir-Si alloys and thus, to calculate their surface properties using only the models characterised by one interaction energy parameter, such as the Quasi Chemical Approximation for regular solution (QCA) and/or Butler's model [40]. However, as in the case of the Co-Si [10,41], the Compound Formation Model (CFM) with four interaction energy parameters would be the most appropriate, but the missing experimental data on the mixing in the Ir-Si liquid phase make impossible its application. Similarly, the calculated values of enthalpy of mixing were used to obtain the viscosity of Ir-Si melts by the Moelwyn-Hughes (MH) model [42] as well as by its extended version with hard sphere contributions [29].

Si-based alloy/SiC type composites are mainly produced by the infiltration processes [9,10-12]. Although this processing route has been in use for a long time, the industries are interested only in the targeting properties to ensure high performances of the final products. The best way to satisfy these needs are *Materials Design* technologies and applications [10,11,41] that involve the knowledge of the thermophysical

and wetting properties of metallic and ceramic components including interactions between them. During the infiltration, the control of reaction is important because, in some cases, the reaction products may cause the degradation of composite mechanical properties and thus, a low reactivity is required [11]. Among the thermophysical properties, the surface tension, viscosity and mass density of alloy melts together with the contact angle between the liquid and solid phases are the key properties to estimate the operating parameters, relevant for the design and optimization of infiltration processes as well as for the simulation of microstructural evolution during solidification. Therefore, taking into account the abovementioned model predicted thermophysical properties data; a case study of Si-Ir (eutectic) / SiC system describing the infiltration mechanism and the effects of various factors on it was presented.

2. Theory

2.1 Predictions of thermodynamic properties of metallic melts

Thermodynamic modelling is the easiest way to calculate the thermodynamic and subsequently the thermophysical properties of alloy melts in the framework of different models [29,40,41]. However, for many systems, in particular those characterized by high melting temperatures of their alloys such as the Ir-Si, is often difficult or even impossible to perform property measurements due to a container and surrounding atmosphere concomitant reactivity to alloy melts. In the present work, the enthalpy of mixing and the excess entropy of Ir-Si melts have been calculated combining Miedema's model and Free volume theory [32,35-38] and the results obtained were used to predict the thermophysical properties of this system. In the following, only the basic equations of both formalisms were reported.

After preliminary data analysis of more than 2500 alloy systems, Takeuchi and Inoue [43] have extended Miedema's model [32,35] introducing a relatively simple description for the enthalpy of mixing ΔH_{mix} of binary alloy melts. Molar volume V_{Alloy} , as a part of ΔH_{mix} , is given as

$$V_{Alloy} = \sum_{i \neq j}^2 x_i \cdot \left\{ \left[1 + a \cdot \left(1 - \frac{x_i V_i^{2/3}}{x_i V_i^{2/3} + x_j V_j^{2/3}} \right) \cdot (\varphi_i - \varphi_j) \right] V_i^{2/3} \right\}^{3/2} \quad \text{Eq.(1)}$$

where V_i , V_j , x_i , x_j , φ_i and φ_j are the molar volumes, compositions and work functions of A and B alloy components and a is a constant. According to the model formalism [43], recalling some equations from model theory and after some algebra, the mixing enthalpy ΔH_{mix} can be calculated using a cubic polynomial of compositions with respect to both alloy components and an interaction parameter Q evaluated at the equiatomic composition, as follows

$$\Delta H_{mix} = 4 \left(\sum_{k=0}^3 Q_k (c_A - c_B)^k \right) x_A x_B \quad \text{Eq.(2)}$$

where x_A and x_B are the compositions of A and B components of an $A - B$ alloy. In the framework of Free Volume Theory [36-38], the grand partition function for an $A - B$ liquid alloy can be evaluated based on those of pure A and B liquid metals. Subsequently, defining the Gibbs energy of A and B pure liquid components, the Gibbs energy of mixing of an $A - B$ alloy can be calculated. Considering the enthalpy of mixing of an alloy in terms of the Gibbs-Helmholtz relation, from the first approximation of the regular solution model, two non-linear equations have been assessed in the form

$$P = \left\{ 1 - 4x_A x_B \left[1 - \exp \left(\frac{\Omega_{AB}}{k_B T} \right) \right] \right\}^{1/2} \quad \text{Eq.(3)}$$

$$\Delta H_{mix} = \frac{2x_A x_B \Omega_{AB}}{P+1} \quad \text{Eq.(4)}$$

where Ω_{AB} is the exchange energy and P is a parameter related to the nearly random configuration of atoms in an $A - B$ alloy, that can be set approximately to be 1. Once Ω_{AB} and P are obtained, using the mathematical formalism of the model including the thermodynamic relations [37]

$$\Delta H_{mix} = \Omega_{AB} x_A x_B \left(1 - x_A x_B \frac{\Omega_{AB}}{RT} \right) \quad \text{Eq.(5)}$$

$$\Delta S^{xs} = \Delta S_{CONF}^{xs} + \Delta S_{VIB}^{xs} \quad \text{Eq.(6)}$$

$$G^{xs} = \Delta H_{mix} - TS^{xs} \quad \text{Eq.(7)}$$

with S^{xs} , S_{CONF}^{xs} , S_{VIB}^{xs} and G^{xs} , are the excess entropy, its configurational and vibrational parts, and excess Gibbs energy, respectively. Therefore, the excess entropy and excess Gibbs energy can be evaluated using the values of the enthalpy of mixing that is often measurable thermodynamic function and excess volume together with some thermophysical properties of alloy components. γ_A and γ_B activity coefficients of A and B alloy components in $A - B$ solution phases are related to the excess Gibbs energy of mixing G^{xs} by the standard thermodynamic relation, as

$$G^{xs} = RT[x_A \cdot \ln \gamma_A + x_B \cdot \ln \gamma_B] \quad \text{Eq.(8)}$$

In the framework of QCA for regular solution [40], the activity coefficients of A and B alloy components are expressed by

$$\gamma_A = \left[\frac{\beta - 1 + 2x_A}{x_A(1+\beta)} \right]^{Z/2} \quad \text{Eq.(9a)}$$

$$\gamma_B = \left[\frac{\beta - 1 + 2x_B}{x_B(1+\beta)} \right]^{Z/2} \quad \text{Eq.(9b)}$$

where Z is the coordination number and β is auxiliary function describing the energetics of the bulk phase.

2.2 Structural information: $S_{cc}(0)$ and α_1 microscopic functions

The concentration-concentration structure factor in the long wavelength limit $S_{cc}(0)$ is an important microscopic function in describing the nature of mixing of liquid alloys in terms of chemical ordering and segregation (or phase separation) [41,44]. Owing to difficulties in diffraction experiments, the theoretical determination of $S_{cc}(0)$ is of great importance when the nature of atomic interactions in the melt has to be analysed. The mixing behaviour of liquid binary alloys can be deduced from the deviation of $S_{cc}(0)$ from $S_{cc}(0, id)$. The presence of chemical order is indicated when $S_{cc}(0) < S_{cc}(0, id)$; on the contrary, if $S_{cc}(0) > S_{cc}(0, id)$, the segregation and demixing in liquid alloys take place. Once the Gibbs energy of mixing G_M of the liquid phase is known, $S_{cc}(0)$ can be expressed either by G_M or by the activities a_A and a_B , as

$$S_{cc}(0) = RT \left(\frac{\partial^2 G_M}{\partial x_A^2} \right)_{T,P,N}^{-1} = x_B a_A \left(\frac{\partial a_A}{\partial x_A} \right)_{T,P,N}^{-1} = x_A a_B \left(\frac{\partial a_B}{\partial x_B} \right)_{T,P,N}^{-1} \quad \text{Eq.(10)}$$

For ideal mixing the energy parameters become zero and Eq.(11) becomes

$$S_{cc}(0, id) = x_A \cdot x_B \quad \text{Eq.(11)}$$

In order to quantify the degree of order and segregation in the melt, another important microscopic function, known as Warren-Cowley short-range order parameter α_1 [41,45]. $S_{cc}(0)$ and α_1 are related to each other, by

$$\frac{S_{cc}(0)}{x_A \cdot x_B} = \frac{1 + \alpha_1}{1 - (Z-1)\alpha_1} \quad \text{Eq.(12)}$$

For the equiatomic composition, the chemical short-range order (CSRO) parameter, often denoted as α_1 , is found to be $-1 \leq \alpha_1 \leq 1$. The negative values of this parameter indicate ordering in the melt, and complete ordering is manifested by $\alpha_1^{min} = -1$. On the contrary, the positive values of α_1 indicate segregation, while if $\alpha_1^{max} = 1$, the phase separation takes place.

2.3 Surface properties

Once the excess Gibbs free energy was obtained in the framework of Free volume theory [37,38], the surface segregation and surface tension of binary liquid alloys can be calculated by the Quasi Chemical Approximation (QCA) for regular solution by

$$\sigma = \sigma_A + \frac{k_B T \cdot (2-p \cdot Z)}{2\alpha} \ln \left(\frac{x_A^S}{x_A} \right) + \frac{Z \cdot k_B T}{2\alpha} \left[p \cdot \ln \frac{(\beta^S - 1 + 2x_A^S)(1+\beta)}{(\beta - 1 + 2x_A)(1+\beta^S)} - q \cdot \ln \frac{(\beta - 1 + 2x_A)}{(1+\beta)x_A} \right] \quad \text{Eq.(13a)}$$

$$\sigma = \sigma_B + \frac{k_B T \cdot (2-p \cdot Z)}{2\alpha} \ln \left(\frac{x_B^S}{x_B} \right) + \frac{Z \cdot k_B T}{2\alpha} \left[p \cdot \ln \frac{(\beta^S - 1 + 2x_B^S)(1+\beta)}{(\beta - 1 + 2x_B)(1+\beta^S)} - q \cdot \ln \frac{(\beta - 1 + 2x_B)}{(1+\beta)x_B} \right] \quad \text{Eq.(13b)}$$

where σ_A and σ_B are the surface tensions of pure components, α is the mean surface area of an $A - B$ alloy, β (Eqs.(9a;b)) and β^S are auxiliary functions describing the energetics of the bulk and surface phase, respectively. p and q are the surface coordination fractions defined as the fractions of the total number of nearest neighbours of an atom in its own layer and that in the adjoining layer. Therefore, $p + q = 1$. For a closed-packed structure, the values of these parameters usually are taken as $\frac{1}{2}$ and $\frac{1}{4}$, respectively. The QCA model has been detailed in [40].

2.4 Transport properties

Viscosity of Ir-Si alloys was evaluated using the Moelwyn-Hughes (MH) model is the simplest one among those reported in [29] as well as by the Terzieff viscosity model [46] representing an extension of the Iida model [47]. The MH viscosity isotherm is described by

$$\eta = (x_1 \eta_1 + x_2 \eta_2) \left(1 - 2x_1 x_2 \cdot \frac{H_{mix}}{RT} \right) \quad \text{Eq.(14)}$$

where η_1 and η_2 are the viscosities of pure components and H_{mix} is the mixing enthalpy of the alloys. The viscosity isotherm calculated by the Terzieff model [46,48] combines the energetics of a system in terms of thermodynamics and the hard sphere approach. According to that model, the relative viscosity of an alloy melt is expressed as the ratio of the excess viscosity and additive viscosity, in the form

$$\frac{\eta^{xs}}{\eta_{id}} = \alpha \cdot \frac{x_1 x_2 (\bar{\sigma}_1 - \bar{\sigma}_2)^2}{x_1 \bar{\sigma}_1^2 - x_2 \bar{\sigma}_2^2} + \beta \cdot \left[\left(1 + \frac{x_1 x_2 (m_1^{0.5} - m_2^{0.5})^2}{(x_1 m_1^{0.5} - x_2 m_2^{0.5})^2} \right) - 1 \right] + \gamma \cdot \frac{2H_{mix}}{RT} + \delta \cdot \frac{2x_1 x_2 |V_1 - V_2|}{V_1 + V_2} \quad \text{Eq.(15)}$$

where H_{mix} , R , x_i , m_i , $\bar{\sigma}_i$, V_i ($i = A, B$) are the enthalpy of mixing, gas constant, atomic fraction, atomic mass, hard sphere diameter and molar volume of a component i , respectively. α , β , γ , δ are statistical weights obtained by fitting to Eq.(15) a large number of experimental viscosity datasets at the equiatomic composition. **Error. Il segnalibro non è definito.** Based on the standard relation $\eta(T) = \eta(T)_{id} + \eta(T)^{xs}$, the viscosity of binary melts [46] can be expressed by

$$\eta(T) = \eta(T)_{id}(1 + \eta(T)^{xs}) \quad \text{Eq.(16)}$$

2.5 Non-reactive infiltration: Metal / Metal and Metal / Ceramic composites

The investigation of reactive infiltration as the most complex part of the infiltration process includes chemical reactions that can be predicted theoretically to some extent [11,12]; therefore, it requires the experimental work. On the contrary, the modelling of non-reactive infiltration is possible if the model predicted thermophysical properties and/or the corresponding literature data are available. Non-reactive infiltration of liquid alloys in contact with porous metallic or ceramic substrates, as the processing route or the processing step, is widely used to produce metal (Me1)/metal (Me2) and metal/ceramic composites [10-13]. Indeed, taking into account a miscibility gap that characterises Me1/Me2 monotectic metallic systems, Eremenko and Lesnik have performed combined experimental-theoretical investigation of non-reactive infiltration of the Ag/Ni, Ag/Fe, Pb/Ag, Pb/Ni and Pb/Fe systems [49]. Concerning the infiltration of porous ceramics by liquid metallic materials, usually two steps can be distinguished, i.e. the initial step of non-reactive infiltration process, lasting a very short time, followed by reactive infiltration, as it has been observed in the case of the Ni-Si / C [50] and Si / C systems [51,52]. Non-reactive infiltration of porous metallic or ceramic samples with metallic infiltrants follows the laws of the Washburn [53] and Deryagin [54] theory of capillary infiltration. The wetting of the surface is the key factor and the infiltration rate, controlled by the viscous flow, depends on the infiltrant composition and its thermophysical properties. The depth of infiltration h varies with time t obeying the Washburn parabolic equation [53] as follows,

$$h^2 = r_{eff} \cdot \frac{\sigma_{LG} \cos(\theta)}{2\eta} \cdot t = Kt \quad \text{Eq.(17)}$$

where θ , σ_{LG} , η , r_{eff} , and K are the contact angle between the liquid and solid phase, surface tension, viscosity, effective pore radius of the preform and constant.

3. Results and discussion

3.1 Thermodynamics of Ir-Si melts: Miedema's model and Free Volume Theory

Based on Miedema's semi-empirical model [32,35] and its refinement [43], the enthalpy of mixing ΔH_{mix} of liquid Ir-Si alloys (Figure 1; curve 1) can be calculated by

$$\Delta H_{mix}^{Ir-Si} (kJ \cdot mol^{-1}) = 4x_{Ir}x_{Si}[-26.2 - 0.8(x_{Ir} - x_{Si})] \quad \text{Eq.(18)}$$

In the framework of Free Volume Theory [37,39], the enthalpy of mixing ΔH_{mix} [43] of liquid Ir-Si alloys and thermophysical property datasets such as the melting temperature, density and molar volume of alloy components [29,55,56] were used to calculate the excess entropy ΔS^{xs} (Table 1), subsequently combined in Eq.(7) to obtain the excess Gibbs free energy (Figure 1; curve 2). Adding the ideal mixture term to Eq.(7), the Gibbs free energy of mixing ΔG_M of Ir-Si melts for T = 1873 K was calculated (Figure 1; curve 3). The curve describing ΔH_{mix} is symmetric, while those of $-T\Delta S^{xs}$ (Figure 1; curve 4), ΔG^{xs} and ΔG_M are slightly asymmetric with respect to the equiatomic composition (Figure 1). Due to the lack of experimental data, a comparison with model predicted values is not possible.

Table 1. Calculated values of the excess entropy of mixing (ΔS_M^{xs}) and the excess energy (ΔG_M^{xs}) of liquid Ir-Si alloys in the framework of Free Volume Theory. The enthalpy of mixing (ΔH_M) and the excess volume (ΔV^{xs}) values were calculated for T = 1873 K by Miedema's model. (The meaning of symbols reported here is given in the Appendix)

x_{Si}	ΔH_M (kJ·mol ⁻¹)	Ω_{Si-Ir} (kJ·mol ⁻¹)	P	U_{Ir} (kJ·mol ⁻¹)	U_{Si} (kJ·mol ⁻¹)	ΔV^{xs} (cm ³ ·mol ⁻¹)	L_{Ir} (10 ⁻⁸ cm)	L_{Si} (10 ⁻⁸ cm)
0.1	-9.202	-92.047	0.8006	-457.83	-407.02	-0.1877	1.414	1.454
0.2	-16.461	-82.441	0.6027	-447.52	-397.11	-0.3457	1.420	1.454
0.3	-21.739	-72.960	0.4096	-431.75	-386.51	-0.4970	1.428	1.454
0.4	-24.998	-64.340	0.2354	-409.27	-373.28	-0.6387	1.438	1.455
0.5	-26.200	-60.026	0.1455	-386.40	-348.51	-0.7665	1.448	1.459
0.6	-25.306	-65.053	0.2339	-382.42	-304.80	-0.8727	1.453	1.469
0.7	-22.277	-74.711	0.4086	-390.22	-261.29	-0.9425	1.454	1.478
0.8	-17.075	-85.493	0.6022	-400.64	-224.52	-0.9440	1.454	1.485
0.9	-9.662	-96.648	0.8.005	-411.72	-193.25	-0.7921	1.454	1.491
x_{Si}	L_{Ir-Si} (10 ⁻⁸ cm)	ΔS_{VIB}^{xs} (J·K ⁻¹ ·mol ⁻¹)	ΔS_{CONF}^{xs} (J·K ⁻¹ ·mol ⁻¹)	ΔS_M^{xs} (J·K ⁻¹ ·mol ⁻¹)	ΔG_M^{xs} (kJ·mol ⁻¹)	U_{IrIr} (kJ·mol ⁻¹)	U_{SiSi} (kJ·mol ⁻¹)	
0.1	1.4542	-0.9548	-0.0906	-1.0454	-7.2435	-464.16	-165.95	
0.2	1.4541	-1.7936	-0.4027	-2.1963	-12.3472			
0.3	1.4540	-2.5055	-1.0079	-3.5133	-15.1588	L_{IrIr} (10 ⁻⁸ cm)	L_{SiSi} (10 ⁻⁸ cm)	
0.4	1.4538	-3.0713	-1.9258	-4.9971	-15.6388			
0.5	1.4538	-3.4509	-2.5974	-6.0484	-14.8714	1.4091	1.4955	
0.6	1.4538	-3.5526	-1.9418	-5.4945	-15.0145			
0.7	1.4540	-3.2887	-1.0163	-4.3049	-14.2137	V_{Ir} (cm ³ ·mol ⁻¹)	V_{Si} (cm ³ ·mol ⁻¹)	
0.8	1.4541	-2.6310	-0.4054	-3.0364	-11.3881			
0.9	1.4541	-1.5506	-0.0911	-1.6417	-6.5876	9.531	11.395	

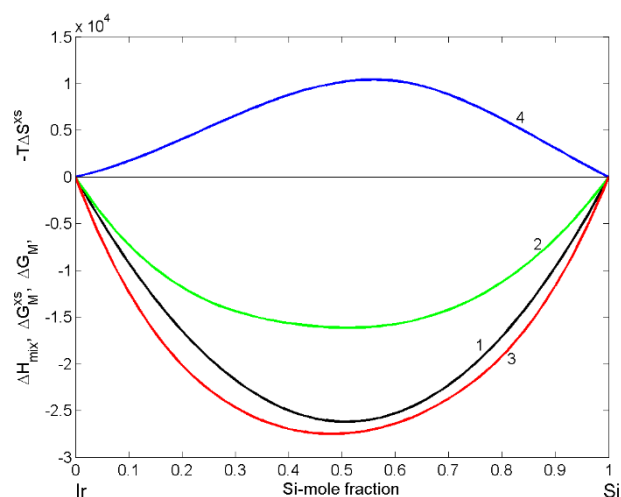


Figure 1. Concentration dependence of thermodynamic properties of liquid Ir-Si alloys calculated for $T = 1873$ K: 1- the enthalpy of mixing (ΔH_M); 2- the excess entropic term ($-T \cdot \Delta S^{xs}$); 3- the excess Gibbs free energy (ΔG_M^{xs}); 4- the Gibbs free energy of mixing (ΔG_M).

In order to evaluate the energetics of this system, the normalised form G_M/RT is appropriate to characterise the type of interactions between Ir and Si-constituent atoms and, the model predicted value of -1.76 at $x_{Si} = 0.52$ is an indicator for a moderately interacting system (Figure 2; curve 1), such as the Si-Co [41], Al-Co [57] and others. The calculated values of Ir and Si activities exhibit strong negative deviation from ideality (Figure 2; curves 2a and 2b), comparable to that observed for liquid Co-Si alloys [41].

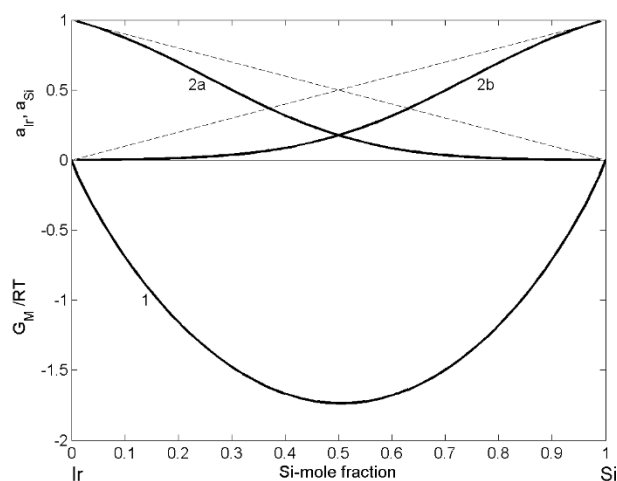


Figure 2. Concentration dependence of the Gibbs free energy of mixing (G_M/RT ; curve 1), the activities of iridium (a_{Ir} ; curve 2a) and silicon (a_{Si} ; curve 2b) of liquid Ir-Si alloys calculated for $T = 1873$ K. (----- the ideal mixture)

The phase diagram show the existence of nine intermetallic compounds in the Ir-Si system [17] and among them, *IrSi* is energetically favoured. Schlesinger summarised the literature data on the enthalpy of formation of *IrSi* [58]. A comparison of these data shows that predicted values vary between -27.2 and -67 kJ [59] and only the last value agrees well with the corresponding experimental value of -63.8 kJ [28], later measured as -64.4 kJ [26] and confirmed in [27].

3.2 Density / molar volume of Ir-Si melts

The importance of density is twofold. Firstly, it affects the atomic structure and short-range ordering of metallic melts and, on the other side, it is implicitly contained in the Rayleigh number that characterises fluid flow in all technological processes that include the presence of the liquid phase. Therefore, the density or molar volume of liquid alloys are used as an input for numerical simulations of abovementioned processes as well as for materials property design. Molar volume isotherm of liquid Ir-Si was calculated (Eq.(2)) for $T = 1873$ K (Figure 3; curve 1). Due to the lack of experimental data, a comparison with model predicted values is not possible. Therefore, for a comparison, the corresponding isotherm of Co-Si melts (Figure 3; curve 2) obtained at the same temperature together with the molar volume data deduced from the experimental data of density measured at $T = 1773$ K [60] are shown (Figure 3; curve 2). The dataset [60] has been obtained at lower temperature and therefore, the data values are lower with respect to the two isotherms. The experimental molar volume isotherm of liquid Co-Si alloys exhibits negative deviation from the ideal mixture and the same behaviour is expected for liquid Ir-Si. In addition, taking into account higher density of liquid Co with respect to that of Ir, higher molar volume predicted values of Ir-Si melts (Figure 3; curve 1) with respect to those of the Co-Si could be deduced.

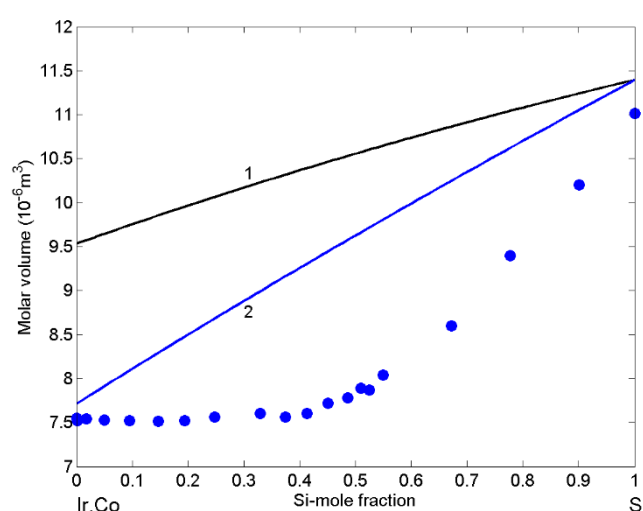


Figure 3. Concentration dependence of the molar volume of liquid Ir-Si (curve 1) and Co-Si (curve 2) alloys calculated for $T = 1873$ K. For a comparison, the molar volume values (●) of Co-Si melts obtained from the density experimental data [60] measured at $T=1773$ K are shown.

3.3 Structural information: Concentration fluctuations in the long-wavelength limit and chemical short-range order parameter in Ir-Si melts

The ordering phenomena in the Ir-Si liquid phase have been analysed by concentration fluctuations in the long-wavelength limit $S_{cc}(0)$ and short-range order parameter (α_1) as functions of bulk compositions. The enthalpy of mixing ΔH_{mix} predicted by Miedema's model and the excess mixing entropy ΔS^{xs} obtained in the framework of Free Volume Theory (Table 1) were combined by means of fundamental thermodynamic equations and these data were used to calculate the Gibbs free energy of mixing ΔG_M for $T = 1873$ K. Subsequently, inserting ΔG_M into Eq.(10), and the obtained values of $S_{cc}(0)$ into Eq.(12), the two microscopic functions $S_{cc}(0)$ and α_1 describing the nature of mixing and the degree of order of Ir-Si melts are shown in Figure 4.

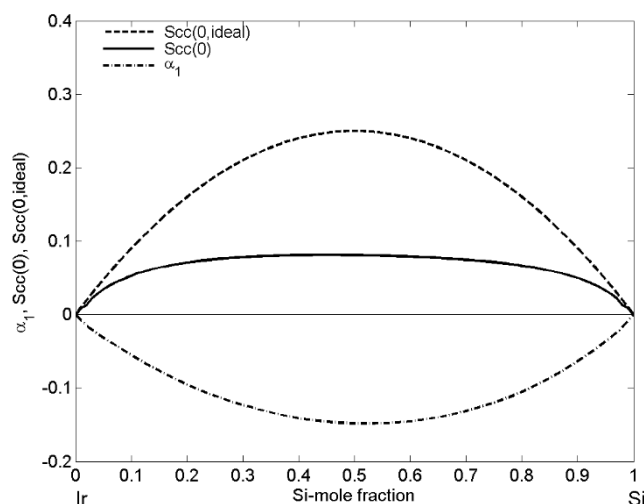


Figure 4. Concentration fluctuations in the long-wavelength limit ($S_{cc}(0)$ and $S_{cc}(0, id)$) and chemical short-range order parameter (α_1) vs. bulk composition (x_{Si}) of liquid Ir-Si alloys calculated for $T = 1873$ K.

$S_{cc}(0)$ curve exhibits the maximum of 0.07, differs significantly from the corresponding ideal curve $S_{cc}(0, id)$, i.e. $S_{cc}(0) < S_{cc}(0, id)$, indicating the formation of $A_\mu B_\nu$ heterocoordinated short-range order elements in alloy melts with μ and ν stoichiometric coefficients describing the stoichiometry of *IrSi* energetically favoured intermetallic compound [26,27]. Symmetric α_1 -curve with respect to the equiatomic composition has the minimum value of -0.15 and together with its negative values over the whole composition range (Figure 4), substantiate the compound forming tendency in the Ir-Si system.

3.4 Surface segregation and surface tension of liquid Ir-Si alloys: QCA modelling

Surface segregation and surface tension of liquid Ir-Si alloys were calculated by the QCA for regular solution [40]. Based on the abovementioned theoretical considerations and taking into account [32,33,43], the excess Gibbs free energy of the liquid phase (Table 1) was calculated by Eq.(7) and together with the molar volume, structural data [29] as well as the surface tension reference data of liquid Ir [56] and Si [61] alloy components were used as input. Combining Eq.(13a) and Eq.(13b), the segregation of Si-atoms to the surface of Ir-Si melts, over the whole composition range was obtained (Figure 5).

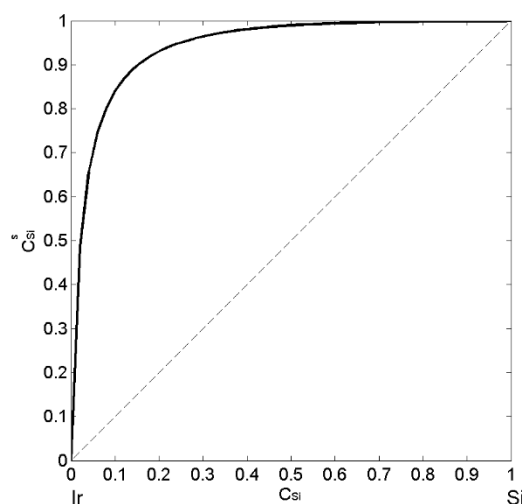


Figure 5. Surface composition (C_{Si}^s) vs. bulk composition (C_{Si}) in liquid Ir-Si alloys calculated by the QCA for regular solution for $T = 1873$ K. (----- the additive rule).

The presence of nine intermetallic compounds in the Ir-Si system [17] leads to the short-range ordering phenomena occurring at least near the liquidus line, that reduce the degree of segregation up to 25 %, as it was observed in the case of liquid Co-Si alloys [41]. Therefore, in the case of Ir-Si melts, the surface enrichment of Si-atoms calculated by the QCA for regular solution seems to be very high, but the lacking of thermodynamic data makes impossible the application of more appropriate model such as the Compound Formation Model (CFM), which has a good prediction accuracy. As a rule, in all alloy systems, the atoms of a component with lower surface tension segregate to the surface and an increase in temperature reduces the degree of segregation.

Inserting the calculated values of surface composition either into Eq.(13a) or Eq.(13b), the surface tension isotherm of Ir-Si liquid alloys (Figure 6; curve 1) can be obtained. The QCA surface tension isotherm is characterized by positive deviations from that calculated by the perfect solution model (Figure 6; curve 2), confirming the opposite deviations of the surface and thermodynamic property curves with respect to the ideal behaviour [29]. Similar behavior of the surface tension was observed for Co-Si melts [41].

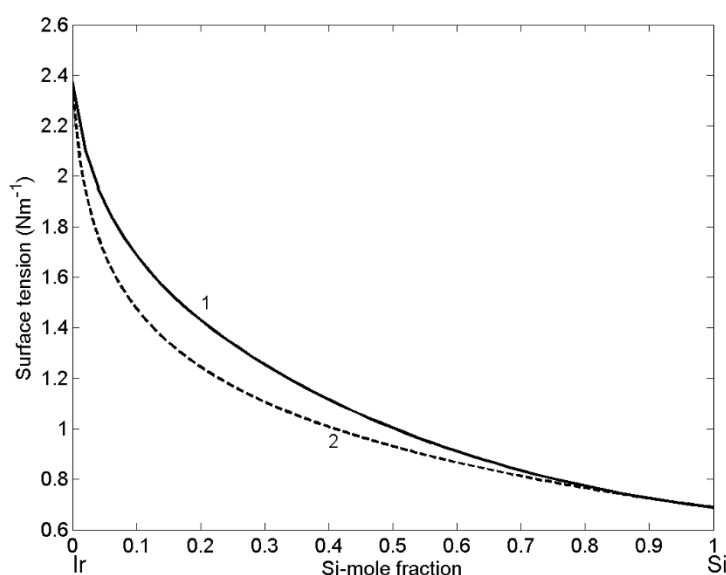


Figure 6. Surface tension isotherm of liquid Ir-Si alloys calculated for $T = 1873$ K by the QCA for regular solutions. (-----) the perfect solution model.

3.5 Viscosity

The enthalpy of mixing is a common input in the Moelwyn-Hughes [42] and Terzieff [63] viscosity models, described by Eq.(14) and Eqs.(15 and 16), respectively. Therefore, to calculate the viscosity of Ir-Si melts, the predicted values of enthalpy of mixing [43] together with the viscosity reference data of liquid Ir [56] and Si [62] were taken as input in the two models. In the case of Terzieff's model [63], the inputs such as the molar volume of Ir and Si [29] and hard sphere diameter of Ir [64] and Si [65] at the melting temperature were also used. The viscosity of liquid Ir-Si alloys was calculated for $T = 1873$ K using Moelwyn-Hughes's (Figure 7a; curve 1) and Terzieff's (Figure 7a; curve 2) models and the two curves exhibit similar trend. Higher viscosity values were obtained by the Terzieff model (Figure 7a; curve 2). Without experimental evidence is difficult to deduce which one of the two suggested viscosity isotherms is better. One of the most effective strategies to compare the two property curves is to analyse the trend of a property data related to a similar system characterised experimentally. Thus, the viscosity isotherm of Ir-Si melts was calculated by MH (Figure 7b; curve 1) and compared to the corresponding datasets of liquid Co-Si alloys. Indeed, combining the thermodynamic data of the Si-Co liquid phase [66] with the viscosity reference data of liquid Si [62] and Co [55,67], the viscosity isotherm was calculated for $T=1673$ K and compared with experimental data [68] obtained

at the same temperature (Figure 7b; curve 2). The two viscosity isotherms are similar and exhibit the same trend with the experimental data [68] as shown in Figure 7b. Therefore, based on the abovementioned, one may figure out that the Moelwyn-Hughes isotherm (Figure 7a; curve 1) describes better the viscosity of liquid Ir-Si alloy. This is further substantiated by the analysis of non-reactive infiltration (see § 3.6).

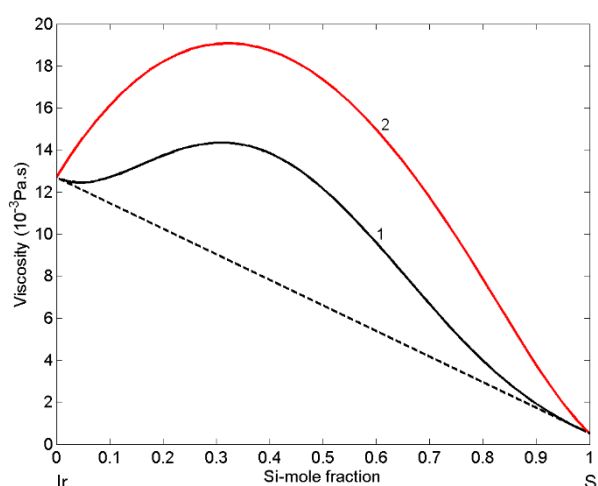


Figure 7a. Viscosity isotherms of liquid Ir-Si alloys for $T = 1873$ K calculated by Moelwyn-Hughes's model (curve 1) and Terzieff's model (curve 2). (-----) the additive rule.

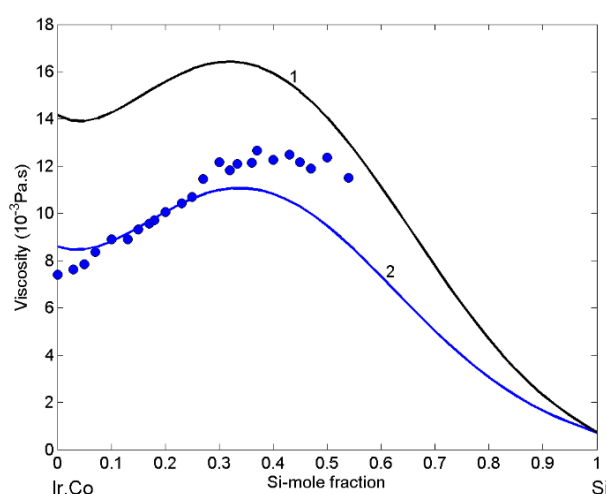


Figure 7b. Viscosity isotherms of liquid Ir-Si (curve 1) and Co-Si (curve 2) alloys calculated by Moelwyn-Hughes's (MH) model for $T = 1773$ K. For a comparison, the Co-Si viscosity isotherm (curve 2) and datasets (●) [68] are shown.

3.6 Non-reactive infiltration: Case study of a liquid Ir-Si alloy / SiC system

Design of metal / metal and metal / ceramic composites by infiltration processing routes includes the experimental and/or theoretical thermophysical properties data of liquid metallic phase and the experimental data on the wettability between liquid and solid phases. Such datasets include the melting temperature, surface tension, density/molar volume and viscosity of liquid metals or alloys, while the wetting is described in terms of the interfacial reactions, contact angle and work of adhesion together with well-defined operating conditions (working atmosphere, operating temperature, time, type of the substrate including its porosity and grain size) [10,41]. The non-reactive infiltration is governed by the viscous flow and it is related to non-reactive wetting [49,69]. Therefore, the modelling of non-reactive infiltration of Ir-Si / SiC systems is based on parabolic

Washburn's equation that is used to calculate the infiltration depth (Eq.(17)). To this aim, the model predicted thermophysical properties datasets, i.e. the surface tension (Eq.(13a) and Eq.(13b)) and viscosity (Eqs.(14)-(16)) of the Ir-80.5Si (at %) eutectic and IrSi₃ alloys were combined with the corresponding experimental contact angle values of $\theta = 10^\circ$ [12] measured at T=1623 K on SiC substrate with an average pore size ($r = 65 \mu\text{m}$) [12]. For a comparison, the same type of datasets for the Co-77.9Si (at %) eutectic alloy and pure liquid Si on SiC with the contact angle data of $\theta = 15^\circ$ [10] and $\theta = 15^\circ$ [70,71], obtained at 1723 and 1853 K, respectively, were used as inputs in Washburn's equation. The calculated curves are shown in Figure 8.

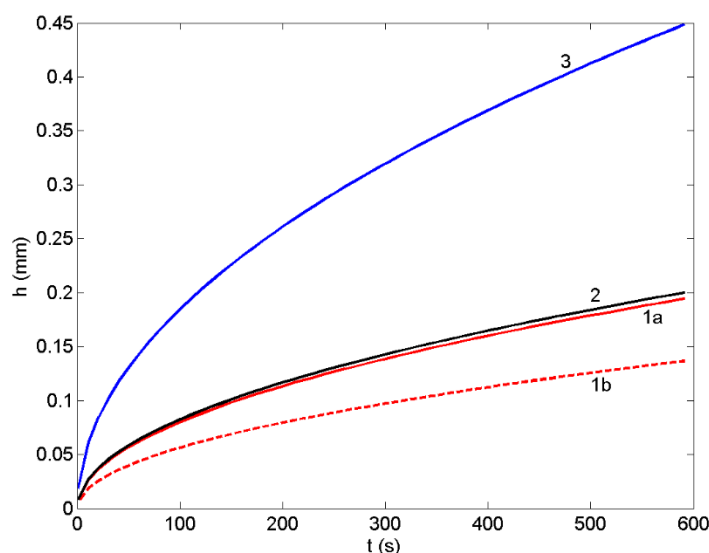


Figure 8. Infiltration depth of liquid Ir-80.5Si (at %) eutectic alloy into a porous SiC-substrate with a pore size of $r = 65 \mu\text{m}$, calculated for T=1873 K using different viscosity models: The Moelwyn-Hughes (curve 1a) and Terzieff's model (curve 1b). For a comparison, non-reactive infiltration of liquid Co-77.9Si (at %) eutectic alloy (curve 2) and pure Si (curve 3) on SiC are also shown.

The infiltration depth in the Ir-80.5Si / SiC system was calculated by Eq.(17) using the Moelwyn-Hughes (Figure 8; curve 1a) and the Terzieff (Figure 8; curve 1b) models for the prediction of the viscosity. Comparing the two infiltration curves with that of the Co-77.9Si / SiC system, (Figure 8; curve 1a), obtained by the Moelwyn-Hughes model seems to be more appropriate confirming the viscosity analysis in § 3.5. The lowest viscosity of liquid Si [62] results in the highest rate of infiltration and thus, the maximum values of the infiltration depth (Figure 8; curve 3).

Design of Si-based alloy / ceramic composites includes the porosity of ceramic preforms with cylindrical pores of radius varying between 0.14 and 1.15 microns [12,50-52,72]. The curves that characterised non-reactive infiltration of liquid Ir-80.5Si (at %) into solid SiC-preforms with porosity of 0.65, 0.85 and 1.15 microns are shown in Figure 9. As it can be expected, the infiltration depth (Eq.(17)) is proportional to the pore size of a porous SiC-preform and thus, for size ($r = 1.15 \mu\text{m}$) the maximum values of can be observed (Figure 9).

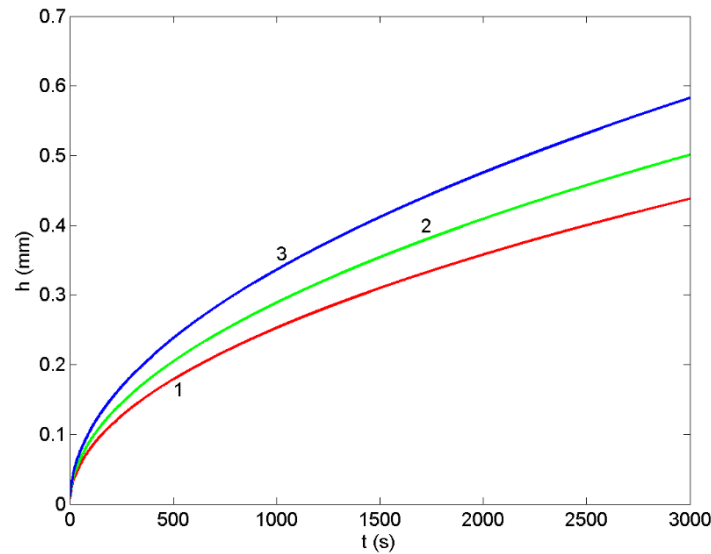


Figure 9. Infiltration depth of liquid Ir-80.5Si (at %) eutectic alloy into a porous SiC-substrate with a pore size (in μm) of $r = 65$ (curve 1), $r = 85$ (curve 2) and $r = 1.15$ (curve 3), calculated for $T=1873$ K by Washburn's equation.

Investigating Si and Si-based alloys in contact with various carbon preforms many authors have considered non-reactive infiltration as an initial step of reactive infiltration processes [10-13,50-52]. The wetting of carbon by liquid Si and its alloys, followed by the reaction between Si and C, lead to the formation of SiC by so-called *reaction-bonded silicon carbide* process [9,12,50]. Recent investigation of reactive infiltration of liquid eutectic Ir-80.5Si (at %) alloy into SiC-C porous preforms [12] showed linear infiltration curves (Figure 10a;b) indicating that the process is governed by the reaction accompanied by the change in the melt composition, i.e. from the Ir-80.5Si (at %) eutectic alloy to the IrSi_3 , resulting in an increase in the viscosity. At the end of the infiltration experiments [12], the infiltration curves (Figure 10a,b; curve 1) exhibit a small deviation of linearity that can be explained by a decreased Si-concentration in the alloy with respect to that necessary for SiC formation [52]. Analysing the experimental results related to liquid IrSi_3 / SiC [12], an irregular infiltration front was found and this may suggest a concomitant role of capillarity and viscous forces, at least at the final stage of reactive infiltration. Therefore, the last part of the infiltration curves may be considered to obey non-reactive infiltration law (Figure 10a,b; curve 2).

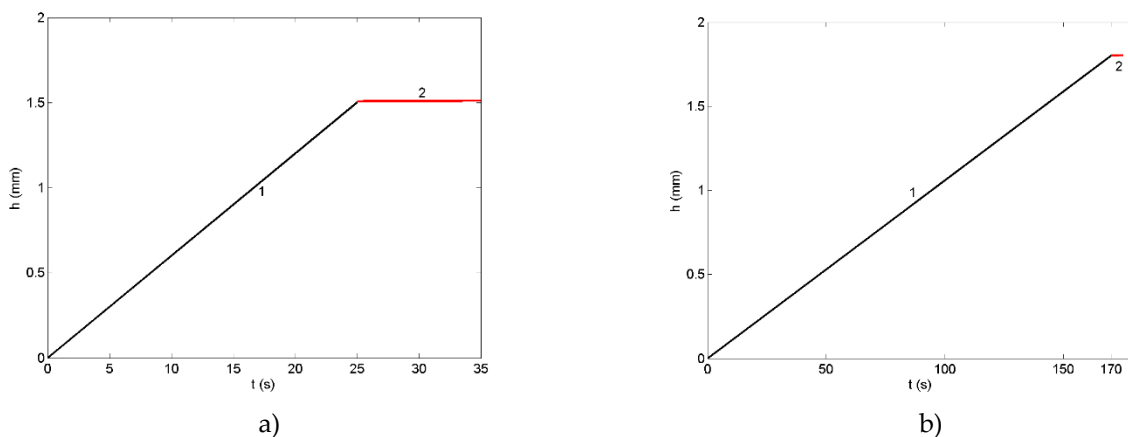


Figure 10. Infiltration curves for liquid IrSi_3 / SiC system for a) short and b) long-time experiments performed at $T=1523$ and $T=1623$ K [12]: the reactive infiltration (curves 1) and “similar to non-reactive” infiltration (curves 2).

Model predicted values of the surface tension and viscosity of liquid $IrSi_3$ alloy together with the contact angle values of liquid $IrSi_3$ / SiC systems measured at $T=1523$ and $T=1623$ K [12] were used to calculate non-reactive infiltration curves for the final stage of infiltration. Due to a very short duration of this stage, the infiltration curve is only slightly concave and look likes linear one (Figure 10a;b). In order to have a clear picture of phenomena occurring in the last stage of reactive infiltration, further investigation is needed.

4. Conclusions

A case study of liquid Ir-Si alloys / SiC systems is an example how the lack of experimental thermodynamic, surface and transport properties data, often necessary for materials and/or processes design, can be compensated by the model predicted values and subsequently combined with the experimental contact angle data to describe non-reactive infiltration. Therefore, in the present work, a step-by-step guide to properties modelling started from the predictions of the enthalpy of mixing and molar volume in terms of Miedema's model and their subsequent use as input to calculate other thermodynamic functions of mixing in the framework of Free Volume Theory. Once the energetic part of liquid Ir-Si alloys was defined, those data were used to simulate their thermophysical properties. Indeed, the surface segregation and surface tension of Ir-Si melts were obtained by the quasi-chemical approximation (QCA) for regular solution model, while the Moelwyn-Hughes model and more complex Terzieff's model were used to predict the viscosity. If possible, it is recommended to compare and discuss the behaviour or trend of model predicted property values of the new investigated system with the corresponding data of similar systems, available in literature. Accordingly, a comparison of the present results with the available properties data of Co-Si melts was done indicating the Moelwyn-Hughes model as more appropriate to describe the viscosity of Ir-Si melts. Based on the abovementioned, parabolic Washburn's equation was used to design non-reactive infiltration of Ir-Si / SiC systems, in terms of the infiltration depth during the process for different temperatures, time and pore size of SiC preforms.

Appendix. Symbols

A, B	components of an $A - B$ alloy
a_i ($i = A, B$)	activity of component i
C_i ($i = A, B$)	composition of component i
$C, 1 - C$	composition of A and B in an $A - B$ alloy
$C^s, 1 - C^s$	surface composition of components A and B
G_M	Gibbs free energy of mixing
G_M^{xs}	excess Gibbs free energy of mixing
H_M	enthalpy of mixing
L_{ii}	distance which interatomic potential extends in a cell of atom i in pure liquid
L_i	distance which interatomic potential extends in a cell of atom i in a liquid $A - B$ alloy
L_{A-B}	approximately the mean of L_{ii}
k_B	Boltzmann's constant
m_i ($i = A, B$)	atomic mass of component i
N	Avogadro's number
P	parameter of nearly random configuration of atoms in an $A - B$ alloy
Q	interaction parameter at the equiatomic composition
p, q	surface coordination fraction
R	gas constant
S	surface area of an alloy
$S_{cc}(0)$	concentration fluctuations in the long wavelength limit
$S_{cc}(0, id)$	concentration fluctuations for the ideal mixing
S_M^{xs}	excess entropy of mixing
S_{CONF}^{xs}	configurational excess entropy
S_{VIB}^{xs}	vibrational excess entropy

T	absolute temperature
V_i ($i = A, B$)	atomic volume of the component i
V^s	excess volume
U_{ii}	depth of potential energy in a cell of atom i in pure liquid i
U_i	depth of potential energy in a cell of atom i in a liquid $A - B$ alloy
Z	coordination number
α	mean surface area of an $A - B$ alloy
α_i ($i = A, B$)	surface area of atomic species i
α_1	short-range order parameter
β	auxiliary function for the bulk phase
β^s	auxiliary function for the surface phase
γ_i ($i = A, B$)	activity coefficient of component i
φ_i, φ_j ($i, j = A, B$)	work function of component i
η	viscosity of $A - B$ liquid alloys
η_i ($i = A, B$)	viscosity of component i
η_{id}	additive viscosity (ideal mixture)
η^{xs}	excess viscosity
μ, ν	stoichiometric coefficients
Ω_{AB}	exchange energy
$\sigma = \sigma_{L-G}$	surface tension (liquid-gas) of liquid $A - B$ alloys
σ_A	surface tension of pure component A
σ_B	surface tension of pure component B
$\bar{\sigma}_i$ ($i = A, B$)	hard sphere diameter of component i
θ	contact angle between liquid and solid phases
K	constant
$r_{eff} = r$	pore radius
h	infiltration depth
t	infiltration time

Author contributions:

All authors have read and agree to the submitted version of the manuscript.

Conceptualization, R.N., D.G., S.D.; methodology, R.N., D.G.; Data curation, R.N., D.G., S.D.; Software, R.N.; validation, R.N., D.G., S.D.; formal analysis D.G., S.D.; investigation D.G., R.N.; Software, R.N.; writing-original draft preparation, R.N., D.G., S.D.; writing-review and editing R.N., D.G., S.D.; supervision R.N., D.G.; Funding resources R.N., D.G.

Conflict of Interest: The authors declare no conflict of interest.

References

- [1] Allevato, C.E.; Vining, C.B. Phase diagram and electrical behavior of silicon-rich iridium silicide compounds. *J. Alloys Compd.* **1993**, *200*, 99-105.
- [2] Chung C.K.; Hwang, J. Epitaxial iridium silicide formation during deposition of Ir on Si(100) at high temperature under ultrahigh vacuum. *J. Appl. Phys.* **1994**, *76*, 1937-1939.
- [3] Lange, D.A.; Gibson, G.A.; Falco, C.M. Growth and structure of IrSi₃ on Si(111). *J. Appl. Phys.* **1994**, *75*(6), 2917-2920.
- [4] Kurt, R.W.; Pitschke, A.; Heinrich, J.; Schumann, Wetzig, K. Preparation of iridium silicide thin films by means of Electron Beam Evaporation. In Proceedings of the 16th Int. Conf. on Thermoelectrics (ICT '97. XVI), Dresden, Germany, August 26-29, 1997; Eds. I.B. Cadoff, E. Miller; IEEE Service Center: Piscataway, NY, USA, 1997, pp. 303-306.
- [5] Almendra, A.; Rodríguez, A.; Rodríguez, T.; Martín, P.; Jiménez, J. Micro-Raman study of iridium silicides. *J. Raman Spectrosc.* **2002**, *33*, 80-83.
- [6] Ma, X. Infrared absorption characteristics of polycrystalline iridium-silicide thin films. *Thin Solid Films* **2005**, *484*, 257-260.
- [7] Allevato, C.E. Vining, C.B.. Thermoelectric properties of semiconducting iridium silicides. In Proceedings of the 28th Intersociety Energy Conversion Engineering Conference (IECEC-93), Atlanta GA, USA, August 8-13, 1993; American Chemical Society: Washington, D.C., USA, 1993; Abstract No. 93497, p. 1239.
- [8] Chung, C.K.; Hwang, J.; Jaw, T.H.; Wu, D.S. Electrical properties of Ir-silicide formation on p-Si(100) in ultra-high vacuum. *Thin Solid Films* **2000**, *373*, 68-72.
- [9] Novakovic, R.; Korthaus, B. Advanced ceramics for use in highly oxidizing and corrosive environments: Silicides. *Key Eng. Mater.* **2001**, *201*, 183-217.
- [10] Caccia, M.; Amore, S.; Giuranno, D.; Novakovic, R.; Ricci, E.; Narciso, J. Towards optimization of SiC/CoSi₂ of composite material manufacture via reactive infiltration: wetting study of SiCo alloys on carbon materials. *J. Euro. Ceram. Soc.* **2015**, *35*(15), 4099-4106.
- [11] Caccia, M.; Narciso, J. Key parameters in the manufacture of SiC-based composite materials by reactive melt infiltration. *Materials* **2019**, *12*, 2425 (pp 1-15).
- [12] Camarano, A.D.; Giuranno, D.; Narciso, J. New advanced SiC-based composite materials for use in highly oxidizing environments: Synthesis of SiC/IrSi₃. *J. Eur. Ceram.* **2020**, *40*(3), 603-611.
- [13] Camarano, A.; Giuranno, D.; Narciso, J. SiC-IrSi₃ for high oxidation resistance. *Materials* **2020**, *13*(1), 98, 1-11.
- [14] Yamabe-Mitarai, Y.; Ro, Y.; Maruko, T.; Harada, H. Ir-Base Refractory Superalloys for Ultra-High Temperatures. *Metall. Mater. Trans. A* **1998**, *29*, 537-549.
- [15] Sha, J.B.; Yamabe-Mitarai, Y. Ir-Nb-Si ternary refractory superalloys with a three-phase fcc/L12/silicide structure for high-temperature applications. *Intermetallics* **2007**, *15*, 1638-1649.
- [16] Okamoto, H. Comment on Ir-Si (Iridium-Silicon), *J. Phase Equilib. Diff.* **1995**, *16*(5), 473-474.
- [17] Okamoto, H. Ir-Si (Iridium-Silicon). *J. Phase Equilib. Diff.* **2007**, *28*, 495.
- [18] Korst, W.L.; Finnie, L.N.; Searcy, A.W. The crystal structures of the monosilicides of Osmium, Iridium and Ruthenium. *J. Phys. Chem.* **1957**, *61*(11), 1541-1543.
- [19] Finnie, L.N. Structures and compositions of the silicides of ruthenium, osmium, rhodium and iridium. *J. Less-Common Met.* **1962**, *4*, 24-34.
- [20] Engström, I.; Zackrisson, F. X-Ray studies of silicon-rich iridium silicides. *Acta Chem. Scand.* **1970**, *24*, 2109-2116.
- [21] White, J.G.; Hockings, E.F. Crystal structure of iridium trisilicide, IrSi₃, *Inorg. Chem.* **1971**, *10*(9), 1034-1035.
- [22] Wittmer, M.; Oelhafen, P.; Tu, K.N. Electronic structure of iridium silicides. *Phys. Rev.* **1986**, *33*(8), 5391-5400.
- [23] Engström, I.; Lindsten, T.; Zdansky, E. The crystal structure of the iridium silicide Ir₃Si₅. *Acta Chem. Scand.* **1987**, *A41*, 237-242.
- [24] Searcy, A.W.; Finnie, L.N. Stability of solid phases in the ternary systems of silicon and carbon with rhenium and the six platinum metals. *J. Am. Ceram.* **1962**, *45*(6), 268-273.
- [25] Sha, J.B.; Yamabe-Mitarai, Y. Phase and microstructural evolution of Ir-Si binary alloys with fcc/silicide structure. *Intermetallics* **2006**, *14*, 672-684.

- [26] Meschel, S.V.; Kleppa, O.J. Standard enthalpies of formation of some 5d transition metal silicides by high temperature direct synthesis calorimetry. *J. Alloy. Compd.* **1998**, *280*, 231-239.
- [27] Meschel, S.V.; Kleppa, O.J. Thermochemistry of alloys of transition metals and lanthanide metals with some IIIB and IVB elements in the periodic table. *J. Alloy. Compd.* **2001**, *321*, 183-200.
- [28] Kleppa, O.J.; Topor, L. Standard enthalpies of formation of RuSi, RhSi, and IrSi. *Z. Metallkunde* **1988**, *79*, 623-628.
- [29] Iida, T.; Guthrie, R.I.L. *The thermophysical properties of liquid metals, Fundamentals*, 1st ed. University Press, Oxford, UK, 2015; Vol. 1, pp. 1-353.
- [30] Pauling, L. *Nature of the Chemical Bonding*, 3rd ed. Cornell University Press, Ithaca, NY, USA, 1960, pp. 1-664.
- [31] Singh, R.N.; March, N.H. Principles. In *Intermetallic Compounds. Principles and Practice*, 1st ed.; J.H. Westbrook, R.L. Fleischer, Eds., John Wiley & Sons, New York, USA, 1995, Vol. 1, pp. 661-686.
- [32] Miedema, A.R.; de Boer, F.R.; Boom, R. Model predictions for the enthalpy of formation of transition metal alloys. *CALPHAD* **1977**, *1*(4), 341-359.
- [33] Niessen, A.K.; de Boer, F.R.; Boom, R.; de Châtel, P.F.; Mattens, W.C.M.; Miedema, A.R. Model predictions for the enthalpy of formation of transition metal alloys II. *CALPHAD* **1983**, *7*(1), 51-70.
- [34] Miedema, A.R.; Niessen, A.K. The enthalpy of solution for solid binary alloys of two 4d-transition metals. *CALPHAD* **1983**, *7*(1), 27-36.
- [35] de Boer, F.R.; Boom, R.; Mattens, W.C.M.; Miedema, A.R.; Niessen, A.K. *Cohesion in Metals, Transition Metal Alloys*, 1st ed.; North Holland, Amsterdam, Netherlands 1988; pp. 1-127.
- [36] Tanaka, T.; Gokcen, N.A.; Morita, Z. Relationship between enthalpy of mixing and excess entropy in liquid binary alloys. *Z. Metallkd.* **1990**, *81*(1), 49-54.
- [37] Tanaka, T.; Gokcen, N.A.; Morita, Z.-I.; Iida, T. Thermodynamic relationship between enthalpy of mixing and excess entropy in liquid binary alloys. *Z. Metallkd.* **1993**, *84*(3), 192-199.
- [38] Tanaka, T.; Gokcen, N.A.; Kumar, K.C.H.; Hara, S.; Morita, Z.-I. Thermodynamic relationship between enthalpy of mixing and excess entropy in solid solutions of binary alloys. *Z. Metallkd.* **1996**, *87*(10), 779-783.
- [39] Novakovic, R.; Tanaka, T.; Muolo, M.L.; Lee, J.; Passerone, A. Bulk and surface transport properties of liquid Ag-X (X = Ti, Hf) compound forming alloys. *Surf. Sci.* **2005**, *591*, 56-69.
- [40] Costa, C.; Delsante, S.; Borzone, G.; Zivkovic, D.; Novakovic, R. Thermodynamic and surface properties of liquid Co-Cr-Ni alloys. *J. Chem. Thermodyn.* **2014**, *6*, 73-84.
- [41] Novakovic, R.; Giuranno, D.; Caccia, M.; Amore, S.; Nowak, R.; Sobczak, N.; Narciso, J.; Ricci, E. Thermophysical properties of liquid Co-Si alloys. *J. Molec. Liq.* **2016**, *221*, 346-353.
- [42] Moelwyn-Hughes, E.A. *Physical Chemistry*, 2nd ed.; Pergamon Press, New York, USA, 1961, pp. 786-788.
- [43] Takeuchi, A.; Inoue, A. Mixing enthalpy of liquid phase calculated by Miedema's scheme and approximated with sub-regular solution model for assessing forming ability of amorphous and glassy alloys. *Intermetallics* **2010**, *18*, 1779-1789.
- [44] Bhatia, A.B.; Thornton, D.E. Structural aspects of the electrical resistivity of binary alloys. *Phys. Rev. B* **1970**, *2*(8), 3004-3012.
- [45] Warren, B.E. *X-ray Diffraction*. 1st ed.; Addison-Wesley, Reading, Massachusetts, USA, 1969, pp. 1-381.
- [46] Terzieff, P. The viscosity of liquid alloys. *J. Alloys Compd.* **2008**, *453*(1-2), 233-240.
- [47] Iida, T.; Ueda, M.; Morita, Z. On the excess viscosity of liquid alloys and the atomic interaction of their constituents. *Tetsu to Hagane* **1976**, *62*, 1169-1178.
- [48] Terzieff, P. The viscosity of liquid alloys of polyvalent metals with Cu, Ag and Au: Theoretical treatments based on the enthalpy of mixing. *Physica B* **2009**, *404*, 2039-2044.
- [49] Eremenko, V.N.; Lesnik, N.D. The kinetics of the infiltration of porous materials with liquid metals. In *The role of surface phenomena in metallurgy*, 1st ed.; Eremenko, V.N.; Consultants Bureau, New York, USA, 1963; pp. 102-116.
- [50] Voytovych, R.; Bougiouri, V.; Calderon, N.R.; Narciso, J.; Eustathopoulos, N. Reactive infiltration of porous graphite by NiSi alloys. *Acta Mater.* **2008**, *56*, 2237-2246.
- [51] Israel, R.; Voytovych, R.; Protsenko, P.; Drevet, B.; Camel, D.; Eustathopoulos, N. Capillary interactions between molten silicon and porous graphite. *J. Mater. Sci.* **2010**, *45*, 2210-2217.

- [52] Eustathopoulos, N.; Israel, R.; Drevet, B.; Camel, D. Reactive infiltration by Si: Infiltration versus wetting. *Scripta Mater.* **2010**, *62*, 966-971.
- [53] Washburn, E.W. The Dynamics of Capillary Flow. *Phys. Rev.* **1921**, *17*, 273-283.
- [54] Deryagin, B. V.; Melnikova, M. K.; Krylova, V. I. *Koll. Zhurn.*, **1952**, *14*, 423-427.
- [55] Assael, M.J.; Armyra, I.J.; Brillo, J.; Stankus, S.V.; Wu, J.; Wakeham, W.A. Reference Data for the Density and Viscosity of Liquid Cadmium, Cobalt, Gallium, Indium, Mercury, Silicon, Thallium, and Zinc. *J. Phys. Chem. Ref. Data* **2012**, *41*, 033101.
- [56] Ishikawa, T.; Paradis, P.-F.; Fujii, R.; Saita, Y.; Yoda, S. Thermophysical property measurements of liquid and supercooled iridium by containerless methods. *Int. J. Thermophys.* **2005**, *26*(3), 893-904.
- [57] Novakovic, R.; Tanaka, T. Bulk and surface properties of Al-Co and Co-Ni liquid alloys. *Physica B* **2006**, *371*, 223-231.
- [58] Schlesinger, M.E. Thermodynamics of solid transition-metal silicides. *Chem. Rev.* **1990**, *90*, 607-628.
- [59] Pasturel, A.; Hicter, P.; Cyrot-Lackmann, F. On the heats of formation of solid germanides and silicides of transition metals. *Physica B* **1984**, *124*, 247-250.
- [60] Shergin, L.M.; Popel, S.I.; Tsarevskii, B.V. Temperature dependence of the density and surface tension of Cobalt-Silicon and Nickel-Silicon melts. Papers of the Institute of Metallurgy, Acad. of Sci. of the USSR (Sverdlovsk), **1971** 25 pp. 52-61. (in Russian)
- [61] Hibiya, T.; Morohoshi, K.; Ozawa, S. Oxygen partial pressure dependence on surface tension and its temperature coefficient for metallic melts: a discussion from the viewpoint of solubility and adsorption of oxygen. *J. Mater. Sci.* **2010**, *45*, 1986-1992.
- [62] Rhim, W.-K.; Ohsaka, K. Thermophysical properties measurement of molten silicon by high-temperature electrostatic levitator: density, volume expansion, specific heat capacity, emissivity, surface tension and viscosity. *J. Cryst. Growth* **2000**, *208*, 313-321.
- [63] Terzieff, P. The viscosity of liquid alloys. *J. Alloys Compd.* **2008**, *453*(1-2), 233-240.
- [64] Protopapas, P.; Andersent, H.C.; Parlee, N.A.D. Theory of transport in liquid metals. I. Calculation of self-diffusion coefficients. *J. Chem. Phys.* **1973**, *59*(1), 15-25.
- [65] Orton, B. A double hard sphere model for molten semiconductors and semimetals. *J. Phys. Colloques* **1980**, *41*(C8), pp.C8-280-C8-283.
- [66] Zhang, L.; Du, Y.; Xu, H.; Pan, Z. Experimental investigation and thermodynamic description of the Co-Si system, *Calphad* **2006**, *30*, 470-481.
- [67] Paradis, P.-F.; Ishikawa, T.; Koike, N. Thermophysical property measurements of liquid and supercooled cobalt. *High Temp.-High Press.* **2008**, *37*(1), 5-11.
- [68] Beltyukova, A.L.; Olyanina, N.V.; Ladyanov, V.I. Dependences of Co-Si melt viscosity on temperature and concentration, *High Temp.* **2019**, *57*(1) 41-48.
- [69] Rado, C.; Kalogeropoulou, S.; Eustathopoulos, N. Wetting and bonding of Ni-Si alloys on silicon carbide. *Acta Mater.* **1999**, *47*(12) 461-473.
- [70] Naidich, Yu. V. *Contact phenomena in metallic alloys*. 1st ed.; Naukova Dumka, Kiev, USSR, 1972, p. 172. (in Russian).
- [71] Naidich, Yu. V. *Progress in surface and membrane science*. Vol. 14, Eds. Cadenhead D.A. et al., Academic Press, New York, 1981, p. 353.
- [72] Calderon, N.R.; Voytovych, R.; Narciso, J.; Eustathopoulos, N. Pressureless infiltration versus wetting in AlSi/graphite system. *J. Mater. Sci.* **2010**, *45*, 4345-4350.