

## Article

# Effects of MWCNTs on Char Layer Structure and Physicochemical Reaction in Ethylene Propylene Diene Monomer Insulators

Zhiheng Chen <sup>a</sup>, Shida Han <sup>a</sup>, Yuan Ji <sup>a</sup>, Hong Wu <sup>a,\*</sup>, Shaoyun Guo <sup>a</sup>, Ning Yan <sup>b,\*</sup> and Hongyan Li <sup>b</sup>

<sup>a</sup> The State Key Laboratory of Polymer Materials Engineering, Polymer Research Institute of Sichuan University, Chengdu 610065, China

<sup>b</sup> Xi'an Modern Chemistry Research Institute, Shaanxi, Xi'an, 710065, China

\* Correspondence: address: \*wh@scu.edu.cn(H.W.); [yanning\\_204@163.com](mailto:yanning_204@163.com)(N.Y.)

**ABSTRACT:** As one of the most promising ablative fillers, multi-walled carbon nanotubes (MWCNTs) have been used to improve the ablative resistance of Ethylene-Propylene-Diene Monomer (EPDM) insulators by facilitating the carbothermal reduction reaction of silica. However, the contribution of MWCNTs to char layer structure of the insulators was unclear. In this work, the effects of MWCNTs on char layer structure and ablative resistance were investigated in different EPDM-based insulators with and without silica. The results showed that adding only 3 phr MWCNTs can reduce the linear ablation rate of EPDM-based insulators without silica by 31.7%, while 6 phr MWCNTs are required to obtain similar results in EPDM-based insulators with silica. Both the char layer morphology of the two insulators gradually evolved into dense porous structure as MWCNTs content increasing, but their formation mechanisms are different. The XRD and Raman spectrum showed that different physicochemical reactions occurred around MWCNTs under different charring components. The proposed ablation mechanism was further verified by designing alternating multilayer distribution of MWCNTs and silica. This work can guide the construction of desirable char layer structure for increasing ablative resistance of EPDM-based insulators.

**Keywords:** Polymer-matrix composites (PMCs); Aramid fibres; High-temperature properties; Thermal properties

## 1. Introduction

Polymer-matrix composites (PMCs) have been commonly applied to thermal protective system of Solid Rocket Motor (SRM) [1-3]. Ethylene-Propylene-Diene Monomer (EPDM) composites are considered the ideal insulators in combustion chamber of SRM, due to their excellent ablative resistance, moderate thermal shock resistance, low density, and so on [4-7]. Generally, a porous char layer formed during the ablation can be the first barrier to resist erosion in EPDM-based insulators [8-11]. Meanwhile, the erosion of heat flow and the escape of pyrolysis gas can be affected by the size and connection of the pores in char layers [12-15], and various ablative fillers (heat resistant fibers, ceramic fillers, phenolic resins and so on) are added to regulate the char layer structure for desirable ablative resistance [16-21]. However, with the advancement of propulsion technology, EPDM-based insulators need better ablative resistance to endure more severe condition.

Multi-walled carbon nanotubes (MWCNTs) with high strength and thermal conductivity are considered as a promising ablative filler to improve the ablative resistance of EPDM-based insulators [22-26]. Li et al. [22-23] found that the addition of MWCNTs in the EPDM-based insulators accelerate the carbothermal reduction reaction of silica to increase the char residue, resulting in the improvement of the ablative resistance. In subsequent work, they [25] found that the char residues formed during the ablation can cover on the surface of MWCNTs, which can effectively reduce the thermal conductivity of the char layers. In fact, the above ablation mechanisms were proposed based on that the introduction of MWCNTs can affect the physicochemical reactions of silica during the ablation, however, the contribution of MWCNTs to char layer structure of EPDM-based insulators was unclear.

For phenolic composites, MWCNTs are regularly used to enhance the char layers to obtain excellent ablative resistance [27-32]. Wang et al. [29] emphasized the importance of

MWCNTs networks on ablative resistance of phenolic composites and found that adding only 0.3% MWCNTs can decrease the linear ablation rate from 0.55mm/s to 0.13 mm/s. Yum et al. [31] found that 0.1wt% MWCNTs can reduce the linear ablation rate of phenolic composites by about 30%, since the crystalline rods formed by the stress graphitization of MWCNTs can strengthen char layers. Besides, Yazdani et al. [32] proposed that the char layers enhanced by MWCNTs network can act as a barrier to protect the char residue, based on the result that adding 1.0wt% MWCNTs can decrease the linear ablation rate of carbon fiber/phenolic composites by 80%. Inspired by the direct contribution of MWCNTs on the char layers of phenolic composites, the effect mechanism of MWCNTs on the char layers of EPDM-based insulators especially without silica should be crucial to fully utilize the ablative potential of MWCNTs.

In this work, different contents of MWCNTs were introduced to EPDM-based insulators with and without silica. The effects of MWCNTs on char layer structure and the physicochemical reactions during the ablation were investigated systematically under the two charring components. Furthermore, the ablation mechanism was proposed based on the relationship between the char layer structure and ablative resistance of EPDM-based insulators, and further verified by designing alternating multilayer distribution of MWCNTs and silica in the insulators.

## 2. Experimental

### 2.1. Materials

A low mooney viscosity EPDM (Keltan 2650C; ethylene content, 46.0 wt%; ENB content, 6.0%;  $ML_{125^{\circ}C}^{1+4}$  25) was purchased from LANXESS Germany. Chopped (6 mm) Kevlar fibers were supplied by Bluestar (Chengdu) New Material Co., Ltd. The type of the MWCNTs (average diameter, 9.5 nm; average length, 1.5  $\mu$ m) is the NC7000 purchased from Belgium. Fumed silica (Average particle size, 5  $\mu$ m) was supplied by Shijiazhuang Ruituo Chemical Technology Co., Ltd. Boron phenolic resins were obtained from Tianyu High-Temperature Resin Materials Co., Ltd. Bis(1-(tert-butylperoxy)-1-methylethyl)-benzene (BIPB) and triallylisocyanurate (TAIC) were supported by Hunan Yixiang Technology Co., Ltd. and Guangzhou Jinchangsheng Technology Co., Ltd, respectively. Paraffin oil, Sulphur, zinc oxide and stearic acid were supplied by Chengdu Chron Chemical Co., Ltd.

### 2.2. Preparation of EPDM-based insulators

Table S1 lists the formulations of EPDM-based insulators. Group NS and group S represent insulators without silica and with silica, respectively. And these insulators are abbreviated as NS-C-x and S-C-x, where x represents the content of MWCNTs. The addition content of MWCNTs was selected as 0 phr (parts per hundred grams of EPDM), 0.3 phr, 0.7 phr, 1.5 phr, 3 phr, 6 phr, which was set to facilitate the investigation of the effect of MWCNTs with low content on the ablative resistance of EPDM-based insulators. The preparation process mainly includes mixing and vulcanization. Firstly, EPDM, silica, MWCNTs, boron phenolic resin, Aramid Fiber (AF) and other fillers were mixed in a two-roll mix mill (LRM-S-150, Labtech) at the roll temperature of 30 °C. When all ingredients were added, lower the roll gaps to less than 0.1mm to obtain a good distribution. Subsequently, after standing for more than 24 hours, the compounds can be vulcanized in the mold at 170 °C and 15 MPa for the optimum cure time T90.

### 2.3. Characterization and tests

#### 2.3.1. Ablation tests

Oxyacetylene ablation test was conducted on a test bed manufactured by Xi'an Zhi Rui Industrial System Engineering Co., Ltd. The flow rates of oxygen-acetylene gas in the test process were 1512L/h and 1116L/h respectively. According to the calculation of the calibrated water-cooled heat flux meter, the actual value of heat flux reached 457 W/ cm<sup>2</sup>.

The test sample size and the distance from the sample surface to the tip of the nozzle are  $\phi 30 \times 10$  mm and 10 mm respectively. The sample center was ablated with an oxyacetylene flame for 30 seconds. The mass ablation rate, linear ablation rate and charring rate are often used to evaluate the ablative resistance of insulators, and they are defined as follows. Mass ablation rate = (original mass of sample – mass of sample after ablation)/ablation time. Linear ablation rate = (original thickness of sample – thickness of sample after ablation)/ablation time. Charring rate = (original thickness of sample – thickness of sample without char layers after ablation)/working time.

In addition, a K-type thermocouple was set on the back face of the ablated sample to measure the maximum back-face temperature ( $T_{\max, b}$ ) of insulators during ablation process, which can be used to characterize the thermal insulation performance of the EPDM-based insulators.

### 2.3.2. Thermal stability and thermal conductivity test

Thermogravimetric analysis (TGA) of MWCNTs and cured insulators were carried out from 30 °C to 800 °C with the heating rate of 10 °C/min under a nitrogen atmosphere, using a thermogravimetric analyzer (TG209F1 Iris. NETZSCH). Thermal conductivity of insulators was measured at room temperature using a transient plane heat source method apparatus (HotDisc1500, Sweden).

### 2.3.3. Morphology observation

The dispersion of MWCNTs in EPDM-based insulators was observed by transmission electron microscopy (TEM, Tecnai G2 F20 S-TWIN, FEI, America). The char layer surface and char layer section were observed in detail by a scanning electron microscopy (SEM, JSM-5900LV, Japan).

### 2.3.4. Mechanical property

An electronic universal testing machine (Model: CMT-4104) was used to test the mechanical properties of the char layers and EPDM-based insulators.

### 2.3.5. Component analysis

Energy-dispersive X-ray spectrometer (EDS) was used to analyze the element content of char layers. The degree of crystallinity of the char layers with different content MWCNTs was analyzed by an X-ray diffractometer (XRD, Ultima IV, Rigaku, Japan) and Raman spectrum (LabRAM HR, HORIBA, France).


## 3. Results and discussion

### 3.1. Dispersion of MWCNTs and thermal stability of EPDM-based insulators

Fig S1 (a) and (b) showed the dispersion of 3 phr MWCNTs in EPDM-based insulators with and without silica, respectively. Most MWCNTs have uniform dispersion in the both EPDM-based insulators, except a few aggregates of MWCNTs. And it can be seen that silica formed larger clusters (Fig. S1(a)), showing poorer dispersion due to the high concentration used. Due to the excellent thermal stability of MWCNTs, the introduction of MWCNTs should enhance the thermal stability of the both EPDM-based insulators. And the TGA results of the insulators collected at the temperature ranging from 30 °C to 800 °C are shown in Fig. S2 (b) and (c). The residual mass of both insulators gradually increases as the increasing of MWCNTs content, suggesting the positive effects of MWCNTs on residual mass of the insulators. And the insulators of group S have higher residual mass than the insulators of group NS, which can be ascribed to the addition of silica with high amount (Fig. S2 (a)).

### 3.2. Ablative resistance and thermal insulation performance of EPDM-based insulators

The ablative resistance of the insulators can be directly represented by the linear ablation rate. As it shown in Fig. 1 (a) and Table S2, the linear ablation rate of both insulators showed different variation trends in two groups as MWCNTs content increasing. In group NS, the linear ablation rate of the insulators decreased to 0.0801 mm/s as the MWCNTs content increased to 3 phr, which is 31.7% lower than that of the insulators without MWCNTs. However, the linear ablation rate of NS-C-6 is higher than that of the NS-C-3, indicating that the addition of excess MWCNTs is not conducive to the ablative resistance of the insulators in group NS. In group S, the linear ablation rate of the insulators increased from 0.0980 mm/s (S-C-0) to 0.1076 mm/s (S-C-0.7) as the MWCNTs content increasing, which revealed that the addition of MWCNTs with low content can slightly decrease the ablative resistance of the insulators. When the MWCNTs content over 0.7 phr, the linear ablation rate of the insulators begins to decrease as the MWCNTs content increasing, and the S-C-6 shows the lowest linear ablation rate of 0.0837 mm/s in group S. Meanwhile, it can be noticed that the linear ablation rate of NS-C-3 is 9% lower than that of S-C-3 under the addition of MWCNTs with the same content, and even is 4.3% lower than that of S-C-6 which has the best ablative resistance in group S. The reason that MWCNTs have different effects on the ablative resistance in the EPDM-based insulators with and without silica will be discussed by analyzing the char layer structure in the next section.

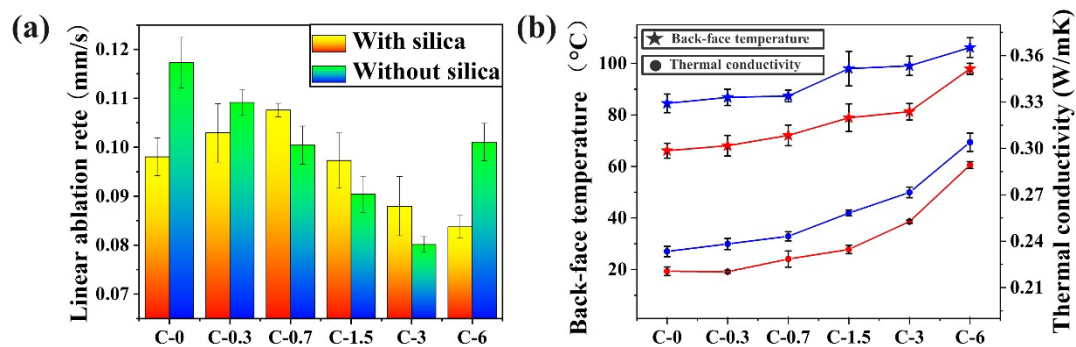

**Figure 1.** Effects of MWCNTs content on linear ablation rate (a) and thermal insulation performance (b) of the EPDM-based insulators with and without silica.

Due to their high thermal conductivity, the addition of MWCNTs is bound to have impact on the heat transfer during the ablation. In this work, the thermal conductivity and the back-face temperature ( $T_{\max, b}$ ) were used respectively to assess the heat transfer rates and thermal insulation performance. As can be seen from Fig. 1 (b) and Table S3, the thermal conductivity and the  $T_{\max, b}$  of the insulators in two groups significantly increase with the increase of the MWCNTs content. The insulators of group S have higher thermal conductivity and  $T_{\max, b}$ , showing poorer thermal insulation performance than the insulators of group NS due to the addition of silica with high thermal conductivity of 27 W/mK. Interestingly, the NS-C-3 with the best ablative resistance has lower  $T_{\max, b}$  than that of all the insulators in group S, especially the  $T_{\max, b}$  of NS-C-3 is even 3 °C lower than the S-C-0 which has the lowest  $T_{\max, b}$  in group S. Besides, the higher thermal conductance ability can accelerate the heat transfer from surface to interior, and enhance the pyrolysis process of EPDM to promote the fast formation of char layers [12, 15, 20]. And it can be noticed that the thickness of char layers increases with the increase of MWCNTs content in the insulators (Table. 1).


**Table 1.** Effects of MWCNTs content on thickness and compress properties of char layer.

Samples	Char layer thickness (mm)	Compress stress (MPa) Compress strain 10%
S-C-0	1.57±0.06	0.50±0.15

S-C-0.3	1.62±0.04	0.47±0.22
S-C-0.7	1.76±0.06	1.26±0.22
S-C-1.5	1.90±0.03	1.65±0.24
S-C-3	2.02±0.02	2.07±0.04
S-C-6	2.03±0.02	2.11±0.08
NS-C-0	1.60±0.11	0.44±0.13
NS-C-0.3	1.89±0.07	0.69±0.23
NS-C-0.7	1.98±0.04	0.93±0.12
NS-C-1.5	1.92±0.05	1.12±0.11
NS-C-3	1.93±0.07	1.16±0.27
NS-C-6	1.84±0.14	1.15±0.25


3.3. Morphological analysis and component analysis of char layers

The char layers are the first barrier of EPDM-based insulators to resist heat flow, and the char layer structure is closely related to the ablative resistance of EPDM-based insulators. Thus, analyzing the variation of char layer structure is essential to in-depth understanding the contribution of MWCNTs on ablative resistance in EPDM-based insulators. As shown in Fig. 2, the char layer surface of group NS varied from a loose structure to a porous structure as the increase of MWCNTs content. It can be observed that the loose structure of NS-C-0 is formed based on the fiber skeleton arising from the exposed AF in Fig. 2 (a) and (e). The loose structure can be easily invaded by the external heat flow, leading to the worst ablative resistance of NS-C-0. With the addition of MWCNTs, the high reactivity of MWCNTs promoted the deposition of pyrolysis gas [24-26, 29-30] and some char residues appeared around the AF skeleton (Fig. 2 (b) and (f)) to improve the compactness of NS-C-0.3 char layer. And as the increase of MWCNTs, the accumulation of char residues based on AF skeleton is improved, making the char layer structure transform from looseness to porosity (Fig. 2 (c) and (g)), which enhances the ability to block heat flow and improves the ablative resistance. Furthermore, the char residues fixed by MWCNTs can prevent the carbon skeleton from contacting with oxygen to protect it from oxidation [27-30], resulting in the improvement of oxidation resistance of the char layers. However, it can be found that the porous structure in char layers of NS-C-6 is denser than that of NS-C-3, while the NS-C-6 insulator shows higher linear ablation rate. In fact, the char layers of NS-C-6 has smaller pore diameter than the char layers of NS-C-3 (Fig. S3), and the char layers with smaller pore has higher pore pressure and need to subject more drastic internal erosion [8,10-11].

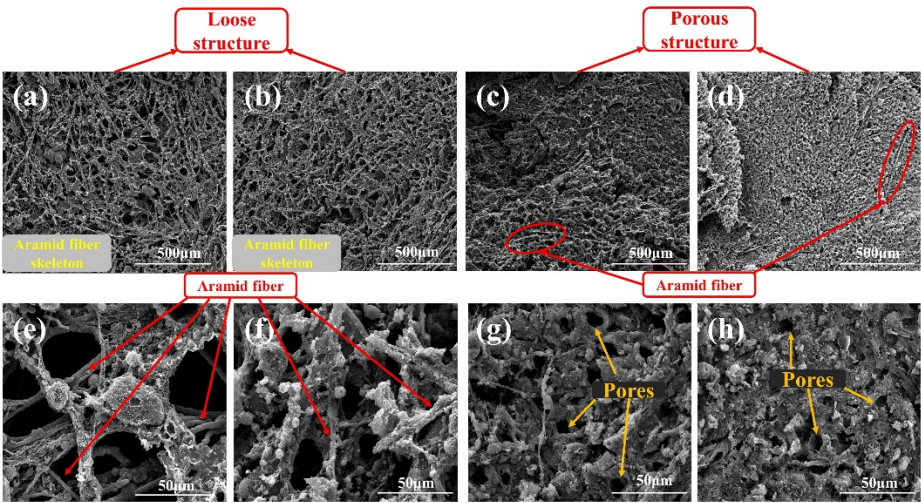

**Figure 2.** Effects of MWCNTs content on char layer surface of EPDM-based insulators without silica: NS-C-0 (a, e), NS-C-0.3 (b, f), NS-C-3 (c, g) and NS-C-6 (d, h).

Since silica can melt and form liquid ceramic film to resist thermal-chemical erosion and promote the deposition of pyrolysis gas during ablation [8, 18], porous char layers were formed based on carbonized matrix in group S, with interspersed AF to enhance the strength and integrity of char layers (as shown in Fig. 3). For S-C-0, the char layers show a dense structure with a few pores (Fig. 3 (a)), while massive pores were generated on the char layers as the addition of a small amount of MWCNTs (such as Fig. 3 (b) and Fig. S5 (b)), which shows high degree of fragmentation. These char layers are conducive to the penetration of external heat into the interior, so the ablative resistance became worse compared to the S-C-0. Interestingly, the pore size of char layers became smaller as the gradual increase of MWCNTs (Fig. S5) and the linear ablation rate starts to decrease continually when the MWCNTs contents exceeds 0.7 phr, which can be attributed to the effective blocking by progressively densified char layers. Meanwhile, elemental analysis was employed to evaluate the components on char layer surface, and it can be seen from Fig. S6 that the proportion of Si obviously increased due to the addition of MWCNTs. And the char layers with more MWCNTs have more proportion of Si (Fig. S6), which revealed that the more gaseous silica was transformed to silicon carbide by the carbothermal reduction reaction under high temperature condition [22-23], with less gaseous silica escaping from char layers.

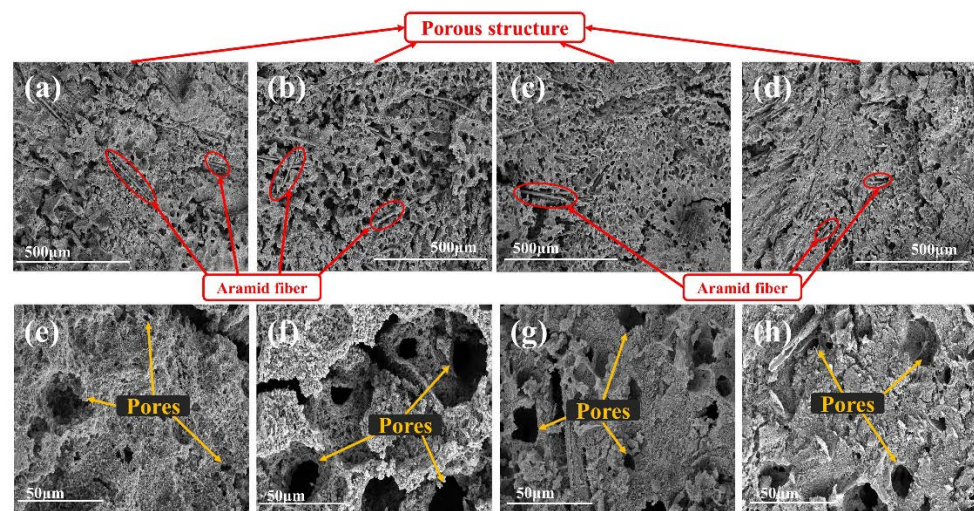


**Figure 3.** Effects of MWCNTs content on the char layer surface of EPDM-based insulators with silica: S-C-0 (a, e), S-C-0.3 (b, f), S-C-3 (c, g), S-C-6 (d, h).

The char layer cross-section of Fig. S4 and Fig. S6 are observed in magnification, and the image results are shown in Fig. S7. The char layers of group NS are obviously loose and have many large pores (red circles in Fig. S7 (a-d)), and the char layers of the group S have only a few small pores and narrow cracks (red circles in Fig. S7 (e-h)). The differences in the morphological structure of the char layers are still attributed to the variations of MWCNTs and silica. For group NS, similar to the evolution trend of their char layer surface, the pores of the char layer cross-section gradually decrease with the increase of MWCNTs content, and the reason can also be attributed to the fixation of pyrolytic carbon by MWCNTs [24-26, 29-30]. Silica can promote the deposition of pyrolysis carbon by melting to form a liquid film [8, 18], resulting in the dense char layers of group S. However, due to the coverage of much pyrolysis carbon, the char layer cross-section of group S are difficult to observe their evolutionary way.

Further magnification and observation of the char layers revealed the difference between the char layers of group NS and group S. The microstructure of char layers of group

NS is shown in Fig. S8 (a-d), char residue increases to form a dense structure in char layers as MWCNTs content increasing, which is similar to the macroscopic evolution of the char layers in Fig. 2. Likewise, the char layers of group S show finer and denser microstructure than that of group NS, and there are many smaller and uniform pores (Fig. S8 (e-h)). The reason is that the carbothermal reduction reaction of silica can consume large chars to generate silicon carbide during the ablation [22-23]. It can be seen from Fig. 4 that the dense structure in char layers is composed of micro networks, but the morphology and EDS results of the micro networks are different in both char layers. The micro networks in char layers of NS-C-3 are denser than that of S-C-3, and there are some aggregates of C element in the micro networks of char layers of NS-C-3 (Fig. 4 (c)). The Si and C element are uniformly distributed in the micro networks of S-C-3 (Fig. 4 (f)), which is because the most deposited chars are consumed by reacting with silica. Thus, the loose micro networks are formed inside the char layers of group S than that of group NS, which can explain the different effects of MWCNTs on ablative resistance in the both EPDM-based insulators. Besides, as the addition of MWCNTs with high content, many dense char residues appeared around the micro networks in the char layers of the two groups (Fig. S8 (c), (d), (g) and (h)), which revealed the excellent ability of the micro networks to fix char residue.

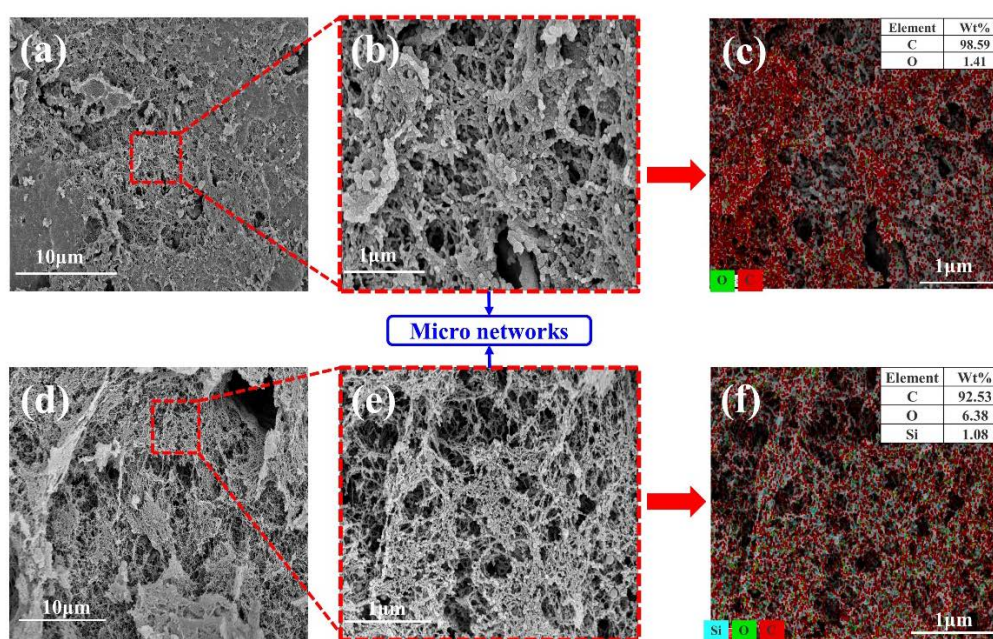


**Figure 4.** Analysis of micro networks in the char layer: NS-C-3 (a, b, c) and S-C-3 (d, e, f).

### 3.4. Compression property and component analysis of char layers


Previous studies [25-27, 29-31] proposed that the MWCNTs can form rod-shape structure by promoting the graphitization of carbonized matrix to strengthen char layers, resulting in the increasing of compression property of char layers. The results of compression test (Table 1) of char layers in our work showed similar findings. As the MWCNTs content increased, char layers showed growing compression stress in two groups. And the char layers of group S have higher compression strength than that of group NS under the addition of MWCNTs with same content, since the MWCNTs can promote the formation of silicon carbide with high hardness [22-23].

XRD test (Fig. 5) and Raman spectrum (Fig. 6) were used to analyze the composition of char layer, and the trend of  $I_D/I_G$  (the ratio of intensities of D band around  $1340\text{ cm}^{-1}$ / G band near  $1570\text{ cm}^{-1}$ , which can on behalf of the metric of “an amount of crystal boundary” or the disorder of graphitic structure [28, 31]) were further calculated for Raman spectra

(shown in Fig. 6 (c)). It can be noticed that the (002) peak corresponding to near-graphite structures improved obviously as the increase of MWCNTs content (Fig. 5 (a) and (b)), which indicated the ordered structure of carbon increased in the two charring components. Actually, MWCNTs were considered can act as crystal growth nuclei for the graphitization of carbonized matrix [28, 31], and improve the content of near-graphite structure of char layers. However, the above effects are obviously different in the two charring components (Fig. 6), and it can be observed that the  $I_D/I_G$  of group NS rapidly decreased as the increase of MWCNTs, while the value of group S only slightly decreased. The results suggest that MWCNTs only can effectively promote the graphitization of pyrolysis carbon in charring component without silica, while the MWCNTs are more trending to promote the carbothermic reduction of silica in the charring component with silica [22-23]. And the formation of silicon carbide can also be proved by the XRD profiles of group S (Fig. 5 (d)), which showed the peak ((111), (220), (311)) corresponding to silicon carbide [23, 28, 31].

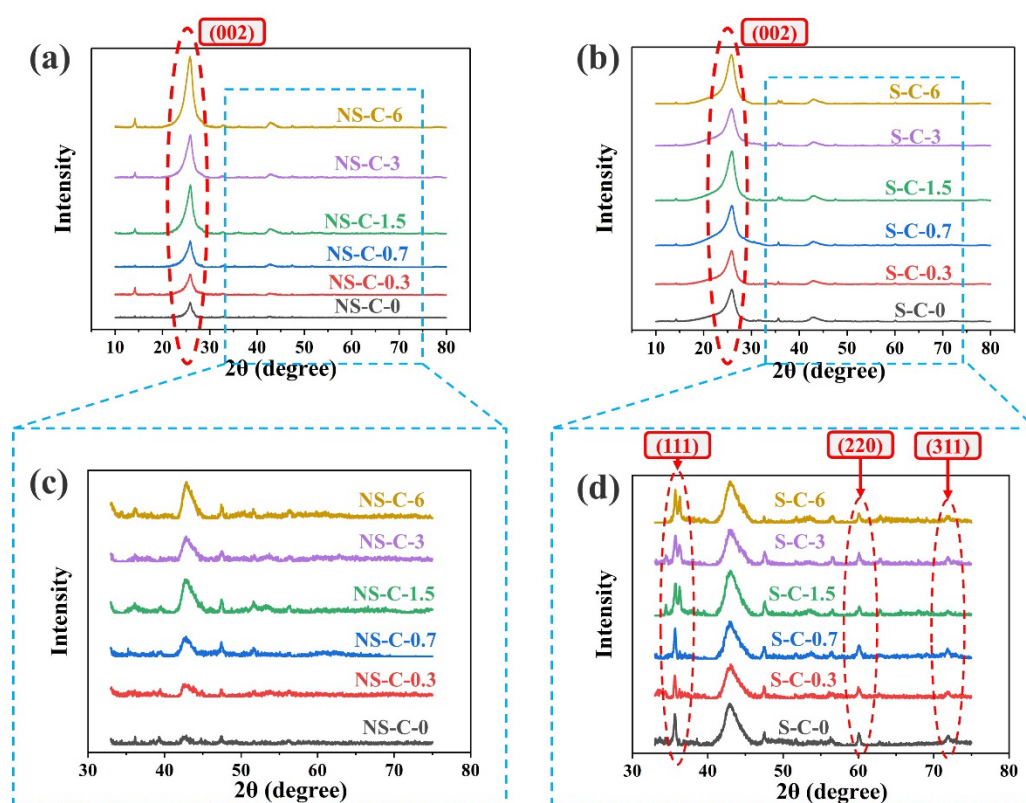


**Figure 5.** Effects of MWCNTs content on the X-ray diffraction profiles of char layers: group NS (a, c) and group S (b, d).

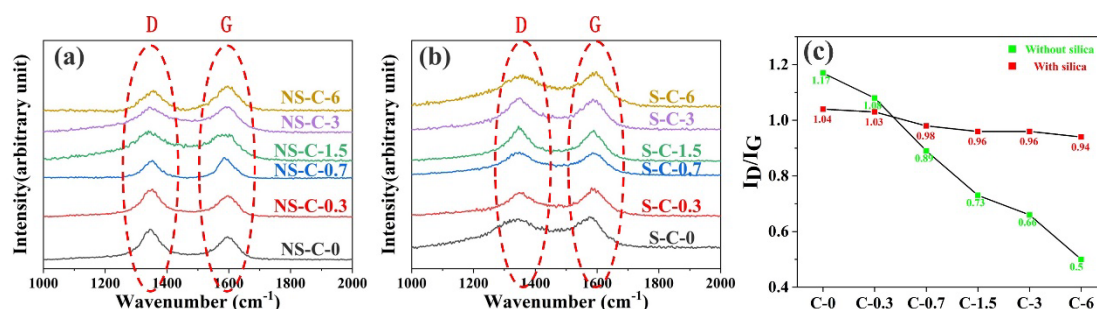

**Figure 6.** Effects of MWCNTs content on the Raman spectrum of char layers: group NS (a), group S (b), and  $I_D/I_G$  (c).

### 3.5. Ablation mechanism

The difference of ablative resistance in EPDM-based insulators can be ascribed to the diversity of their char layer structure. So, we attempt to explain the contribution of MWCNTs on ablative resistance in EPDM-based insulators by analyzing the effects of MWCNTs on the char layer structure. In the EPDM-based insulators without silica, a loose char layer can be formed during the ablation, which is formed based on the carbonized AF skeleton (Fig. 2 (e) and Fig. 7 (a)). The introduction of MWCNTs can form the micro networks to fix many micro char residues around the AF skeleton (Fig. 2 (f) and Fig. 7 (b)), which can improve the compactness of char layers. And more micro networks are formed with the increase of MWCNTs content, which result the evolution of char layer morphology from loose structure to porous structure (Fig. 2 (g) and Fig. 7 (c)). The denser porous structure can more efficiently block heat flow than the loose structure in char layers. Meanwhile, the introduction of MWCNTs can efficiently enhance the oxidation resistance and strength of char layers by accelerating the graphitization of pyrolysis carbon (Fig. 5 and Fig. 6). Thus, the ablative resistance of EPDM-based insulators gradually improves as the MWCNTs increase to a certain content. However, the increase of the heat transfer rate and the reduction of pore diameter in char layers occur simultaneously, which can make char layers to subject more drastic internal erosion [10-11], resulting in the decrease of ablative resistance in EPDM-based insulators with high MWCNTs content.

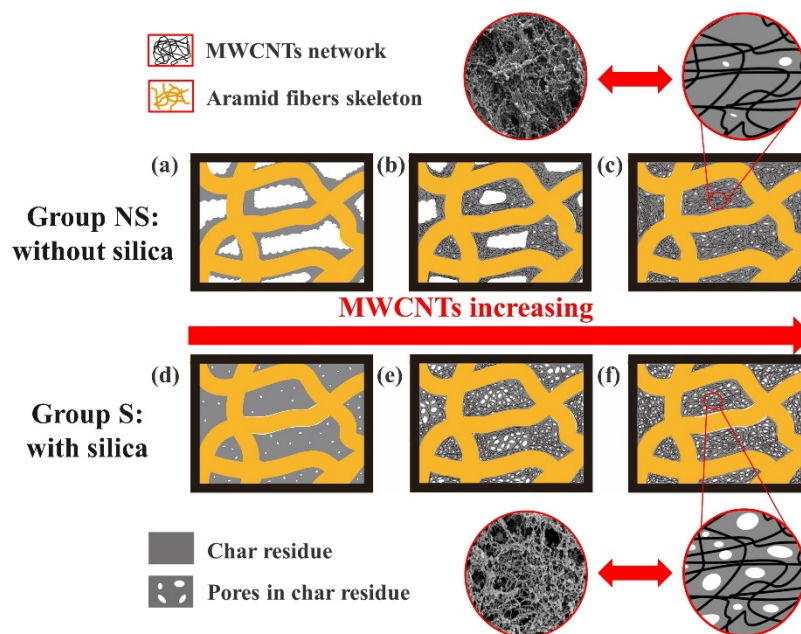


**Figure 7.** Effects of MWCNTs on char layer structure in EPDM-based insulators.

In the EPDM-based insulators with silica, silica can form liquid silica film by melting to increase the overflow resistance of pyrolysis gas and promote the deposition of pyrolysis gas [8, 18]. Thus, a dense char layer based on the carbonized EPDM and phenolic resin can be formed by the deposition of pyrolysis gas (Fig. 3 (e) and Fig. 7 (d)). However, the addition of MWCNTs with low content can accelerate the pyrolysis of the insulators due to their high thermal conductivity, resulting in the formation of massive pores on the char layers surface (Fig. 3 (f) and Fig. 7 (e)). And the porous structure intensifies the intrusion of high-speed heat flow and the thermal oxidation erosion of the char layers, which lead to the decrease of ablative resistance of the insulators. And the big pores in the char layers gradually become smaller with the increase of MWCNTs content (Fig. 3 (g) and Fig. 7 (f)), since MWCNTs can more efficiently accelerate the carbothermal reduction reaction of silica to increase char residue. Furthermore, the introduction of MWCNTs with high content can form silicon carbide to enhance the strength of char layers and improve the oxidation

resistance of char layers. Therefore, the ablative resistance of the EPDM-based insulators with silica enhances as the MWCNTs content increase.

To further verify the above ablation mechanism, alternating multilayer distribution of MWCNTs and silica in the insulators was designed by using S-C-0 and NS-C-3 (Fig. 8(d)), and the variation of ablation resistance is same to previous result (MWCNTs have high ablation resistance efficiency in the insulators without silica). As shown in Fig. 8 (a), it can be found that the multilayer insulators obviously show lower linear ablation rate, and the linear ablation rate of 20 layers insulators decreased 21.2% than the Mixture insulators. On the one hand, the multilayer insulators have lower thermal conductivity than Mixture insulators (Fig. 8 (b)), which can be ascribed that the alternating multilayer structure disrupts the heat transfer network of the MWCNTs in the vertical direction. On the other hand, the multilayer insulators also have excellent mechanical properties as the local aggregation of MWCNTs and silica. In summary, the insulators with alternating multilayer structure not only have excellent thermal insulation performance and mechanical properties, but also can more fully exploit the ablation resistance potential of MWCNTs.

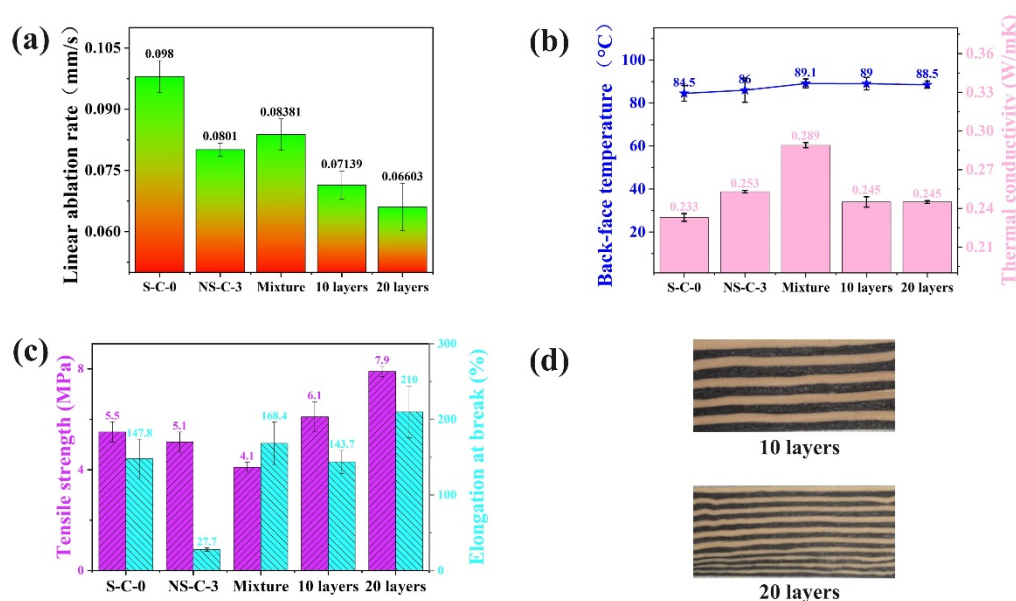

**Figure 8.** The ablation resistance (a), thermal insulation performance (b), mechanical properties (c) and morphology (d) of multilayer insulators.

#### 4. Conclusion

In this work, the effects of MWCNTs content on the char layer structure and physicochemical reaction were investigated in EPDM-based insulators with and without silica. The introduction of MWCNTs shown efficient performance in improving the ablation resistance of EPDM-based insulators, but it also led to a rapid decrease in their thermal insulation properties. It was found that the MWCNTs with the same content have different effects on ablative resistance in EPDM-based insulators with and without silica, which can be ascribed to the effects of MWCNTs on the char layer structure. Although both the char layer morphology of the two insulators gradually evolved into dense porous structure as MWCNTs content increasing, but their formation mechanisms are different. The introduction of MWCNTs can promote the graphitization of carbonized EPDM matrix under the charring component without silica. When the charring components contain silica, the effects of MWCNTs tends to facilitate the carbothermal reduction reaction of silica. Besides, as the addition of MWCNTs, many micro networks were found in char layers, which were considered the key to densify the char layers of EPDM-based insulators. This work proposed the ablation mechanism based on the relationship between the char layers enhanced

by MWCNTs and ablative resistance of EPDM-based insulators and further exploit the ablation resistance potential of MWCNTs by designing the alternating multilayer distribution of MWCNTs and silica in the insulators, which can provide guidance for the construction of desirable char layer structure and promote the advancement of ablative composites.

**Acknowledgments:** This work was funded by the National Natural Science Foundation of China (51790501 and 51721091), State Key Laboratory of Polymer Materials Engineering and the Fundamental Research Funds for the Central Universities. And the authors thank Jiangsu Industrial Technology Research Institute of Advanced Polymer Materials for the assistance in ablation test.

## Reference

1. Natali M, Kenny JM, Torre L. Science and technology of polymeric ablative materials for thermal protection systems and propulsion devices: a review. *Prog. Mater. Sci.* 2016; 84: 192-275.
2. Jia Y, Yao X, Sun J, Li H. Effect of ZrC particle size on the ablation resistance of C/C-ZrC-SiC composites. *Mater. Design.* 2020; 191: 108623.
3. Li K, Shen X, Li H, Zhang S, Zhang L. Ablation of the carbon/carbon composite nozzle-throats in a small solid rocket motor. *Carbon.* 2011, 49 (4), 1208-1215.
4. Shen L, Wu H, Guo S. Improvement of hardness and compression set properties of EPDM seals with alternating multilayered structure for PEM fuel cells. *Int. J. Hydrogen Energy.* 2016; 41 (48): 23164–23172.
5. Rallini M, Puri I, Torre L, Natali M. Boron based fillers as char enhancers of EPDM based heat shielding materials for SRMs: A comparative analysis. *Compos. Struct.* 2018; 198: 73-83.
6. Natali M, Rallini M, Torre L. Effect of Wollastonite on the ablation resistance of EPDM based elastomeric heat shielding materials for solid rocket motors. *Polym. Degrad. Stabil.* 2016; 130: 47-57.
7. Hao H, Zhou X, Shen Z, He J, Yang R. Study on the ablative properties of ethylene propylene diene terpolymer/silsesquioxane insulation materials. *J. Appl. Polym. Sci.* 2020; 137(6).
8. Li J, Xi K, Lv X, Li Q, Wang S. Characteristics and formation mechanism of compact/porous structures in char layers of EPDM insulation materials. *Carbon.* 2018; 127: 498-509.
9. Rallini M, Puri I, Torre L, Natali M. Thermal and ablation properties of EPDM based heat shielding materials modified with density reducer fillers. *Compos. Appl. Sci. Manuf.* 2018; 112: 71-80.
10. Dimitrienko Y. Modeling of erosion combustion of energetic materials in high-enthalpy flows. *Combust. Flame.* 1997; 111 (3): 161-174.
11. Dimitrienko Y, Dimitrienko I. Effect of thermomechanical erosion on heterogeneous combustion of composite materials in high-speed flows. *Combust. flame* 2000; 122 (3): 211-226.
12. Jia X, Li G, Sui G, Li P, Yu Y, Liu H, Yang X. Effects of pretreated polysulfonamide pulp on the ablation behavior of EPDM composites. *Mater Chem Phys.* 2008; 112: 823-830.
13. Gao G, Zhang Z, Li X, Meng Q, Zheng Y. An excellent ablative composite based on PBO reinforced EPDM. *Polym. Bull.* 2010; 64: 607-622.
14. Han Z, Qi S, Liu W, Han E, Wu Z, Wu D. Surface-modified polyimide fiber-filled ethylenepropylenediene monomer insulations for a solid rocket motor: processing, morphology, and properties. *Ind. Eng. Chem. Res.* 2013; 52(3): 1284-1290.
15. Ji Y, Han SD, Xia LC, Li CH, Wu H, Guo S. Synergetic effect of aramid fiber and carbon fiber to enhance ablative resistance of EPDM-based insulators via constructing high-strength char layer. *Compos. Sci. Technol.* 2021; 201: 108494.
16. Zhang S, Zhang P, Ali S, Akram R, Wu D, Wu Z. Effects of PAN-based carbon fibers and its precursors on ethylenepropylenediene monomer insulations: morphology and properties. *Polym. Composite.* 2017.
17. Ding J, Huang ZX, Qin Y, Shi MX, Huang C, Mao JW. Improved ablation resistance of carbon-phenolic composites by introducing zirconium silicide particles. *Compos. B Eng.* 2015; 82: 100-107.
18. Li J, Liu K, Guo M, Liu Y, Wang J, Lv X. Ablation and erosion characteristics of EPDM composites under SRM operating conditions. *Compos. Appl. Sci. Manuf.* 2018; 109: 392–401.
19. Gao G, Zhang Z, Li X, Meng Q, Zheng Y, Jin Z. Study on Mechanical and Ablative Properties of EPDM/OMMT Thermal Insulating Nanocomposites. *J. Nanosci. Nanotechnol.* 2010; 10: 7031–7035.
20. Rallini M, Puri I, Torre L, Natali M. Effect of liquid resol on the mechanical and thermal properties of EPDM/kynol elastomeric heat shielding materials. *Polym. Eng. Sci.* 2017.
21. Gao G, Li X, Meng Q, Zheng Y, Jin Z. Effect of weight ratio of thermoplastic and thermosetting boron-containing phenolic resin on mechanical, bonding, and ablative properties of thermal insulating composites. *J. Appl. Polym. Sci.* 2010; 118: 266–274.
22. Guo MF, Li J, Liu Y, Ji JB. Effect of multi-walled carbon nanotubes on thermal stability and ablation properties of EPDM insulation materials for solid rocket motors. *Acta. Astronaut.* 2019; 159: 508–516.
23. Guo MF, Li J, Xi K, Liu Y, Ji JB, Ye CQ. Effects of multi-walled carbon nanotubes on char residue and carbothermal reduction reaction in ethylene propylene diene monomer composites at high temperature. *Compos. Sci. Technol.* 2020; 186: 107916.

- 
24. Li J, Hu BW, Hui K, Li K, Wang L. Effects of inorganic nanofibers and high char yield fillers on char layer structure and ablation resistance of ethylene propylene diene monomer composites. *Compos. Appl. Sci. Manuf.* 2021; 150: 106633.
  25. Guo MF, Li J, Wang YW. Effects of carbon nanotubes on char structure and heat transfer in ethylene propylene diene monomer composites at high temperature. *Compos. Sci. Technol.* 2021; 211: 108852.
  26. Xi K, Li J, Wang YW, Guo MF, Li K. Thermal insulation and char layer mechanical properties of a novel ethylene propylene diene monomer composite reinforced with carbon nanotubes coated via chemical vapour deposition. *Compos. Sci. Technol.* 2021; 201: 108537.
  27. Natali M, Monti M, Puglia D, Kenny JM, Torre L. Ablative properties of carbon black and MWNT/phenolic composite: a comparative study. *Compos. Appl. Sci. Manuf.* 2012; 43: 174–82.
  28. Ko SJ, Yum SH, Kim HS. Improvement of ablation resistance of epoxy composites reinforced with low concentrations of multi walled carbon nanotubes. *Compos. Appl. Sci. Manuf.* 2019; 124: 105471.
  29. Wang ZJ, Kwon DJ, Gu GY, Lee WI, Park JK, DeVries KL. Ablative and mechanical evaluation of CNT/phenolic composites by thermal and microstructural analyses. *Compos. B Eng.* 2014; 60: 597–602.
  30. Wang SR, Qiu JJ. Enhancing thermal conductivity of glass fiber/polymer composites through carbon nanotubes incorporation. *Compos. B Eng.* 2010; 41: 533–536.
  31. Yum SH, Kim SH, Lee WI, Kim HS. Improvement of ablation resistance of phenolic composites reinforced with low concentrations of carbon nanotubes. *Compos. Sci. Technol.* 2015; 121: 16–24.
  32. Mirzapour M, Farshad Yazdani. Thermal and mechanical properties of phenolic-based composites reinforced by carbon fibres and multiwall carbon nanotubes. *Compos. Appl. Sci. Manuf.* 2015; 72: 22–31.