

---

Article

# The Influence of Varying Thermal Treatment Conditions on Reducing Zinc Content from a Steelmaking and Blast Furnace Sludge

Vladislav Kurka <sup>1\*</sup>, Petr Jonšta <sup>1</sup>, Ladislav Kander <sup>1</sup>, Ondřej Kotásek <sup>1</sup>, Jiří Pyš <sup>2</sup>, Ivana Klásková <sup>1</sup>, Roman Noga <sup>1</sup>, Marek Vindyš <sup>1</sup> and Gražyna Simha Martynková<sup>3</sup>

<sup>1</sup> MATERIAL AND METALLURGICAL RESEARCH, Ltd., Pohraniční 693/31, Vítkovice, 703 00 Ostrava, Czech Republic; vladislav.kurka@mmvyzkum.cz (V.K.); petr.jonsta@mmvyzkum.cz (P.J.), ondrej.kotasek@mmvyzkum.cz (O.K.), ladislav.kander@mmvyzkum.cz (L.K.), ivana.klaskova@mmvyzkum.cz (I.K.), roman.noga@mmvyzkum.cz (R.N.), marek.vindys@mmvyzkum.cz (M.V.)

<sup>2</sup> Liberty Ostrava a.s., Vratimovská 689/117, 719 00 Ostrava-Kunčice; Czech Republic  
jiri.pys@libertysteelgroup.com

<sup>3</sup> Nanotechnology Centre, CEET, VŠB—Technical University of Ostrava, 17. Listopadu 15/2172, 70800 Ostrava, Czech Republic; grazyna.simha@vsb.cz

\* Correspondence: vladislav.kurka@mmvyzkum.cz

**Abstract:** The prospects of processing blast furnace and steelmaking sludge using Waelz process in a laboratory rotary kiln is shown. The influence of varying thermal treatment modes, furnace atmosphere and type of reducing agents on the level of zinc reduction from sludges was analyzed. In general, the blast furnace sludge contains a high portion of iron (approx.48 wt. %) and can be reused as a charge after satisfactory zinc reduction. It was found that N- atmosphere and high content of the graphite or coke oven reducing agent in combination with high temperature can reduce the content of Zn in the sludge to 0.08 wt. % at 1200 °C for mixture of steelmaking and blast furnace sludge. A significant reduction in the Zn content to 0.66 wt. % occurs at 1100 °C. The content and type of reducing agent play an important role; graphite has shown a better reducing ability compared to coke oven dust. When nitrogen is used, zinc is reduced even without an additional reducing agent, since the carbon contained in the sludge is made use of for the reduction. In an air atmosphere, without the use of a reducing agent, there was no reduction in the Zn content.

**Keywords:** blast furnace sludges; steelmaking sludges; carbothermal reduction; Waelz-kiln process; zinc; zinc oxide

---

## 1. Introduction

From a global perspective, 50 % of the largest sources of waste consist of industrial activity, 40 % is the energy industry and 10 % is waste from the municipal sector and agriculture. Industrial waste is of various kinds, from gangue, through metallic and non-metallic wastes, to very toxic or otherwise dangerous substances.

Metallurgical wastes include in particular blast furnace and steelworks dust and sludges, oily sludges, sewage sludge. Based on the state in which they occur can be also divided into solid (slag, scale, returnable steelmaking waste, etc.), liquid (sludge, water, oil, lye, etc.), and gaseous (flue gases, exhalation). Sludge can furthermore be divided according to its usability into directly returnable waste (materials that can be returned without treatment to the metallurgical cycle, e.g. steelmaking waste), returnable after treatment (metal-bearing substrates, which need to be physically and chemically treated before re-processing, e.g. sludge, fly ash), metallurgically irreversible (raw materials that are usable in other industries, e.g. blast furnace slag), irreversible (mostly mixed materials, not yet usable, e.g. residues of textiles, rubber, linings, oils). Furthermore, waste is divided into metallic, metal-bearing and non-metallic. Metal-bearing wastes occur in gaseous and

condensed form, and this is also related to the methods of their capture and the possibility of further processing them. This group of wastes includes the following materials: sludges and effluents from agglomerations and blast furnaces, scale, steel dust and sludges, metal-bearing fractions from the processing of steel slag. [1]

Blast furnace and steelmaking sludges are a by-product of the production of pig iron, i.e. steel in blast furnaces and oxygen converters. Blast furnace sludges and dust are captured in certain types of separators in the process of cleaning blast furnace gas in a dry or wet way. [2-4] Some elements that these sludges contain (Cr, Pb, Cd, Zn, Na, K) are described as harmful, both for the environment and because they can cause problems in the blast furnace, especially the accumulation of zinc in the lining of the blast furnace, saturation in the molten metal and the subsequent expansion of its volume that destroys the lining. [5] For example, during the production of steel from scrap iron in an electric arc furnace, 11-20 kg of sludge is produced from each tone of steel. [6]

The dominant component of blast furnace sludge is reduced iron, and carbon and blast furnace slag components such as calcium or magnesium oxide. Zinc occurs here in the form of an oxide. Table 1 shows an example of the chemical composition of blast furnace sludge. [3] Table 2 gives examples of the chemical composition of steelmaking sludges.

**Table 1.** Chemical composition of blast furnace sludge [wt. %] [3]

Fe	ZnO	C	SiO <sub>2</sub>	Al <sub>2</sub> O <sub>3</sub>	CaO	MgO	K <sub>2</sub> O	Na <sub>2</sub> O	Pb	LOI
33.94	3.57	16.30	5.54	1.90	6.52	2.82	1.64	0.92	0.29	13.04

**Table 2.** Chemical composition of steelmaking sludge [wt. %]


Source	Ca	Fe	Mg	Mn	Pb	Zn	Author
Dofasco Hamilton	-	61.0	-	-	-	1.59	Kelebek [7]
Dofasco Hamilton	-	50.16	-	-	-	2.4	Goetz [8]
Tata Steel Port	-	-	-	-	-	4.8	Steer [9]
Tata Steel Port	3.0-	50.0-80.0	0.20-5.0	0.40-2.20	0.20-1.80	1.7-6.5	Heinrich [10]
ArcelorMittal	4.18	50.65	1.49	-	0.07	4.37	Cantarino [11]
US Steel Košice	5.5	49.87	2.68	-	0.24	9.37	Vereš [12]

In the past, these sludges were considered waste and disposed of in landfills. Due to economic and ecologic aspects, today manufacturing companies try to process and recycle these sludges with various technical means. In general, the processes of recovering valuable metals from dust can be divided into dry and wet processing. Dry includes the Waelz method and the plasma method. Electrolytic wet processing involves the method of using an alkaline leach solution and an acid leach solution. [4]

One of the very harmful elements which must be removed from sludge before their reuse is zinc. Zinc has a negative effect across equipment in the metallurgical industry, reducing the service life of blast furnace linings and steel aggregates, and at the same time its occurrence in steel is undesirable. In 2020, 12,000 tons of zinc were mined worldwide, of which approximately 30 % came from recycled or secondary zinc. Sources of recycled zinc include galvanized steel waste, zinc from car batteries and, more recently, zinc from blast furnace and steelmaking sludges. [13]

According to [14], approximately 80 % of the Waelz kilns rotary kiln is now used to recycle these sludges. Therefore, research into recycling the material in these furnaces has environmental and economic benefits. In January 2022, the market price of zinc was approximately 3,600 USD/ton, in April 2022 the market price of zinc was 4,331 USD/ton. [15] The Waelz process, see Figure 1, is a method of recovering zinc and other relatively

low boiling-point metals from metallurgical waste (typically EAF flue dust) and other recycled materials using a rotary kiln or similar equipment. [16, 17] The process is based on the carbothermal reduction of Zn and Fe oxides. This is shown by the following equations (1-4), which are described in a number of publications and used by the author [18] below in (1) to (4).



These processes take place in a rotary kiln at temperatures of approximately 1200 °C. The sludge is mixed with carbon or a slag-forming agent and placed in a furnace. The carbon reduces the dust, forcing the volatile elements such as Zn, Pb, and Cd along with halides to evaporate. [6]

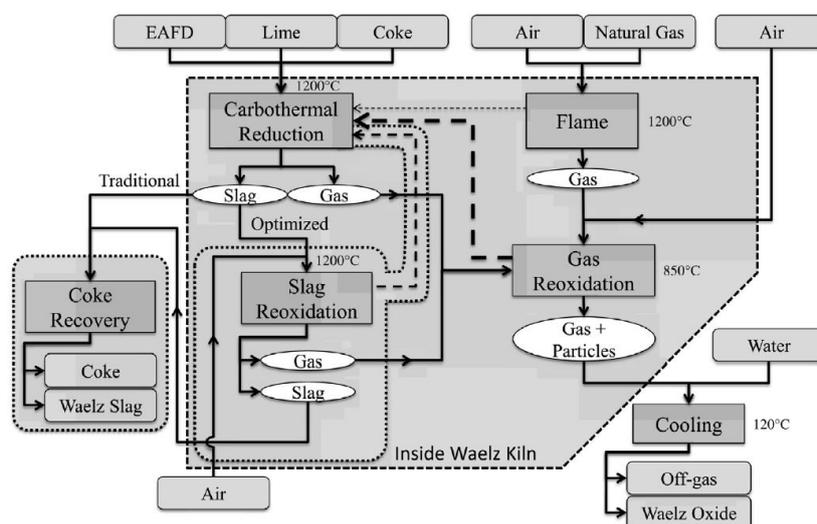



Figure 1. Schema of Waelz process [16]

The process flow sheet of the Waelz Kiln process showing both the traditional and the optimized operation. The gray-rounded rectangles represent the input and output streams, while internal-process streams are represented as white ellipses. For the optimized operation, the slag stream is first treated in the slag reoxidation reaction before passing through the coke recovery treatment, whereas for the traditional operation, the slag is only treated with coke recovery. The dashed arrows in this figure indicate the heat flow in the process. [6]

The authors [18] performed an experiment in which they measured the efficiency of the carbothermal reduction of ZnO with the addition of CaCO<sub>3</sub>, Fe<sub>2</sub>O<sub>3</sub> and iron scale at different temperatures. The purity of the substances used in the case of Fe<sub>2</sub>O<sub>3</sub>, ZnO and CaCO<sub>3</sub> was 99.9 wt. % and in the case of graphite 99.99 wt. %. The chemical composition of iron scale was 59.20 wt. % FeO and 39.03 wt. % Fe<sub>2</sub>O<sub>3</sub>. The reaction took place in a horizontal tube furnace with a nitrogen atmosphere. The authors [19] found that the optimal ratio of ZnO:Fe<sub>2</sub>O<sub>3</sub> is 1:0.05 and that with increasing temperature the reduction of Zn from sludge increases. Better results were obtained using iron scales containing 59.20 wt. % FeO and 39.03 wt. % Fe<sub>2</sub>O<sub>3</sub>. The best results were obtained using a ratio of 1:0.10 for ZnO : Fe scale. The highest reduction rate was achieved using CaCO<sub>3</sub>. The authors [19] assume that the cause of the acceleration of the reaction after the addition of CaCO<sub>3</sub> is the

decomposition of  $\text{CaCO}_3$  into  $\text{CaO}$  and  $\text{CO}_2$ , which participates in the Boudouard reaction. The ideal ratio of  $\text{ZnO}$  to  $\text{CaCO}_3$  is 1:0.10.

In addition to carbon itself, methane can also serve as an effective reducing agent for zinc reduction. The reducing ability of methane can be used in the removal of zinc compounds from metallurgical waste. The main source of zinc is zinc oxide, the removal of which proceeds according to the equation (5). [20-22]



The author [20] performed an experiment in which dust from a foundry furnace with a high zinc content was heated at a rate of  $10 \text{ }^\circ\text{C} \cdot \text{min}^{-1}$  with 90 min. withstands a temperature of  $900 \text{ }^\circ\text{C}$  and subsequent cooling at a rate of  $10 \text{ }^\circ\text{C} \cdot \text{min}^{-1}$  with a constant supply of  $\text{CH}_4$  and an inert gas ( $\text{Ar}$ ,  $\text{N}_2$ ). A simple furnace of square cross-section filled from above with the possibility of a gas supply and exhaust was used for heating. The reaction itself described in equation (5) proceeds at a temperature of  $900 \text{ }^\circ\text{C}$ , and the reduced zinc, whose boiling point is  $907 \text{ }^\circ\text{C}$ , evaporates immediately. The advantage of methane reduction is the lower reduction temperature, which is around the boiling point of  $\text{Zn}$ . The disadvantage is the need to introduce methane into the furnace environment in the gaseous state and the associated costs and possible safety risks. It is not possible to predict whether this method would be effective in the processing of steelmaking and blast furnace sludges with a  $\text{Zn}$  content many times lower than used by the author in his experiment. [20]

From an ecological, raw material and economic point of view, it is very important to ensure that waste from production plants is subsequently converted into usable raw materials. Either in the company or in other industries [21 -24]. Due to the current low use of sludge as a secondary raw material, this work is focused on the influence of varying thermal treatment conditions on reducing zinc content from a steelmaking and blast furnace sludge.

## 2. Materials and Methods

A total of 41 experiments to reduce the content of  $\text{Zn}$  from metallurgical sludges were carried out in laboratory rotary kiln type 8016T-MMV (Czech Republic, CLASIC CZ, 2020), see Figure 2.

The chemical composition of the steelmaking sludge (SS) and mixtures of steelmaking and blast furnace sludge (SS + BFS) and coke oven dust (COD) used for experiments is shown in Table 3. Samples for X-ray analysis were prepared on a FLUXANA VULCAN device (HD ELEKTRONIK, Germany) and subsequently measured on an ARL ADVANT'X device (THERMO SCIENTIFIC, Switzerland). Carbon and sulphur were analyzed on a CS 230 device (LECO, USA). The  $\text{Fe}$  content in the samples was determined on a LAMBDA 20 instrument, UV/VIS spectrometer (USA).

During the experiments, the gases air and nitrogen (purity 99.99 %  $\text{N}$ ) were used, as well as Graphite fine powder extra pure with a Particle size  $< 50 \text{ } \mu\text{m}$  (min. 99.5 %).

**Table 3.** The chemical composition of the steelmaking sludge and mixtures of steelmaking and blast furnace sludge and coke oven dust [wt. %]

	C	S	Fe <sub>metal</sub>	FeO	Fe <sub>2</sub> O <sub>3</sub>	Fe <sub>total</sub>	Al <sub>2</sub> O <sub>3</sub>	CaO	SiO <sub>2</sub>	Cr <sub>2</sub> O <sub>3</sub>
Steelmaking sludge	4.3	0.11	0.21	11.65	55.63	48.17	0.880	1.800	2.200	0.230
Steelmaking and blast furnace sludge	2.34	0.1	0.01	14.58	55.19	2.37	0.319	1.430	1.805	0.255
Coke oven dust	15.60	x	x	x	5.80	x	18.06	2.88	28.59	0.03


Continued Table 3

	MgO	MnO	P <sub>2</sub> O <sub>5</sub>	TiO <sub>2</sub>	V <sub>2</sub> O <sub>5</sub>	BaO	CdO	CuO	PbO	Zn
Steelmaking sludge	1.650	1.120	0.230	0.030	0.010	<0.01	<0.01	0.100	0.430	11.17
Steelmaking and blast furnace sludge	1.091	0.975	0.265	0.004	0.017	0.008	0.000	0.137	0.408	7.77
Coke oven dust	3.02	0.07	0.36	0.48	0.03	0.10	0.00	0.00	0.00	0.03

The weights in one experimental batch were as follows:

- SS+N - 50 g of steelmaking sludge (SS) processed in a nitrogen atmosphere (N),
- SS+air - 50 g of steelmaking sludge (SS) processed in an air atmosphere,
- SS+N+graphite - 50 g of steelmaking sludge (SS) with the addition of 50 g of graphite processed in a nitrogen atmosphere (N),
- SS+BFS+air - 50 g of a mixture of steelmaking (SS) and blast furnace sludge (BFS) processed in an air atmosphere,
- SS+BFS+air+COD - 50 g of a mixture of steelmaking (SS) and blast furnace sludge (BFS) with the addition of 50 g of coke oven dust (COD) processed in an air atmosphere,
- SS+BFS+air+graphite - 50 g of a mixture of steelmaking (SS) and blast furnace sludge (BFS) with the addition of 25 g of graphite processed in an air atmosphere.
- SS+BFS+air+COD+2.0RPM - 50 g mixture of steelmaking (SS) and blast furnace sludge (BFS) with 50 g of coke oven dust (COD) in an air atmosphere with 0.5, 2.0 and 4.0 revolutions per second (RPM)

The experimental batch was poured into a ceramic shell of Al<sub>2</sub>O<sub>3</sub> material. The shell was then inserted into a rotating ceramic tube of OD 90 mm/ID 80 mm and a length of 1200 mm made of Al<sub>2</sub>O<sub>3</sub>, located in a rotary kiln. In the rotary kiln, nitrogen or air was blown into the furnace with a flow rate of 150 ml.min<sup>-1</sup>. The device is equipped with a rotating mechanism driving a ceramic tube with a set speed of 1.0 RPM. In the rotary kiln, the experiments were prepared in the temperature range 700-1200 °C with a heating rate and a cooling rate of 200 °C.h<sup>-1</sup>, with a temperature control accuracy of 1 °C.

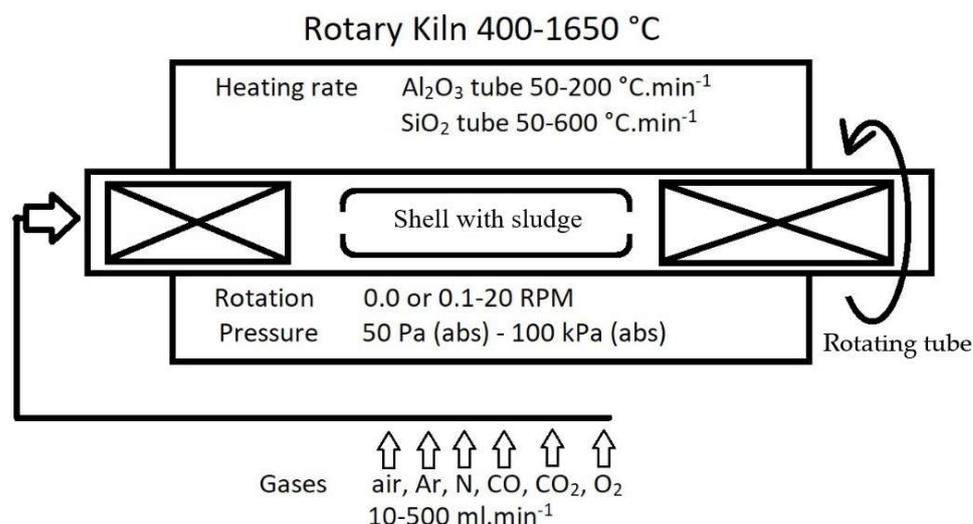

**Figure 2.** Experimental scheme of technological process in laboratory rotary kiln.

### 3. Results and Discussion

Thermally treated sludges were evaluated mainly in terms of changes in their Zn content, but during processing there was also a change in the content of  $\text{Fe}_2\text{O}_3$ , FeO, metallic Fe and C. The samples were analyzed for contents of Zn. All zinc oxides were captured by this analysis and evaluation.

In experimental batches that contained the reducing agent graphite or COD, or were performed in an inert nitrogen atmosphere, the  $\text{Fe}_2\text{O}_3$  content was reduced, see Figure 3. Figure 3 shows that the reduction of the  $\text{Fe}_2\text{O}_3$  content already occurs at temperatures above  $900\text{ }^\circ\text{C}$  and the most significant is the reduction of the  $\text{Fe}_2\text{O}_3$  content at the temperature of  $1100\text{ }^\circ\text{C}$ . In the experimental batches that were thermally processed in an oxidizing air environment and did not use a graphite or COD reducing agent, the  $\text{Fe}_2\text{O}_3$  content increased.

The reduction of the  $\text{Fe}_2\text{O}_3$  content, i.e. the reduction of iron, took place in individual batches with a simultaneous increase in the FeO content, see Figure 4, and also mainly with a simultaneous increase in the metallic Fe content, see Figure 5. The thermal treatment of sludge has a secondary effect, i.e. a reduction in iron. The highest reduction in iron was achieved in the SS+BFS+air+graphite charge, at a temperature of  $1000\text{ }^\circ\text{C}$ , when the metallic Fe content increased to 65 wt. %.

The C contained in the sludge was also used to reduce the oxygen from the sludge, the content of which decreased after thermal treatment, see Figure 6. The carbon content of the batch dropped to zero, using the batch without an additional reducing agent and under the simultaneous action of an air atmosphere. On the contrary, in the batch with the graphite reducing agent and under the action of air, 3.6 wt. % C remained in the sludge after thermal treatment. We can conclude that the carbon contained in the sludge itself also contributes to the reduction process in the rotary kiln. However, if an external carbon source is added, this external source is consumed first and only then the carbon contained in the sludge.

The reduction of the zinc content was thermally achieved in the same experiments in which the metallic Fe was increased. Increasing the metallic Fe content and decreasing the Zn content are interdependent. These were batches in which graphite, COD were added and an inert atmosphere used. The reduction of the Zn content begins in the same way for all these batches, when the batch is heated above  $900\text{ }^\circ\text{C}$ , see Figure 7. They concern these batches: SS+N+graphite, SS+N, SS+BFS+air+COD and SS+BFS+air+graphite. The lowest content of 0.06 wt. % Zn was reached in SS+BFS+air+COD batch, at a temperature of  $1200\text{ }^\circ\text{C}$ . In contrast, a batch that did not contain a reducing agent and which took place in an air atmosphere showed almost no reduction in the Zn content, see the SS+air and

SS+BFS+air batches in Figure 7. Figure 7 shows that the content of the reducing agent and only then the atmosphere in the rotary kiln play a crucial role in reducing the Zn content of the sludge. The experiments carried out and presented have shown that the baseline temperature for reducing the Zn content is 900 °C. Above 900 °C, the Zn content decreases. However, if there is no reduction at 1000 °C, the Zn content will not decrease even at higher temperatures. The results are summarized in more detail in Table 4 and Table 5, which also show that the lowest Zn content is achieved at 1200 °C for SS+BFS+air+COD.

For the best process found to reduce the Zn content of steelmaking and blast furnace sludge, designated SS+BFS+air+COD, an evaluation was performed to see whether the rate of reduction of the Zn content is influenced by the speed of the rotary kiln. The above chemical analyses indicated in Table 6 and Figure 8 show that speeds in the range of 0.5-4 s<sup>-1</sup> do not have an effect on reducing the Zn content.

The content and type of reducing agent, the atmosphere in the rotary kiln and, last but not least, the temperature play an important role in reducing the Zn content.

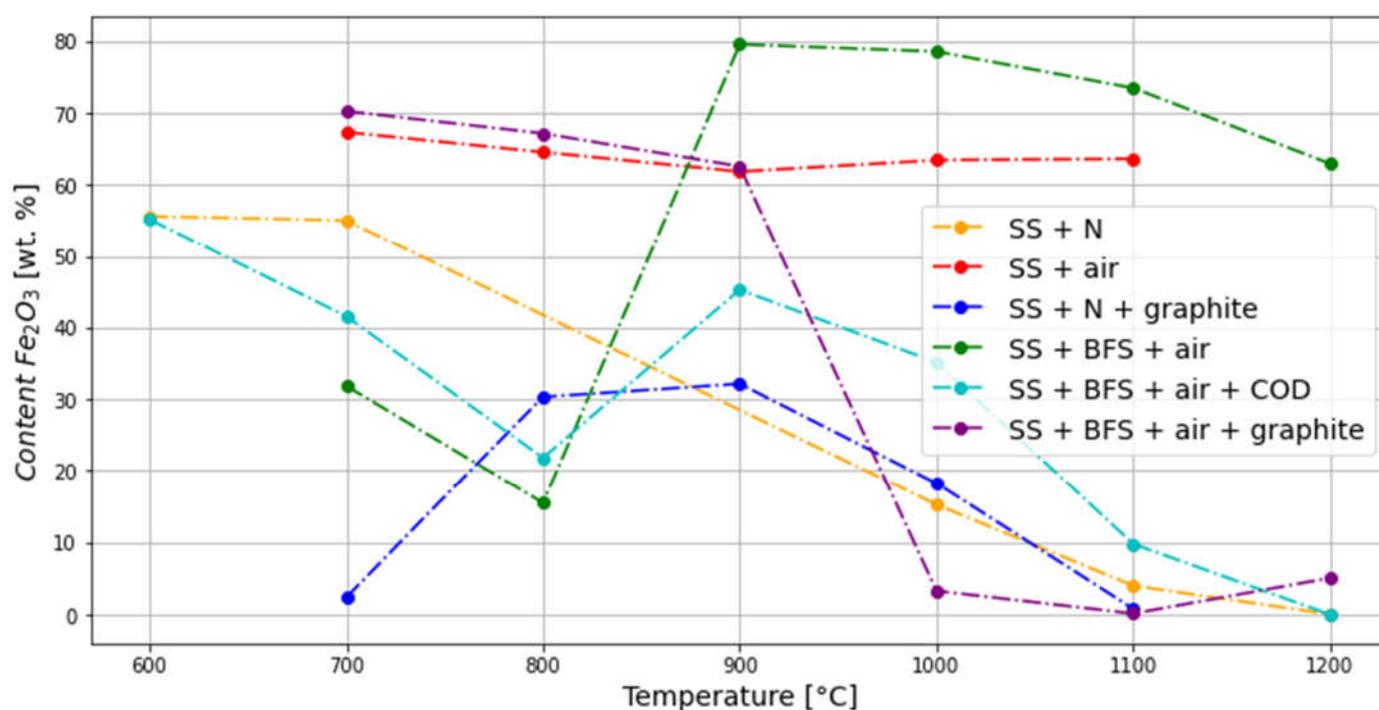


Figure 3. Effect of temperature, atmosphere and reducing element on Fe<sub>2</sub>O<sub>3</sub> content in sludge.

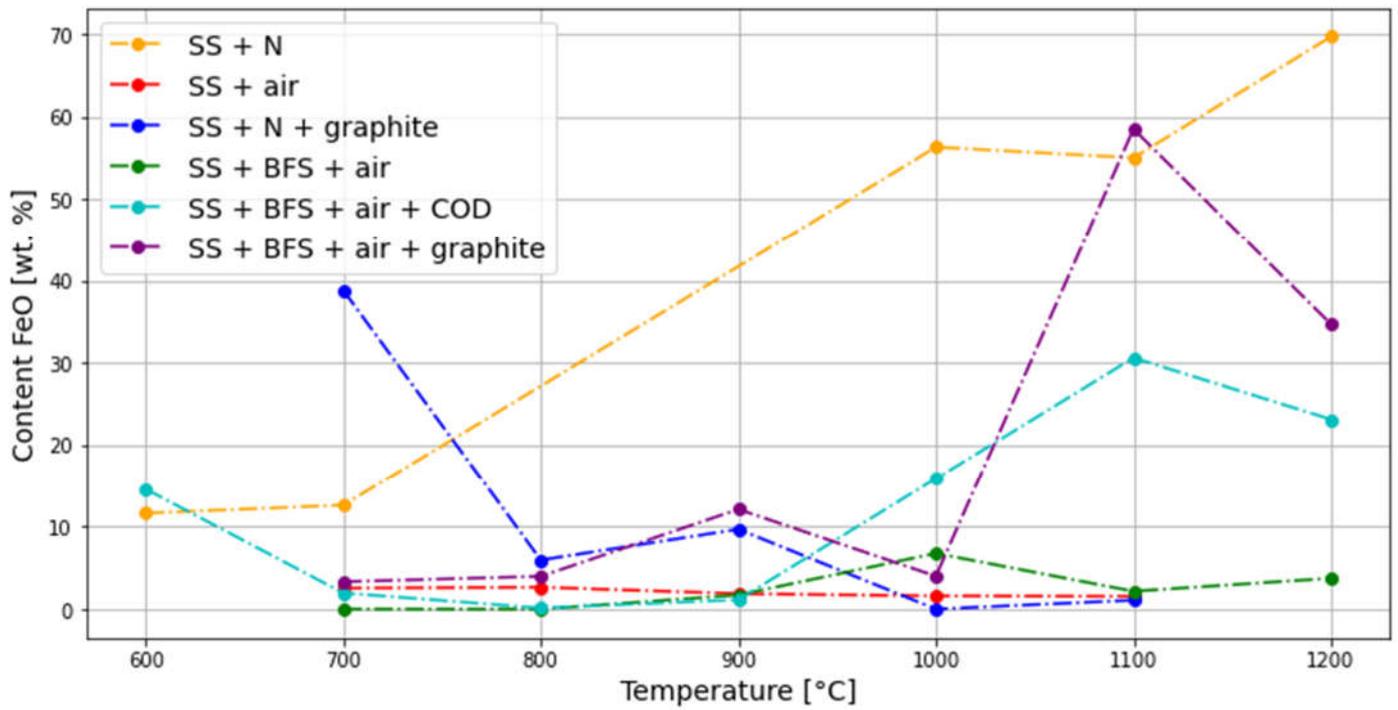


Figure 4. Effect of temperature, atmosphere and reducing element on FeO content in sludge.

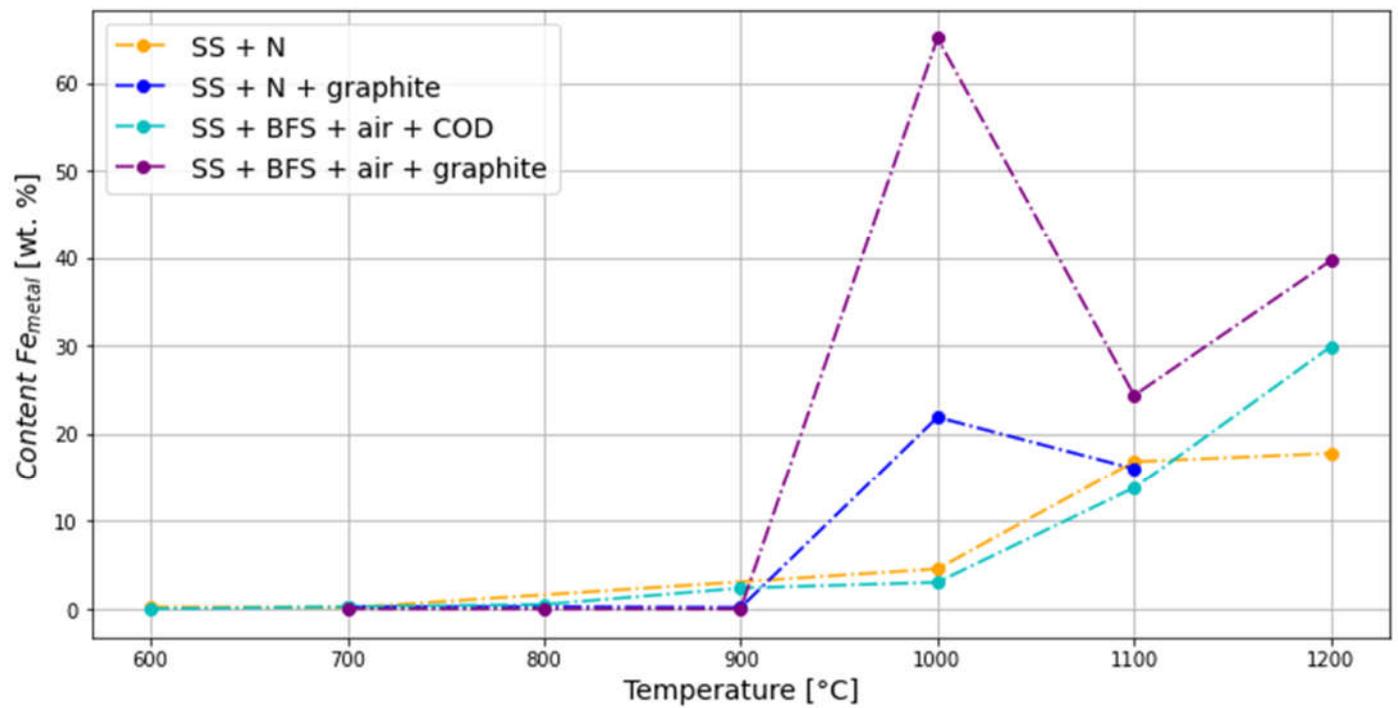


Figure 5. Effect of temperature, atmosphere and reducing element on metallic Fe content in sludge

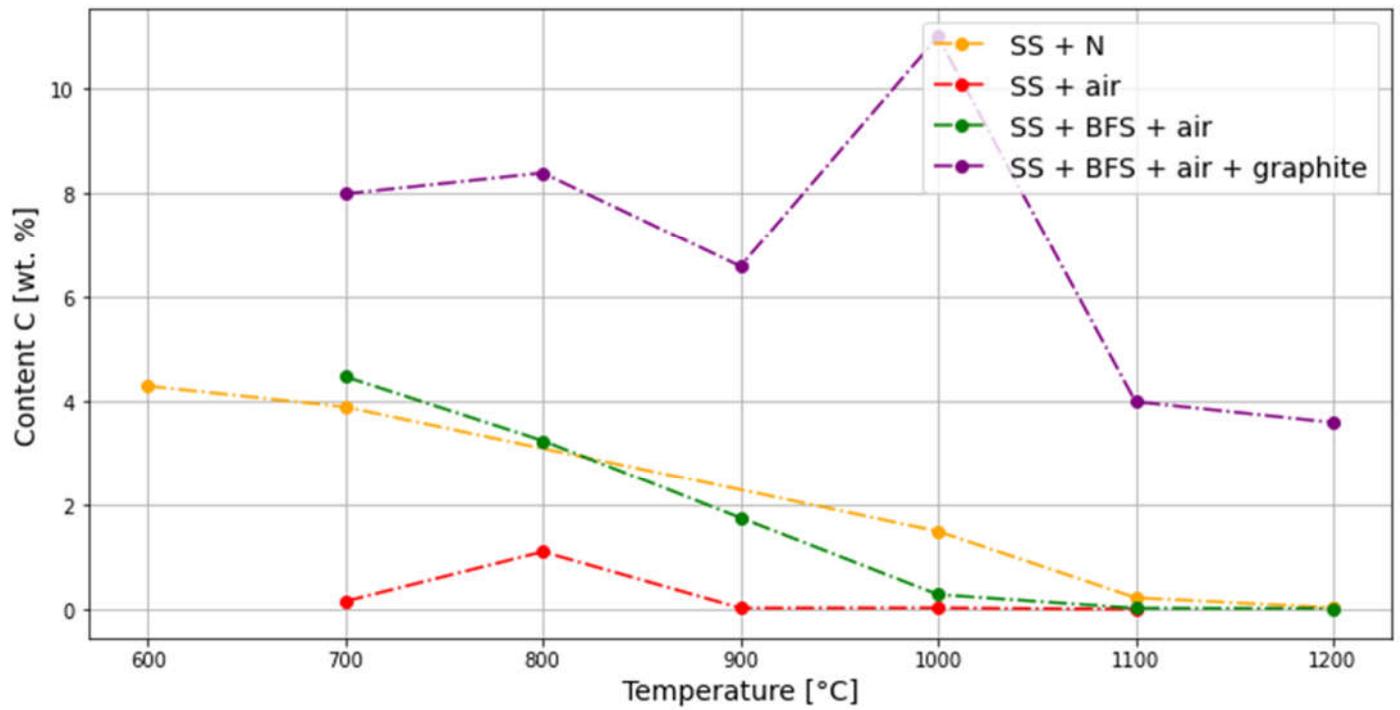


Figure 6. Effect of temperature, atmosphere and reducing element on C content in sludge


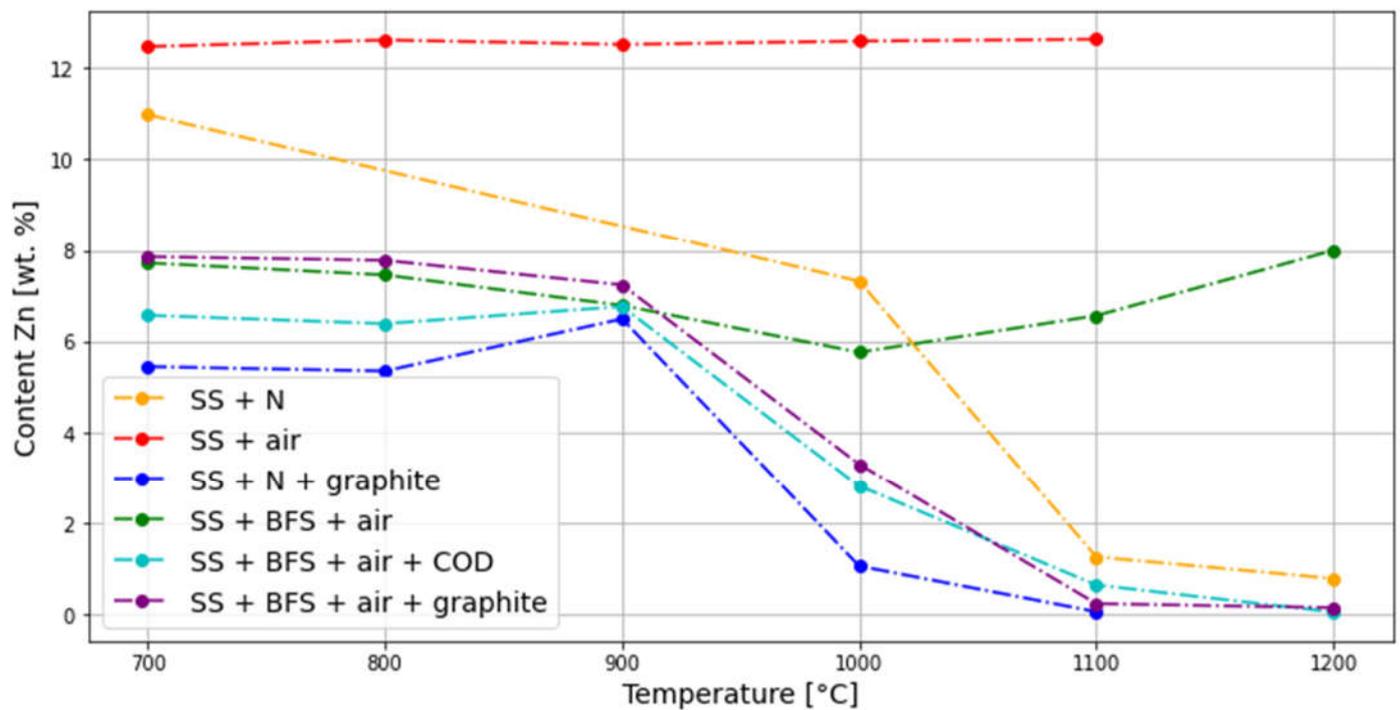


Figure 7. Effect of temperature, atmosphere and reducing element on Zn content in sludge

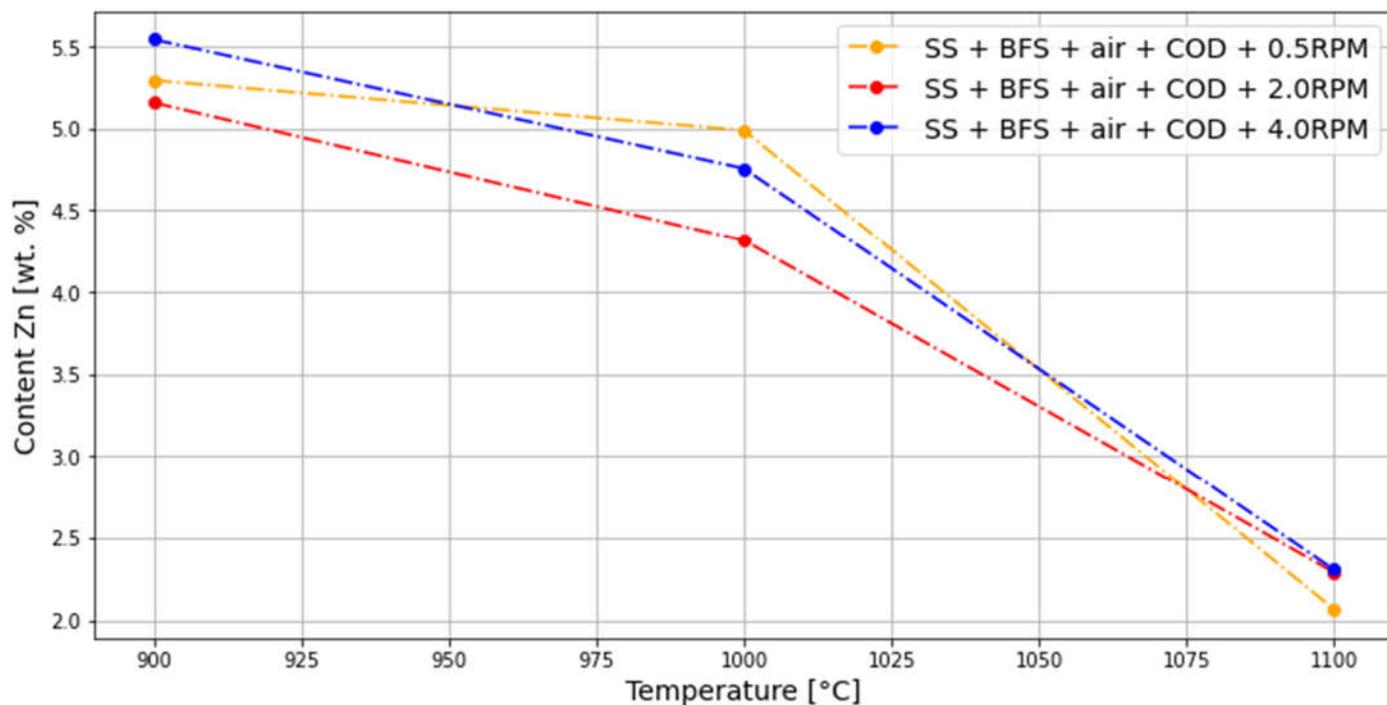

**Figure 8.** Effect of temperature, atmosphere and reducing element on Zn content in sludge in a mixture of steelmaking and blast furnace sludge in an atmosphere of air with coke oven dust, depending on the speed of rotation.

**Table 4.** The chemical composition of the experiments carried out for steelmaking sludge [wt. %]

Composition of experimental sludge	Temperature °C	C	Fe <sub>metal</sub>	FeO	Fe <sub>2</sub> O <sub>3</sub>	Zn
SS+N steelmaking sludge (SS) in a nitrogen atmosphere (N)	700	3.9	0.1	12.6	55.0	10.98
	1000	1.5	4.6	56.3	15.2	7.32
	1100	0.2	16.8	55.0	4.0	1.27
	1200	0.0	17.8	69.7	0.0	0.80
SS+N+graphite steelmaking sludge (SS) with graphite in a nitrogen atmosphere (N)	700	x	0.2	38.9	2.3	5.45
	800	x	0.3	6.0	30.3	5.35
	900	x	0.2	9.7	32.2	6.49
	1000	x	21.9	0.0	18.2	1.07
	1100	x	16.0	1.1	0.8	0.07
SS+air steelmaking sludge (SS) in an air atmosphere	700	0.2	0.2	2.6	67.3	12.46
	800	1.1	0.0	2.7	64.6	12.61
	900	0.0	0.0	1.9	61.9	12.51
	1000	0.0	0.0	1.6	63.5	12.58
	1100	0.0	0.0	1.6	63.7	12.62

**Table 5.** The chemical composition of the experiments carried out for mixture of steelmaking and blast furnace sludge [wt. %]

Experimental batch components	Temperature °C	C	Fe <sub>metal</sub>	FeO	Fe <sub>2</sub> O <sub>3</sub>	Zn
SS+BFS+air+COD mixture of steelmaking (SS) and blast furnace sludge (BFS) with coke oven dust (COD) in an air atmosphere	700	x	0.2	2.0	41.6	6.57
	800	x	0.5	0.1	21.8	6.39
	900	x	2.4	1.1	45.3	6.77
	1000	x	3.0	15.9	35.1	2.82
	1100	x	13.8	30.6	9.8	0.66
	1200	35.0	29.9	23.1	0.0	0.06
SS+BFS+air+graphite a mixture of steelmaking (SS) and blast furnace sludge (BFS) with graphite in an air atmosphere,	700	8.0	0.0	3.3	70.3	7.86
	800	8.4	0.0	4.0	67.2	7.78
	900	6.6	0.0	12.1	62.6	7.24
	1000	11.0	65.1	4.0	3.3	3.30
	1100	4.0	24.4	58.5	0.1	0.25
	1200	3.6	39.7	34.7	5.1	0.16
SS+BFS+air mixture of steelmaking (SS) and blast furnace sludge (BFS) in an air atmosphere	700	4.5	0.0	0.0	31.9	7.72
	800	3.3	0.0	0.0	15.5	7.46
	900	1.8	0.0	1.7	79.6	6.79
	1000	0.3	0.0	6.8	78.6	5.76
	1100	0.0	0.0	2.2	73.5	6.56
	1200	0.0	0.0	3.8	63.0	7.99

**Table 6.** Chemical composition of the experiments performed for the mixture of steelmaking and blast furnace sludge, at different speeds [wt. %].

Experimental batch components	Temperature °C	Zn
SS+BFS+air+COD+0.5 RPM	900	5.29
mixture of steelmaking (SS) and blast furnace sludge (BFS) with coke oven dust (COD) in an air atmosphere at 0.5 revolutions per second (0.5 RPM)	1000	4.99
	1100	2.06
	SS+BFS+air+COD+2.0 RPM	900
mixture of steelmaking (SS) and blast furnace sludge (BFS) with coke oven dust (COD) in an air atmosphere at 2.0 revolutions per second (2.0 RPM)	1000	4.31
	1100	2.29
	SS+BFS+air+COD+4.0 RPM	900
mixture of steelmaking (SS) and blast furnace sludge (BFS) with coke oven dust (COD) in an air atmosphere at 4.0 revolutions per second (4.0 RPM)	1000	4.76
	1100	2.31

## 5. Conclusions

The paper presented the results of the influence of varying thermal treatment conditions on reducing zinc content from a steelmaking and blast furnace sludge

It was found that the level of zinc reduction depends strongly on the atmosphere and the reducing element used. A neutral atmosphere and high content of the graphite or coke oven dust reducing agent in combination with high temperature can reduce the content of Zn in the sludge to 0.08 wt. % at 1200 °C for mixture of steelmaking and blast furnace

sludge (SS+BFS+air+COD). A significant reduction in the Zn content to 0.66 wt. % already occurs at temperatures of 1100 °C. For this best found process (SS+BFS+air+COD) to reduce the Zn content of steelmaking and blast furnace sludge, it was verified that a change in speed in the range of 0.5–4 s<sup>-1</sup> has no effect on reducing the Zn content.

Obtained results showed that the baseline temperature for reducing the Zn content is 900 °C. Above 900 °C, the Zn content decreases. The content and type of reducing agent play an important role in reducing the Zn content; graphite has shown a better reducing ability compared to coke oven dust. When nitrogen is used, zinc is reduced even without the use of an additional reducing agent, since the carbon contained in the sludge is made use of for the reduction. In an air atmosphere, without the use of a reducing agent, there was no reduction in the Zn content.

The results are original and usable for subsequent industrial research and experimental development in the field of metallurgical waste management. From the viewpoint of laboratory conditions, further work should be focused on reducing the Zn content by leaching and subsequent heat treatment in a rotary kiln.

**Author Contributions:** Conceptualization V.K. and P.J.; methodology V.K., P.J., J.P.; coordinating research activities L.K.; validation and formal analysis O.K.; chemical analysis I.K.; analysed and discussed the data R.N., M.V.; editing, G.S.M., All authors have read and agreed to the published version of the manuscript

**Funding:** This work was supported by the EU Regional Development Fund within the Operational Programme Research, Development and Education under the aegis of Ministry of Education, Youth and Sports of the Czech Republic; Project number CZ.02.1.01/0.0/0.0/17\_049/0008426.

**Conflicts of Interest:** The authors declare no conflict of interest.

## References

1. Das, B.; Prakash, S.; Reddy, P.S.R.; Misra, V.N. An overview of utilization of slag and sludge from steel industries. *Conservation and Recycling* **2007**, Volume 50, p. 40–57. [10.1016/j.resconrec.2006.05.008](https://doi.org/10.1016/j.resconrec.2006.05.008).
2. Bartusek, J. Impact of blast furnace and steelmaking sludge disposal on the environment, Thesis, PhD., VSB - Technical University of Ostrava, Ostrava, 2010.
3. Stewart, D.J.C.; Barron, A.R. Pyrometallurgical removal of zinc from basic oxygen steelmaking dust – A review of best available technology, *Resources, Conservation and Recycling* **2020**, Volume 157, 51 p. ISSN 0921-3449, <https://doi.org/10.1016/j.resconrec.2020.104746>.
4. Wang, J.P.A. Study on the Reduction of Zinc Dust using Methane Gas. *International Journal of Engineering Research and Technology* **2019**, Vol. 12, 3 p.
5. Wang, Y.J.; Ning, X.J.; Zhang, J. L.; Jiao, K.X.; Wang, C. Effect of harmful elements on the coke ratio of blast furnace. *Ironmaking & Steelmaking* **2019**, Vol. 46, No 3, pp. 253–258. DOI: 10.1080/03019233.2017.1368955
6. Suetens, T.; Klaasen, B.; Acker, K.V.; Blanpain, B. Comparison of electric arc furnace dust treatment technologies using exergy efficiency. *Journal of Cleaner Production* **2014**, Vol. 65, pp. 152–167. ISSN 0959-6526, <https://doi.org/10.1016/j.jclepro.2013.09.053>.
7. Kelebek, S.; Yörük, S.; Davis, B. Characterization of basic oxygen furnace dust and zinc removal by acid leaching. *Miner. Eng.* **2004**, Vol. 17, No 2, pp. 285–291. DOI:10.1016/j.mineng.2003.10.030.
8. Goetz, F. The Mechanism of B.O.F. Fume Formation. Thesis, MEng., McMaster University, Toronto, 1980, 199 p.
9. Steer, J.; Griffiths, A.; Heinrich, T.; Thomas, A.; Barnes, C. Correlation of BOS Process Variables with dust mass formation and zinc content. *Ironmaking and Steelmaking* **2014**, Vol. 41, No. 7, pp. 554–560. DOI:10.1179/1743281213Y.0000000152
10. Heinrich, T. Reducing zinc contamination in basic oxygen steelmaking dust. Thesis, PhD. Cardiff University, Cardiff, 2015.
11. Cantarino, M. V.; Filho, D.C.; Mansur, M.B. Selective removal of zinc from basic oxygen furnace sludges. *Hydrometallurgy* **2012**, Vol. 111–112, No. 1, pp. 124–128. DOI:10.1016/j.hydromet.2011.11.004.
12. Vereš, J.; Šepelák, V.; Hredzák, S. Chemical, mineralogical and morphological characterisation of basic oxygen furnace dust. *Mineral Processing and Extractive Metallurgy* **2015**, Vol. 124, No. 1, p. 1–8. DOI: 10.1179/1743285514Y.0000000069.
13. Esezobor, D.E.; Balogun, S.A. Zinc accumulation during recycling of iron oxide wastes in the blast furnace. *Ironmaking and Steelmaking* **2006**, Vol. 33, No 5, pp. 419–425. DOI 10.1179/174328106X114020
14. Wang, J.; Zhang, Y.; Cui, K.; Fu, T.; Gao, J.; Hussain, S.; AlGarni, T.S. Pyrometallurgical recovery of zinc and valuable metals from electric arc furnace dust – A review. *Journal of Cleaner Production* **2021**, Vol. 298, 23 p. ISSN 0959-6526,
15. Westmetall. Available online: [https://www.westmetall.com/en/markdaten.php?action=averages&field=LME\\_Zn\\_cash](https://www.westmetall.com/en/markdaten.php?action=averages&field=LME_Zn_cash) (10.4. 2022)

16. Mantovani, M.C.; Takano, C.; Büchler, P.M. Electric arc furnace dust-coal composite pellet: effects of pellet size, dust composition, and additives on swelling and zinc removal. *Ironmaking & Steelmaking* **2002**, Vol. 29, No. 4, pp. 257-265.
17. Xing, L.L.; Zheng-jian, L.; Jian-liang, Z.; Xiang-dong, X. Recovery of iron and zinc from blast furnace dust using iron-bath reduction. *High Temperature Materials and Processes* **2019**, Vol. 38, pp. 767-772.
18. Byung-Su, K.; Jae-Min, Y.; Park, J.T.; Jae-chun, L. A Kinetic Study of the Carbothermic Reduction of Zinc Oxide with Various Additives. *Materials Transactions* **2006**, Vol. 47, No. 9, pp.
19. Kurka, V.; Pindor, J.; Vlček, J.; Jonšta, P. Reduction of Unwanted Zinc Content in Metallurgical Wastes and Design of Rotary Kiln. In *Metal 2019*, Brno, Czech Republic, (22.-24.5.2019).
20. Kim, B. S.; Yoo, J-M.; Park, J-T.; Lee, J-Ch. A Kinetic Study of the Carbothermic Reduction of Zinc Oxide with Various Additives. *Materials Transactions* **2006**, Vol. 47, No. 9, pp. 2421-2426.
21. Čech Barabaszová, K.; Slíva, A.; Kratošová, G.; Holešová, S.; Volodarskaja, A.; Cetinkaya, T.; Brožová, S.; Kozubek, L.; Simha Martynková, G. Phase Transformation after Heat Treatment of Cr-Ni Stainless Steel Powder for 3D Printing. *Materials* **2022**, *15*, 5343.
22. Martynková, G.S., Kratošová, G., Brožová, S., Sathish, S.K. Recyclability, circular economy, and environmental aspects of lithium-sulfur batteries- Lithium-Sulfur Batteries, 2022
23. Brožová, S.; Lisinska, M.; Saternus, M.; Gajda, B.; Martynková, G.S.; Slíva, A. Hydrometallurgical recycling process for mobile phone, printed circuit boards using ozone. *Metals*, 2021, vol. 11, no. 5, p. 820..
24. Brožová, S.; Drápala, J.; Kursá, M.; Pustějovská, P.; Jursová, S. Leaching refuse after sphalerite mineral for extraction zinc and cobalt. *Metalurgija*, 2016, vol. 55, no. 3, pp. 497-499. ISSN 0543-5846.