

Review

Not peer-reviewed version

Sustainability of Cs₂AgBiBr₆ and Cs₂TiBr₆ Perovskite Solar Cells: The Challenges and Research Roadmap for Power Conversion Efficiency Improvement

[Taame Abraha Berhe](#) ^{*}, Etsana Kiros Ashebir, Berhe Tadese Abay

Posted Date: 20 June 2024

doi: 10.20944/preprints202403.1340.v2

Keywords: sustainability; Cs₂AgBiBr₆; Cs₂TiBr₆; all inorganic; halide double perovskite



Preprints.org is a free multidiscipline platform providing preprint service that is dedicated to making early versions of research outputs permanently available and citable. Preprints posted at Preprints.org appear in Web of Science, Crossref, Google Scholar, Scilit, Europe PMC.

Copyright: This is an open access article distributed under the Creative Commons Attribution License which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Review

Sustainable Cs₂AgBiBr₆ and Cs₂TiBr₆ Perovskite Solar Cells: The Challenges and Research Roadmap for Power Conversion Efficiency Improvement

Etsana Kiros Ashebir, Berhe Tadese Abay and Taame Abraha Berhe *


Department of Chemistry, Adigrat University, Adigrat, 50, Tigray, Ethiopia

* Correspondence: Taame Abraha Berhe (taameabr188@gmail.com)

Abstract : The stability issues in the widely known organic inorganic halide perovskite, CH₃NH₃PbI₃, lead to the development of alternative halide double perovskite materials which get great attention in recent times. Although the stability issue seems promising, both materials and device performance of these photovoltaic materials remain inferior and challenging for improvements. Furthermore, the power conversion efficiency of single junction organic inorganic halide perovskite is now 24.2% and 29.15% for textured monolithic perovskite/silicon tandem solar cell, but for all-inorganic halide perovskite solar cell is 7.11% and halide double perovskite solar cells based on Cs₂AgBiBr₆ and Cs₂TiBr₆ is 2.8% and 3.3%, respectively, which is far less than 24.2% and 29.15%, respectively. This creates big question and concern that can both all-inorganic halide perovskite solar cell and halide double perovskites solar cells really be an acceptable alternatives to replace organic inorganic halide perovskite solar cells or lead based perovskite solar cells in the market in order to realize the sustainable practical applications? Not only this concern, but also there are many other big challenges facing by halide double perovskite solar cells. Such big challenges include: a) geometric constraints and limited integration with interfacial materials, b) dynamic disorder and a wide band gap and localized conduction band caused by cubic unit cell which restrains the interactions of orbitals, c) high processing temperature which may limit on the diverse applications, d) low electronic dimensionality making them less appropriate for single junction solar cell purpose and etc. Moreover, origin of electronic and optical properties such as the polarizability, the presence of molecular dipoles and their influence on the dynamics of the photo-excitations in the halide double perovskites remains unlock concern that need to be elucidated. Now, another big question is how to develop overcoming mechanisms for such challenges. Can we really overcome these current limitations faced by halide double perovskites so that we use them for sustainable commercialization? This research roadmap for performance improvement is suggested focusing on: materials surface and bulk engineering, band gap engineering, interfacial engineering, composition engineering, doping engineering, device architectural engineering, polar and domain order engineering. This was the reason that this review was developed in order to forward great contributions to the readers and commercial ventures.

Keywords: sustainability; Cs₂AgBiBr₆; Cs₂TiBr₆; all inorganic; halide double perovskite

Graphical abstract

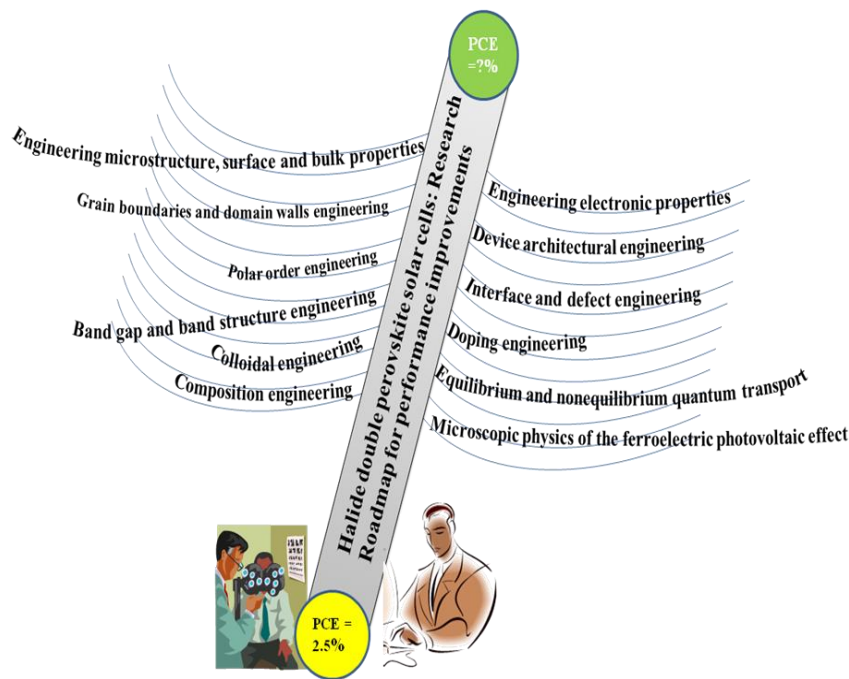

Engineering strategies to improve performance of Cs₂AgBiBr₆ and Cs₂TiBr₆ based solar cells.

Table of Contents

Abstract.....	1
1. Background.....	4
2. Modification strategies from CH ₃ NH ₃ PbI ₃ into many Halide Double Perovskites	5
3. Origin of Electronic and optical property variations	6
4.1 Effect of Polarizability and Molecular Dipoles on the dynamics of the photo-excitations	
6	
4.2 Effects of tilting on the band structure and electron-hole transport	7
5. Energy Applications of halide double perovskites	7
6. Challenges in Lead and Tin free all-inorganic halide double perovskite solar cell	7
6.1 Discouraging power conversion efficiency.	8
6.2 Mismatch among various interfacial layers of the device architecture	8
6.3 Unclear charge-transport properties of these materials	8
6.4 Quantum confinement effect	8
6.5 Low electronic dimensionality	8

	3
6.6 Indirect and wide bandgap	8
6.7 Energetic disorder	9
6.8 Geometrical constraints	9
6.9 High processing temperature:	9
6.10 Shortage of a broad-spectrum of speculative guidelines	9
6.11 Lack of stoichiometric design and compatibility of various layers	9
6.12 Incomplete order	9
6.13 Challenges in achieving high quality films	10
7. Suggested research roadmap engineering strategies for material and device performance improvement.....	10
7.1 Engineering materials microstructure, surface and bulk properties	11
7.2 Engineering domain wall and grain boundaries	11
7.3 Polar order engineering	11
7.4 Band Gap and Band Structure Engineering.....	11
7.5 Crystallization process and colloidal engineering	11
7.6 Composition engineering.....	12
7.7 Engineering electronic properties	12
7.8 Interface and defect engineering.....	12
7.9 Device architectural engineering	13
7.10 Doping engineering:	13
7.11 Equilibrium and non-equilibrium quantum transport	13
7.12 Microscopic physics of the ferroelectric photovoltaic effect	13
8. Promising candidate properties to substitute Pb metal.....	13
9. Concluding remark	14
10. Reference.....	15

1. Background

A definitive objective of materials utilized in optoelectronic applications ought to be founded on the „triple-E” terms: financially economical, vitality effective and naturally efficient. In spite of their very great execution in lead halide perovskite based solar cells with efficiencies reached 24.2% and the rising application for lasers,¹ light-radiating diodes (LEDs),² and field-effect light-producing transistors (FETs),³ organic-inorganic lead halide perovskites experience the ill effects of high substance of lethal, contaminating, and bioaccumulative Pb, which may in the end hamper their commercialization. Progressively, It turn out to be accordingly of essential significance to consider and create alternative classes of lead free halide double perovskites for various optoelectronic applications.⁴ The need of creating practical advances dependent on ecologically neighborly, earth-inexhaustible, and financially savvy materials normally drives the consideration toward the change metals, where especially appealing metals (e.g., Fe²⁺, Cu²⁺, Zn²⁺) and post transition elements.^{5,6} For example, Tin⁷⁻⁹, Rubidium^{10,11}, Indium-Silver,^{12,13} Titanium,¹⁴ Bismuth and Silver-Bismuth^{12,15-18} and Copper¹⁹ based perovskites have been found as potential choices to toxic perovskites. Thanks to their rich science, their utilization may tremendously broaden engineered courses of new halide double perovskites for photovoltaic and light-radiating applications enhancing the tunability of the material. Moreover, the discovery of lead-free double perovskites provides a feasible way of searching for air-stable and environmentally benign solar cell absorbers.^{6,19-25} Since the 1970s, a large number of double perovskites (which are well known as elpasolites) with nominal chemical compositions of A₂M^IM^{III}X₆ (A and M^I = Li⁺, Na⁺, K⁺, Rb⁺, Cs⁺, Ag⁺, Tl⁺, etc., M^{III} = Bi³⁺, Al³⁺, Ln³⁺, Ga³⁺, Fe³⁺, etc., and X = F, Cl, Br, or I) have been initially reported as ferroelectric materials.^{26,27} However, the Lead and Tin free all-inorganic halide double perovskite solar cell power conversion efficiency is far smaller than the power conversion efficiency (PCE) of lead based perovskite solar cells. The reason why the Lead and Tin free all-inorganic halide double perovskites PCE improvement is too slow compared to lead halide perovskites PCE become great concern and active research direction for the halide double perovskite scientific community. In conjunction with the advancement of halide double perovskite solar cells, interesting concepts covering cationic exchange, doping and alloying for engineering the electronic structure of double perovskites,²⁸ and its crystal structure, preparation approaches, physicochemical properties and material various applications,²⁹ various strategies such as hetero-substitution of Pb to form quaternary halide double perovskites,⁵ and a strategy for achieving small band gaps in this family of materials.³⁰ Moreover, the PCE of single junction lead based perovskite is now 24.2%,³¹ 25.2%³² and 29.15%³³ for textured monolithic perovskite/silicon tandem solar cell, but the record for lead free all inorganic cesium tin-germanium triiodide (CsSn_{0.5}Ge_{0.5}I₃) solid-solution perovskite is 7.11%.³⁴ According to the simulation results reported, CsSn_{0.5}Ge_{0.5}I₃ perovskite material can have power conversion efficiency of 18.79%³⁵ and 24.63%.³⁶ Furthermore, CsSn_{0.5}Ge_{0.5}I₃/FASnI₃ device architecture is reported with simulated power conversion efficiency of 31.58%.³⁷ This indicates that CsSn_{0.5}Ge_{0.5}I₃/FASnI₃ device is promising device for high performance lead free solar cells.


This efficiency can be achieved if encapsulation mechanisms, fabrication procedures and material parameters such as defect density, layer thickness, operating temperature, electron affinity potential energy are well optimized during experiment. Moreover, tin based perovskite solar cells have promising efficiency next to lead based perovskite solar cells, devices made of Tin based perovskite materials exhibit insufficient stability³⁸ and it contains intrinsically deep defects that are detrimental to the perovskite solar cell performance.³⁹ Even the most stable CsSn_{0.5}Ge_{0.5}I₃ based perovskite solar cell showed 10% decay in efficiency after 500 h of continuous operation in N₂ atmosphere under one-sun illumination.³⁴ Hence, to overcome the toxicity of lead and insufficient stability of Tin, efforts to find alternative perovskite materials, which are earth-abundant, non-toxic, stable and biocompatible, are still in progress.

Based on these needs, lead and tin free all-inorganic solar cells such as Cs₂AgBiBr₆ and Cs₂TiBr₆ have been reported recently. The record for Cs₂AgBiBr₆ and Cs₂TiBr₆ lead and tin free all-inorganic halide double perovskite solar cell are 2.5%⁴⁰ (current report is 2.81%⁴¹ with photoelectronic conversion efficiency of hydrogenated Cs₂AgBiBr₆ perovskite solar cell of 6.37%⁴²) and 3.3%,⁴³ respectively, which are far less than 24.2% for single junction lead based halide perovskite solar cells

and 29.15% for tandem solar cell. Consequently, the progress is yet too slow to reach the hybrid lead halide perovskite solar cells. From theoretical perspective, simulation results reported that Cs_2TiBr_6 has achieved 11.49 % power conversion efficiency.⁴⁴ This is promising to manufacture practical lead free double halide perovskite solar cell. More recently, an $\text{Au/CuSbS}_2/\text{Cs}_2\text{TiBr}_6/\text{CdS/TCO}$ configuration has achieved power conversion efficiency of 23.77% as reported by simulated results.⁴⁵ This is again more promising result in this field. Unless the real and bottleneck challenges and bottleneck solutions are clearly identified, $\text{Cs}_2\text{AgBiBr}_6$ and Cs_2TiBr_6 based halide double perovskite solar cell will not be able to be first alternative solar cell to replace the hybrid lead halide perovskite solar cells. Thus, this review article is designed to identify the challenges and possible solutions for power conversion efficiency improvement of halide double perovskite solar cells that will be considered as research roadmap for performance improvements in this field. Hence, this is a comprehensive review that concisely reviews the modification strategies from $\text{CH}_3\text{NH}_3\text{PbI}_3$ into many halide double perovskites materials, origin of electronic and optical properties variations, key challenges and areas of research for possible solutions and performance improvement strategies of both Lead and Tin free all-inorganic halide double perovskite solar cells. Moreover, this will provide a new perspective and research roadmap for performance improvement to the scientific community and research industries.

2. Modification Strategies from $\text{CH}_3\text{NH}_3\text{PbI}_3$ into $\text{Cs}_2\text{AgBiBr}_6$ and Cs_2TiBr_6 Halide Double Perovskites

Solar cell devices made of organic-inorganic lead halide perovskite material ($\text{CH}_3\text{NH}_3\text{PbI}_3$) has been reported in 2009 with cell efficiency of 3.81%,⁴⁶ indicating that $\text{CH}_3\text{NH}_3\text{PbI}_3$ with efficiency of 24.2%³¹ achieved in 2019 and currently has reached 29.15%.³³ This is promising if the device made of it is further optimized continuously. Gradually, modification of $\text{CH}_3\text{NH}_3\text{PbI}_3$ has been done at three sites as shown in Scheme 1:⁴⁷ **strategy 1)** halogen atoms like chlorine, bromine and combination of all these halogens,⁴⁸⁻⁵¹ **strategy 2)** organic part⁵²⁻⁵⁵ and **Strategy 3)** at inorganic Pb metal site such as Ge,⁵⁶ bismuth or antimony and noble metals^{57, 12,18,19,58-61} resulting many derivatives of $\text{CH}_3\text{NH}_3\text{PbI}_3$ materials classified as organic-inorganic perovskites, fully inorganic perovskites and halide double perovskites etc. All these modifications are the subject of this section and classified as cation displacement at A and B site, anion displacement at X-site. Furthermore, all these cation and anion modifications as well as the tunable structural dimensions, cation-anion order disorder, distortions and tilting of the octahedral unit, BX_6 , from the ideal structure are collectively considered as the origin of diversity in materials structure, dimension and optoelectronic properties. In addition, the low stability and Pb toxicity challenges in $\text{CH}_3\text{NH}_3\text{PbI}_3$ led to find other alternatively stable and nontoxic halide perovskites materials, which lead to the discovery of halide double perovskites materials, which are the focus of this review.

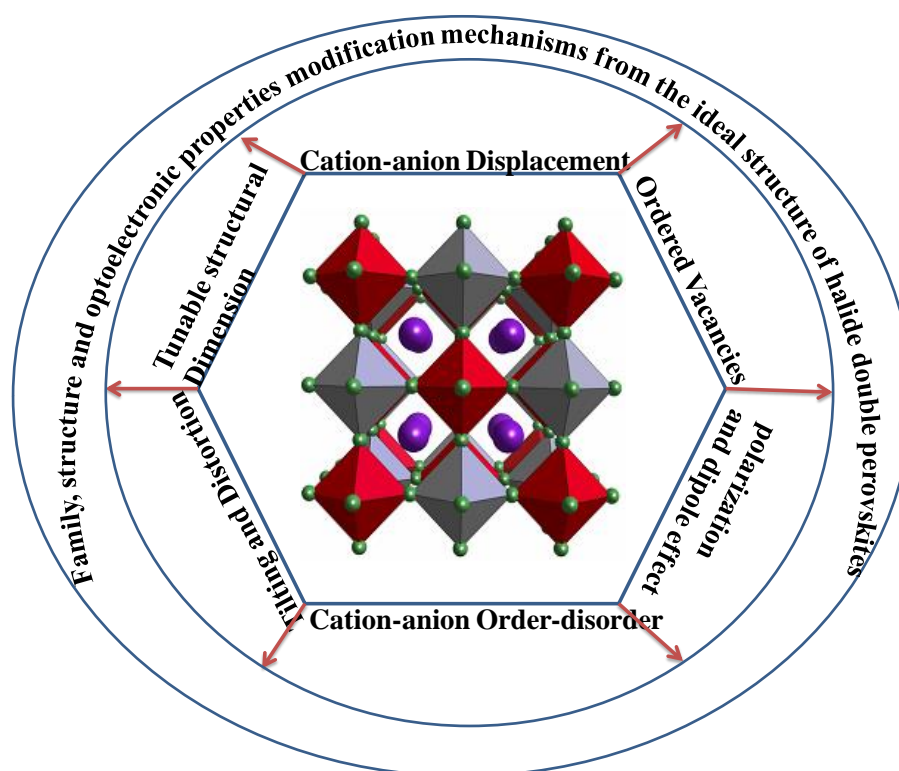

Scheme 1. Halide double perovskite family, structure and optoelectronic properties modification mechanisms.

3. Origin of Electronic and Optical Property Variations

In addition to the structural variations, optoelectronic properties such as absorption, electron-hole diffusion length, carrier life time, carrier mobility, charge carrier dynamics, electronic structure such as band structure and density of state, effective mass of electron, thermal properties and other electrical properties such as ferroelectric, pyroelectric and piezoelectric properties are the main materials properties that everyone wants to deal with for further energy application of materials. Recently, the field of organic-inorganic hybrid halide perovskite becomes to revolutionize the field of photovoltaic. Moreover, modifying the halide perovskites gives new halide double perovskites for which the stated properties are not well studied. Thus, understanding the origin of these optoelectronic property variations would be of great interest for the development of halide double perovskite materials performance. In this section, molecular dipoles, tilting of octahedron, transition metal cation size and its oxidation states, band structure, photoluminescence, and other optoelectronic properties are considered as potential origin of improvement of the performance $\text{Cs}_2\text{AgBiBr}_6$ and Cs_2TiBr_6 halide double perovskite solar cells.

4.1. Effect of Polarization and Molecular Dipoles on the Dynamics of the Photo-Excitations

Regardless of fast improvements in both photovoltaic and light producing device execution, the comprehension of the optoelectronic properties of halide double perovskites is as yet fragmented. Specifically, the polarization of the material, the nearness of sub-atomic dipoles, and their impact on the dynamics of the photo-excitations remains an open issue to be cleared up. From now on, the imperative subject of discussion has been to do with the seemingly perpetual polarization of the perovskite under connected electric fields.^{62,63} This impact shows itself as a huge hysteresis in the deliberate flow – voltage bends of perovskite sun oriented cells and LEDs in planar heterojunction designs, contingent upon the contact materials used.^{62,64,65} The people group has been attempting to comprehend whether the watched polarization is because of the relocation of versatile charged imperfections, atomic dipole arrangement, or to a ferroelectric reaction. The vast majority of the ongoing work underpins the speculation that particle migration^{62,65,66}, ought to rule any ferroelectric

conduct at room temperature.⁶⁷ Researchers such as Leijtens *et.al.*⁶⁸ explored the impact of a connected outer electric field on the photograph energized types of $\text{CH}_3\text{NH}_3\text{PbI}_3$ thin movies, both at room temperature and at low temperature, by checking the photoluminescence (PL) yield and PL rots. At room temperature these creators discovered proof for electric field – incited decrease of radiative bimolecular bearer recombination together with movement of charged imperfections that influences the non-radiative rot rate of the photoexcited species. This has been allotted to field incited arrangement of the atomic dipoles, which diminishes the vibrational opportunity of the cross section and the related nearby screening, and henceforth results in a more grounded electron gap interaction.⁶⁸

4.2. Effects of Tilting on the Band Structure and Electron-Hole Transport

Diverse degrees of tilting of the octahedral structure offer ascent to various precious crystal fields, which results in various electronic and optical properties. The degrees of tilting may influence the band structure, electron transport properties, photoluminescence, and dielectric conduct. Tilting at the organic cage causes distortion of perovskite lattice either by tilting at PbX_6 octahedra or bringing isotropic lattice contractions. In the first case it increases the band gap by reducing orbital overlap while in the second it reduces.⁶⁹⁻⁷¹

5. Energy Applications of Halide Double Perovskites

The key point researchers deal with materials property is to obtain promising materials property for certain promising applications²¹. So many researchers are working on the halide double perovskites for some applications⁷² because these materials show promising solar cell absorber,^{21,73} tandem solar cell^{33,73,74}, photocatalytic^{21,29,75-77} and light emission devices.²¹

6. Challenges in Lead and Tin Free All-Inorganic Halide Double Perovskite Solar Cell

Unlike their encouraging efficiency, lead and tin based perovskite solar cells faced from both the toxicity of Pb metal and device instability,⁷⁸⁻⁸⁰ which limit the practical applications. Consequently, a great deal has been dedicated to the look for alternative perovskite materials such as lead and tin free halide double perovskites and lead and tin free all inorganic perovskites.⁸¹⁻⁸⁶ The great opportunity to use double halide perovskites is because of the following important points: 1) More stable to moisture compared to $(\text{MA})\text{PbI}_3$. A 30-day exposure to 55% humidity⁷³ causes no decomposition in the material, whereas $(\text{MA})\text{PbI}_3$ is mostly converted to PbI_2 .^{21,87, 6,87} Additionally, 2) halide double perovskites are more stable to heat compared to $(\text{MA})\text{PbX}_3$. Volatile organics in $(\text{MA})\text{PbX}_3$ perovskites leave the material at low temperatures. Although CsPbI_3 is more thermally stable, it does not form a 3D perovskite under ambient conditions. In contrast, the Bi-containing perovskites can be heated to ca. 350°C without decomposition.^{24,59,88} Furthermore, 3) long photoluminescence lifetimes (660ns),⁸⁹ which are very promising for solar-cell applications and band gap is ideal for pairing with Si absorbers in a dual-absorber tandem solar cell.⁸⁸ On the other hand, halide double perovskites have challenges relating to their physical chemistry and chemical physics, to date, which need further investigations for more advancement. Moreover, the lead halide perovskite solar cells have shown promise for low cost solar energy conversion (e.g., they have strong light absorption⁹⁰, long excited state lifetimes⁹⁰, efficient separation and transport of opposite charge carriers^{91,92}). As a result, revolutionary advances have been claimed in lead halide perovskite photovoltaic, i.e. PCE has reached greater than 24.2%³¹ for single junction organic inorganic halide perovskite in only a few years of development⁹³⁻⁹⁵ and 29.15% for textured monolithic perovskite/silicon tandem solar cell³², rendering lead halide perovskites as a unique type material for solar energy capture, but the record for Lead free all inorganic halide perovskite is 7.11%, and for both Lead and Tin free all inorganic halide double perovskite solar cell, the record is 2.8%³⁴ and 3.3%^{43,96}, which is far less than 24.2% for single junction and 29.15% for tandem solar cell, respectively. This creates big question and concern that can $\text{Cs}_2\text{AgBiBr}_6$ and Cs_2TiBr_6 based halide double perovskites solar cells really be an acceptable alternatives to replace organic inorganic halide

perovskite solar cells in the market in order to realize the practical applications?⁹⁷ The key challenging mechanisms during performance improvements are suggested as follows, which will be considered as core ideas for advancement. These forward looking points of discussion are expected to improve the photovoltaic performance in addition to the questions raised elsewhere.⁹⁸

6.1. Discouraging Power Conversion Efficiency

Regardless of the quick development of halide double perovskite solar cells, the cell power conversion efficiency remains about 2.5% which was achieved using $\text{Cs}_2\text{AgBiBr}_6$ ³⁴ and 3.3% using Cs_2TiBr_6 .⁴³ Furthermore, the strategy to improve both material and device efficiency made of these materials becomes great concern. More interestingly, looking halide double perovskite light absorbers of high-quality with high absorption coefficient, longer diffusion length, free of defects, trap states with less radiative centers are assignment of this concern. In accordance with the Shockley-Queisser limit, a theoretical maximum PCE of 16.4% can be obtained with an E.g. of 2.2 eV, thus holding promise for working double perovskite based photovoltaic.⁹⁹ Even though, the theoretical maximum PCE of $\text{Cs}_2\text{AgBiBr}_6$ does not reach the highest reported PCEs of single junction MAPbI_3 based photovoltaic, $\text{Cs}_2\text{AgBiBr}_6$ is a promising candidate for applications in tandem solar cells as it was already shown for MAPbBr_3 , which features a slightly larger E.g. of 2.3 eV.¹⁰⁰ Not only the energy alignment and band gap with the charge extraction layers, but also charge collection efficiency is vital to manufacture high-efficiency solar cells.⁶⁰

6.2. Mismatch among Various Interfacial Layers of the Device Architecture

This is another key challenge in halide double perovskite solar cells which remains unexplored area of research. Furthermore, poor interfacial integration might lead to broadening of the depletion width, poor band alignment, inefficient charge collection, enhanced recombination, insufficient charge transport and finally poor overall device performance. For instance, such mismatch in energy levels was occurred in materials such as $(\text{MA})_2\text{AgBiI}_6$ and Cs_2PdBr_6 . For example, $(\text{MA})_2\text{AgBiI}_6$ was observed not compatible with TiO_2 but well-matched with SnO_2 and C_{60} .¹⁰¹

6.3. Unclear Charge-Transport Properties of These Materials

Whether or not they're as favorable as for lead-based perovskites, this time is not well known. Lately, the optoelectronic properties of $\text{Cs}_2\text{AgBiBr}_6$ and combined antimony–bismuth halide double perovskites with the general system $\text{Cs}_2\text{AgBi}_{1-x}\text{SbxBr}_6$, which display comparable rate-transport mechanism to lead-based totally perovskites.¹⁶ Thus, this charge transport property requires greater attention for further improvement of the field.

6.4. Quantum Confinement Effect

The quantum confinement effect in the last shells due to restricted orbital interactions of the adjacent cations particularly B' and B'' cations in the cubic unit cell of the $\text{AB}'\text{B}''\text{X}_6$ double halide perovskite materials might result a narrow and localized conduction band edge as well as broad energy gap, which deteriorate the device performance.^{29,97} Consequently, finding way to move into another unite cell structure is expected to overcome such challenges.

6.5. Low Electronic Dimensionality

High dimensionality i.e. 3D dimension of lead halide perovskites achieved high performance. The majority of these materials demonstrated 3D dimensionality,²⁴ on the other hand, halide double perovskites showed broad band gaps, which means structural dimensionality is a factor affecting PCE in addition to the electronic band gap that is affected by the electronic dimensionality. This might make halide double perovskites inappropriate for single junction solar cell function though these materials crystallize into 3D.⁸¹

6.6. Indirect and Wide Band Gap

Higher performance of organic inorganic halide perovskites was achieved due to their direct and lower band gap, but halide double perovskites possess indirect and wide band gap which limit absorption of light for solar cell and is not ideal for thin film PV applications cases and this field need band gap engineering. For instance, in recent times bismuth and silver based perovskites were anticipated as a choice to replace MAPbI₃.^{57,88} The band gaps are indirect, which is not ideal for single junction solar cell applications, though bismuth/silver based double perovskites absorb from 1.9 to 2.2 eV¹⁰². The reason that the indirect semiconductors are not preferable compared to the direct semiconductors is due to the weak oscillator strengths for radiative recombination and for optical absorption, which might be a challenge if there is low carrier mobility.

6.7. Energetic Disorder

Understanding energetic disorder in halide double perovskites becomes necessary of the time scales connected with atomic and molecular motion as well as the variation of the disorder from single crystal to the thin film. Knowing the variations might also be vital during processing of these light absorbing materials

6.8. Geometrical Constraints

There are variations reflecting the coordination and local chemistry. As these uncertainties transfer to the octahedral and tolerance factors, the stability ranges proposed so far are descriptive rather than predictive. There are some geometric factors restricting the formation of stable 3D halide double perovskites. A lot of promising routes towards Pb-free halide double perovskites have been explored to replace Pb by elements such as germanium,⁵⁶ bismuth or antimony and noble metals⁵⁷^{12,18,19,58-61} However, the geometrical constraints imposed by the necessity of forming an ideal perovskite lattice, in addition to the common oxidation states of these optional cations (e.g., +3 of Bi and Sb), still cause to be not easy the discovery of lead-free materials that could rival the optoelectronic properties of prototypes such as MAPbI₃.

6.9. High Processing Temperature

While organic inorganic halide perovskites need annealing temperatures usually less than 100 °C, the halide double perovskites are only fabricated at higher annealing temperature up to 285 °C.^{40,103} Such prerequisites for fabrication might damage the integration of the device architecture and further restrict wide range function of these materials. Additionally, such high energy consumption for materials fabrication is not economically cost effective, environmentally none green and is not sustainable. As a result, looking alternative methods that could minimize such higher processing temperature becomes an impressive research area in this field.

6.10. Shortage of a Broad-Spectrum of Speculative Guidelines

In spite of considerable contributions, there is no well refined guideline and theoretical understanding on what kind of mixed B-site cation halide double perovskites as well as on how to design Pb and Sn free halide double perovskites for enhancing collective optical, electrical, thermal and mechanical properties and long term stabilities of these materials for wide range applications. In order to minimize such bottleneck challenges, detail knowledge of the electronic structures of these materials with respect to of B'/B'' cation arrangement and design become attractive research directions in the field of halide double perovskites.

6.11. Lack of Stoichiometric Design and Compatibility of Various Layers

Stoichiometric design of the perovskite¹⁰³ has been known as a strategy to develop solar cells with enhanced performance. Moreover, unique stoichiometric design and compatibility of various interfacial device layers are essential aspects that require more attentions in this field.^{20,28,104}

6.12. Incomplete Order

Elucidating the arrangement and position of the ions is another concern in halide double perovskites. Because the B cations generally determine the physical properties of double perovskites, there are three B-cation sublattice types known for double perovskites: random, rock salt, and layered. The latter two are ordered arrangements. In some situations it is observed that the order is not complete, especially in $A'A''B'B''X_6$ structure. Interestingly, order-disorder effects are mainly come across when the charge variation between B' and B'' is two or less. Although the degree of order is an important subject, the dynamic nature of order-disorder behavior is quite useful parameter.^{12,105-}

107

6.13. Challenges in Achieving High Quality Films

Unlike organic inorganic halide perovskites, achieving high quality film in halide double perovskites become a challenge. High quality film might be defined as a material with excellent crystallinity, uniform morphology, less defects, high absorption coefficient, superior ambipolar carrier transport ability¹⁰⁸ and high coverage or pinhole free film.^{109,110} All these parameters are well known to deter both materials and device performance in halide double perovskite solar cells if the quality of these materials is not well optimized during processing steps. For that reason, the light harvesting and active layer that is the halide double perovskite monolayer in the perovskite solar cells is one of the very important research topics that researchers deal with. Moreover, controlling and designing the colloidal properties of the precursor and solvent engineering¹¹¹⁻¹¹³ should get a considerable attention to enhance the required film with high quality.¹¹⁴⁻¹¹⁶

7. Suggested Research Roadmap Engineering Strategies for Material and Device Performance Improvement

In order to overcome the key challenging mechanisms faced by halide double perovskite solar cell, suggesting key areas of research, which will be considered as research roadmap for improvement of both material and device performance, is quite important. These includes engineering microstructure, surface and bulk properties, grain boundary and domain wall engineering, polar order engineering, band gap and band structure engineering, colloidal engineering, composition engineering, engineering electronic properties, device architectural engineering, interface and defect engineering, doping engineering, equilibrium and nonequilibrium quantum transport and ferroelectric engineering as shown in Figure 1.

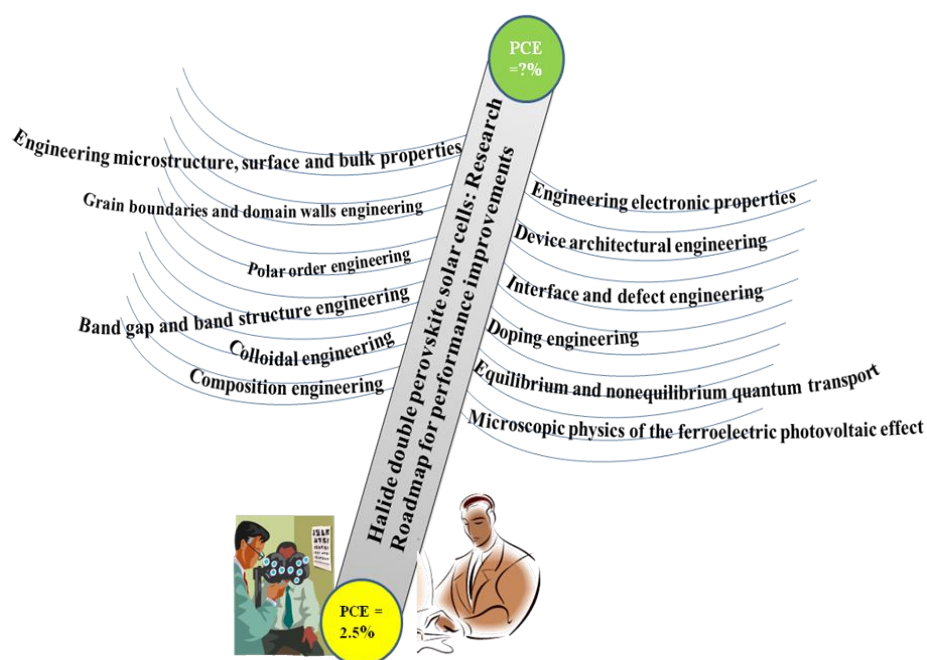


Figure 1. Suggested research roadmap for performance improvement in lead and tin free halide double perovskite solar cells.

7.1. Engineering Materials Microstructure, Surface and Bulk Properties

Engineering microstructure, surface and bulk properties of halide double perovskites are important mechanisms and research areas for improvement for both material and device.¹¹⁷⁻¹²¹ Microstructure influences virtually all aspects of the behavior of materials. Moreover, it is the spatial distribution of material in the useful object that is the goal of the endeavor and is the most richly variable, and thus the most susceptible to control, of the elements in the materials structural hierarchy. Engineering microstructure of materials^{119,122} comprises the concepts of morphology or topological properties and geometry, thermodynamic properties, surface and bulk properties and grain growth as well as bulk and Nano scale domain structures.

7.2. Engineering Domain Wall and Grain Boundaries

The halide double perovskite microstructure might offer optional lanes for conductivity and electron-hole disjointing. Because grain boundaries have an impact on the long-term stability along with the ferroelastic domain boundaries that might be different from regular grain boundaries, the finding of ferroelasticity offers a novel parameter to regard as in the pursuit in favor of enhancing their stability as well as facilitating their extensive implementation.¹²³ Additionally, grain engineering and morphology control through the introduction of additives to the perovskite precursor is another way for performance improvement.³² Sub-micron sized crystal grains in perovskite thin films, on the other hand, have been obtaining considerable attention due to their fundamental morphological properties in the course of twin domain,^{124,125} which are highly essential for understanding the basic mechanisms, for instance, low recombination rate and long diffusion length of the device's high performance.¹²⁶ Moreover, the presence of charged domain walls will significantly reduce the band gap by 20–40% and can serve as segregated channels for the motions of charge carriers, while the presence of uncharged domain walls has no substantial impact on the band gap.¹²⁷

7.3. Polar Order Engineering

Effect of polarization, molecular dipoles, tilting of octahedron and transition metal cation size and its oxidation states on photo-excitation, band structure and photoluminescence are not well investigated. Notwithstanding the microscopic model, polar order is accepted to recline at the center of the ferroelectric photovoltaic impact.¹²⁸ Besides, it is outstanding that interactions between lattice, orbital, and polarization order parameters in ferroelectric materials initiate upgrade of their physical properties close to phase boundaries.¹²⁹ On the road to advance performance, conventional approaches spotlight primarily on reducing the band gap to superior fit the solar spectrum, departure the basic relation between polar order and photovoltaic effect basically ignored.¹²⁹ Hence, spotlighting on both narrowing the band gap and basic relation between polar order and photovoltaic effect become an attractive research topic this time.

7.4. Band Gap and Band Structure Engineering

The fundamental bottleneck restraining the function of halide double perovskites is their bigger energy gap.^{18,130-134} The most favorable band gap for the single junction solar cells ought to be close to 1.3 eV.¹³⁵ As a result, band gap and band structure engineering is vital if halide double perovskites are to be suggested optional contender materials.^{12,17,105,121,136-138} On the other hand, Cs₂Ag_{0.95}Ga_{0.05}Br₆ based double halide perovskite solar cell show small performance improvement of 4.52% via band gap reduction.¹³⁸ If the suggested engineering strategies are implemented, it is promising to maximize the power conversion efficiency of these solar materials.

7.5. Crystallization Process and Colloidal Engineering

The nucleation and growth, coordination chemistry and coordination engineering of halide double perovskites need to be studied: In addition to the photophysics properties, the nucleation and growth, coordination chemistry and coordination engineering concepts are equally important and quite essential for developing new halide double perovskite materials.¹³⁹ Therefore, colloidal engineering, colloidal chemistry and ion exchange reactions during synthesis of halide double perovskites are important ideas that need to be controlled for synthesizing high quality thin film for high performance.

7.6. Composition Engineering

Cation and anion displacement, cation-anion order disorder effects, cation size mismatch, distortion, tilting, ordered vacancies, hydrogen bonding, charge disproportionation and stereochemistry or lone air effects need to get more attention in order to improve stability, inferior material and device performance and engineering a new halide double perovskite materials.^{13,137,156-158} In addition, creation of new chemical composition by using new elements in to the mixed halide double perovskite structure is an acceptable strategy to tune the band gap and of other optoelectronic properties.¹⁴⁰ Currently, $\text{Cs}_2\text{AgBiBr}_6$ and Cs_2TiBr_6 based lead and tin free all-inorganic halide double perovskites are reported as alternative type of perovskite solar cells. The later has energy gap of 1.8 eV in addition to its >100 nm carrier diffusion length.⁴³ The composition engineering due to modifications at the halide anion from Br to I results reduction in band gap ranging from 1.0 to 1.8 eV.³⁸ This band gap is suitable for single junction halide double perovskite solar cells.³⁸ Furthermore, modifications at the cation site, A-site and B site are not yet confirmed. Similarly, $\text{Cs}_2\text{AgBiBr}_6$ has high band gap which ranged from 1.83 to 2.21 eV.^{60,88,141} Composition engineering at the A, B and X sites may reduce the band gap to make it more suitable for single junction halide double perovskite solar cells.¹⁴² Recently, precursor engineering is suggested as rout to enhance power conversion efficiency of $\text{Cs}_2\text{AgBiBr}_6$ materials showing 40% enhancement.¹⁴³ This result indicated that precursor engineering is one type of composition engineering responsible for obtaining smooth, large grains and high-coverage $\text{Cs}_2\text{AgBiBr}_6$ films.

7.7. Engineering Electronic Properties

Ferroelectrics, dielectrics, piezoelectrics, pyroelectrics, electro- and photocatalytic properties, thermoelectric properties, electrical transport properties and other optoelelctric properties are not yet studied.^{12,21,123,144}

7.8. Interface and Defect Engineering

In the field of halide double perovskites, the interfacial properties especially between the active perovskite layer and the hole transporting layers is not well touched. Recently, using Cu_2O as hole transporting material a power conversion efficiency of 11.32% $\text{Cs}_2\text{AgBiBr}_6$ based solar cell has been achieved as indicated by the numerical simulations.¹⁴⁵ This indicates hole transport layer with suitable alignment to the active layer to make efficient charge transport process can improve the challenges faced by Cs_2TiBr_6 and $\text{Cs}_2\text{AgBiBr}_6$. Furthermore, the grain boundary interfaces present in the active perovskite layer in addition to the other grain boundary interfaces present between various layers is vital research lesson for improving the PEC and generally the performance. This is because considerable detrimental trap states in the electronic state of the valence and conduction band states of the halide double perovskite semiconductors might exist, which in turn increases the carrier recombination rate and reduces the open circuit voltage significantly.¹⁴⁶⁻¹⁵² Therefore, the engineering of the grain boundaries to eliminate the detrimental trap states in polycrystalline thin films becomes a long-standing and important issue for high performance optoelectronic devices.¹⁵³⁻¹⁵⁷ In addition to the detrimental trap states, understanding the defect properties of the surface and bulk perovskite films, grain boundary and surface passivation mechanisms, defect properties of the interface during engineering the device architecture is quite crucial aspect, which need serious

interface and defect engineering.^{153,154} Moreover, Cs_2TiBr_6 is reported as a sensitive material to defect density^{44,158,159} though it demonstrate power conversion efficiency of 14.8%.¹⁶⁰ If all possible solar parameters are optimized this solar material is promising candidate in the future of perovskite solar cells. Moreover, the numerical approach showed that power conversion efficiency of 24.49% can be achieved by Cs_2Ptl_6 -based Cs_2TiBr_6 perovskite solar cell while Cs_2TiBr_6 is just 9.81% if well optimized.¹⁶¹ Furthermore, the poor device performance of Cs_2TiBr_6 based perovskite solar cell is because of bulk defect present within the Cs_2TiBr_6 active light absorbing layer. Hence, defect passivation approaches are expected to solve defect related challenges in these materials. Thus, Based on this defect optimization methods, 9.9% efficiency has been achieved for Cs_2TiBr_6 based perovskite solar cell.¹⁶²

7.9. Device Architectural Engineering

Engineering the light harvesting active halide double perovskite layer and interface between the active layer and different charge transporting layers as well as between the transporting layers and the charge collecting electrodes are indispensable prerequisites for appreciable performance. However, engineering the materials and the interface among various layers are not adequate. This is due to the fact that the closing stages are eventually paying attention to the device performance for a specified appliance. As a result, engineering appropriate device architecture¹⁶³⁻¹⁶⁵ is mandatory at the end of the day.

7.10. Doping Engineering

This time halide double perovskites become less suitable solutions to replace the unstable organic inorganic halide perovskite solar cells. This is due to their indirect or direct as well as larger band gap.¹⁶⁶⁻¹⁶⁸ Therefore, doping engineering,^{19,144,169-174} is another strategy to achieve a band gap, which is suitable for light harvesting applications. This with chemical substitution approach might be done in all lattice sites of the double perovskite ($\text{A}_2(\text{B}^+, \text{B}^{3+})\text{X}_6$) available for substitution.¹⁷⁵⁻¹⁷⁷ In this case, the degrees of freedom, with over 34 choices of trivalent metals available for selection is mostly provided from B^{3+} lattice site.¹⁷⁸⁻¹⁸⁰

7.11. Equilibrium and non-Equilibrium Quantum Transport

These transport properties and effect of the spin-orbit on these properties are still unclear: Studies on these properties could shed light to provide insightful understanding on why inferior device performances of halide double perovskites solar cells are happening.

7.12 Microscopic Physics of the Ferroelectric Photovoltaic Effect

This property becomes inadequately known as well as tarnished. Moreover, diverse methods have been suggested to explain research output in a variety of device architectures, such as, asymmetric momentum distribution of the non-equilibrium carriers,^{181,182} shift current through coherent evolution,¹⁸³⁻¹⁸⁵ polarization-dependent interfacial band bending^{186,187} and bulk depolarization field.¹⁸⁶

8. Promising Candidate Properties to Substitute Pb Metal

The organic-inorganic halide perovskites become capable of photovoltaic and energy applications beyond photovoltaic. However, the large scale commercialization of the perovskite harvester faced considerable limitations due to the toxicity of lead metal in addition to the perovskite absorber degradation.^{6,79,106,188} For this reason, there is an interest to discover nontoxic and stable perovskites for betterment of this field. The degradation concern can be treated by carbon encapsulation, multi-cation substitution on top of incorporation of hydrophobic moieties,^{79,189} On the other hand, substitution of Pb using non-toxic transition metal atoms is the single strategy to overcome the toxicity problems.^{57,106,121} Consequently, the optoelectronic properties^{20,133,190-197} such as direct band gaps, defect tolerance, high absorption coefficient, small carrier effective masses, intrinsic

thermodynamic stability, long charge carrier diffusion lengths, low exciton binding energies, higher dielectric constant and compatibility with low-cost and solution-supported fabrication procedures are considered as promising candidate properties to replace lead-based solar cell light harvesting materials in perovskite solar cells. Solving the predictable restrictions of solution-processed semiconductors are another important candidate topics that need to be considered in doing the lead replacement process.¹⁹⁸⁻²⁰³

9. Issue of Sustainability

The issue of sustainability in lead halide perovskite solar cells is the biggest challenge. This sustainability concept is not only understood in terms of economic viability, toxicity, stability but also affordability, availability of materials, energy independence, quality of being able to continue over a period of time, free of hazardous materials, etc. Now, can $\text{Cs}_2\text{AgBiBr}_6$ and Cs_2TiBr_6 perovskite solar cells answer all concepts of sustainability so that it can revolutionize the photovoltaic field of research or not? Researchers shall dig on this regard.

10. Concluding Remark

Recently, lead free halide double perovskite solar cells have been reported as promising nontoxic and stable candidates to replace organic inorganic halide perovskite solar cells. Thus, such lead free halide double perovskite have (1) diversity of various families, (2) diversity of structural, optical and electrical properties and (3) wide range energy applications. Furthermore, the key origins of these diversities and variations are: cation displacement, cation anion ordering, ordered vacancies, tuneability of structural dimension, octahedral distortions and tilting from the ideal structure. In addition, polarization, molecular dipoles and tilting on the band structure are key origins of optoelectronic properties in halide double perovskites. Although lead free halide double perovskite solar cells have promising opportunities such as relatively longer photoluminescence lifetime and higher stability towards moisture, temperature and light compared to lead halide perovskites, these solar cell devices still have bottleneck challenges both at material, interface and device level. Such challenges include a) inferior material and device power conversion efficiency, which is 2.5% Using $\text{Cs}_2\text{AgBiBr}_6$ and 3.3% using Cs_2TiBr_6 , b) limited integration with interfacial materials, c) quantum confinement effect of interacting orbitals of adjacent cations, which might result broader band gap and localized conduction bands d) high processing temperature which may limit on the diverse applications, e) low electronic dimensionality making them less appropriate for single junction solar cell function. Thus, it is suggested that materials surface and bulk engineering, device architectural engineering, interfacial engineering, composition engineering, band gap engineering, doping engineering, polar and domain order engineering, etc. may be possible mechanisms to overcome the challenges. In addition, promising candidate characteristics, for instance, long charge carrier diffusion lengths, defect tolerance, low exciton binding energies, small carrier effective masses, intrinsic thermodynamic stability, direct band gaps, high absorption coefficient and compatibility with low-cost and solution-supported fabrication procedures are highlighted for further considerations. This review will serve as research roadmap for performance improvement of lead and tin free halide double perovskite solar cell scientific community, research institutions and commercial enterprises. Moreover, the challenge in most solar cells is the issue of sustainability. With this in mind, the sustainability issue of $\text{Cs}_2\text{AgBiBr}_6$ and Cs_2TiBr_6 perovskite solar cells shall be analyzed not only in terms of the balance among environment, equity, economy, affordability, energy independence and availability of desirable materials and conditions over the long term but also the quality of being able to continue over a period of time. Thus, the researchers have to work in the way that they can be able to confirm the sustainability issue of $\text{Cs}_2\text{AgBiBr}_6$ and Cs_2TiBr_6 perovskite solar cells.

Funding: No funding available.

Acknowledgments: Adigrat University is acknowledged for the facilities and access.

Conflicts of Interest: The authors declare no conflict of interest.

References

- Xing, G. M., N.; Lim, S.; Yantara, N.; Liu, X.; Sabba, D.; Graetzel, M.; Mhaisalkar, S.; Sum, T. . *Nat. Mater.* **13**, 476–480 (2014).
- Tan, Z.-K. M., R. S.; Lai, M. L.; Docampo, P.; Higler, R.; Deschler, F.; Price, M.; Sadhanala, A.; Pazos, L. M.; Credgington, D.; Hanusch, F.; Bein, T.; Snaith, H. J.; Friend, R. H. . *Nat. Nanotechnol.* **9**, 687–692 (2014).
- Chin, X. Y. C., D.; Yin, J.; Bruno, A.; Soci, C. . *Nat. Commun.* **6**, 7383 (2015).
- Boix, P. P. N., K.; Mathews, N.; Mhaisalkar, S. G. . *Mater. Today* **17**, 16–23 (2014).
- Xin-Gang Zhao, 4 Dongwen Yang,1,4 Ji-Chang Ren,2,4 Yuanhui Sun,1 Zewen Xiao,3,* and Lijun Zhang1,* . Rational Design of Halide Double Perovskites for Optoelectronic Applications. *Joule* doi:<https://doi.org/10.1016/j.joule.2018.06.017> (2018).
- Li, Z. & Yin, W. Recent progress in Pb-free stable inorganic double halide perovskites. *Journal of Semiconductors* **39**, 071003, doi:10.1088/1674-4926/39/7/071003 (2018).
- Kumar, M. H. D., S.; Leong, W. L.; Boix, P. P.; Prabhakar, R. R.; Baikie, T.; Shi, C.; Ding, H.; Ramesh, R.; Asta, M.; Graetzel, M.; Mhaisalkar, S. G.; Mathews, N. . *Adv. Mater.* **26**, 1–6 (2014).
- Hao, F. S., C. C.; Cao, D. H.; Chang, R. P. H.; Kanatzidis, M. G. . *Nat. Photonics* **8**, 489–494 (2014).
- Chung, I. L., B.; He, J.; Chang, R. P. H.; Kanatzidis, M. G. . *Nature* **485**, 486–489 (2012).
- Harikesh PC, M. H., Ghosh B, et al. . Rb as an alternative cation for templating inorganic lead-free perovskites for solution processed photovoltaics. . *Chem Mater.* **28**, 7496–7504 (2016).
- Matthew R. Linaburg, E. T. M., Jackson D. Majher, and Patrick M. Woodward*. Cs1-xRbxPbCl3 and Cs1-xRbxPbBr3 Solid Solutions: Understanding Octahedral Tilting in Lead Halide Perovskites. *Chem. Mater.* **29**, 3507–3514 (2017).
- Volonakis, G. et al. Cs2InAgCl6: A New Lead-Free Halide Double Perovskite with Direct Band Gap. *The Journal of Physical Chemistry Letters* **8**, 772–778, doi:10.1021/acs.jpcclett.6b02682 (2017).
- Zhao XG, Y. D., Sun YH, et al. . Cu-In halide perovskite solar absorbers. . *J Am Chem Soc.* **139**, 6718–6725 (2017).
- Ming-Gang Ju, § Min Chen,‡,§ Yuanyuan Zhou,* ,‡ Hector F. Garces,‡ Jun Dai,† Liang Ma,† Nitin P. Padture,* ,‡ and Xiao Cheng Zeng* ,†. Earth-Abundant Nontoxic Titanium(IV)-based Vacancy-Ordered Double Perovskite Halides with Tunable 1.0 to 1.8 eV Bandgaps for Photovoltaic Applications. *ACS Energy Lett.* **3**, 297–304 (2018).
- Pazoki M, J. M., Zhu HM, et al. . Bismuth iodide perovskite materials for solar cell applications: Electronic structure, optical transitions, and directional charge transport. . *J Phys Chem C.* **120**, 29039–29046 (2016).
- Eline M. Hutter, †,‡ María C. Gelvez-Rueda, ′ ‡ Davide Bartesaghi,‡ Ferdinand C. Grozema,‡ and Tom J. Savenije*,‡. Band-Like Charge Transport in Cs2AgBiBr6 and Mixed Antimony–Bismuth Cs2AgBi1-xSbxBr6 Halide Double Perovskites. *ACS Omega* **3**, 11655–11662 (2018).
- Gray, M. B., McClure, E. T. & Woodward, P. M. Cs2AgBiBr6-xClx solid solutions – band gap engineering with halide double perovskites. *Journal of Materials Chemistry C* **7**, 9686–9689, doi:10.1039/C9TC02674F (2019).
- Hong, K.-H., Kim, J., Debbichi, L., Kim, H. & Im, S. H. Band Gap Engineering of Cs3Bi2I9 Perovskites with Trivalent Atoms Using a Dual Metal Cation. *The Journal of Physical Chemistry C* **121**, 969–974, doi:10.1021/acs.jpcc.6b12426 (2017).
- Karmakar, A., Dodd, M. S., Agnihotri, S., Ravera, E. & Michaelis, V. K. Cu(II)-Doped Cs2SbAgCl6 Double Perovskite: A Lead-Free, Low-Bandgap Material. *Chemistry of Materials* **30**, 8280–8290, doi:10.1021/acs.chemmater.8b03755 (2018).
- Zhou, J. et al. Composition design, optical gap and stability investigations of lead-free halide double perovskite Cs2AgInCl6. *Journal of Materials Chemistry A* **5**, 15031–15037, doi:10.1039/C7TA04690A (2017).
- Chu, L. et al. Lead-Free Halide Double Perovskite Materials: A New Superstar Toward Green and Stable Optoelectronic Applications. *Nano-Micro Letters* **11**, 16, doi:10.1007/s40820-019-0244-6 (2019).
- Tang, Y. et al. Lead-free double halide perovskite Cs3BiBr6 with well-defined crystal structure and high thermal stability for optoelectronics. *Journal of Materials Chemistry C* **7**, 3369–3374, doi:10.1039/C8TC05480K (2019).
- Luo, J. et al. Efficient and stable emission of warm-white light from lead-free halide double perovskites. *Nature* **563**, 541–545, doi:10.1038/s41586-018-0691-0 (2018).

- 24 Meyer, E., Mutukwa, D., Zingwe, N. & Taziwa, R. Lead-Free Halide Double Perovskites: A Review of the Structural, Optical, and Stability Properties as Well as Their Viability to Replace Lead Halide Perovskites. *Metals* **8**, 667 (2018).
- 25 Filip, M. R., Liu, X., Miglio, A., Hautier, G. & Giustino, F. Phase Diagrams and Stability of Lead-Free Halide Double Perovskites $\text{Cs}_2\text{BB}'\text{X}_6$: B = Sb and Bi, B' = Cu, Ag, and Au, and X = Cl, Br, and I. *The Journal of Physical Chemistry C* **122**, 158-170, doi:10.1021/acs.jpcc.7b10370 (2018).
- 26 I.N. Flerova, M.V. Goreva, K.S. Aleksandrova, A. Tressaudb, J. Grannecb, M. Couzic. Phase transitions in elpasolites (ordered perovskites). *Mater. Sci. Eng., R*, **24**, 81-151 (1998).
- 27 Morss, L. R., Siegal, M., Stenger, L. & Edelstein, N. Preparation of cubic chloro complex compounds of trivalent metals: $\text{Cs}_2\text{NaMCl}_6$. *Inorganic chemistry* **9**, 1771-1775, doi:10.1021/ic50089a034 (1970).
- 28 Sasha Khalfin, Y. B., 2. Advances in Lead-Free Double Perovskite Nanocrystals, Engineering Band-gaps and Enhancing Stability Through Composition Tunability. *Nanoscale*, doi:DOI: 10.1039/C9NR01031A (2019).
- 29 Femi Igbari, Z.-K. W., * and Liang-Sheng Liao. Progress of Lead-Free Halide Double Perovskites. *Adv. Energy Mater.*, 1803150 (2019).
- 30 Adam H. Slavney, L. L., Abraham Saldivar Valdes, Davide Bartesaghi, Tom J. Savenije, Jeffrey B. Neaton, and Hemamala Karunadasa. Small-Bandgap Halide Double Perovskites. *Angew. Chem. Int. Ed.* 10.1002/anie.201807421 (2018).
- 31 NREL Efficiency Chart. This Plot Is Courtesy of the National Renewable Energy Laboratory, Golden, CO. Available online: <https://www.nrel.gov/pv/assets/pdfs/best-research-cell-efficiencies.20190411.pdf> (accessed on 14 April 2019).
- 32 Chen, B. et al. Grain Engineering for Perovskite/Silicon Monolithic Tandem Solar Cells with Efficiency of 25.4%. *Joule* **3**, 177-190, doi:10.1016/j.joule.2018.10.003 (2019).
- 33 Al-Ashouri, A. et al. Monolithic perovskite/silicon tandem solar cell with >29% efficiency by enhanced hole extraction. *Science* **370**, 1300-1309, doi:doi:10.1126/science.abd4016 (2020).
- 34 Chen, M. et al. Highly stable and efficient all-inorganic lead-free perovskite solar cells with native-oxide passivation. *Nature Communications* **10**, 16, doi:10.1038/s41467-018-07951-y (2019).
- 35 Nalianya, M. A. et al. Numerical study of lead free $\text{CsSn}_0.5\text{Ge}_0.5\text{I}_3$ perovskite solar cell by SCAPS-1D. *Optik* **248**, 168060, doi:<https://doi.org/10.1016/j.ijleo.2021.168060> (2021).
- 36 Liu, X. et al. Lead free $\text{CsSn}_0.5\text{Ge}_0.5\text{I}_3$ perovskite solar cell with different layer properties via SCAPS-1D simulation. *The Canadian Journal of Chemical Engineering* **101**, 6792-6806, doi:<https://doi.org/10.1002/cjce.25009> (2023).
- 37 Singh, N. K. & Agarwal, A. Performance assessment of sustainable highly efficient $\text{CsSn}_0.5\text{Ge}_0.5\text{I}_3/\text{FASnI}_3$ based Perovskite Solar Cell: A numerical modelling approach. *Optical Materials* **139**, 113822, doi:<https://doi.org/10.1016/j.optmat.2023.113822> (2023).
- 38 Ju, M.-G. et al. Earth-Abundant Nontoxic Titanium(IV)-based Vacancy-Ordered Double Perovskite Halides with Tunable 1.0 to 1.8 eV Bandgaps for Photovoltaic Applications. *ACS Energy Letters* **3**, 297-304, doi:10.1021/acsenergylett.7b01167 (2018).
- 39 Saporov, B. et al. Thin-Film Deposition and Characterization of a Sn-Deficient Perovskite Derivative Cs_2SnI_6 . *Chem.mater.* **28**, 2315-2322, doi:10.1021/acs.chemmater.6b00433 (2016).
- 40 Greul, E., Petrus, Michiel L., Binek, A., Docampo, P. & Bein, T. Highly stable, phase pure $\text{Cs}_2\text{AgBiBr}_6$ double perovskite thin films for optoelectronic applications. *Journal of Materials Chemistry A* **5**, 19972-19981, doi:10.1039/C7TA06816F (2017).
- 41 Xiaoqing Yang, Y. C., Pengyun Liu, Huimin Xiang, Wei Wang,* Ran Ran, Wei Zhou, and Zongping Shao*. Simultaneous Power Conversion Efficiency and Stability Enhancement of $\text{Cs}_2\text{AgBiBr}_6$ Lead-Free Inorganic Perovskite Solar Cell through Adopting a Multifunctional Dye Interlayer. *Adv. Funct. Mater.* 2001557 (2020).
- 42 Zhang, Z. et al. Hydrogenated $\text{Cs}_2\text{AgBiBr}_6$ for significantly improved efficiency of lead-free inorganic double perovskite solar cell. *Nature Communications* **13**, 3397, doi:10.1038/s41467-022-31016-w (2022).
- 43 Min Chen, M.-G. J., 2 Alexander D. Carl,3 Yingxia Zong,1 Ronald L. Grimm,3 Jiajun Gu,4 Xiao Cheng Zeng,2 Yuanyuan Zhou,1,* and Nitin P. Padture1,5,* Cesium Titanium(IV) Bromide Thin Films Based Stable Lead-free Perovskite Solar Cells. *Joule* **2**, 1-13 (2018).
- 44 Ahmed, S., Jannat, F., Khan, M. A. K. & Alim, M. A. Numerical development of eco-friendly Cs_2TiBr_6 based perovskite solar cell with all-inorganic charge transport materials via SCAPS-1D. *Optik* **225**, 165765, doi:<https://doi.org/10.1016/j.ijleo.2020.165765> (2021).

- 45 Mercy, P. A. M. & Wilson, K. S. J. Development of environmental friendly high performance Cs₂TiBr₆ based perovskite solar cell using numerical simulation. *Applied Surface Science Advances* **15**, 100394, doi:<https://doi.org/10.1016/j.apsadv.2023.100394> (2023).
- 46 Kojima, A., Teshima, K., Shirai, Y. & Miyasaka, T. Organometal Halide Perovskites as Visible-Light Sensitizers for Photovoltaic Cells. *J. Am. Chem. Soc.* **131**, 6050-6051, doi:10.1021/ja809598r (2009).
- 47 Ghanshyam Pilania^{1*}, P. V. B., Chiho Kim³ and Turab Lookman². Finding New Perovskite Halides via Machine Learning. *Frontiers in Materials* (2016).
- 48 Gonzalez-Pedro, V. *et al.* General Working Principles of CH₃NH₃PbX₃ Perovskite Solar Cells. *Nano Letters* **14**, 888-893, doi:10.1021/nl404252e (2014).
- 49 Uddin, M. A., Calabro, R. L., Kim, D.-Y. & Graham, K. R. Halide exchange and surface modification of metal halide perovskite nanocrystals with alkyltrichlorosilanes. *Nanoscale* **10**, 16919-16927, doi:10.1039/C8NR04763D (2018).
- 50 Protesescu, L. *et al.* Nanocrystals of Cesium Lead Halide Perovskites (CsPbX₃, X = Cl, Br, and I): Novel Optoelectronic Materials Showing Bright Emission with Wide Color Gamut. *Nano Letters* **15**, 3692-3696, doi:10.1021/nl5048779 (2015).
- 51 Nedelcu, G. *et al.* Fast Anion-Exchange in Highly Luminescent Nanocrystals of Cesium Lead Halide Perovskites (CsPbX₃, X = Cl, Br, I). *Nano Letters* **15**, 5635-5640, doi:10.1021/acs.nanolett.5b02404 (2015).
- 52 N.J. Jeon, J. H. N., W.S. Yang, Y.C. Kim, S. Ryu, J. Seo, S.I. Seok, . Compositional engineering of perovskite materials for high-performance solar cells, . *Nature* **517**, 476-480, doi:<http://dx.doi.org/10.1038/nature14133>. (2015).
- 53 Jin-Wook Lee , D.-H. K., Hui-Seon Kim , Seung-Woo Seo , Sung Min Cho, and Nam-Gyu Park *. Formamidinium and Cesium Hybridization for Photo- and Moisture-Stable Perovskite Solar Cell. *Adv. Energy Mater.* **5**, 1501310 (2015).
- 54 Yun Hee Park, I. J., Seunghwan Bae, Hae Jung Son, Phillip Lee, Jinwoo Lee, Chul-Ho Lee,* and Min Jae Ko*. Inorganic Rubidium Cation as an Enhancer for Photovoltaic Performance and Moisture Stability of HC(NH₂)₂PbI₃ Perovskite Solar Cells. *Adv. Funct. Mater.*, 1605988 (2017).
- 55 Dmitry Baranov² , Z. D., Mirko Prato³ , Filippo Drago², Maurizio Ferretti¹, Valerio Pinchetti⁴, Marco Fanciulli⁴, Sergio Brovelli⁴, Luca De Trizio^{2*}, Liberato Manna^{2*} Colloidal Synthesis of Double Perovskite Cs₂AgInCl₆ and Mn-doped Cs₂AgInCl₆ Nanocrystals Federico Locardi^{1,2}, Matilde Cirignano². *J. Am. Chem. Soc.*, (2018).
- 56 Stoumpos, C. C. F., L.; Clark, D. J.; Kim, Y. S.; Rhim, S. H.; Freeman, A. J.; Ketterson, J. B.; Jang, J. I.; Kanatzidis, M. G. . Hybrid Germanium Iodide Perovskite Semiconductors: Active Lone Pairs, Structural Distortions, Direct and Indirect Energy Gaps, and Strong Nonlinear Optical Properties. . *J. Am. Chem. Soc.*, **137**, 6804-6819 (2015).
- 57 Volonakis, G. F., M. R.; Haghighirad, A. A.; Sakai, N.; Wenger, B.; Snaith, H. J.; Giustino, F. Lead-Free Halide Double Perovskites via Heterovalent Substitution of Noble Metals. . *J. Phys.Chem. Lett.* **7**, 1254-1259 (2016).
- 58 Slavney, A. H. H., T.; Lindenberg, A. M.; Karunadasa, H. I. A bismuth-halide double perovskite with long carrier recombination lifetime for photovoltaic applications. . *J. Am. Chem. Soc.* **138**, 2138-2141 (2016).
- 59 al., K. e. HALIDE DOUBLE PEROVSKITE Cs₂AgBiBr₆ SOLAR-CELL ABSORBER HAVING LONG CARRIER LIFETIMES. U.S. Published Patent Application US 2017/O1941 01 A1 (2017).
- 60 Enrico Greul, a. M. L. P., a Andreas Bineka, Pablo Docampo and Thomas Bein*. Highly stable, phase pure Cs₂AgBiBr₆ double perovskite thin films for optoelectronic applications. *J. Mater. Chem. A* **00**, 1-3 (2017).
- 61 Xiao ZW, D. K., Meng WW, et al. Intrinsic instability of Cs₂In(I)M(III)X₆ (M = Bi, Sb; X = Halogen) double perovskites: A combined density functional theory and experimental study. . *J Am Chem Soc.* **139**, 6054-6057 (2017).
- 62 Xiao, Z. Y., Y.; Shao, Y.; Wang, Q.; Dong, Q.; Bi, C.; Sharma, P.; Gruverman, A.; Huang, J. Giant Switchable Photovoltaic Effect in Organometal Trihalide Perovskite Devices. . *Nat. Mater.* **14**, 193-198 (2015).
- 63 Bertoluzzi, L. S., R. S.; Liu, L.; Lee, J.-W.; Mas-Marza, E.; Han, H.; Park, N.-G.; Mora-Sero, I.; Bisquert, J. . *Energy Environ. Sci.* **8**, 910-915 (2015).
- 64 Snaith, H. J. A., A.; Ball, J. M.; Eperon, G. E.; Leijtens, T.; Noel, N. K.; Stranks, S. D.; Wang, J. T.-W.; Wojciechowski, K.; Zhang, W. Anomalous Hysteresis in Perovskite Solar Cells. . *J. Phys. Chem. Lett.* **5**, 1511-1515 (2014).

- 65 Tress, W. M., N.; Moehl, T.; Zakeeruddin, S. M.; Nazeeruddin, M. K.; Gratzel, M., . Understanding the Rate-Dependent J-V Hysteresis, Slow Time Component, and Aging in $\text{CH}_3\text{NH}_3\text{PbI}_3$ Perovskite Solar Cells: The Role of a Compensated Electric Field. *Energy & Environmental Science* **8**, 995-1004 (2015).
- 66 Hoke, E. T. *et al.* Reversible photo-induced trap formation in mixed-halide hybrid perovskites for photovoltaics. *Chem. Sci.* **6**, 613-617, doi:10.1039/c4sc03141e (2015).
- 67 Fan, Z. X., J.; Sun, K.; Chen, L.; Hu, Y.; Ouyang, J.; Ong, K. P.; Zeng, K.; Wang, J.,. Ferroelectricity of $\text{CH}_3\text{NH}_3\text{PbI}_3$ Perovskite. *J. Phys. Chem. Lett.* **6**, 1155-1161 (2015).
- 68 Tomas Leijtens ¹, Ajay Ram Srimath Kandada^{1*}, Giles E. Eperon², Giulia Grancini¹, Valerio D'Innocenzo^{1,3}, James M. Ball¹, Samuel D. Stranks^{2#}, Henry J. Snaith², and Annamaria Petrozza^{1*}. Modulating the Electron - Hole Interaction in a Hybrid Lead Halide Perovskite with an Electric Field *J. Am. Chem. Soc.*, doi:DOI: 10.1021/jacs.5b09085 (2015).
- 69 Chaves, A. *et al.* Bandgap engineering of two-dimensional semiconductor materials. *npj 2D Materials and Applications* **4**, 29, doi:10.1038/s41699-020-00162-4 (2020).
- 70 Prasanna, R. *et al.* Band Gap Tuning via Lattice Contraction and Octahedral Tilting in Perovskite Materials for Photovoltaics. *Journal of the American Chemical Society* **139**, 11117-11124, doi:10.1021/jacs.7b04981 (2017).
- 71 Lee, J.-H. *et al.* Resolving the Physical Origin of Octahedral Tilting in Halide Perovskites. *Chemistry of Materials* **28**, 4259-4266, doi:10.1021/acs.chemmater.6b00968 (2016).
- 72 Lei, H., Hardy, D. & Gao, F. Lead-Free Double Perovskite $\text{Cs}_2\text{AgBiBr}_6$: Fundamentals, Applications, and Perspectives. *Advanced Functional Materials* **31**, 2105898, doi:10.1002/adfm.202105898 (2021).
- 73 Metal-halide double perovskites as solar-cell absorbers *Stanford University/OFFICE OF TECHNOLOGY LICENSING*/http://techfinder.stanford.edu/technologies/S15-455_metal-halide-double-perovskites-as.
- 74 Palmstrom *et al.* Enabling Flexible All-Perovskite Tandem Solar Cells. *Joule* **3** 1-12, doi:<https://doi.org/10.1016/j.joule.2019.05.009> (2019).
- 75 Lei Zhou, Y.-F. X., Bai-Xue Chen, Dai-Bin Kuang,* and Cheng-Yong Su. Synthesis and Photocatalytic Application of Stable LeadFree $\text{Cs}_2\text{AgBiBr}_6$ Perovskite Nanocrystals. *Small* **14**, 1703762 (2018).
- 76 Zhenzhen Zhanga, b., Yongqi Liangb, Hanlin Huangb, Xingyi Liub, Qi Lib, Langxing Chena*, Dongsheng Xub*. Stable and Highly Efficient Photocatalysis with Lead-Free DoublePerovskite of $\text{Cs}_2\text{AgBiBr}_6$. *Angew. Chem. Int. Ed.* **10.1002/anie.201900658** (2019).
- 77 Cho, J., DuBose, J. T. & Kamat, P. V. Charge Injection from Excited $\text{Cs}_2\text{AgBiBr}_6$ Quantum Dots into Semiconductor Oxides. *Chemistry of Materials* **32**, 510-517, doi:10.1021/acs.chemmater.9b04243 (2020).
- 78 Qin, X., Zhao, Z., Wang, Y., Wu, J., Jiang, Q., and You, J. Recent progress in stability of perovskite solar cells. *J. Semicond.* **38** 011002 (2017).
- 79 Berhe, T. A. *et al.* Organometal halide perovskite solar cells: degradation and stability. *Energy & Environmental Science* **9**, 323-356, doi:10.1039/C5EE02733K (2016).
- 80 Berhe, T. A. *et al.* Identification of the physical origin behind disorder, heterogeneity, and reconstruction and their correlation with the photoluminescence lifetime in hybrid perovskite thin films. *Journal of Materials Chemistry A* **5**, 21002-21015, doi:10.1039/C7TA04615D (2017).
- 81 Xiao, Z., Meng, W., Wang, J., Mitzi, D.B., and Yan, Y. Searching for promising new perovskite-based photovoltaic absorbers: the importance of electronic dimensionality. *Mater. Horiz.* **4**, 206-216 (2017).
- 82 Zhang, Q., Ting, H., Wei, S., Huang, D., Wu, C., Sun, W., Qu, B., Wang, S., Chen, Z., and Xiao, L. Recent progress in lead-free perovskite (-like) solar cells. *Mater. Today Energy* **8**, 157-165 (2018).
- 83 Jodlowski, A., Rodr'iguez-Padro ' n, D., Luque, R., and de Miguel, G. Alternative perovskites for photovoltaics. *Adv. Energy Mater.* , 201703120., doi:<https://doi.org/10.1002/aenm>. (2018).
- 84 Liang, L., and Gao, P. . Lead-free hybrid perovskite absorbers for viable application: can we eat the cake and have it too? *Adv. Sci.(Weinh)* **5**, 1700331 (2018).
- 85 Abate, A. Perovskite solar cells go lead free. *Joule* **1** 659-664 (2017).
- 86 Xu, Q., Yang, D., Lv, J., Sun, Y.-Y., and Zhang, L. Perovskite solar absorbers: materials by design. *Small Methods* **2**, 1700316 (2018).
- 87 George Volonakis¹ and Feliciano Giustino¹, a. Surface properties of lead-free halide double perovskites: Possible visible-light photo-catalysts for water splitting featured. *Appl. Phys. Lett.* **112**, 243901, doi:<https://doi.org/10.1063/1.5035274> (2018).
- 88 Slavney, A. H., Te Hu, Aaron M. Lindenberg, and Hemamala I. Karunadasa. . A Bismuth-Halide Double Perovskite with Long Carrier Recombination Lifetime for Photovoltaic Applications. *J. Am. Chem. Soc.* **138**, 2138-2141 (2016).

- 89 al., K. e. HALIDE DOUBLE PEROVSKITE Cs₂AgBiBr₆ SOLAR-CELL ABSORBER HAVING LONG CARRIER LIFETIMES. *US20170194101A1* (2017).
- 90 Yang, Y. *et al.* Top and bottom surfaces limit carrier lifetime in lead iodide perovskite films. *Nature Energy* **2**, 16207, doi:10.1038/nenergy.2016.207
<https://www.nature.com/articles/nenergy2016207#supplementary-information> (2017).
- 91 Dong, Q. *et al.* Electron-hole diffusion lengths > 175 μm in solution-grown CH₃NH₃PbI₃ single crystals. *Science* **347**, 967-970, doi:10.1126/science.aaa5760 (2015).
- 92 Xing, G. *et al.* Long-Range Balanced Electron- and Hole-Transport Lengths in Organic-Inorganic CH₃NH₃PbI₃. *Science* **342**, 344-347, doi:10.1126/science.1243167 (2013).
- 93 Saparov, B. & Mitzi, D. B. Organic-Inorganic Perovskites: Structural Versatility for Functional Materials Design. *Chemical Reviews* **116**, 4558-4596, doi:10.1021/acs.chemrev.5b00715 (2016).
- 94 Burschka, J. *et al.* Sequential deposition as a route to high-performance perovskite-sensitized solar cells. *Nature* **499**, 316, doi:10.1038/nature12340
<https://www.nature.com/articles/nature12340#supplementary-information> (2013).
- 95 Best Research-Cell Efficiency Chart. <https://www.nrel.gov/pv/cell-efficiency.html> (2019).
- 96 Bhojak, V., Bhatia, D. & Jain, P. K. Investigation of photocurrent efficiency of Cs₂TiBr₆ double perovskite solar cell. *Materials Today: Proceedings* **66**, 3692-3697, doi:<https://doi.org/10.1016/j.matpr.2022.07.443> (2022).
- 97 Savory, C. N., Walsh, A. & Scanlon, D. O. Can Pb-Free Halide Double Perovskites Support High-Efficiency Solar Cells? *ACS Energy Lett* **1**, 949-955, doi:10.1021/acsenergylett.6b00471 (2016).
- 98 Pecunia, V., Occhipinti, L. G., Chakraborty, A., Pan, Y. & Peng, Y. Lead-free halide perovskite photovoltaics: Challenges, open questions, and opportunities. *APL Materials* **8**, doi:10.1063/5.0022271 (2020).
- 99 S. Rühle. *Phys. Status Solidi A*, 1600955 (2017).
- 100 R. Sheng, A. W. Y. H.-B., S. Huang, M. Keevers, X. Hao, L. Jiang, Y.-B Cheng, and M. A. Green, . *J. Phys. Chem. Lett.* **6**, 3931-3934 (2015).
- 101 Sani, F., Shafie, S., Lim, H. N. & Musa, A. O. Advancement on Lead-Free Organic-Inorganic Halide Perovskite Solar Cells: A Review. *Materials (Basel)* **11**, 1008, doi:10.3390/ma11061008 (2018).
- 102 Filip, M. R. H., S.; Haghighirad, A. A.; Snaith, H. J.; Giustino, F. . Band Gaps of the Lead-Free Halide Double Perovskites Cs₂BiAgCl₆ and Cs₂BiAgBr₆ from Theory and Experiment. *J. Phys. Chem. Lett.* **7**, 2579-2585, doi:DOI: 10.1021/acs.jpcllett.6b02682777 (2016).
- 103 Igbari, F. *et al.* Composition Stoichiometry of Cs₂AgBiBr₆ Films for Highly Efficient Lead-Free Perovskite Solar Cells. *Nano Letters* **19**, 2066-2073, doi:10.1021/acs.nanolett.9b00238 (2019).
- 104 Bush, K. A. *et al.* Compositional Engineering for Efficient Wide Band Gap Perovskites with Improved Stability to Photoinduced Phase Segregation. *ACS Energy Lett* **3**, 428-435, doi:10.1021/acsenergylett.7b01255 (2018).
- 105 Yang, J., Zhang, P. & Wei, S.-H. Band Structure Engineering of Cs₂AgBiBr₆ Perovskite through Order-Disordered Transition: A First-Principle Study. *The Journal of Physical Chemistry Letters* **9**, 31-35, doi:10.1021/acs.jpcllett.7b02992 (2018).
- 106 Zhang, P., Yang, J. & Wei, S.-H. Manipulation of cation combinations and configurations of halide double perovskites for solar cell absorbers. *Journal of Materials Chemistry A* **6**, 1809-1815, doi:10.1039/C7TA09713A (2018).
- 107 Jongseob Kim¹, H. K., Mahesh Chandran³, Seung-Cheol Lee^{3,a}), Sang Hyuk Im⁴, and Ki-Ha Hong^{5,b}). Impacts of cation ordering on bandgap dispersion of double perovskites. *APL Materials* **6**, 084903 (2018).
- 108 Liu, Z. *et al.* Solution-Processed Inorganic Perovskite Flexible Photodetectors with High Performance. *Nanoscale Research Letters* **14**, 284, doi:10.1186/s11671-019-3120-x (2019).
- 109 Chilvery, A., Das, S., Guggilla, P., Brantley, C. & Sunda-Meya, A. A perspective on the recent progress in solution-processed methods for highly efficient perovskite solar cells. *Science and technology of advanced materials* **17**, 650-658, doi:10.1080/14686996.2016.1226120 (2016).
- 110 Seo, J., Noh, J. H. & Seok, S. I. Rational Strategies for Efficient Perovskite Solar Cells. *Acc. Chem. Res.* **49**, 562-572, doi:10.1021/acs.accounts.5b00444 (2016).

- 111 Arain, Z. *et al.* Elucidating the dynamics of solvent engineering for perovskite solar cells. *Science China Materials* **62**, 161-172, doi:10.1007/s40843-018-9336-1 (2019).
- 112 Li, J. *et al.* Optimization of anti-solvent engineering toward high performance perovskite solar cells. *J. Mater. Res.* **34**, 2416-2424, doi:10.1557/jmr.2019.122 (2019).
- 113 Jeon, N. J. *et al.* Solvent engineering for high-performance inorganic–organic hybrid perovskite solar cells. *Nat. Mater.* **13**, 897-903, doi:10.1038/nmat4014 (2014).
- 114 Duan, J. *et al.* Inorganic perovskite solar cells: an emerging member of the photovoltaic community. *Journal of Materials Chemistry A* **7**, 21036-21068, doi:10.1039/C9TA06674H (2019).
- 115 Li, B. *et al.* Pathways toward high-performance inorganic perovskite solar cells: challenges and strategies. *Journal of Materials Chemistry A* **7**, 20494-20518, doi:10.1039/C9TA04114A (2019).
- 116 Wang, P. *et al.* Solvent-controlled growth of inorganic perovskite films in dry environment for efficient and stable solar cells. *Nature Communications* **9**, 2225, doi:10.1038/s41467-018-04636-4 (2018).
- 117 Chu, L. *et al.* *Lead-Free Halide Double Perovskite Materials: A New Superstar Toward Green and Stable Optoelectronic Applications*. Vol. 11 (2019).
- 118 Volonakis, G. & Giustino, F. *Surface properties of lead-free halide double perovskites: Possible visible-light photocatalysts for water splitting*. Vol. 112 (2018).
- 119 DeHoff, R. T. Engineering of microstructures. *Materials Research* **2**, 111-126 (1999).
- 120 Clemens, H., Mayer, S. & Scheu, C. 1-20 (2017).
- 121 Khalfin, S. & Bekenstein, Y. Advances in lead-free double perovskite nanocrystals, engineering band-gaps and enhancing stability through composition tunability. *Nanoscale* **11**, 8665-8679, doi:10.1039/C9NR01031A (2019).
- 122 Szuromi, P. Microstructural Engineering of Materials. *Science* **277**, 1183-1183, doi:10.1126/science.277.5330.1183 (1997).
- 123 Chen, L. *et al.* Tailoring properties of hybrid perovskites by domain-width engineering with charged walls. *npj Computational Materials* **4**, 75, doi:10.1038/s41524-018-0134-3 (2018).
- 124 Schade, L. *et al.* Structural and Optical Properties of Cs₂AgBiBr₆ Double Perovskite. *ACS Energy Letters* **4**, 299-305, doi:10.1021/acsenergylett.8b02090 (2019).
- 125 Lozhkina, O. A. *et al.* Microstructural analysis and optical properties of the halide double perovskite Cs₂BiAgBr₆ single crystals. *Chem. Phys. Lett.* **694**, 18-22, doi:10.1016/j.cplett.2018.01.031 (2018).
- 126 Wei Liu 1, Y. L., Ju Wang 1, Cuncun Wu 1, Congyue Liu 1, Lixin Xiao 1, Zhijian Chen 1, Shufeng Wang 1,2,* ID and Qihuang Gong 1,2. Twin Domains in Organometallic Halide Perovskite Thin-Films. *Crystals* **8**, 216 (2018).
- 127 Shi Liu, F. Z., Nathan Z. Koocher, Hiroyuki Takenaka, Fenggong Wang, and Andrew M. Rappe*. Ferroelectric Domain Wall Induced Band Gap Reduction and Charge Separation in Organometal Halide Perovskites. *J. Phys. Chem. Lett.* **6**, 693–699 (2015).
- 128 You, L. *et al.* Enhancing ferroelectric photovoltaic effect by polar order engineering. *Science Advances* **4**, eaat3438, doi:10.1126/sciadv.aat3438 (2018).
- 129 Lu You1*, F. Z., Liang Fang3*, Yang Zhou1, Liang Z. Tan2, Zeyu Zhang4, Guohong Ma4, Daniel Schmidt5‡, Andrivo Rusydi5, Le Wang1§, Lei Chang1, Andrew M. Rappe2¶, Junling Wang1¶. Enhancing ferroelectric photovoltaic effect by polar order engineering *Sci. Adv.* **4** (2018).
- 130 Chen, B. *et al.* Interface band structure engineering by ferroelectric polarization in perovskite solar cells. *Nano Energy* **13**, 582-591, doi:<https://doi.org/10.1016/j.nanoen.2015.03.037> (2015).
- 131 Du, K., Meng, W., Wang, X., Yan, Y. & B Mitzi, D. *Bandgap Engineering of Lead-Free Double Perovskite Cs₂AgBiBr₆ through Trivalent Metal Alloying*. (2017).
- 132 Torkzadeh, S., Maghsoudipour, A., Khanlarkhani, A. & Tajabadi, F. *Bandgap Engineering of Mixed-Halide Perovskites, A DFT Study*. (2017).
- 133 Roknuzzaman, M. *et al.* Electronic and optical properties of lead-free hybrid double perovskites for photovoltaic and optoelectronic applications. *Scientific Reports* **9**, 718, doi:10.1038/s41598-018-37132-2 (2019).
- 134 Li, Q. *et al.* High-Pressure Band-Gap Engineering in Lead-Free Cs₂AgBiBr₆ Double Perovskite. *Angewandte Chemie (International Edition)*, Medium: X; Size: p. 15969-15973 (2017).
- 135 Shockley, W. Q., H. J. . Detailed Balance Limit of Efficiency of P-N Junction Solar Cells. *J. Appl. Phys.* **32** (3), 510-511 (1961).

- 136 Adam H. Slavney, a., °] Linn Leppert,[b ,°] Abraham Saldivar Valdes,[a] Davide Bartesaghi,[c,d] Tom J. Savenije,[c] Jeffrey B. Neaton,*[e, f, g] and Hemamala I. Karunadasa*[a]. Small-Bandgap Halide Double Perovskites. *Angew. Chem. Int. Ed.* 10.1002/anie.201807421 (2018).
- 137 Walsh, A. Principles of Chemical Bonding and Band Gap Engineering in Hybrid Organic–Inorganic Halide Perovskites. *The Journal of Physical Chemistry C* **119**, 5755-5760, doi:10.1021/jp512420b (2015).
- 138 Ihtisham ul, h. *et al.* Bandgap reduction and efficiency enhancement in Cs₂AgBiBr₆ double perovskite solar cells through gallium substitution. *RSC Advances* **14**, 5440-5448, doi:10.1039/D3RA08965G (2024).
- 139 Yan, K. *et al.* Hybrid Halide Perovskite Solar Cell Precursors: Colloidal Chemistry and Coordination Engineering behind Device Processing for High Efficiency. *Journal of the American Chemical Society* **137**, 4460-4468, doi:10.1021/jacs.5b00321 (2015).
- 140 R. F. Berger and J. B. Neaton. *Phys. Rev. B: Condens. Matter Mater. Phys.* **86**, 165211 (2012).
- 141 Mcclure, E. T. B., M. R.; Windl, W.; Woodward, P. M. . Cs₂AgBiX₆ (X = Br, Cl) -new visible light absorbing, lead-free halide perovskite semiconductors. . *Chem. Mater.* **6** 2-4 (2016).
- 142 Creutz, S. E., Crites, E. N., De Siena, M. C. & Gamelin, D. R. Colloidal Nanocrystals of Lead-Free Double-Perovskite (Elpasolite) Semiconductors: Synthesis and Anion Exchange To Access New Materials. *Nano Lett.* **18**, 1118-1123, doi:10.1021/acs.nanolett.7b04659 (2018).
- 143 Hou, P. *et al.* Precursor engineering for high-quality Cs₂AgBiBr₆ films toward efficient lead-free double perovskite solar cells. *Journal of Materials Chemistry C* **9**, 9659-9669, doi:10.1039/D1TC01786A (2021).
- 144 Kangsabanik, J., Sugathan, V., Yadav, A., Yella, A. & Alam, A. Double perovskites overtaking the single perovskites: A set of new solar harvesting materials with much higher stability and efficiency. *Physical Review Materials* **2**, 055401, doi:10.1103/PhysRevMaterials.2.055401 (2018).
- 145 Mohandes, A., Moradi, M. & Nadgaran, H. Numerical simulation of inorganic Cs₂AgBiBr₆ as a lead-free perovskite using device simulation SCAPS-1D. *Optical and Quantum Electronics* **53**, 319, doi:10.1007/s11082-021-02959-z (2021).
- 146 D. Shi, V. A., R. Comin, M. Yuan, E. Alarousu, A. Buin, Y. Chen, S. Hoogland, A. Rothenberger, K. Katsiev, Y. Losovyj, X. Zhang, P. A. Dowben, O. F. Mohammed, E. H. Sargent, O. M. Bakr, . *Science* **347**, 519 (2015).
- 147 W. Nie, H. T., R. Asadpour, J.-C. Blancon, A. J. Neukirch, G. Gupta, J. J. Crochet, M. Chhowalla, S. Tretiak, M. A. Alam, H.-L. Wang, A. D. Mohite, . *Science* **347**, 522 (2015).
- 148 W. Zhang, G. E. E., H. J. Snaith, . *Nat. Energy* **1**, 16048 (2016).
- 149 H. Tan, A. J., O. Voznyy, X. Lan, F. P. García de Arquer, J. Z. Fan, R. Quintero-Bermudez, M. Yuan, B. Zhang, Y. Zhao, F. Fan, P. Li, L. N. Quan, Y. Zhao, Z.-H. Lu, Z. Yang, S. Hoogland, E. H. Sargent,. *Science* **355**, 722 (2017).
- 150 N. De Marco, H. Z., Q. Chen, P. Sun, Z. Liu, L. Meng, E. P. Yao, Y. Liu, A. Schiffer, Y. Yang, . *Nano Lett.* **16**, 1009 (2016).
- 151 D. Luo, W. Y., Z. Wang, A. Sadhanala, Q. Hu, R. Su, R. Shivanna, G. F. Trindade, J. F. Watts, Z. Xu, T. Liu, K. Chen, F. Ye, P. Wu, L. Zhao, J. Wu, Y. Tu, Y. Zhang, X. Yang, W. Zhang, R. H. Friend, Q. Gong, H. J. Snaith, R. Zhu *Science* **360**, 1442 (2018).
- 152 L. Liu, S. H., Y. Lu, P. Liu, Y. Zhao, C. Shi, S. Zhang, J. Wu, H. Zhong, M. Sui, H. Zhou, H. Jin, Y. Li, Q. Chen,. *Adv. Mater.* **30**, 1800544 (2018).
- 153 Slavney, A. H. *et al.* Defect-Induced Band-Edge Reconstruction of a Bismuth-Halide Double Perovskite for Visible-Light Absorption. *Journal of the American Chemical Society* **139**, 5015-5018, doi:10.1021/jacs.7b01629 (2017).
- 154 Wang, F., Bai, S., Tress, W., Hagfeldt, A. & Gao, F. Defects engineering for high-performance perovskite solar cells. *npj Flexible Electronics* **2**, 22, doi:10.1038/s41528-018-0035-z (2018).
- 155 Han, T.-H. *et al.* *Interface and Defect Engineering for Metal Halide Perovskite Optoelectronic Devices.* (2019).
- 156 Jian Xu, J.-B. L., * Bai-Xin Liu, Jianfeng Wang, and Bing Huang. Defect Engineering of Grain Boundaries in Lead-Free Halide Double Perovskites for Better Optoelectronic Performance. *Adv. Funct. Mater.*, 1805870 (2019).
- 157 Ramamoorthy Ramesha, b., c,1. Defect engineering using crystal symmetry. *PNAS* **vol. 115 (38)**, 9344-9346 (September 18, 2018).
- 158 Samanta, M., Ahmed, S. I., Chattopadhyay, K. K. & Bose, C. Role of various transport layer and electrode materials in enhancing performance of stable environment-friendly Cs₂TiBr₆ solar cell. *Optik* **217**, 164805, doi:<https://doi.org/10.1016/j.jileo.2020.164805> (2020).

- 159 He, Y., Xu, L., Zheng, H. & Guo, X. Numerical Exploration of Lead-Free Inorganic Perovskite Cs₂TiBr₆ Solar Cell. *Journal of Physics: Conference Series* **2021**, 012069, doi:10.1088/1742-6596/2021/1/012069 (2021).
- 160 Jani, M. R. *et al.* Exploring solar cell performance of inorganic Cs₂TiBr₆ halide double perovskite: A numerical study. *Superlattices and Microstructures* **146**, 106652, doi:<https://doi.org/10.1016/j.spmi.2020.106652> (2020).
- 161 Sultana, F., Jannat, F., Ahmed, S. & Alim, M. A. A comparative numerical approach between lead-free inorganic Cs₂TiBr₆ and Cs₂PtI₆-based perovskite solar cells. *Results in Optics* **13**, 100567, doi:<https://doi.org/10.1016/j.rio.2023.100567> (2023).
- 162 He, Y. *et al.* Defect Investigation of Ti-Based Vacancy-Ordered Double Perovskite Solar Cell using SCAPS-1D. *Journal of Physics: Conference Series* **2044**, 012100, doi:10.1088/1742-6596/2044/1/012100 (2021).
- 163 Hussain, I. *et al.* Functional materials, device architecture, and flexibility of perovskite solar cell. *Emergent Materials* **1**, 133-154, doi:10.1007/s42247-018-0013-1 (2018).
- 164 Kopacic, I. *et al.* *Enhanced Performance of Germanium Halide Perovskite Solar Cells through Compositional Engineering*. Vol. 1 (2018).
- 165 Song, Z., Waththage, S. C., Phillips, A. B. & Heben, M. J. *Pathways toward high-performance perovskite solar cells: review of recent advances in organo-metal halide perovskites for photovoltaic applications*. Vol. 6 (SPIE, 2016).
- 166 E. Greul, M. L. P., A. Binek, P. Docampo, T. Bein, . *J. Mater. Chem. A* **5**, 19972 (2017).
- 167 J. Luo, S. L., H. Wu, Y. Zhou, Y. Li, J. Liu, J. Li, K. Li, F. Yi, G. Niu, J. Tang. *ACS Photonics* **5**, 398 (2018).
- 168 A. Karmakar, M. S. D., S. Agnihotri, E. Ravera, V. K. Michaelis, . *Chem. Mater.* **30**, 8280 (2018).
- 169 Locardi, F. *et al.* Colloidal Synthesis of Double Perovskite Cs₂AgInCl₆ and Mn-Doped Cs₂AgInCl₆ Nanocrystals. *Journal of the American Chemical Society* **140**, 12989-12995, doi:10.1021/jacs.8b07983 (2018).
- 170 Luo, B. *et al.* B-Site doped lead halide perovskites: synthesis, band engineering, photophysics, and light emission applications. *Journal of Materials Chemistry C* **7**, 2781-2808, doi:10.1039/C8TC05741A (2019).
- 171 Zhang, X., Li, L., Sun, Z. & Luo, J. Rational chemical doping of metal halide perovskites. *Chemical Society Reviews* **48**, 517-539, doi:10.1039/C8CS00563J (2019).
- 172 Ye, T. *et al.* Enhanced Charge Carrier Transport and Device Performance Through Dual-Cesium Doping in Mixed-Cation Perovskite Solar Cells with Near Unity Free Carrier Ratios. *ACS Applied Materials & Interfaces* **9**, 2358-2368, doi:10.1021/acsami.6b12845 (2017).
- 173 Jun Zhou, X. R., Peng Zhang, Maxim S. Molokoev, Peijia Wei, Quanlin Liu, Xiuwen Zhang,* and Zhiguo Xia*. Manipulation of Bi³⁺/In³⁺ Transmutation and Mn²⁺-Doping Effect on the Structure and Optical Properties of Double Perovskite Cs₂NaBi_{1-x}In_xCl₆. *Adv. Optical Mater.*, 1801435 (2019).
- 174 Zhifang Tan, J. L., Cheng Zhang, Zha Li, Qingsong Hu, Zewen Xiao,* Toshio Kamiya, Hideo Hosono, Guangda Niu, Efrat Lifshitz, Yibing Cheng, and Jiang Tang*. Highly Efficient Blue-Emitting Bi-Doped Cs₂SnCl₆ Perovskite Variant: Photoluminescence Induced by Impurity Doping *Adv. Funct. Mater.*, 1801131 (2018).
- 175 K. Z. Du, W. M., X. Wang, Y. Yan, D. B. Mitzi, . *Angew. Chem., Int. Ed.* **56**, 8158 (2017).
- 176 T. T. Tran, J. R. P., J. R. Chamorro, J. R. Morey, T. M. McQueen, . *Mater. Horiz.* **4**, 688 (2017).
- 177 M. R. Filip, X. L., A. Miglio, G. Hautier, F. Giustino, . *J. Phys. Chem. C* **122**, 158 (2018).
- 178 F. Giustino, H. J. S. *ACS Energy Lett.* **1**, 1233 (2016).
- 179 Q. Sun, J. W., W. J. Yin, Y. Yan, . *Adv. Mater.* **30**, 1705901 (2018).
- 180 K.-z. Du, X. W., Q. Han, Y. Yan, D. B. Mitzi, . *ACS Energy Lett.* **2**, 2486 (2017).
- 181 Fridkin, V. M. Bulk photovoltaic effect in noncentrosymmetric crystals. *Crystallogr. Rep.* **46**, 654-658 (2001).
- 182 Peng Gao¹, Heng-Jui Liu³, Yen-Lin Huang³, Ying-Hao Chu^{3,4}, Ryo Ishikawa⁵, Bin Feng⁵, Ying Jiang^{2,6}, Naoya Shibata⁵, En-Ge Wang^{2,6} & Yuichi Ikuhara^{5,7,8}. Atomic mechanism of polarization-controlled surface reconstruction in ferroelectric thin films. *Nat. Commun.* **7**, 11318 (2016).
- 183 R. von Baltz, W. K. Theory of the bulk photovoltaic effect in pure crystals. *Phys. Rev.* **B 23**, 5590-5596 (1981).
- 184 S. M. Young, A. M. R. First principles calculation of the shift current photovoltaic effect in ferroelectrics. *Phys. Rev. Lett.* **109**, 116601 (2012).
- 185 S. M. Young, F. Z., A. M. Rappe First-principles calculation of the bulk photovoltaic effect in bismuth ferrite. *Phys. Rev. Lett.* **109**, 236601 (2012).
- 186 Padinhare Cholakkal Harikesh, B. W., Biplab Ghosh, Rohit Abraham John, Stener Lie, Krishnamoorthy Thirumal, Lydia Helena Wong, Tze Chien Sum, Subodh Mhaisalkar, and Nripan Mathews*. Doping and Switchable Photovoltaic Effect in Lead-Free Perovskites Enabled by Metal Cation Transmutation. *Adv. Mater.*, 1802080 (2018).

- 187 D. Lee, S. H. B., T. H. Kim, J.-G. Yoon, C. M. Folkman, C. B. Eom, T. W. Noh, . Polarity control of carrier injection at ferroelectric/metal interfaces for electrically switchable diode and photovoltaic effects. *Phys. Rev. B* **84**, 125305 (2011).
- 188 Dai, X., Deng, Y., Van Brackle, C. H. & Huang, J. Meniscus fabrication of halide perovskite thin films at high throughput for large area and low-cost solar panels. *International Journal of Extreme Manufacturing* **1**, 022004, doi:10.1088/2631-7990/ab263e (2019).
- 189 Tiing, T. V. e. a. Octadecylamine-Functionalized Single-Walled Carbon Nanotubes for Facilitating the Formation of a Monolithic Perovskite Layer and Stable Solar Cells. . *Adv. Funct. Mater.* **28(10)**, 1705545 (2018).
- 190 Stoumpos, C. C., Malliakas, C. D. & Kanatzidis, M. G. Semiconducting Tin and Lead Iodide Perovskites with Organic Cations: Phase Transitions, High Mobilities, and Near-Infrared Photoluminescent Properties. *Inorganic Chemistry* **52**, 9019-9038, doi:10.1021/ic401215x (2013).
- 191 Ponseca, C. S. *et al.* Organometal Halide Perovskite Solar Cell Materials Rationalized: Ultrafast Charge Generation, High and Microsecond-Long Balanced Mobilities, and Slow Recombination. *Journal of American Chemical Society* **136**, 5189-5192, doi:10.1021/ja412583t (2014).
- 192 Xing, G. *et al.* Long-Range Balanced Electron- and Hole-Transport Lengths in Organic-Inorganic CH₃NH₃PbI₃. *Science* **342**, 344-347, doi:10.1126/science.1243167 (2013).
- 193 Etgar, L. *et al.* Mesoscopic CH₃NH₃PbI₃/TiO₂ Heterojunction Solar Cells. *Journal of American Chemical Society* **134**, 17396-17399, doi:10.1021/ja307789s (2012).
- 194 Pham, H. Q., Holmes, R. J., Aydil, E. S. & Gagliardi, L. Lead-free double perovskites Cs₂InCuCl₆ and (CH₃NH₃)₂InCuCl₆: electronic, optical, and electrical properties. *Nanoscale* **11**, 11173-11182, doi:10.1039/C9NR01645G (2019).
- 195 Ankur Tayaa), P. R., and Manish K. Kashyap. Structural, electronic and optical studies of Pb-free halide double perovskite Cs₂BiAgBr₆; an mBJLDA approach. *AIP Conf. Proc.* **2093**, 020028, doi:<https://doi.org/10.1063/1.5097097> (2019).
- 196 Zhang, Q. *et al.* Perovskite solar cells: must lead be replaced – and can it be done? *Science and Technology of Advanced Materials* **19**, 425-442, doi:10.1080/14686996.2018.1460176 (2018).
- 197 Wei, F. *et al.* Synthesis and Properties of a Lead-Free Hybrid Double Perovskite: (CH₃NH₃)₂AgBiBr₆. *Chem.mater.* **29**, 1089-1094, doi:10.1021/acs.chemmater.6b03944 (2017).
- 198 Ball, J. M., Lee, M. M., Hey, A. & Snaith, H. J. Low-temperature processed meso-superstructured to thin-film perovskite solar cells. *Energy & Environmental Science* **6**, 1739-1743, doi:10.1039/C3EE40810H (2013).
- 199 Jeon, N. J. *et al.* Solvent engineering for high-performance inorganic–organic hybrid perovskite solar cells. *Nat. Mater.* **13**, 897-903, doi:10.1038/nmat4014 <http://www.nature.com/nmat/journal/v13/n9/abs/nmat4014.html#supplementary-information> (2014).
- 200 Burschka, J. *et al.* Sequential deposition as a route to high-performance perovskite-sensitized solar cells. *Nature* **499**, 316-319, doi:10.1038/nature12340 <http://www.nature.com/nature/journal/v499/n7458/abs/nature12340.html#supplementary-information> (2013).
- 201 Liu, D. & Kelly, T. L. Perovskite solar cells with a planar heterojunction structure prepared using room-temperature solution processing techniques. *Nat Photon* **8**, 133-138, doi:10.1038/nphoton.2013.342 <http://www.nature.com/nphoton/journal/v8/n2/abs/nphoton.2013.342.html#supplementary-information> (2014).
- 202 Eperon, G. E. *et al.* Formamidinium lead trihalide: a broadly tunable perovskite for efficient planar heterojunction solar cells. *Energy & Environmental Science* **7**, 982-988, doi:10.1039/C3EE43822H (2014).
- 203 Hodes, G. Perovskite-Based Solar Cells. *Science* **342**, 317-318, doi:10.1126/science.1245473 (2013).

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.