

Article

Not peer-reviewed version

3D-Printed Phenylboronic Acid-bearing Hydrogels for Glucose-Triggered Drug Release

[Jeremy Odent](#)*, [Nicolas Baleine](#), Serena Maria Torcasio, [Sarah Gautier](#), [Olivier Coulembier](#), [Jean-Marie Raguez](#)

Posted Date: 24 July 2024

doi: 10.20944/preprints2024071819.v1

Keywords: 3D printing; drug eluting implants; glucose responsiveness



Preprints.org is a free multidiscipline platform providing preprint service that is dedicated to making early versions of research outputs permanently available and citable. Preprints posted at Preprints.org appear in Web of Science, Crossref, Google Scholar, Scilit, Europe PMC.

Copyright: This is an open access article distributed under the Creative Commons Attribution License which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Article

3D-Printed Phenylboronic Acid-bearing Hydrogels for Glucose-Triggered Drug Release

Jérémy Odent *, Nicolas Baleine, Serena Maria Torcasio, Sarah Gautier, Olivier Coulembier and Jean-Marie Raquez

Affiliation; e-mail@e-mail.com

* Correspondence: jeremy.odent@umons.ac.be

Abstract: Diabetes is a major health concern that the next-generation of on-demand insulin releasing implants may overcome for personalized therapy. Therein, 3D-printed phenylboronic acid-containing subcutaneous implants with on-demand glucose-triggered drug release abilities are produced using high resolution stereolithography technology. To that end, the methacrylation of phenylboronic acid is targeted following a two-step reaction. The resulting photocurable phenylboronic acid derivative is accordingly incorporated within bioinert polyhydroxyethyl methacrylate-based hydrogels at varying loadings. The end result are sub-centimeter scaled 3D-printed bioinert implants that can be remotely activated with 1,2-diols and 1,3-diols such as glucose for on-demand drug administration such as insulin. As a proof of concept, varying glucose concentration from hypoglycemia to hyperglycemia levels readily allow the release of pinacol, *i.e.* a model molecule with similar release properties than insulin, at respectively low and high rates. In addition, the results demonstrated that adjusting the geometry and size of the 3D-printed part is a simple and suitable method for tailoring the release behavior and dosage.

Keywords: 3D printing; drug eluting implants; glucose responsiveness

Introduction

Diabetes mellitus is one of the most worldwide diffuse chronic disease related to a population concern that is expected to grow in the next years [1]. The current therapy is provided by insulin administration through invasive delivery methods such as repetitive subcutaneous injections. This mode of administration is painful and may lead to *e.g.* injection phobia, infections and incorrect medication dose [2]. In this regard, significant efforts have been made to develop long-lasting insulin delivery systems [3,4]. Since the *in vivo* insulin fluctuation is not linear, the elaboration of such systems require the modulation of insulin release through the action of biological stimulus such as the glucose concentration [5]. Therein, insulin-lectin (*e.g.* concanavalin A) complexes proved their efficiency *in vitro* but still have the competitive set point between insulin and glucose above the typical range of hyperglycemia concentration [8–10]. Alternatively, chemically controlled glucose responsive systems have been widely investigated over the last few decades. Among them, pH-responsive materials allow on-demand release of a pre-loaded insulin dose using a glucose-specific enzyme (*e.g.* glucose oxidase) that can convert the glucose into gluconic acid in the presence of oxygen, thereby causing a decrease in local pH [11–13]. Despite high activity and low toxicity, these systems suffers from major hurdles, particularly the loss of biological activity after oral administration, their blood oxygen dependence and their high sensitivity to environmental changes [14–16]. Alternative glucose-responsive systems based on phenylboronic acid (PBA), which could program the insulin release rate in response to different glucose concentrations, have therefore emerged [17,18]. PBA is likely well-known to have substantial affinities for glucose because of its ability to bind specifically and reversibly with 1,2- and 1,3-diols through reversible boronate ester formation [19–24]. In addition, PBA has high operational stability, in particular compared with glucose oxidase and lectin, which are widely used for glucose sensing.

Considering regulation of blood glucose levels by insulin, the fast and stable bond formation between PBA and glucose is used as the basis for forming reversible molecular assemblies capable of trapping and releasing insulin [28–33]. It is therein assumed that PBA-glucose complexes of both 2:1 and 1:1 stoichiometries are formed [26]. As the glucose concentration increases, the 2:1 complex is thereby converted to two 1:1 complexes, leading to a decrease of the number of crosslinks and an increase of the number of free anionic 1:1 complexes, which in turn endow an expansion in the hydrogel volume [26]. The resulting glucose-dependent volumetric changes ultimately accelerates the release kinetics of physically entrapped insulin. In an effort to delineate the key parameters influencing the PBA-glucose esterification, Zhang *et al.* demonstrated that substituents in the aromatic ring of PBAs further affect the kinetics of the esterification/transesterification [36]. In addition, Achilli *et al.* evidenced that the hydrolysis of boronate esters is dependent on both the substituents in the aromatic ring and the pH of the solution [37]. Although, the release kinetics can be controlled remotely through molecular design, novel manufacturing technologies surely offers new possibilities to maximize the personalization through the combination of the right material with the right three-dimensional geometry.

Healthcare innovations to medical devices and manufacturing will enable devices to be more modular and adaptable while creating new opportunities to improve the personalization, quality and safety of treatment. Additive manufacturing (AM), *i.e.* 3D printing, has become one of the most innovative technologies in the pharmaceutical field [38,39]. Currently, multiple 3D-printing techniques and materials are investigated with regard to manifold characteristics for drug-eluting implants such as shape, surface, microstructure, mechanical properties and drug release behavior [40]. Therein, complex microstructures such as internal channeled[41,42], grid-like[43] or honeycomb[44] already demonstrated their ability to tailor drug release. Stereolithography (SLA) offers the highest versatility with respect to the freedom in material development, scalability and speed of fabrication [45–47]. The advantages of SLA compared to all other AM, when biological (macro)molecules such as proteins[48–50], genetic materials (*e.g.* DNA, RNA)[51–53] and other biological molecules[36,54,55] are concerned, have been well-established thanks to its mild operating conditions that prevent undesired degradations [56]. Still, the development of biocompatible materials that enable the fabrication of large-scale 3D-printed objects are required [57,58]. Therein, our group have investigated the multivariate photochemistry of SLA and reported the rapid 3D printing of tough, highly solvated, and antifouling hybrid zwitterionic hydrogels for potential uses in biomedical applications [59]. In addition, bioinert composite elastomers that can be rapidly 3D-printed into complex geometries with high-resolution features via SLA 3D printing that are expected to contribute to the development of medical devices from readily available materials are produced [60]. Interestingly, Robinson *et al.* exploited boronate esters as a key building block for the development of 3D-printed objects with the ability to undergo room-temperature exchange at the crosslinking sites [61]. As far as insulin delivery systems are concerned, Wu *et al.* 3D-printed insulin-loaded PBA-containing microneedle patches, allowing the diffusive release of entrapped insulin [62]. Still, 3D-printed tailored dosage forms with on-demand glucose-triggered drug release abilities are needed.

In the present work, new bioinert PBA-containing polyhydroxyethyl methacrylate (PHEMA)-based hydrogels of tailored dosage forms are 3D-printed at high-resolution features using commercial SLA technology. Methacrylation of phenylboronic acid is thereby envisioned for its effective incorporation within bioinert PHEMA-based hydrogels at varying loadings. Resulting glucose-responsive systems should thereby endow reversible volume change with respect to the glucose concentration as the 2:1 complex is converted to two 1:1 complexes, and vice-versa. Pinacol, a 1,2-diol-containing model molecule, is used to demonstrate the controlled glucose-triggered drug release ability of our system [63]. As far as insulin administration is concerned, diol-functionalized insulin is required instead of pinacol to endow the precise regulation of blood glucose level. Therein, Hashimoto *et al.* already demonstrated that the biological activity of insulin is maintained as high as *ca.* 90% after its chemical modification [64]. Overall, the present contribution further demonstrated our ability to photo-pattern complex 3D objects with unusual geometries on-demand to comply with the individual needs of each patient in term of release and dosage forms.

Experimental

Materials

4-Carboxybenzeneboronic acid (4CPBA, $\geq 99\%$, Apollo Scientific), 2-hydroxyethyl methacrylate (HEMA, 97%, Merck), poly(ethylene glycol) methacrylate (PEGMA, $M_w = 500$ g/mol, $\geq 99\%$, Sigma-Aldrich), poly(ethylene glycol) dimethacrylate (PEGDMA, $M_w = 550$ g/mol, $\geq 99\%$, Sigma-Aldrich), 2,3-dimethylbutane-2,3-diol (pinacol, $\geq 99\%$, Merck), diphenyl(2,4,6-trimethylbenzoyl) phosphine oxide (TPO, 97%, Sigma-Aldrich) and trifluoroacetic anhydride (TFAA $\geq 99\%$, Sigma-Aldrich) are purchased as indicated and used without further purification. Tetrahydrofuran (THF, 99%, VWR) is dried using a MBraun Solvent Purification System (model MB-SPS 800) equipped with alumina drying columns.

Synthesis of Phenylboronic Acid-Based Methacrylate

The reaction involves a two-step synthesis. The first step relies on an equimolar reaction of 4CPBA ($m = 500$ mg, $n = 3$ mmol) with pinacol ($m = 356$ mg, $n = 3$ mmol) in 10 mL of dry THF. After 3h under agitation at room temperature, the as-protected phenylboronic acid is isolated under vacuum for 12 hours, leading to compound **1** (see Figure 1A). In a second step, the resulting pinacol protected 4-carboxybenzeneboronic acid ($m = 747.6$ mg, $n = 3$ mmol) and 1 eq. of TFAA ($m = 623.8$ mg, $n = 3$ mmol) are mixed to 10 mL of dried THF at room temperature. After 15 minutes, 1 equivalent of PEGMA ($m = 1.51$ g, $n = 3$ mmol) is slowly added to the reaction medium. The solution is allowed to stir for an additional 12-hours at room temperature. The resulting α -methacrylate ω -pinacolyl boronic ester poly(ethylene glycol) (PEGMA-PBA-Pinacol), *i.e.* compound **2** (see Figure 1A), is isolated by simple drying procedure under vacuum. Yield = 98%, $M_n = 788.53$ g/mol, $\bar{M}_w = 1.16$, $^1\text{H-NMR}$ ($\text{DMSO-}d_6$, 500 MHz): δ (ppm): 7.95 (2H, CH), 7.79 (2H, CH), 6.03-5.69 (2H, CH₂), 4.51 (2H, CH₂-O-CO), 4.21 (2H, CH₂-O), 1.88 (3H, CH₃-CO), 1.31 (12H, CH₃); FT-IR (ATR, cm^{-1}): 1358 (B-O).

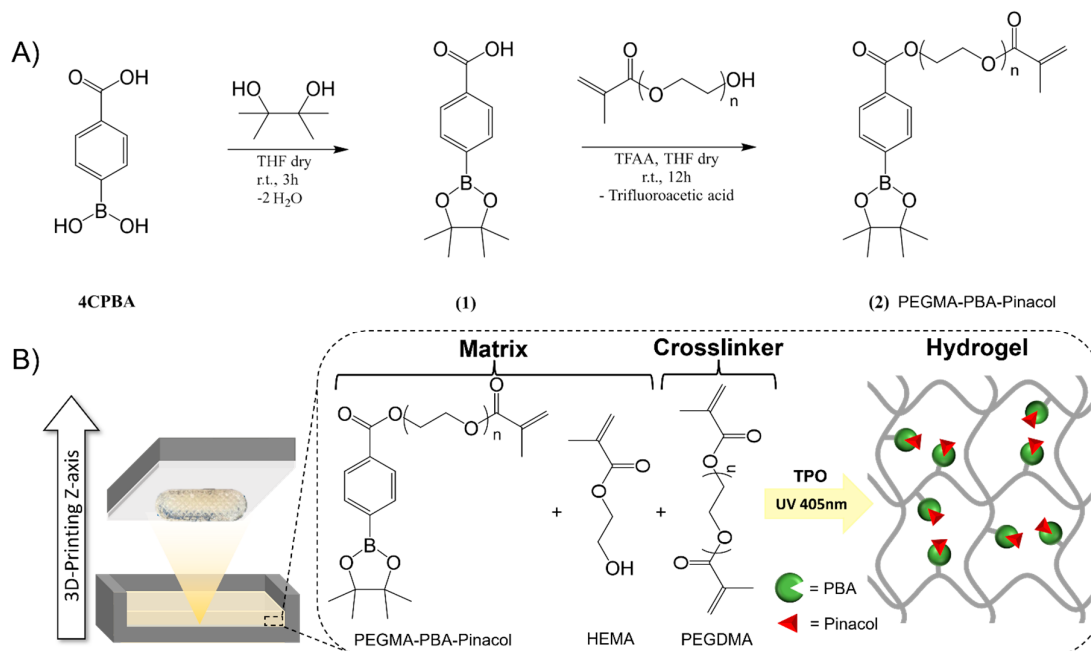


Figure 1. A) Synthetic route of α -methacrylate ω -pinacolyl boronic ester poly(ethylene glycol) (PEGMA-PBA-Pinacol, *i.e.* compound **2**). B) Fast bottom-up fabrication of PBA-containing hydrogels via photopolymerization of HEMA and PEGMA-PBA-Pinacol using PEGDMA crosslinker and TPO photo-initiator.

3D Printing of Bioinert Phenylboronic Acid-Containing Hydrogels

Different ratios in HEMA and compound **2** are used in conjunction with 1 mol% of PEGDMA and 0.5 mol% of TPO. A full-spectrum light exposure (OmniCure S1000, Lumen Dynamics, 405 nm) allows the photocuring of the formulations in several shapes (*e.g.* disks). The 3D printer is a Liquid Crystal Precision 1.5 by Photocentric using a LCD screen of 405 nm wavelength, as-controlled by an open source software. All the .stl files are designed using Autodesk Fusion 360 modeling software and then imported on Photocentric studio to slice the design into discrete 100 μm layers. Layer exposure times are set at 45s per discrete 100 μm layer. Resulting 3D objects are washed successively in an excess of isopropanol for 24h and in a PBS solution for an extra 24h. While the gel fraction is systematically over 97%, no potentially toxic unreacted moieties are released from the materials, as confirmed by ^1H -NMR after washing. Samples are named PHEMA-PBA x with x corresponding to the molar percentage of PEGMA-PBA-Pinacol (*i.e.* compound **2**) in the hydrogel matrix.

Transesterification of Phenylboronic Pinacol Ester with Glucose

Stability of compound **2** towards glucose transesterification are evaluated in a 100 mM sodium phosphate buffer at pH 7.4. To that end, compound **2** is solubilized in three buffer solutions at an initial concentration of *ca.* 4 mM containing different amounts of glucose (*i.e.* 4, 8 and 12 mM). Phenylboronic pinacol ester – glucose transesterification is quantified by ^1H -NMR spectroscopy. We can further determine the nature of diffusion of the entrapped drug from the hydrogels by plotting the relative pinacol release *vs.* the square root of immersion time. The diffusion coefficients (D) could be further estimated from the slope-values according to equation 1.

$$\varphi = \frac{4}{d} \sqrt{\frac{Dt}{\pi}} \quad (1)$$

where D is the diffusion coefficient, φ is the relative pinacol release and d is the thickness of the sample in cm.

In Vitro Drug Release Testing

Samples are immersed in a pH 7.4 phosphate buffer saline (PBS) solution with various concentrations of glucose (*i.e.* 0, 4, 8 and 12 mM). 5 mL of the buffer solution is taken out at preset time points and samples are re-immersed in fresh buffer solution. Pinacol release is followed by ^1H -NMR spectroscopy.

Additional Techniques

^1H -NMR spectra are recorded on a Bruker Avance III HD 500 MHz spectrometer at 293 K. Chemical shifts are reported as δ in parts per million (ppm) and referenced to the residual solvent signal ($\text{DMSO-}d_6$, $\delta = 2.50$ ppm).

Fourier transform infrared spectroscopy (FTIR) measurements are carried out with a Spectrum One FTIR spectrometer (Perkin Elmer instruments). Spectra are obtained in transmission mode at room temperature in the $4000\text{--}600\text{ cm}^{-1}$ region with a resolution of 4 cm^{-1} and 32 scans.

Photo-rheological measurements are performed using a rheometer MCR 302 (Anton-Paar) connected to a UV-light source (OmniCure S1000, Lumen Dynamics). During photo-exposure (irradiance $E_e = 22.5\text{ mW/cm}^2$), frequency ($\omega = 1\text{ Hz}$) and amplitude ($\epsilon = 1\%$) oscillatory shear are constant. Samples are placed between circular parallel plates (diameter = 25 mm) with a gap of 1 mm. Rheological measurements are performed using a rheometer MCR 302 (Anton-Paar) using a plate-plate geometry system with a 25 mm diameter and a gap of 1 mm. Strain sweep measurements are performed at $25\text{ }^\circ\text{C}$ with a frequency of 1 Hz and a strain range between 0.01% and 100%. All samples are swelled at equilibrium in PBS solution containing different glucose concentration before measurement (*i.e.* from 0 to 12 mM). The relationship between the storage modulus in the rubbery plateau and the crosslinking density is given by the following equation:

$$\nu_e = \frac{G'}{RT} \quad (2)$$

where ν_e is the crosslinking density, G' is the shear modulus obtained in the rubbery plateau, R is gas constant and T is the temperature in Kelvin. The relationship between the storage modulus in the rubbery plateau and the mesh size is given by the following equation:

$$r_{mesh} = \sqrt[3]{\frac{6RT}{\pi N_{Av} G'}} \quad (3)$$

where r_{mesh} is the mesh size, R is the gas constant, T is the temperature in Kelvin, N_{Av} is the Avogadro's number and G' is the shear modulus in the rubbery plateau region.

Results and Discussion

3D-Printed Bioinert Phenylboronic Acid-Containing Hydrogels

The number of commercially available resins suitable for SLA 3D printing being limited, the approach involved the end-functionalization of PBA, as a glucose-responsive trigger, with highly reactive methacrylate groups to readily undergo rapid free radical photo-polymerization under near-UV exposure. The synthesis of photocurable PBA-based glucose-responsive derivative is thereby performed following a two-step reaction (Figure 1A). Firstly, treatment of 4CPBA with pinacol afforded the corresponding pinacolyl boronate esters, *i.e.* compound **1** (see Figure 1A). Unlike boronic acid precursor, being more prone to dehydration to afford an insoluble anhydride trimeric boroxine[65], 4CPBA is remarkably soluble in common organic solvents, allowing its reaction to be conducted in dried THF at room temperature during 3h. The resulting pinacolyl boronate ester is then esterified with a low molecular weight PEGMA under very mild conditions using TFAA, which was converted into the corresponding α -methacrylate w-pinacolyl boronic ester poly(ethylene glycol), *i.e.* compound **2** (see Figure 1A) [66]. Such approach obviates the necessity of a multi-step process while enabling a direct reaction to occur between the acidic group of 4CPBA and the hydroxyl function of PEGMA at room temperature during 12 hours. ¹H-NMR analyses clearly evidenced the quantitative formation of compound **1** and compound **2** (Figure S1 in the ESI). As the transesterification reaction of phenylboronic pinacol esters is known to be dependent on both the substituents in the aromatic ring and the pH of the solution, the second step of this synthesis readily allows to attach an electron-donor PEG segment in *para* position to the boronic ester derivative, thus reducing undesired drug release. Indeed, Achilli *et al.* demonstrated that the rate of hydrolysis is slower when an electron-donor group is attached in *para* position to the boronic moiety on the aromatic ring [37]. Moreover, it allows to attach a photopolymerizable methacrylate moiety to the boronic ester derivative, thus allowing its use for SLA 3D printing.

The stability of compound **2** towards competitive transesterification of the boronate with glucose is first evaluated in a 100 mM sodium phosphate buffer at pH 7.4. To mimic conditions associated to hypo-, normal and hyper-glycemia levels, the conversion of phenyl boronic pinacol esters to phenyl boronic glucose ester by transesterification reaction at varying glucose concentrations (*i.e.* 4, 8 and 12 mM respectively) is determined after three days (*i.e.* at thermodynamic equilibrium) by ¹H-NMR (Figure S2 in the ESI). In hypoglycemia conditions (*i.e.* 4 mM), only 31% of pinacol is released, suggesting very little transesterification reaction between the free diols and boronate ester bonds (Figure S3 in the ESI). As the glucose concentration increases, the transesterification reaction turned favorable, releasing 41% and 84% of pinacol at normal glycemia (*i.e.* 8 mM) and hyperglycemia (*i.e.* 12 mM) conditions respectively. Note that the nearly complete transesterification in hyperglycemia conditions readily allow the effective release of entrapped cargo for on-demand drug administration such as insulin.

Photo-rheology allows for the *in-situ* monitoring of chemical and mechanical characteristics during the photo-polymerization reactions, providing key data concerning the suitability of the synthesized compound **2** towards SLA 3D printing technology. (Figure S4 in the ESI) [67,68]. The

key requirement is the ability to rapidly reach a high degree of conversion using a near-UV source of equivalent wavelength to our SLA equipment. Compound **2** is thereby incorporated within PHEMA-based hydrogels at varying concentrations (*i.e.* 2-10 mol%). While PEGDMA crosslinker is used at 1 mol%, TPO is used as a type-I photo-initiator, enabling free radical photo-polymerization of the acrylate groups with near-UV SLA systems. Initially exhibiting a liquid-like behavior with a loss modulus (G'') greater than the storage modulus (G') and with an initial viscosity below 1 Pa.s, the viscosity starts to increase as the gelation process occurs under near-UV exposure, leading to solid-like behavior as characterized by G' greater than G'' . Resulting compound **2** displayed a slower polymerization kinetics than neat HEMA with a gel point occurring at longer near-UV exposures (*ca.* 38s vs. 32 s, see Figure S4 in the ESI). When combined, the new material thereby displays an intermediate behavior (*i.e.* 34 s at 10 mol% of compound **2** within HEMA). Still, HEMA and compound **2** (or combination) are suitable for SLA 3D printing, allowing us to design PBA-containing PHEMA-based hydrogels. Fabrication of such hydrogels into complex geometries of high-resolution features is performed on a LC Precision 1.5 (Photocentric, $\lambda = 405$ nm) SLA printer. The characteristic B-O asymmetric stretching band at 1358 cm^{-1} in the FTIR spectra confirmed the incorporation of boronic acid moieties within the PHEMA-based hydrogels (Figure S5 in the ESI).

Glucose Responsiveness Features

The unique feature of boronic acid is that they are capable of forming reversible covalent complexes with 1,2- or 1,3-diols, including glucose [26]. While boronate ester formation lead to the creation of 2:1 complex at low glucose concentration, the later 2:1 complex is converted to two 1:1 complexes as the glucose concentration increases (Figure 2A). As a result, a decrease of the number of crosslinks and an increase in the hydrogel volume, which in turn accelerates the release kinetics of physically entrapped drugs, including insulin, are expected. In hypoglycemia conditions (*i.e.* 4 mM), PBA is largely in excess compared to glucose, leading to 2:1 complexes and highly crosslinked PHEMA-based hydrogel network (Figure 2B). In contrast, glucose saturates boronic acid sites as the glucose concentration increases over a critical limit (*i.e.* beyond normal glucose conditions, > 8 mM), converting 2:1 complex into 1:1 complexes with respect to loosely crosslinked PHEMA-based hydrogel network (Figure 2B). The later conversion at varying glucose concentrations from hypoglycemia to hyperglycemia levels (*i.e.* from 4 to 12 mM) is evidenced by rheological measurements (Figure S6 and Table S1 in the ESI). Oscillation amplitude sweeps thereby attested for a typical elastic solid behavior since storage modulus (G') in each case is higher than loss modulus (G''). An estimation of the effective crosslinking density is further assessed by storage modulus measurements in the rubbery plateau region given equation 2 [69]. In addition, the mesh sizes which refer to average distance between the entanglements within the resulting PHEMA-based hydrogel network are further estimated given equation 3 [70]. While the estimated crosslinking density and related mesh size of neat PHEMA hydrogel does not change at varying glucose concentrations, PBA-containing PHEMA-based hydrogels show significant decrease of the estimated crosslinking density and increase of the mesh size from hypoglycemia to hyperglycemia levels (see Table S1 in the ESI). In addition, the higher the PBA loading within the PHEMA-based hydrogel, the more crosslinked hydrogel networks with respect to higher crosslinking density and lower mesh size. Recall that highly crosslinked 2:1 complexes are formed in hypoglycemia conditions which are converted into loosely crosslinked 1:1 complexes in hyperglycemia conditions. Such a decrease in the number of crosslinks and increase in the mesh size thereby endow an expansion in the hydrogel volume which should ultimately accelerates the release kinetics of physically entrapped drug, including insulin. While the drug release is mainly dominated by diffusion process if the mesh size is larger than the hydrodynamic radius of the diffusive drug molecule, similar or smaller mesh size than the hydrodynamic radius of the diffusive drug molecule will result to a slower drug release rate with respect to steric hindrance. Note that insulin is either found in the body as a free molecule or as a complexed hexamer of *ca.* 3 nm for storage purpose[71], so that diffusion of physically entrapped insulin should be dominated by steric hindrance in hypoglycemia and normal conditions with

respect to recorded mesh sizes around *ca.* 3 nm, while rather dictated by diffusion process in hyperglycemia conditions with respect to mesh sizes around *ca.* 5 nm.

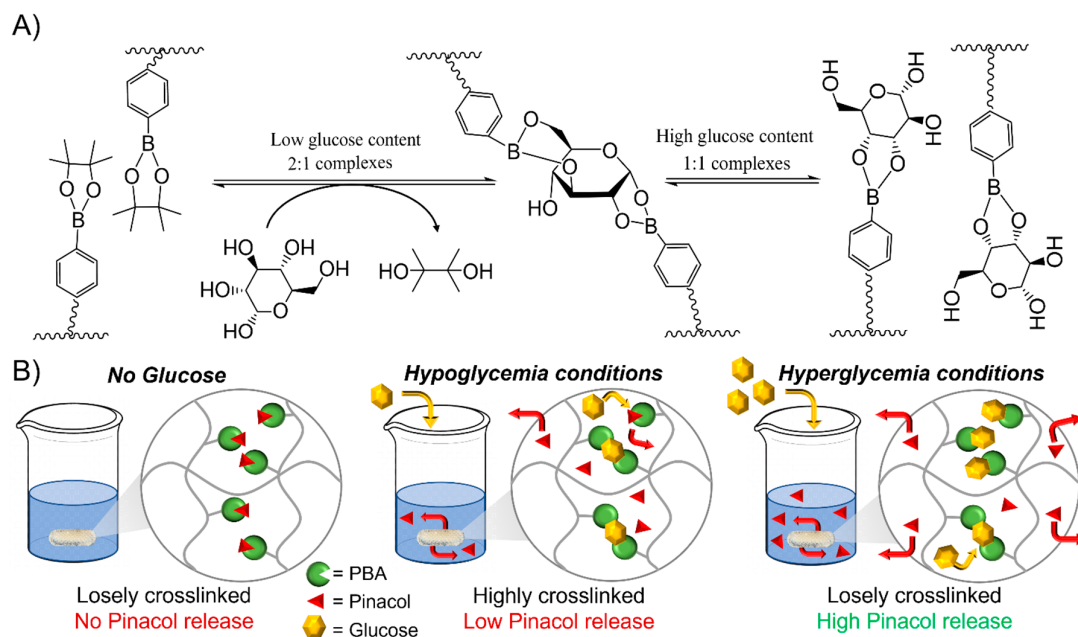


Figure 2. A) Schematic representation of interaction of phenylboronic acid pinacol ester with glucose at varying glucose levels. B) Graphic representation of the reversible molecular assemblies capable of trapping and releasing insulin by transesterification reaction at varying glucose concentrations, converting the 2:1 complex into two 1:1 complexes, which in turn decrease the number of crosslinks and endow an expansion in the hydrogel volume to accelerate the drug release kinetic.

Drug Release Kinetics

Pinacol, a model molecule, is used to demonstrate the controlled glucose-responsive drug delivery ability of the resulting 3D-printed PHEMA-based hydrogels. The main difference between pinacol and insulin release would be attributed to the steric hindrance, which endows a slower release rate for insulin [72]. Note, though, that diol-functionalized insulin is required to endow the precise regulation of blood glucose level [64]. To study the release kinetics, PHEMA-PBA_x (with $x = 2$ or 10 mol%) are first immersed in buffer solution in the absence of glucose (*i.e.* 0 mM) to determine the background rate of release due to hydrolysis of the pinacol ester (Figure 4). Overall, a pinacol release as low as *ca.* 1% after 3 days attested for very little hydrolysis. Subsequently, the amount of released pinacol are measured by ¹H-NMR analyses over times (*i.e.* up to 72h) at varying glucose conditions going from hypo-, normal, and hyper-glycemia (Figure 4). As a result, a rapid release of pinacol is observed during the first hour, suggesting a burst effect, as evidenced by the perfect fit of the rapid release period with the fast swelling of the hydrogel (Figure S7 in the ESI) [73]. The burst effect is followed by a steady release. While the glucose concentration does not seem to impact the burst release with an effective release of *ca.* 15% of pinacol after 1h for all compositions, the steady release is clearly affected under varying glucose levels. While PHEMA-PBA₁₀ releases *ca.* 30-33% of pinacol after 24h (and *ca.* 45-50% after 3 days) with a steady release of *ca.* 0.45%/h (*i.e.* 1×10^{-6} mol/h) in hypoglycemia (*i.e.* 4 mM) and normal glycemia (*i.e.* 8 mM) conditions, the release is boosted to *ca.* 49% (and 84% after 3 days) under hyperglycemia (*i.e.* 12 mM) conditions (Figure 3). The pinacol release as a function of the square root of time for the steady release period show a linear increase, suggesting simple Fickian diffusion (Figure S8 in the ESI), leading to the diffusion coefficient derived from equation 3 (Table S2 in the ESI) [74]. While the diffusion coefficient does not seem to vary with the chemical incorporation of PBA (*i.e.* via compound 2) within the PHEMA-based hydrogel, the diffusion coefficient increase from hypoglycemia to hyperglycemia levels. Recall that the estimated

mesh size of the resulting PHEMA-based hydrogel networks increase with respect to the glucose concentration, leading to an expansion in the hydrogel volume which ultimately accelerates the release kinetics of physically entrapped drugs (see Table S1 in the ESI). The high sensitivity toward glucose is further assessed by alternatively immersing PHEMA-PBA10, under hypoglycemia and hyperglycemia conditions every 30 min (Figure 5). Overall, high release of pinacol is observed under hyperglycemia condition (*i.e.* 12 mM), while low release (remaining almost constant) is recorded under hypoglycemia condition (*i.e.* 4 mM). Overall, *ca.* 1% of pinacol is released during the first cycle according to the burst effect, to equilibrate around *ca.* 0.5% during the second and third cycles. The latter results suggest that PBA-containing PHEMA-based hydrogels can be used as an on-off switching system as a function of the glucose concentration, enabling on-demand release of a desired molecule. To demonstrate function, resulting glucose-responsive PHEMA-based hydrogels are 3D-printed into centimeter-scaled drug eluting implants with modifications in the geometry and size resulting in changes to the drug release and dosage behavior. Therein, adjusting the specific surface area to volume ratio of the drug eluting implants by controlling the 3D-printing infill density from 100% (*i.e.* solid) to 50% (*i.e.* opened structure) appear as a simple way to endow faster drug release kinetics (Figure 5A) [43]. As far as the pinacol release is concerned, the drug eluting implant with an infill density of 50% provided faster burst effect than the solid implant as well as higher steady release (Figure 6B and Figure S9 in the ESI). While the implant with an infill density of 50% showed a burst effect during the first 40 minutes with a release of *ca.* 15%, the implant with an infill density of 100% lasts one hour to reach *ca.* 15% of release. In addition, release rates of *ca.* 40%/day and *ca.* 22%/day, leading to a complete release after 48h and 72h, are respectively recorded for the 50% infilled and the solid implant in hyperglycemia conditions. The difference in the pinacol release is further assessed by plotting the amount of released pinacol as a function of time (Figure 6C). Therein, a release rate of *ca.* $4.1 \cdot 10^{-5}$ mol/day and *ca.* $5.4 \cdot 10^{-5}$ mol/day in hyperglycemia conditions is respectively observed for the implants with an infill density of 50% and 100% respectively. If we rationalize this rate as a function of the volume of the implant, the release rate becomes $1.7 \cdot 10^{-5}$ mol/mm³.day and $1 \cdot 10^{-5}$ mol/mm³.day respectively for the implants with an infill density of 50% and 100%. Recall that the lower the infill density, the higher the surface area to volume ratio, which in turn endow faster release of entrapped drug. The later demonstrated the ability to tailor drug release through the combination of the right material with the right three-dimensional geometry using high resolution stereolithography technology for personalized therapy.

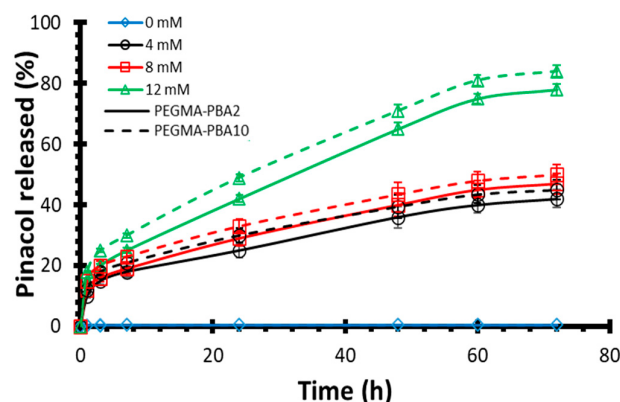


Figure 3. Pinacol release kinetics profiles of PHEMA-PBA2 (solid line) and PHEMA-PBA10 (dashed line) at varying glucose levels (*i.e.* 0 mM (blue), 4 mM (black), 8 mM (red) and 12 mM (green)).

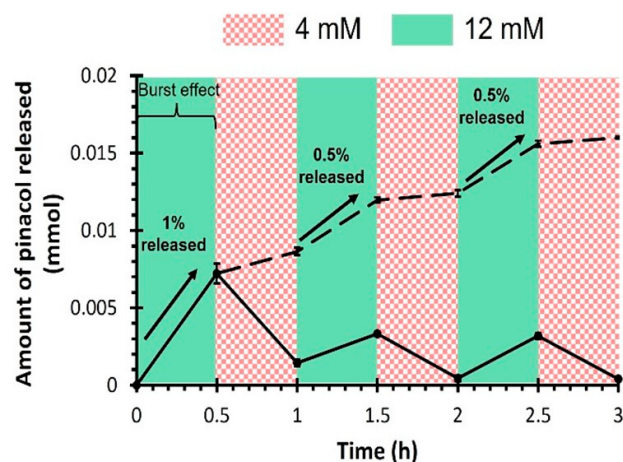


Figure 4. Pulsatile release of pinacol of PHEMA-PBA10 by alternatively immersing in hypoglycemia and hyperglycemia conditions (*i.e.* 4 mM and 12 mM), leading to the amount of pinacol released at each cycle step (full line) and the total amount of pinacol released over time (dashed line).

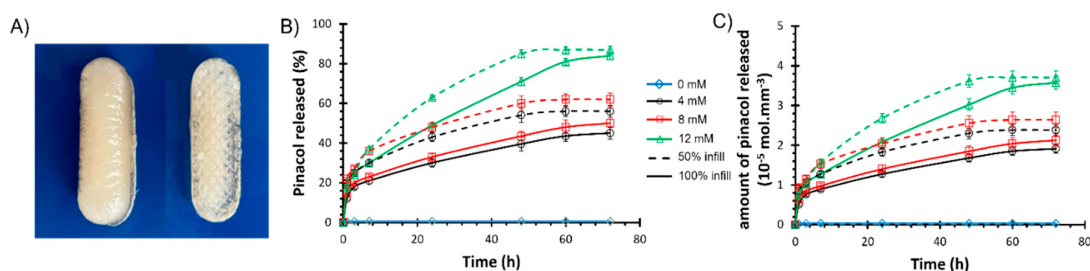


Figure 5. **A)** Visual aspect of 3D-printed drug eluting implants with an infill density of 100% (left) and 50% (right). **B)** Relative release of pinacol and **C)** amount of pinacol released rationalized by the volume of the implant for the PHEMA-PBA10-based drug eluting implants with an infill density of 100% (solid line) and 50% (dashed line) at varying glucose levels (*i.e.* 0 mM (blue), 4 mM (black), 8 mM (red) and 12 mM (green)).

Conclusions

3D-printed PBA-containing PHEMA-based hydrogels with on-demand glucose-triggered drug release abilities are successfully produced using high resolution stereolithography technology as the next-generation of drug eluting implants for personalized therapy. To that end, photocurable PBA-based glucose-responsive derivatives are synthesized following a two-step reaction. The resulting derivatives are incorporated within bioinert PHEMA-based hydrogels at varying loadings, leading to centimeter-scaled 3D-printed drug eluting implants that can be remotely activated with diols such as glucose for on-demand drug administration such as insulin. Resulting glucose-responsive systems endow reversible volume change with respect to the glucose concentration as the 2:1 complex is converted to two 1:1 complexes, leading to a decrease of the number of crosslinks which ultimately accelerates the release kinetics of physically entrapped drug. In the present work, pinacol, a 1,2-diol-containing model molecule, is accordingly used to demonstrate the controlled glucose-triggered drug release ability of our system. A $2 \cdot 10^{-6}$ mol/h released rate has been observed under hyperglycemia conditions. Such rate allows to deliver *e.g.* 2 units of insulin, corresponding to the required dose of insulin to treat a 4 mM increase in glucose concentration within 3 minutes. Still, diol-functionalized insulin is required instead of pinacol to endow the precise regulation of blood glucose level. To demonstrate function, 3D-printed into centimeter-scaled drug eluting implants are fabricated using high resolution stereolithography technology. Adjusting the specific surface area to volume ratio of the resulting implants by controlling the 3D-printing infill density further demonstrated the ability

to tailor drug release through the combination of the right material with the right three-dimensional geometry for personalized therapy.

Supplementary Materials: The following supporting information can be downloaded at the website of this paper posted on Preprints.org.

Acknowledgements: We gratefully acknowledge support from both Wallonia and the European Commission “FSE and FEDER”. The authors acknowledge the Interreg France-Wallonie-Vlaanderen program “3D4MED”, with the financial support of the European Regional Development Fund (ERDF). O. Coulembier and J.- M. Raquez are Senior Research Associate at F.R.S.-F.N.R.S. of Belgium.

Conflicts of interest: There are no conflicts to declare.

References

1. Cho NH, Shaw JE, Karuranga S, Huang Y, da Rocha Fernandes JD, Ohlrogge AW, *et al.* IDF Diabetes Atlas: Global estimates of diabetes prevalence for 2017 and projections for 2045. *Diabetes Res Clin Pract.* 2018;138:271–81.
2. Johnson-Rabbett B, Seaquist ER. Hypoglycemia in diabetes: The dark side of diabetes treatment. A patient-centered review. *J Diabetes.* 2019;11(9):711–8.
3. Gordijo CR, Koulajian K, Shuhendler AJ, Bonifacio LD, Huang HY, Chiang S, *et al.* Nanotechnology-Enabled Closed Loop Insulin Delivery Device: *In vitro* and *In vivo* Evaluation of Glucose-Regulated Insulin Release for Diabetes Control. *Adv Funct Mater.* 2011;21(1):73–82.
4. Chu MKL, Chen J, Gordijo CR, Chiang S, Ivovic A, Koulajian K, *et al.* *In vitro* and *in vivo* testing of glucose-responsive insulin-delivery microdevices in diabetic rats. *Lab Chip.* 2012;12(14):2533.
5. Sarwar N, Gao P, Kondapally Seshasai SR, Gobin R, Kaptoge S, Di Angelantonio E, *et al.* Diabetes mellitus, fasting blood glucose concentration, and risk of vascular disease: a collaborative meta-analysis of 102 prospective studies. *The Lancet.* 2010;375(9733):2215–22.
6. Brownlee M, Cerami A. A Glucose-Controlled Insulin-Delivery System: Semisynthetic Insulin Bound to Lectin. *Science.* 1979;206(4423):1190–1.
7. Brownlee M, Cerami A. Glycosylated Insulin Complexed to Concanavalin A: Biochemical Basis for a Closed-Loop Insulin Delivery System. *Diabetes.* 1983;32(6):499–504.
8. Ballerstadt R, Evans C, McNichols R, Gowda A. Concanavalin A for *in vivo* glucose sensing: A biotoxicity review. *Biosens Bioelectron.* 2006;22(2):275–84.
9. Yin R, Tong Z, Yang D, Nie J. Glucose-responsive microhydrogels based on methacrylate modified dextran/concanavalin A for insulin delivery. *J Controlled Release.* 2011;152:e163–5.
10. Xu M, Huang J, Jiang S, He J, Wang Z, Qin H, *et al.* Glucose sensitive konjac glucomannan/concanavalin A nanoparticles as oral insulin delivery system. *Int J Biol Macromol.* 2022;202:296–308.
11. Wang J, Ye Y, Yu J, Kahkoska AR, Zhang X, Wang C, *et al.* Core-Shell Microneedle Gel for Self-Regulated Insulin Delivery. *ACS Nano.* 2018;12(3):2466–73.
12. Luo FQ, Chen G, Xu W, Zhou D, Li JX, Huang YC, *et al.* Microneedle-array patch with pH-sensitive formulation for glucose-responsive insulin delivery. *Nano Res.* 2021;14(8):2689–96.
13. Wang Y, Fan Y, Zhang M, Zhou W, Chai Z, Wang H, *et al.* Glycopolypeptide Nanocarriers Based on Dynamic Covalent Bonds for Glucose Dual-Responsiveness and Self-Regulated Release of Insulin in Diabetic Rats. *Biomacromolecules.* 2020;21(4):1507–15.
14. Liu Q, Rauth AM, Wu XY. Immobilization and bioactivity of glucose oxidase in hydrogel microspheres formulated by an emulsification–internal gelation–adsorption–polyelectrolyte coating method. *Int J Pharm.* 2007;339(1–2):148–56.
15. Wen J, Anderson SM, Du J, Yan M, Wang J, Shen M, *et al.* Controlled Protein Delivery Based on Enzyme-Responsive Nanocapsules. *Adv Mater.* 2011;23(39):4549–53.
16. Dutta K, Hu D, Zhao B, Ribbe AE, Zhuang J, Thayumanavan S. Templated Self-Assembly of a Covalent Polymer Network for Intracellular Protein Delivery and Traceless Release. *J Am Chem Soc.* 2017;139(16):5676–9.
17. Wang J, Wang Z, Yu J, Kahkoska AR, Buse JB, Gu Z. Glucose-Responsive Insulin and Delivery Systems: Innovation and Translation. *Adv Mater.* 2020;32(13):1902004.
18. Sharma G, Sharma AR, Nam JS, Doss GPC, Lee SS, Chakraborty C. Nanoparticle based insulin delivery system: the next generation efficient therapy for Type 1 diabetes. *J Nanobiotechnology.* 2015;13(1):74.
19. Horgan AM, Marshall AJ, Kew SJ, Dean KES, Creasey CD, Kabilan S. Crosslinking of phenylboronic acid receptors as a means of glucose selective holographic detection. *Biosens Bioelectron.* 2006;21(9):1838–45.
20. Ngo YLT, Choi WM, Chung JS, Hur SH. Highly biocompatible phenylboronic acid-functionalized graphitic carbon nitride quantum dots for the selective glucose sensor. *Sens Actuators B Chem.* 2019;282:36–44.

21. Tang Z, Guan Y, Zhang Y. Contraction-type glucose-sensitive microgel functionalized with a 2-substituted phenylboronic acid ligand. *Polym Chem.* 2014;5(5):1782–90.
22. Meng H, Zheng J, Wen X, Cai Z, Zhang J, Chen T. pH- and Sugar-Induced Shape Memory Hydrogel Based on Reversible Phenylboronic Acid-Diol Ester Bonds. *Macromol Rapid Commun.* 2015;36(6):533–7.
23. Matsumoto A, Ishii T, Nishida J, Matsumoto H, Kataoka K, Miyahara Y. A Synthetic Approach Toward a Self-Regulated Insulin Delivery System. *Angew Chem Int Ed.* 2012;51(9):2124–8.
24. Yin W, Wang Y, Xiao Y, Mao A, Lang M. Phenylboronic acid conjugated mPEG-b-PCL micelles as DOX carriers for enhanced drug encapsulation and controlled drug release. *Eur Polym J.* 2022;173:111235.
25. Zhang J, Xu J, Lim J, Nolan JK, Lee H, Lee CH. Wearable Glucose Monitoring and Implantable Drug Delivery Systems for Diabetes Management. *Adv Healthc Mater.* 2021;10(17):2100194.
26. Alexeev VL, Sharma AC, Goponenko AV, Das S, Lednev IK, Wilcox CS, *et al.* High Ionic Strength Glucose-Sensing Photonic Crystal. *Anal Chem.* 2003;75(10):2316–23.
27. Banach L, Williams GT, Fossey JS. Insulin Delivery Using Dynamic Covalent Boronic Acid/Ester-Controlled Release. *Adv Ther.* 2021;4(11):2100118.
28. Yang T, Ji R, Deng XX, Du FS, Li ZC. Glucose-responsive hydrogels based on dynamic covalent chemistry and inclusion complexation. *Soft Matter.* 2014;10(15):2671.
29. Yesilyurt V, Webber MJ, Appel EA, Godwin C, Langer R, Anderson DG. Injectable Self-Healing Glucose-Responsive Hydrogels with pH-Regulated Mechanical Properties. *Adv Mater.* 2016;28(1):86–91.
30. Dong Y, Wang W, Veisheh O, Appel EA, Xue K, Webber MJ, *et al.* Injectable and Glucose-Responsive Hydrogels Based on Boronic Acid–Glucose Complexation. *Langmuir.* 2016;32(34):8743–7.
31. Yu J, Wang J, Zhang Y, Chen G, Mao W, Ye Y, *et al.* Glucose-responsive insulin patch for the regulation of blood glucose in mice and minipigs. *Nat Biomed Eng.* 2020;4(5):499–506.
32. Marco-Dufort B, Willi J, Vielba-Gomez F, Gatti F, Tibbitt MW. Environment Controls Biomolecule Release from Dynamic Covalent Hydrogels. *Biomacromolecules.* 2021;22(1):146–57.
33. Xiang Y, Xian S, Ollier RC, Yu S, Su B, Pramudya I, *et al.* Diboronate crosslinking: Introducing glucose specificity in glucose-responsive dynamic-covalent networks. *J Controlled Release.* 2022;348:601–11.
34. Peppas N, Bures P, Leobandung W, Ichikawa H. Hydrogels in pharmaceutical formulations. *Eur J Pharm Biopharm.* 2000;50(1):27–46.
35. Lin CC, Metters AT. Hydrogels in controlled release formulations: Network design and mathematical modeling. *Adv Drug Deliv Rev.* 2006;58(12–13):1379–408.
36. Zhang C, Losego MD, Braun PV. Hydrogel-Based Glucose Sensors: Effects of Phenylboronic Acid Chemical Structure on Response. *Chem Mater.* 2013;25(15):3239–50.
37. Achilli C, Ciana A, Fagnoni M, Balduini C, Minetti G. Susceptibility to hydrolysis of phenylboronic pinacol esters at physiological pH. *Open Chem.* 2013;11(2):137–9.
38. Trivedi M, Jee J, Silva S, Blomgren C, Pontinha VM, Dixon DL, *et al.* Additive manufacturing of pharmaceuticals for precision medicine applications: A review of the promises and perils in implementation. *Addit Manuf.* 2018;23:319–28.
39. Zhang J, Vo AQ, Feng X, Bandari S, Repka MA. Pharmaceutical Additive Manufacturing: a Novel Tool for Complex and Personalized Drug Delivery Systems. *AAPS PharmSciTech.* 2018;19(8):3388–402.
40. Domsta V, Seidlitz A. 3D-Printing of Drug-Eluting Implants: An Overview of the Current Developments Described in the Literature. *Molecules.* 2021;26(13):4066.
41. Sadia M, Arafat B, Ahmed W, Forbes RT, Alhnan MA. Channelled tablets: An innovative approach to accelerating drug release from 3D printed tablets. *J Controlled Release.* 2018;269:355–63.
42. Arafat B, Wojsz M, Isreb A, Forbes RT, Isreb M, Ahmed W, *et al.* Tablet fragmentation without a disintegrant: A novel design approach for accelerating disintegration and drug release from 3D printed cellulosic tablets. *Eur J Pharm Sci.* 2018;118:191–9.
43. Verstraete G, Samaro A, Grymonpré W, Vanhoorne V, Van Snick B, Boone MN, *et al.* 3D printing of high drug loaded dosage forms using thermoplastic polyurethanes. *Int J Pharm.* 2018;536(1):318–25.
44. Kyobula M, Adediji A, Alexander MR, Saleh E, Wildman R, Ashcroft I, *et al.* 3D inkjet printing of tablets exploiting bespoke complex geometries for controlled and tuneable drug release. *J Controlled Release.* 2017;261:207–15.
45. Tayebi L, Rasoulianboroujeni M, Moharamzadeh K, Almela TKD, Cui Z, Ye H. 3D-printed membrane for guided tissue regeneration. *Mater Sci Eng C.* 2018;84:148–58.
46. Visscher LE, Dang HP, Knackstedt MA, Hutmacher DW, Tran PA. 3D printed Polycaprolactone scaffolds with dual macro-microporosity for applications in local delivery of antibiotics. *Mater Sci Eng C.* 2018;87:78–89.
47. Ambrosi A, Pumera M. 3D-printing technologies for electrochemical applications. *Chem Soc Rev.* 2016;45(10):2740–55.
48. Economidou SN, Lamprou DA, Douroumis D. 3D printing applications for transdermal drug delivery. *Int J Pharm.* 2018;544(2):415–24.

49. Mizuno Y, Takasawa K, Hanada T, Nakamura K, Yamada K, Tsubaki H, *et al.* Fabrication of novel-shaped microneedles to overcome the disadvantages of solid microneedles for the transdermal delivery of insulin. *Biomed Microdevices*. 2021;23(3):38.
50. Xenikakis I, Tsongas K, Tzimtzimis EK, Katsamenis OL, Demiri E, Zacharis CK, *et al.* Transdermal delivery of insulin across human skin *in vitro* with 3D printed hollow microneedles. *J Drug Deliv Sci Technol*. 2022;67:102891.
51. Arora A, Prausnitz MR, Mitragotri S. Micro-scale devices for transdermal drug delivery. *Int J Pharm*. 2008;364(2):227–36.
52. Chen W, Li H, Shi D, Liu Z, Yuan W. Microneedles As a Delivery System for Gene Therapy. *Front Pharmacol* [Internet]. 2016 [cited 2022];7. Available from: <http://journal.frontiersin.org/Article/10.3389/fphar.2016.00137/abstract>
53. Dorsey PJ, Rubanov M, Wang W, Schulman R. Digital Maskless Photolithographic Patterning of DNA-Functionalized Poly(ethylene glycol) Diacrylate Hydrogels with Visible Light Enabling Photodirected Release of Oligonucleotides. *ACS Macro Lett*. 2019;8(9):1133–40.
54. Jin X, Zhu DD, Chen BZ, Ashfaq M, Guo XD. Insulin delivery systems combined with microneedle technology. *Adv Drug Deliv Rev*. 2018;127:119–37.
55. Liu H, Li W, Liu C, Tan J, Wang H, Hai B, *et al.* Incorporating simvastatin/poloxamer 407 hydrogel into 3D-printed porous Ti-6Al-4V scaffolds for the promotion of angiogenesis, osseointegration and bone ingrowth. *Biofabrication*. 2016;8(4):045012.
56. Goyanes A, Buanz ABM, Hatton GB, Gaisford S, Basit AW. 3D printing of modified-release aminosaliclylate (4-ASA and 5-ASA) tablets. *Eur J Pharm Biopharm*. 2015;89:157–62.
57. Filipović VV, Božić Nedeljković BD, Vukomanović M, Tomić SLj. Biocompatible and degradable scaffolds based on 2-hydroxyethyl methacrylate, gelatin and poly(beta amino ester) crosslinkers. *Polym Test*. 2018;68:270–8.
58. Tzeng JJ, Yang TS, Lee WF, Chen H, Chang HM. Mechanical Properties and Biocompatibility of Urethane Acrylate-Based 3D-Printed Denture Base Resin. *Polymers*. 2021;13(5):822.
59. Pan W, Wallin TJ, Odent J, Yip MC, Mosadegh B, Shepherd RF, *et al.* Optical stereolithography of antifouling zwitterionic hydrogels. *J Mater Chem B*. 2019;7(17):2855–64.
60. Odent J, Wallin TJ, Pan W, Kruemplestaedter K, Shepherd RF, Giannelis EP. Highly Elastic, Transparent, and Conductive 3D-Printed Ionic Composite Hydrogels. *Adv Funct Mater*. 2017;27(33):1701807.
61. Robinson LL, Self JL, Fusi AD, Bates MW, Read de Alaniz J, Hawker CJ, *et al.* Chemical and Mechanical Tunability of 3D-Printed Dynamic Covalent Networks Based on Boronate Esters. *ACS Macro Lett*. 2021;10(7):857–63.
62. Wu M, Zhang Y, Huang H, Li J, Liu H, Guo Z, *et al.* Assisted 3D printing of microneedle patches for minimally invasive glucose control in diabetes. *Mater Sci Eng C*. 2020;117:111299.
63. Mayer JP, Zhang F, DiMarchi RD. Insulin structure and function. *Biopolymers*. 2007;88(5):687–713.
64. Hashimoto M, Takada K, Kiso Y, Muranishi S. Synthesis of Palmitoyl Derivatives of Insulin and Their Biological Activities. *Pharm Res*. 1989;06(2):171–6.
65. Korich AL, Iovine PM. Boroxine chemistry and applications: A perspective. *Dalton Trans*. 2010;39(6):1423–31.
66. Stacey M, Bourne EJ, Tatlow JC, Tedder JM. A General Method of Esterification using Trifluoroacetic Anhydride. *Nature*. 1949;164(4173):705–705.
67. Wang C, Lin B, Zhu H, Bi F, Xiao S, Wang L, *et al.* Recent Advances in Phenylboronic Acid-Based Gels with Potential for Self-Regulated Drug Delivery. *Molecules*. 2019;24(6):1089.
68. DeRosa ME, Baker LS, Melock TL, Yang B. Ultraviolet cure kinetics of a low Tg polyurethane acrylate network under varying light intensity and exposure time. *Prog Org Coat*. 2021;158:106353.
69. Hill LW. Calculation of crosslink density in short chain networks. *Prog Org Coat*. 1997;31(3):235–43.
70. Schurz J. Rheology of polymer solutions of the network type. *Prog Polym Sci*. 1991;16(1):1–53.
71. Jensen SS, Jensen H, Cornett C, Møller EH, Østergaard J. Insulin diffusion and self-association characterized by real-time UV imaging and Taylor dispersion analysis. *J Pharm Biomed Anal*. 2014;92:203–10.
72. Li J, Mooney DJ. Designing hydrogels for controlled drug delivery. *Nat Rev Mater*. 2016;1(12):16071.
73. Bhattacharjee S. Understanding the burst release phenomenon: toward designing effective nanoparticulate drug-delivery systems. *Ther Deliv*. 2021;12(1):21–36.
74. Bove L, D'Aniello C, Gorrasi G, Guadagno L, Vittoria V. Transport properties of dichloromethane in glassy polymers. VI. Poly(ethylene terephthalate). *J Appl Polym Sci*. 1996;62(7):1035–41.

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.