

Article

Not peer-reviewed version

Dissimilar Resistance Welding of NiTi Microwires for High Performance SMA Bundle Actuators

[Dominik Scholtes](#)^{*}, Ralf-Kilian Zäh, Benedikt Faupel, Stefan Seelecke, [Paul Motzki](#)^{*}

Posted Date: 6 August 2024

doi: 10.20944/preprints202408.0356.v1

Keywords: actuator; joining; sensor; shape memory alloy; welding



Preprints.org is a free multidiscipline platform providing preprint service that is dedicated to making early versions of research outputs permanently available and citable. Preprints posted at Preprints.org appear in Web of Science, Crossref, Google Scholar, Scilit, Europe PMC.

Copyright: This is an open access article distributed under the Creative Commons Attribution License which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Article

Dissimilar Resistance Welding of NiTi Microwires for High Performance SMA Bundle Actuators

Dominik Scholtes ^{1,2,*}, Ralf-Kilian Zäh ¹, Benedikt Faupel ³, Stefan Seelecke ^{1,2} and Paul Motzki ^{1,2,*}

¹ Intelligent Material Systems Lab, Center for Mechatronics and Automation Technologies – ZeMA gGmbH, Saarbruecken, Germany

² Intelligent Material Systems Lab, Department of Systems Engineering, Department of Material Science and Engineering, Saarland University, Saarbruecken, Germany

³ University of Applied Sciences Saarbruecken (HTW), Saarbruecken, Germany

* Correspondence: dominik.scholtes@uni-saarland.de or d.scholtes@zema.de (D.S.); paul.motzki@uni-saarland.de or p.motzki@zema.de (P.M.); Tel.: +49-681-302-71360 (D.S.)

Abstract: Shape memory alloys (SMA) are becoming a more important factor in actuation technology. Due to their unique features, they bring the potential to save weight, installation space and reduce energy consumption. The system integration of the generally small diameter NiTi wires is an important cornerstone for the emerging technology. Crimping, a common method for the mechanical and electrical connection of SMA wires, has several drawbacks when it comes to miniaturization and high force outputs. For high force applications for example, multiple SMA wires in parallel are needed to keep actuation frequencies high, while scaling up the actuation force. To meet these challenges, the proposed study deals with the development of a resistance welding process for manufacturing NiTi wire bundles. The wires are welded to sheet metal substrate, resulting in promising functional properties and high joint strengths. The welding process benefits from low cost, easy to control parameters and good automation potential. A method for evaluating the resistance welding process parameters is presented. With these parameters in place, a manufacturing process for bundled wire actuators is discussed and implemented. The welded joints are examined by peel tests, microscopy, and fatigue experiments. The performance of the manufactured bundle actuators is demonstrated by comparison to a single wire with the same accumulated cross-sectional area.

Keywords: actuator; joining; sensor; shape memory alloy; welding

1. Introduction

Shape memory alloys (SMA) have many beneficial attributes, especially in the form of thin wires. Among those are a high energy density, high actuation frequency, self-sensing capability and a unique form factor. [1–4] On the other hand, there are applications that would benefit from SMA technology, with reduced weight and smaller installation space, but requirements like high forces combined with short cycle times cannot be met by usual designs of SMA actuators. As the force scales with the cross-sectional area of the SMA wire, the thermal effects of volume to surface ratio result in long cooling periods.

Efficient product design requires a small number of parts and simple assembly processes. Of course, this is also true for SMA actuators. The state of the art joining technology for SMA wires is crimping. The crimp itself is an additional part, which needs to be clamped on the wire. Compared to an SMA microwire, the crimp is heavy and large, and it needs to be accessible from at least two sides for assembly. Additionally, high forces are needed to fix the crimp.

For both issues with SMA wire technology there are solutions available. High forces combined with high dynamics are achieved by bundling many small diameter SMA wires in parallel, so their force output adds up, but the volume to surface ratio is consistent. [3,5,6] The difficult crimping

process on the other hand, can be replaced by substance-to-substance bonds like glueing, soldering or welding. Where the latter shows most promising results.

The SMA phenomenon in NiTi alloys was discovered in the 1960s and a lot of research is conducted on the topic since then. [7,8] Today NiTi is still the commercially most successful SMA material. Depending on the alloy composition, it behaves either superelastic or quasiplastic at room temperature. The superelastic alloys are by far the most common and are widely used for medical applications like stents, guidewires, braces, and other devices. [9] They can fully recover strains up to 10%. [10,11] Rather new developments based on superelastic alloys are the so-called elastocalorics, where superelastic SMA are used as solid-state heat pumps [12–15] as well as SMA based stretchable electronic with auxetic structures. [16,17] The titanium-rich, quasiplastic variant of NiTi can be plastically deformed at room temperature by applying a load. When subsequently heated above the phase transformation temperature however, the deformation of about 5% is fully recovered in conjunction with high force outputs. Both effects are based on a phase transformation of the crystal lattice structure between austenite (high temperature phase) and martensite (low temperature phase). NiTi has a high electrical resistivity which changes significantly, depending on the composition of the crystal lattice, the geometry, and the temperature. This effect, called self-sensing, is used to generate a position feedback signal of an SMA actuator by measuring its resistance during operation. SMA microwires (diameter smaller 100 μm) feature cooling times around one second and below under natural convection at air and room temperature, furthermore their unique form factor allows them to be fitted in tight spatial conditions.

Welding of NiTi and similar alloys is an extensive field of research. [18,19] It is mostly concentrated on similar and dissimilar laser welding of superelastic material for medical applications, where good results of joint strength and material properties are achieved. Laser welding is also investigated for NiTi actuator wires, down to diameters of 100 μm . [20] It is shown that joints between NiTi and stainless steel as well as copper are feasible. [21,22] Welded joints of NiTi and stainless steel have proven to show good mechanical properties. Other welding technologies like electron beam welding, friction stir welding, TIG welding, impact welding and resistance welding are also investigated. [23–25] Published work on resistance welding however, is not found in great numbers but suggests promising results for micro-dimensions. [26–29] The previous work of Scholtes et al. suggests that NiTi actuator wires with diameters between 100 μm and 25 μm can be welded to stainless steel sheet metal by spot welding, keeping 80 to 90% of the materials break load. [30]

This research article discusses dissimilar resistance spot welding of NiTi wires with 100 μm diameter from an engineering perspective. The main targets are high joint break loads, good fatigue life, as well as the development of an automatable welding and bundling process. The detailed microstructural investigation of the samples is not part of this work. Welding parameters are evaluated by pull off tests as well as peel tests. The welded samples also undergo an actuation fatigue test.

SMA wire bundles are investigated due to the need to achieve high actuation frequencies while also scaling up the force. [3,31,32] Bundling large diameter wires enables high force outputs of several kilonewton which is otherwise only possible by using SMA rods or bars [5,33]. These bundles are typically manufactured by clamping and wrapping, which usually comes with the disadvantages of many single parts, relatively large clamp sizes and inconsistent electrical connections of the single wires. Welded bundles, however, need only two substrates for the wires to be joined to. If these are sheet metal parts, the bundles are very flat and feature an ideal installation space. However, they are not restricted to that formfactor and SMA wire bundles based on a tubular or rectangular design are also possible.

The rest of the article is split into three sections followed by a conclusion with an outlook. Section two covers the setup of the welding machine and the experimental methods to evaluate the welding parameters. In section three, the results of the parameter studies are discussed and complemented by actuation and fatigue tests. Section four deals with the process of manufacturing welded SMA wire bundles and the evaluation of the same by actuation experiments.

2. Materials and Methods

Resistance spot welding is a process where electrical current and pressure are used to join two metallic alloys by melting them together at the point of contact, where a weld nugget is formed. [34] It is commonly used in the automotive industry to join metal sheets of the car body. Compared to laser welding, resistance welding is more cost efficient, and the process is easier to control.

In usual spot-welding applications two opposing electrodes clamp the workpieces, which makes accessibility from two sides necessary. As it is beneficial from manufacturing and assembly perspective to perform the joining process from only one side, this work is utilizing a gap welding machine. As displayed in Figure 1, both electrodes are aligned with a small gap in between them. The lower work piece, in this case a sheet metal, rests on a support while the upper workpiece, the NiTi wire, is held in place by the pressure of either two electrodes (series or gap welding) or one electrode, while the second electrode contacts the sheet metal (step welding). By passing a current through the workpieces, their interface is heated to melting temperature by the Joule effect. After solidification, the pressure of the electrodes is released.

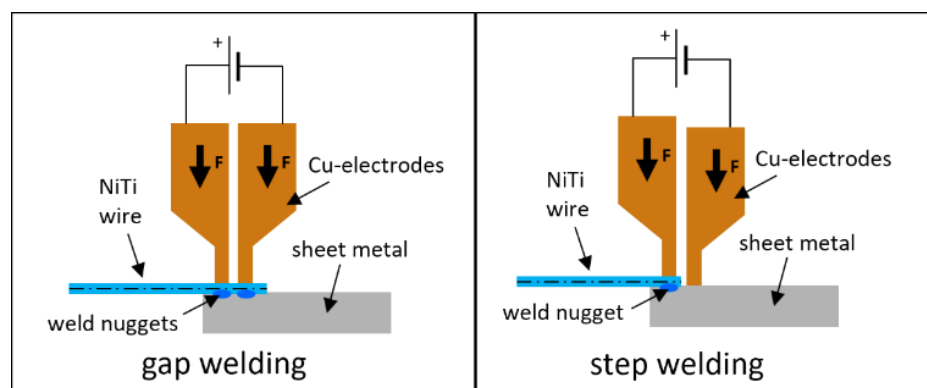


Figure 1. Schematic of resistance gap welding (left) and resistance step welding (right) of NiTi wires to a sheet metal. Displayed are the two copper-based electrodes, pressing down on the work pieces.

The generated heat H calculates by

$$H = I^2 * R * t * K, \quad (1)$$

where I is the welding current, R the overall resistance, t the welding time and K a thermal constant that depends on geometry material and welding force. The resistance is the sum of the individual resistances of the workpieces and the electrodes as well as the contact resistances between them. When studying Figure 2, it can be derived, that the highest individual resistance is required at R_4 , the contact resistance between the weld partners.

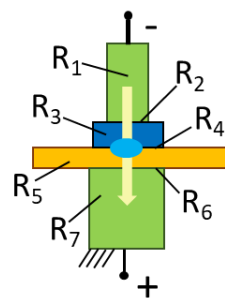


Figure 2. Schematic of the distribution of the overall resistance in a resistance welding process. R_2 , R_4 , and R_6 are contact resistances. R_1 and R_2 are the bulk resistances of the electrodes. R_3 and R_5 are the bulk resistances of the weld partners.

The welding machine used in this work is a resistance gap welding head (Unitek Thin-Line) with spring loaded electrodes and adjustable force up to 100 N. The spring loading allows the weld head to follow the collapsing of the weldment when melting. The welding transformer Mac Gregor DC 1000 supplies a current of up to 1000 A (DC) in a double pulse with adjustable durations of 1 ms to 100 ms and ramp up/down. For all experiments electrodes made of CuCr1 with a tip area of 0.64 mm² are used.

The SMA wire used for the experiments is a commercially available SAES Getters SmartFlex NiTi actuator wire with 100 µm diameter and a thin amber colored oxide layer. [35] For the sheet metal substrate to which the wire is to be welded, a sample geometry of 5 mm x 10 mm with a 3 mm hole is designed. This allows for easy installation and fixation in the welding setup, the testing setups, and in possible applications.

From application perspective copper and copper alloys are highly interesting as a welding partner for the NiTi wires, as the electrical wiring can be soldered with common methods. Furthermore, the next step, could be a direct integration of SMA actuators wires onto PCBs for micro actuators. However, difficulties with good welding results are expected, as relevant material parameters like electrical and thermal conductivity, displayed in Table 1, differ greatly between NiTi and Cu-alloys. [36] While the resistivity of copper alloys is about a tenfold smaller than that of NiTi and the thermal conductivity is the same amount larger, SS offers similar parameters compared to NiTi. Differences in those two parameters lead to an unfavorable shift in the resistance and heat distribution of the weld partners. Therefore, good weldability of NiTi to steel is expected. A feasibility study by Scholtes et al. confirms this assumption and presents promising results with SMA wire diameters down to 25 µm. [30] With special flux and solder (e.g. DIN EN 29453 (solder): S-Sn96Ag4 and DIN EN 29454.1, 3.2.2.A (F-SW11) (flux)), copper wires can also be joined to stainless steel with low process temperatures.

Table 1. MATERIAL PARAMETERS RELEVANT FOR RESISTANCE WELDING OF NITIL, STAINLESS STEEL AND COPPER ALLOYS. [37–40].

	NiTi	Steel	CuSn6	CuZn30
Resistivity (20°C) in Ω*mm ² /m	0,86	0,75	0,11	0,06
Thermal Conductivity (20°C) in W/m*K	10	15	75	121

For investigating resistance welding of NiTi to copper alloys, CuSn6 (DIN 2.1020) and CuZn30 (DIN 2.0265) are used. Alloying with zinc or tin increases the resistivity of copper and reduces the thermal conductivity. The samples have a thickness of 0.4 mm. With X6CrNiMoTi17-12-2 (DIN 1.4571) and X2CrNiMo17-12-2 (DIN 1.4404) two similar steel alloys are used in this study. They both feature particularly good weldability and corrosion resistance, while the 1.4571 is additionally alloyed with a small amount of Titanium. The main difference for the experiments lies in the sample thickness (1 mm for 1.4571, 0.3 mm for 1.4404).

The welding procedure used in this work is displayed in Figure 3 in four steps. The sheet metal sample is positioned in the workpiece holder. The NiTi wire, guided through a small funnel, is placed on top of the welding partner. The weld head with two copper electrodes is moved down, pressing on wire and sheet metal with 100 N, as is displayed in Figure 3 on picture 2. Then the welding current is run through the weld partner, while the NiTi wire is slack. On close inspection of picture 3 in Figure 3, the red-hot metal between the tips of the electrodes is recognizable. After a short cooling time, the weld head is moved upwards, as is depicted on picture 4 in Figure 3, and the NiTi wire is joined to the steel sample.

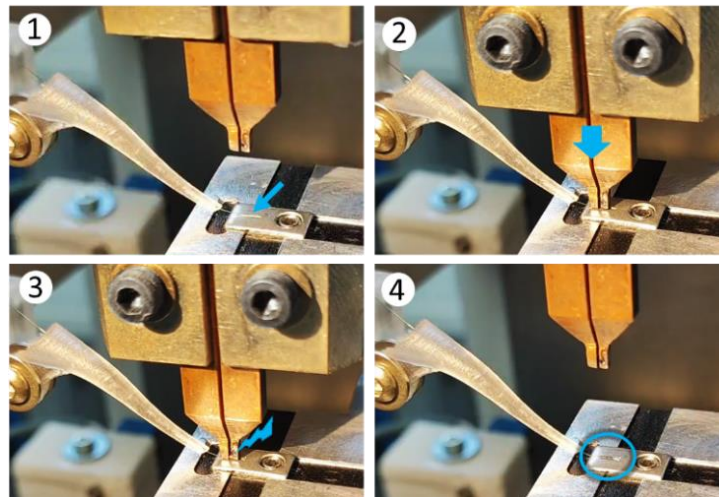


Figure 3. Step by step pictures of the resistance welding process. 1: Placement of sheet metal sample and NiTi wire under weld head 2: Weld head moved down applying pressure on SMA wire with both electrodes; 3: welding current is run through workpieces via copper electrodes; 4: Weld head is moved up and NiTi wire is joined to steel substrate.

As stated by (1), the influence of the welding current is squared, while the welding time has a linear effect on the generated heat. This work therefore focuses on the variation of the welding current because it has the greatest influence on the results. The welding time is set to a constant value of two pulses with 15 ms holding time and additional 5 ms for ramping up and down. The delay between the pulses is set to 10 ms.

For evaluating the welded samples with pull off tests, a custom designed test bench (Figure 4) is used. It is mainly made to measure the break loads and joint strength of NiTi microwires. Two different pull-off tests are applied to examine the quality of the weld. In a straight pull, the joint is loaded with a shear stress which corresponds to the load in an actuator application. For a better identification of the best process parameters, a peel test is applied, where the NiTi wire is pulled off under an angle of 45 °.

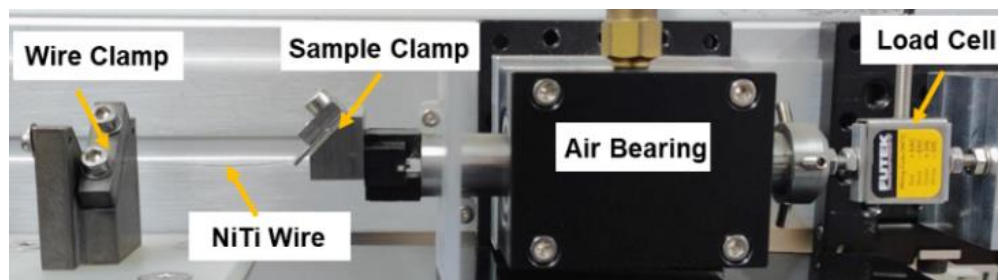


Figure 4. Picture of the test setup for pull-off and peel tests of the welded samples. The sample clamp is replaceable according to the type of experiment.

The most promising result is afterwards examined by optical as well as SEM microscopy of microsections and undergoes fatigue testing in cyclic actuator tests. The test setup for fatigue testing is presented by Mayer et al. [41] and can also be used for basic spring biased SMA actuator characterization. The SMA wire bundles, which are manufactured with the elaborated welding parameters, are built by using an X-Y-stage and a stress-controlled installation of the NiTi wires. The actuator characteristics of the high performance SMA bundles are examined on the same test rig. Therefore, a comparison of force and dynamics with equal length SMA actuators are made. A bundle of four parallel 100 μm NiTi wires is compared to a 200 μm diameter. The actuators have the same accumulated cross-sectional area and thus deliver the same force output at equal material stress.

3. Results & Discussion

3.1. Parameter Study: Evaluation and Discussion

First feasibility tests of resistance welding NiTi wires in various micro diameters to stainless steel quickly lead to good results. [30] The thermo-mechanical characteristics in a stress-strain diagrams, show no measurable difference between welded samples and clamped or crimped samples. It is expected that the welding heat affects the properties of the NiTi in the welding area and leads to brittleness and a loss of shape memory effect in the heat affected zone. The brittleness is to expect due to the intermetallic compounds that are formed. [29] However, as displayed in Figure 5 on the left, the thermal mass of any wire mounting element in comparison to a microwire is so large, that the SMA does not undergo phase transformation in proximity to the fastener. [5] Due to this uneven heat distribution, welding does not alter the functionality of SMA actuator wires. As illustrated in Figure 5, the heat-affected zone is smaller than the non-activated length at the edges of an SMA microwire.

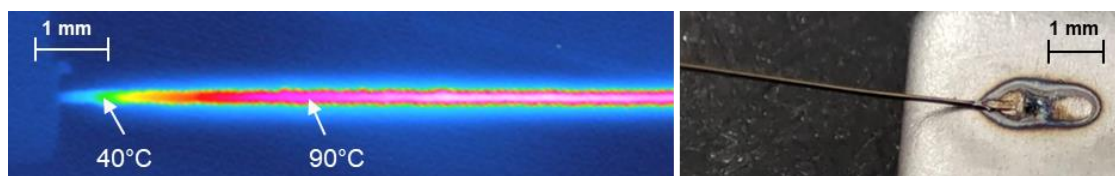


Figure 5. Left: Thermography of a crimped 76 μm NiTi wire, where influence of the heat sink on the temperature distribution in an activated SMA wire is visible. Right: The heat affected zone of a resistance welded 100 μm NiTi to stainless steel is recognized by the tempering colors.

Welding experiments with the introduced copper alloys are more challenging, and satisfying results are not as easily achieved compared to steel joints. Due to the low resistivity of CuSn6 and CuZn30, the contact resistance between the welding partner and NiTi is similar to the contact resistance to the copper electrodes. This results in unsuccessful welds, where the NiTi wire sticks to the electrodes of the weld head instead of the copper-alloy sample. The CuZn30 additionally tends to create an electric arc in the welding process as the zinc evaporates, resulting in unusable welds. The most promising results are achieved with gap welding where the electrodes only contact the NiTi wire, and welding currents of 400 A. The welded joint strength is significantly weaker than the joints to steel with 300 A, which is display in Figure 6. The straight pull-off tests are conducted with five samples for each test. Because of the reasons discussed previously, more than five welding attempts with the copper alloys are necessary to get five usable samples.

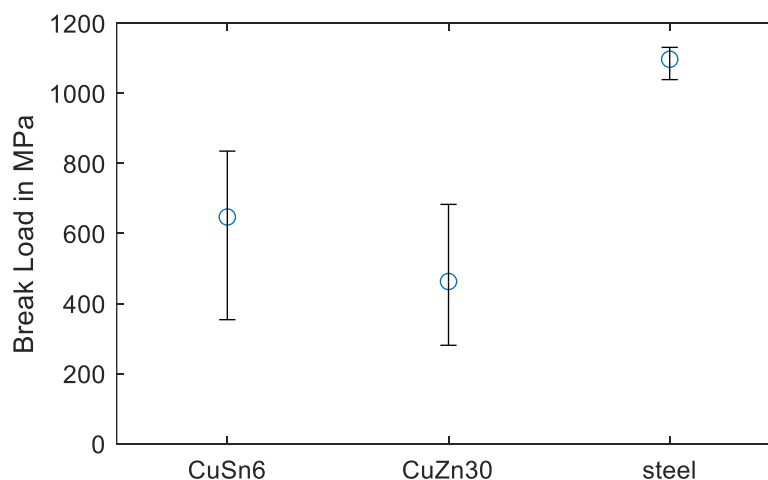


Figure 6. Comparison of the joint break loads of a 100 μm NiTi wire welded to CuSn6, CuZn30 and stainless steel. The results for average value and the spread of the straight pull of tests are displayed.

The rupture of the NiTi wire usually happens in the heat affected zone, which is to be expected. The NiTi weld bead stays joined to the sheet metal. However, welded samples with the copper alloys that result in weak joint strengths mostly feature a full separation of NiTi wire and sheet metal. The welding results with stainless steel are repeatable, consistent and show high pull-off strength levels. The spread in the samples of both, already pre-selected, copper alloys is four to five times higher than that of steel with about half the average break load. Due to these factors, the investigation is continued with stainless steel samples only.

The joint break loads in straight pull-off tests of samples with varied welding currents with NiTi and 1.4571 exhibit values from 1000 MPa to 1200 MPa and differences are hardly recognized. Therefore, the parameters for the optimal welding current are evaluated by peel tests, which is a common testing method for resistance welded sheet metals for car body parts in the automotive industry. The test series starts with a current of 150 A and is increased in 100 A steps up to a welding current of 550 A.

With each current five samples are manufactured by step welding. The mean values and spreads of peel test results are displayed in *Figure 7*. As a sweet spot around 250 A and 350 A is recognizable, a further test series with 300 A welding current is added. Standard deviation is not displayed. Because of the relatively small number of samples, the spread is more meaningful. The data shows a noticeable trend, where the average joint break load of 300 A welding current is at a maximum with 417 MPa under peel load. Increasing and decreasing the welding current level leads to a drop in average break load. It can also be determined that the spread of the peel break loads increases with increasing welding current. From the results of the straight pull-off tests, as well as the peel tests it can be derived, that resistance step welding of NiTi wires in micro diameters to stainless steel sheets is a robust and well to control process. This is promising for the application of an automated process for the manufacturing of SMA wire bundles and the direct wire integration by resistance welding in SMA driven systems.

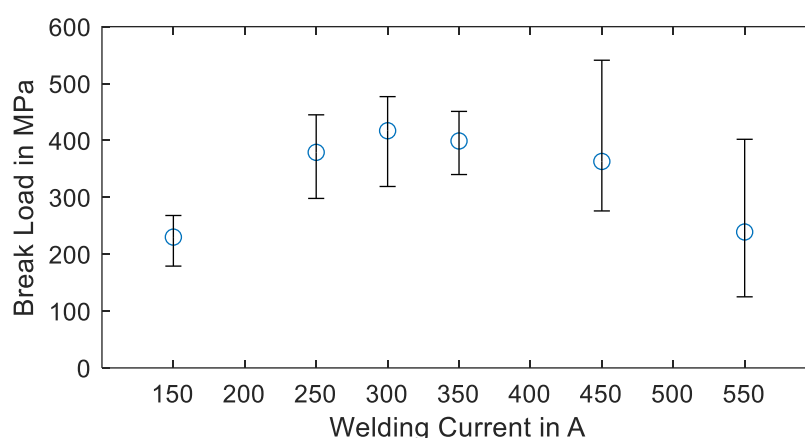


Figure 7. Average values and spread for the joint break loads achieved by peel tests with 100 μ m NiTi wire resistance step welded to 1.4571 steel sheet metal.

As other parameters are known to influence the weld quality as well, following additional tests are performed with 300 A current:

- Gap welding
- Welding with negative electrode, step welding
- Pressure force reduced to 35N, step welding
- 1.4404 with 0,3 mm thickness, step welding
- Thicker oxide layer on NiTi wire, step welding

The data of these added tests is displayed in *Figure 8*, with the 300 A step welding result as a reference value. It is recognizable that changing the welding method to gap welding and a different steel alloy with smaller thickness, do not measurably influence the joint break load under peel stress. Reducing the force of the electrodes from 100 N to 35 N results in slightly lower strength.

The Peltier effect is known to influence the formation of the weld bead in resistance welding of small dimensions. [41,42] The heat transfer in the thermoelectric effect occurs with the direction of the current, which is why the negative electrode should be placed on the smaller or thinner weld partner. A positive result on the weld strength by changing the electrodes polarity is seen in this study as well. Placing the negative electrode on the NiTi microwire increases the joint break load of peel tests slightly, as can be read from the data displayed in Figure 8. During the manufacturing of NiTi wires an oxide layer, mostly consisting of Titanium-oxide, is formed. Commercially available NiTi actuator wires come with oxide layers of different thicknesses. In general, it can be determined that a darker wire surface corresponds to a thicker oxide layer.

As the oxide layer is expected to influence the contact resistance in a negative way, the tests in this study are performed with a wire having a thin oxide layer. To compare both versions, in Figure 8 the peel tests results of a 100 μm wire with a thick dark oxide layer are displayed. The joint break load is significantly decreased. This indicates that the oxide layer must be reduced or removed for proper resistance welding strength. The experimental parameter identification for a dissimilar resistance welding process results in a robust parameter set. With 300 A a 100 μm NiTi wire with thin (amber colored) oxide layer can be welded SS substrates with high joint strength and good repeatability. The exact steel alloy and thickness, as well as the electrode configuration have only minor influences on the results. Common actuator applications work with up to 200 MPa of material stress, which corresponds to a safety factor of over five when the wire is not loaded under an angle.

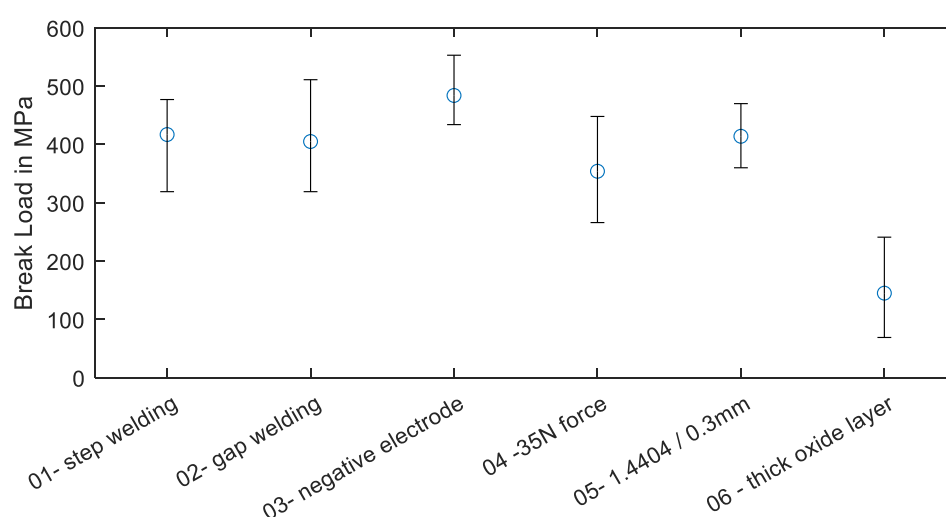


Figure 8. Average values and spreads of joint break loads of peel tests with various parameters and 300 A of welding current.

For further investigations, microsections of the weld bead are prepared and microscopically examined. The sample is embedded in resin and cut down to where the weld bead begins. After that, the sample is basically sliced, and microsection are prepared approximately every 100 μm . The sections of the weld bead are etched and examined with optical microscopy and the fusion zone is investigated by SEM and EDS, of which the results are displayed in Figure 9. The radial cuts through the NiTi wire on the left side in Figure 9 show the deformation of the NiTi under the influence of welding heat and pressure. The wire is flattened out and is pushed into the steel, which also softens due to the welding heat. Resistance welding can join two materials by a solid-state bond as well as a fusion bond. The first is known to show little strength under peel loads and can be identified by a clear separating line in microscopical images. Additional to the high peel strength, pictures 4 to 6 in Fig 9 suggest that a fusion bond is evident. Based on the SEM (see Figure 9 on the right) and the added EDS of a microsection of a sample with the same welding parameters, the fusion bond can be verified. A transition zone between NiTi and 1.4571 steel is visible. The data of a line EDS through this zone, displayed in Figure 9 on the lower right, shows a gradual distribution of the main alloying

elements of the two joining partners. This suggests a melting of steel and NiTi in the welding area resulting in a strong fusion bond.

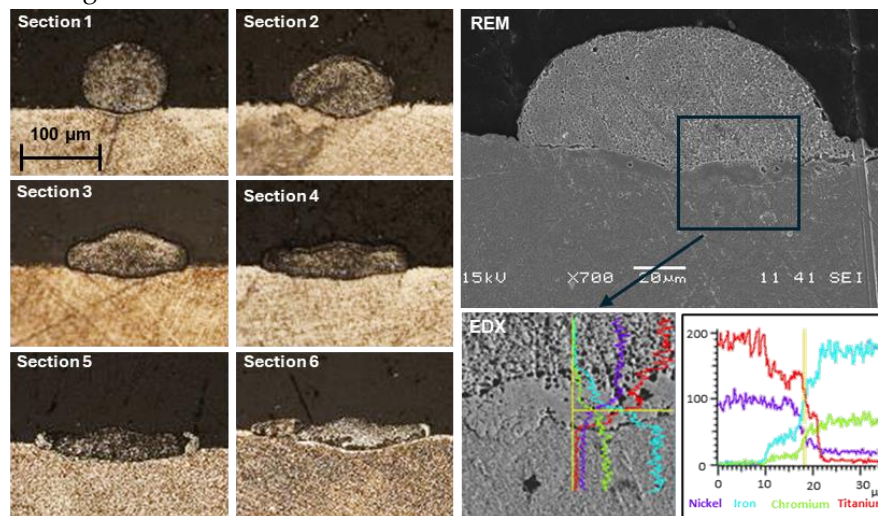


Figure 9. Microscopic analysis of resistance welded NiTi to stainless steel. “Section 1” to “Section 6” show microscopic pictures of samples cut radial to the wire with distances of 100µm in between. On the right a SEM picture of a different sample is displayed with the results of an EDS below.

For fatigue tests with the elaborated parameters, three samples with a 70 mm SMA wire welded on both ends to 1.4404 sheet metal are manufactured. The NiTi wire is welded on one side via step welding with the positive electrode and the opposite side is joined to the steel by step welding with the negative electrode towards the load. This is because of the design of the setup of the welding machine and the workpiece holder on an X-Y-stage, which is also explained in the following section. Each sample is installed on a lifetime test bench for fatigue testing detailed by Mayer et al [43]. The layout of the setup is horizontal and consists of three identical measurement stages aligned beside each other. The SMA actuators are biased with a tension spring. For each activation cycle, the maximum and minimum values for stroke as well as force are recorded. The samples are preloaded with 300 MPa (2.35 N) and heated with an electrical current of 300 mA until 3% of stroke are reached, which leads to increase in stress due to the spring characteristic to 400 MPa (3.14 N). After the specified stroke is reached, the samples cool for 3 s. The activation is repeated until failure of the sample. The results of the fatigue tests are illustrated in Figure 10 where the evolution of the stroke over the cycles is displayed. This behavior is typical for high stress actuation of SMA wires. The failure of all three samples was due to breaking of the wire in 30% to 50% of the wire length from the weld spot. Sample Nr.1 failed after 26208 cycles, sample Nr.2 after 26362 cycles and sample Nr.3 after 33407 cycles.

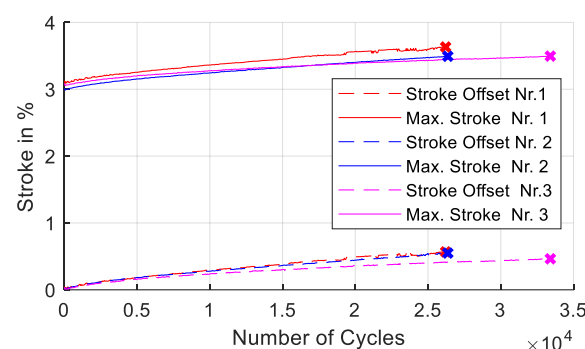


Figure 10. Fatigue test of three samples of 100 µm NiTi wire welded to steel sheet metal. Displayed is maximum and minimum stroke of each cycle until failure.

The slight differences in stroke are due to differences in friction in the test setups as well as deviations in spring stiffness and pretension of up to 5%.

The results indicate that resistance welding does not affect the fatigue strength of NiTi actuator wires in a negative way. With the joint strength under straight pull of 80% to 90% of the NiTi break load and fatigue strength in the same region as unwelded SMA wires, the welding process is a promising joining technology for actuator applications. Because of the material-to-material bond, the electrical connection is superior to clamping or crimping, which can lead to enhancement of the resistance signal quality for self-sensing applications.

3.2. Welded SMA Bundle Actuators

To scale the force of an SMA actuator wire, the straightforward way is to increase the wire diameter. However, this measure reduces the dynamics of the actuator drastically because the cooling time increases. The cyclic dynamics of actuators is crucial for many applications. Therefore, installing several thin NiTi wires mechanically in parallel is beneficial. To allow air convection between the single wires, a determined distance between the wires needs to be set.

In this work, flat wire bundles, as displayed in Figure 11, are designed and manufactured. They feature installation space for up to seven microwires on a width of 5 mm. This results in a force output of 11 N at 200 MPa combined with short cooling times. The manufacturing process is based on an X Y stage with two workpiece carriers for the sheet metal substrates. The stage is positioned under the resistance weld head. The adjustable distance between both carriers defines the length of the actuator bundle. The NiTi wire is guided from the reel through a funnel (see Figure 3) and positioned on a specified spot on the steel substrate. After the SMA wire is welded to the first sheet metal, the workpiece holders move sideways and pull wire through the funnel from the reel until the second sheet metal is positioned under the weld head. The wire length is set with a defined prestress, which is then released for the welding process. After the wire is attached on both ends, it is cut, and the next NiTi wire is placed in a defined distance from the first one. The procedure is repeated until the desired number of parallel wires is attached.

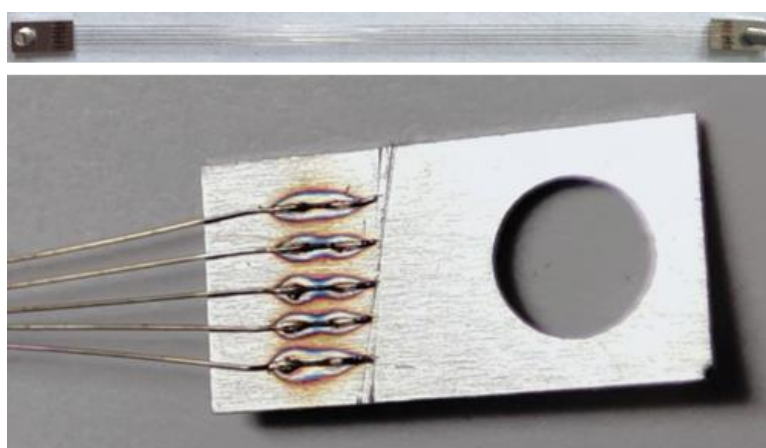


Figure 11. Pictures of a welded SMA wire bundle consisting of five 100 μm wires welded to stainless steel substrates. Upper picture shows a whole bundle with 105 mm wire length. Bottom picture shows a detailed view of the weld spots.

For evaluating the performance of the bundle, actuator tests to compare a bundle to a single wire with larger diameter are run. A 200 μm diameter wire features the same accumulated cross-sectional area as four 100 μm wires. Therefore, they feature similar force output at the same material stress level. The experiment is run on the same setup as the fatigue tests. Both actuator samples have a length of 70 mm and are biased with the same spring. The samples are prestressed to 4.15 N (130 MPa) and activated via Joule heating with a constant current pulse of 800 mA for a duration of 2 s. The activation is repeated three times with a cooling time of 8 s in between. The experimental data is displayed in Figure 12. Both samples reach a stroke of 4% and a force of 10.8 N (340 MPa). The crucial

part of the data is the time response of both samples. While the single wire heats faster than the bundle, it takes distinctively longer to cool. This is due to the difference in ratio of surface to cross-sectional area. The bundle dissipates heat faster via natural convection than the 200 μm wire.

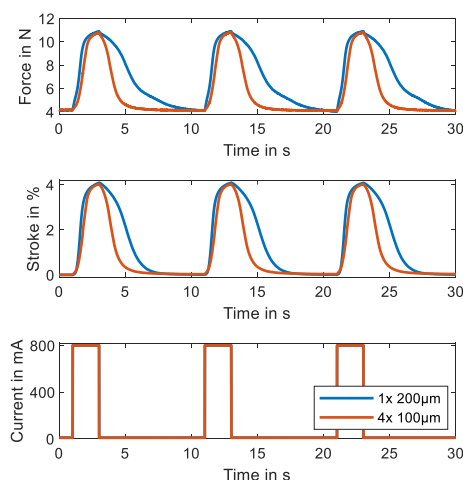


Figure 12. Comparison between bundle of four 100 μm and a single 200 μm diameter wire. Displayed are force, stroke and current over time of three consecutive actuation tests.

The single wire resets by 1% after 1.5 s, the bundle resets by 3.3%. The bundle reaches 95% reset of stroke after 2.3 s, while the 200 μm wire takes 3.7 s. Also, it takes 7 s for the single wire to reach the initial force value, while the bundle takes only about 50% of that time. It can be assumed, that the dynamics do not change when adding more wires to the bundle to increasing the force output further.

Compared to the manufacturers data of a 100 μm SMA wire, the cooling time measured in this experiment is slightly higher. [44] This can be explained by the proximity of the heated wires in the bundle that reduce the heat transfer to the ambient air as also discussed by Britz et al. [5]

The SMA actuator bundles presented in this work are already used in a variety of different research projects. Scholtes et al. designed different industrial grippers driven by the presented bundles. [45–47] The latest version of a gripper driven by SMA bundles with six wires in parallel is awarded “Hardware Winner” on the “CASmart 4th Design Challenge” at SMST conference 2021. [48] Furthermore, Simone et al. used the developed actuator bundles for their design of a bioinspired gripping system and Pirritano et al. utilized them to drive a small rotary motor. [49,50]

4. Conclusions

Resistance welding represents a valid joining technology for NiTi microwires. The presented work demonstrates the feasibility to join the SMA wires to stainless steel as well as copper alloys, without negatively influencing the material properties. Especially the welding results to steel are very promising. The verified fusion bond leads to high pull-off strength as well as high fatigue strength. Peel tests prove to be a useful tool for the parameter identification of resistance welding processes for NiTi wire. The welding process itself is robust, as the parameter identification can prove. Due to this robustness, the process can be easily automated. With the help of resistance welding, automated and reliable bundling processes are possible in the future. Compared to laser welding, the resistance welding technology is cheaper, easier to control and the positioning of the wire on the weld partner is simplified. The designed bundles are compact and flat, while showing high performance compared to single wires. The performance of the bundles is already successfully used in a variety of technology demonstrators and prototypes.

The joining of NiTi wires to copper alloys is an open question for future work. Although a welded joint between the two materials can be established, further research to improve the joint strength is needed. Another field that needs to be examined is the design parameters of NiTi wire

bundles. The understanding of the influence of wire distance, wire number and geometrical arrangement on the cooling time is important for a further development of the technology.

Author Contributions: Conceptualization, D.S.; methodology, D.S. and R.-K.Z.; software, D.S.; validation, D.S.; formal analysis, D.S.; investigation, D.S.; resources, D.S.; data curation, D.S.; writing—original draft preparation, D.S.; writing—review and editing, P.M.; visualization, D.S.; supervision, P.M. and B.F. and S.S.; project administration, P.M.; funding acquisition, P.M. and R.-K.Z. All authors have read and agreed to the published version of the manuscript.”.

Funding: This work was funded by the European Regional Development Fund (ERDF) and Saarland Government in the project *ProForm*.

Conflicts of Interest: The authors declare no conflicts of interest.

References

1. H. Janocha, T. Bonertz, and G. Pappert, *Unkonventionelle Aktoren : eine Einführung*. München: Oldenbourg Wissenschaftsverlag, 2013.
2. J. Prechtl, S. Seelecke, P. Motzki, and G. Rizzello, “Self-Sensing control of antagonistic sma actuators based on resistance-Displacement hysteresis compensation,” in *ASME 2020 Conference on Smart Materials, Adaptive Structures and Intelligent Systems, SMASIS 2020*, Virtual, Online: ASME, Sep. 2020. doi: 10.1115/SMASIS2020-2224.
3. S.-M. Kirsch *et al.*, “SMA Antagonistic-Micro-Wire Bundle: First Measurement Results,” in *ASME 2020 Conference on Smart Materials, Adaptive Structures and Intelligent Systems*, Virtual, Online: ASME, Sep. 2020. doi: 10.1115/SMASIS2020-2261.
4. E. Williams and M. H. Elahinia, “An Automotive SMA Mirror Actuator: Modeling, Design, and Experimental Evaluation,” *J. Intell. Mater. Syst. Struct.*, vol. 19, no. 12, pp. 1425–1434, Dec. 2008, doi: 10.1177/1045389X07087328.
5. R. Britz and P. Motzki, “Analysis and evaluation of bundled SMA actuator wires,” *Sensors Actuators A Phys.*, vol. 333, no. 1-2 SPEC. ISS, p. 113233, Jan. 2022, doi: 10.1016/j.sna.2021.113233.
6. F. Simone, G. Rizzello, S. Seelecke, and P. Motzki, “A Soft Five-Fingered Hand Actuated by Shape Memory Alloy Wires: Design, Manufacturing, and Evaluation,” *Front. Robot. AI*, vol. 7, p. 197, Dec. 2020, doi: 10.3389/frobt.2020.608841.
7. W. J. Buehler, J. V. Gilfrich, and R. C. Wiley, “Effect of Low-Temperature Phase Changes on the Mechanical Properties of Alloys near Composition TiNi,” *J. Appl. Phys.*, vol. 34, no. 5, pp. 1475–1477, May 1963, doi: 10.1063/1.1729603.
8. W. J. Buehler and F. E. Wang, “A summary of recent research on the nitinol alloys and their potential application in ocean engineering,” *Ocean Eng.*, vol. 1, no. 1, pp. 105–120, Jul. 1968, doi: 10.1016/0029-8018(68)90019-x.
9. T. Duerig, A. Pelton, and D. Stöckel, “An overview of nitinol medical applications,” *Mater. Sci. Eng. A*, vol. 273–275, pp. 149–160, Dec. 1999, doi: 10.1016/s0921-5093(99)00294-4.
10. P. H. Adler, W. Yu, A. R. Pelton, R. Zadno, T. W. Duerig, and R. Barresi, “On the tensile and torsional properties of pseudoelastic NiTi,” *Scr. Metall. Mater.*, vol. 24, no. 5, pp. 943–947, May 1990, doi: 10.1016/0956-716X(90)90142-4.
11. D. C. Lagoudas, *Shape Memory Alloys*, vol. 1. Boston, MA: Springer US, 2008. doi: 10.1007/978-0-387-47685-8.
12. S. Wang, Y. Shi, Y. Li, H. Lin, K. Fan, and X. Teng, “Solid-state refrigeration of shape memory alloy-based elastocaloric materials: A review focusing on preparation methods, properties and development,” *Renew. Sustain. Energy Rev.*, vol. 187, p. 113762, Nov. 2023, doi: 10.1016/j.rser.2023.113762.

13. H. Hou *et al.*, "Fatigue-resistant high-performance elastocaloric materials made by additive manufacturing," *Science* (80-.), vol. 366, no. 6469, pp. 1116–1121, Nov. 2019, doi: 10.1126/science.aax7616.
14. M. Schmidt, A. Schütze, and S. Seelecke, "Scientific test setup for investigation of shape memory alloy based elastocaloric cooling processes," *Int. J. Refrig.*, vol. 54, pp. 88–97, Jun. 2015, doi: 10.1016/j.ijrefrig.2015.03.001.
15. F. Bruederlin, H. Ossmer, F. Wendler, S. Miyazaki, and M. Kohl, "SMA foil-based elastocaloric cooling: from material behavior to device engineering," *J. Phys. D. Appl. Phys.*, vol. 50, no. 42, p. 424003, Oct. 2017, doi: 10.1088/1361-6463/aa87a2.
16. S. M. Curtis *et al.*, "Thin-Film Superelastic Alloys for Stretchable Electronics," *Shape Mem. Superelasticity*, vol. 9, no. 1, pp. 35–49, Mar. 2023, doi: 10.1007/s40830-023-00422-4.
17. D. Dengiz, H. Goldbeck, S. M. Curtis, L. Bumke, J. Jetter, and E. Quandt, "Shape Memory Alloy Thin Film Auxetic Structures," *Adv. Mater. Technol.*, vol. 8, no. 12, Jun. 2023, doi: 10.1002/admt.202201991.
18. J. P. Oliveira, R. M. Miranda, and F. M. Braz Fernandes, "Welding and Joining of NiTi Shape Memory Alloys: A Review," *Prog. Mater. Sci.*, vol. 88, pp. 412–466, 2017, doi: 10.1016/j.pmatsci.2017.04.008.
19. T. Deepan Bharathi Kannan, T. Ramesh, and P. Sathya, "A Review of Similar and Dissimilar Micro-joining of Nitinol," *JOM*, vol. 68, no. 4, pp. 1227–1245, Apr. 2016, doi: 10.1007/s11837-016-1836-y.
20. H. Gugel, A. Schuermann, and W. Theisen, "Laser welding of NiTi wires," *Mater. Sci. Eng. A*, vol. 481–482, no. 1-2 C, pp. 668–671, May 2008, doi: 10.1016/j.msea.2006.11.179.
21. H. Gugel and W. Theisen, "Laserstrahlschweißen von Mikrodrähten aus Nickel-Titan-Formgedächtnislegierungen und austenitischem Stahl," *Materwiss. Werksttech.*, vol. 38, no. 6, pp. 489–493, Jun. 2007, doi: 10.1002/mawe.200700160.
22. Z. Zeng, B. Panton, J. P. Oliveira, A. Han, and Y. N. Zhou, "Dissimilar laser welding of NiTi shape memory alloy and copper," *Smart Mater. Struct.*, vol. 24, no. 12, Dec. 2015, doi: 10.1088/0964-1726/24/12/125036.
23. L. F. A. Rodrigues, F. A. Amorim, E. N. D. Grassi, P. L. L. dos Santos, and C. J. de Araújo, "TIG spot welding applied to NiTi shape memory wires optimized by factorial design," *Int. J. Adv. Manuf. Technol.*, vol. 121, no. 11–12, pp. 7749–7762, Aug. 2022, doi: 10.1007/s00170-022-09848-z.
24. J. Li, B. Panton, Y. Mao, A. Vivek, and G. Daehn, "High strength impact welding of NiTi and stainless steel wires," *Smart Mater. Struct.*, vol. 29, no. 10, p. 105023, Oct. 2020, doi: 10.1088/1361-665X/aba847.
25. A. Barcellona, L. Fratini, D. Palmeri, C. Maletta, and M. Brandizzi, "Friction stir processing of Niti shape memory alloy: microstructural characterization," *Int. J. Mater. Form.*, vol. 3, no. S1, pp. 1047–1050, Apr. 2010, doi: 10.1007/s12289-010-0950-6.
26. B. Tam, A. Pequegnat, M. I. Khan, and Y. Zhou, "Resistance Microwelding of Ti-55.8 wt pct Ni Nitinol Wires and the Effects of Pseudoelasticity," *Metall. Mater. Trans. A*, vol. 43, no. 8, pp. 2969–2978, Aug. 2012, doi: 10.1007/s11661-012-1115-7.
27. A. Shamsolhodaei *et al.*, "Resistance spot welding of NiTi shape memory alloy sheets: Microstructural evolution and mechanical properties," *J. Manuf. Process.*, vol. 81, pp. 467–475, Sep. 2022, doi: 10.1016/j.jmapro.2022.07.006.
28. V. Delobelle, P. Delobelle, Y. Liu, D. Favier, and H. Louche, "Resistance welding of NiTi shape memory alloy tubes," *J. Mater. Process. Technol.*, vol. 213, no. 7, pp. 1139–1145, Jul. 2013, doi: 10.1016/j.jmatprotec.2013.01.013.
29. K. Zhang *et al.*, "Revealing microstructural evolution and mechanical properties of resistance spot welded NiTi-stainless steel with Ni or Nb interlayer," *J. Mater. Sci. Technol.*, vol. 180, pp. 160–173, May 2024, doi: 10.1016/j.jmst.2023.05.057.

30. D. Scholtes, R.-K. Zäh, M. Schmidt, P. Motzki, B. Faupel, and S. Seelecke, "Resistance Welding of NiTi Actuator Wires," in *ACTUATOR 2018: 16th International Conference on New Actuators*, Bremen: VDE, 2018, pp. 500–504.
31. M. J. Mosley and C. Mavroidis, "Design and Control of a Shape Memory Alloy Wire Bundle Actuator," in *Volume 7B: 26th Biennial Mechanisms and Robotics Conference*, American Society of Mechanical Engineers, Sep. 2000, pp. 973–979. doi: 10.1115/DETC2000/MECH-14157.
32. R. Kratz, M. Stelzer, and O. Von Stryk, "Macroscopic SMA Wire Bundle Actuator/Sensor System: Design, Measurement, Control Approach," in *IFAC Proceedings Volumes*, IFAC, 2006, pp. 1054–1058. doi: 10.3182/20060912-3-DE-2911.00181.
33. R. Britz *et al.*, "SMA Wire Bundles - Mechanical and Electrical Concepts," in *ACTUATOR 2018: 16th International Conference on New Actuators*, Bremen: VDE, 2018.
34. M. Pfeifer, "Manufacturing Process Considerations," in *Materials Enabled Designs*, Elsevier, 2009, pp. 115–160. doi: 10.1016/b978-0-7506-8287-9.00005-7.
35. SAES Group, "SmartFlex Springs and Wires." [https://www.saesgetters.com/sites/default/files/SMARTFLEX SPRINGS AND WIRES.pdf](https://www.saesgetters.com/sites/default/files/SMARTFLEX%20SPRINGS%20AND%20WIRES.pdf) (accessed Jul. 06, 2018).
36. Amada Miyachi America, "Fundamentals of Small Parts Resistance Welding." [https://www.amadaweldtech.eu/sites/default/files/images/knowledgebase/AMYA Fundamentals Resistance Welding 03-16.pdf](https://www.amadaweldtech.eu/sites/default/files/images/knowledgebase/AMYA_Fundamentals%20Resistance%20Welding%2003-16.pdf) (accessed Mar. 08, 2024).
37. Deutsches Kupferinstitut, "CuSn6." <https://kupfer.de/wp-content/uploads/2019/11/CuSn6-1.pdf> (accessed Mar. 08, 2024).
38. Deutsches Kupferinstitut, "CuZn30." <https://kupfer.de/wp-content/uploads/2019/11/CuZn30-1.pdf> (accessed Mar. 08, 2024).
39. A. Jury, X. Balandraud, and L. Heller, "Thermal Conductivity and Specific Heat Capacity of Austenite and Stress-Induced Martensite in Superelastic NiTi at Ambient Temperature," *Int. J. Thermophys.*, vol. 44, no. 11, p. 162, Nov. 2023, doi: 10.1007/s10765-023-03279-y.
40. D. Scholtes, S. Seelecke, and P. Motzki, "Electro-thermo-mechanical characterization of shape memory alloy wires for actuator and sensor applications—Part 1: The effects of training," *Eng. Reports*, p. e12867, Feb. 2024, doi: 10.1002/ENG2.12867.
41. W. Eagar, T. "Resistance Welding: A Fast, Inexpensive and Deceptively Simple Process," in *3rd International Conference on Trends in Welding Research*, S. A. David and J. M. Vitek, Eds., Gatlinburg: ASM International, 1992, pp. 347–351. doi: n.a.
42. L. Deng, Y. B. Li, W. Cai, A. S. Haselhuhn, and B. E. Carlson, "Simulating Thermoelectric Effect and Its Impact on Asymmetric Weld Nugget Growth in Aluminum Resistance Spot Welding," *J. Manuf. Sci. Eng. Trans. ASME*, vol. 142, no. 9, Sep. 2020, doi: 10.1115/1.4047243.
43. J. Mayer, P. Molitor, Y. Goergen, and P. Motzki, "Design of a Modular Lifespan Test Bench for Shape Memory Alloy Wires," in *ASME 2022 Conference on Smart Materials, Adaptive Structures and Intelligent Systems*, Dearborn: ASME, Sep. 2022. doi: 10.1115/SMASIS2022-90483.
44. Saes Getters, "SmartFlex® Wire." www.saesgroup.com (accessed Apr. 17, 2024).
45. D. Scholtes, S. Seelecke, G. Rizzello, and P. Motzki, "Design of A compliant industrial gripper driven by A bistable shape memory alloy actuator," in *ASME 2020 Conference on Smart Materials, Adaptive Structures and Intelligent Systems, SMASIS 2020*, Virtual, Online: ASME, Nov. 2020. doi: 10.1115/SMASIS2020-2204.

46. D. Scholtes, S. Seelecke, and P. Motzki, "Development of a Bistable SMA Actuated Industrial Gripper Based on a Compliant Design," in *ACTUATOR; International Conference and Exhibition on New Actuator Systems and Applications* 2021, Virtual, Online: VDE, 2021, pp. 181–184. [Online]. Available: <https://ieeexplore.ieee.org/stamp/stamp.jsp?tp=&arnumber=9400576>
47. D. Scholtes, S. S. Seelecke, and P. Motzki, "Design of a lightweight SMA driven parallel gripper for collaborative robots," in <https://doi.org/10.1117/12.2658402>, Long Beach: SPIE, Apr. 2023, p. 34. doi: 10.1117/12.2658402.
48. "CASmart 4th Design Challenge." <https://www.casmart.org/home/student-design-challenges/casmart-4th-design-challenge> (accessed Apr. 17, 2024).
49. F. Simone, G. Rizzello, S. Seelecke, and P. Motzki, "A Soft Five-Fingered Hand Actuated by Shape Memory Alloy Wires: Design, Manufacturing, and Evaluation," *Front. Robot. AI*, vol. 7, no. December, 2020, doi: 10.3389/frobt.2020.608841.
50. C. Pirritano *et al.*, "Fully Integrated Rotary Motor Based on Antagonistic Shape Memory Alloy Wire Bundles," in *Proceedings of ASME 2023 Conference on Smart Materials, Adaptive Structures and Intelligent Systems, SMASIS 2023*, Austin: ASME, Nov. 2023. doi: 10.1115/SMASIS2023-111255.

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.