

Article

Not peer-reviewed version

Comparative Study on the Microwave-Assisted and Conventional Dyeing of Polyamide Fabric with Acid Dyes

[Raşit Dağlı](#)*, [Murat Teker](#), [Ayşe Usluoğlu](#)

Posted Date: 27 January 2026

doi: 10.20944/preprints202511.0485.v2

Keywords: polyamide; microwave dyeing; acid dyes; conventional dyeing



Preprints.org is a free multidisciplinary platform providing preprint service that is dedicated to making early versions of research outputs permanently available and citable. Preprints posted at Preprints.org appear in Web of Science, Crossref, Google Scholar, Scilit, Europe PMC.

Copyright: This open access article is published under a [Creative Commons CC BY 4.0 license](#), which permit the free download, distribution, and reuse, provided that the author and preprint are cited in any reuse.

Article

Comparative Study on the Microwave-Assisted and Conventional Dyeing of Polyamide Fabric with Acid Dyes

Raşit Dağlı^{1,*}, Murat Teker¹ and Ayşe Usluoğlu²

¹ Department of Chemistry, Faculty of Science, Sakarya University, Sakarya, Turkey

² SAKTAŞ, Sakarya Teknokent, Sakarya University, Sakarya, Turkey

* Correspondence: rasit.dagli@ogr.sakarya.edu.tr

Abstract

This study compares the acid dyeing of Polyamide 6 (PA6) fabric using conventional heating and microwave-assisted techniques and examines reaction parameters (temperature, time, pH, dye concentration) on conventional and microwave system. C.I. Acid Blue 324 was used to explore the effects of critical process parameters, including pH, temperature, dyeing time, and dye concentration, on color strength (K/S). Conventional and Microwave Dyeing showed an inverse correlation between pH and K/S, with optimal color yield achieved at pH 3.0. Dye uptake was enhanced by increasing temperature, with maximum K/S obtained at 95 °C for 30 minutes and the highest dye concentration (1.50%). In contrast, the microwave-assisted dyeing methodology (160 W) drastically accelerated the process. Optimal conditions for microwave dyeing also favored an acidic media (pH 3.0) and showed a strong positive correlation between microwave exposure time and K/S. The microwave-assisted technique is confirmed as a rapid, energy-efficient, green process and effective alternative for dyeing PA6, offering significant potential for reduced processing time.

Keywords: polyamide; microwave dyeing; acid dyes; conventional dyeing

1. Introduction

Nylon is one of the most important synthetic fibers in the textile industry, which is usually dyed with acid and metal complex dyes. Nylon is well known for its durability, lightweightness, greater tensile strength, and damage resistance properties. Nylon has advantages over cotton fiber in achieving high color strength. Polyamide fibers, particularly nylon 6 and nylon 6.6, represent a cornerstone of the contemporary textile industry. Their widespread application, ranging from high-performance apparel to advanced technical textiles, stems from their exceptional physiochemical properties, including superior tensile strength, elasticity, and remarkable abrasion resistance. The coloration of these versatile materials is predominantly achieved through the use of acid dyes, which form robust ionic interactions with the protonated amino groups inherent in the polyamide fiber structure. This interaction ensures excellent dye affinity, colorfastness, and the production of vibrant, durable shades.[1–11]

Acid dyes represent the most commonly used class of dyes for polyamide fiber dyeing due to their excellent affinity and color fastness properties. The dyeing mechanism involves ionic interactions between the sulfonic acid groups of the dye molecules and the amino groups present in the polyamide fiber structure. The dyeing process is typically conducted under acidic conditions (pH 4–6) to protonate the amino groups in the fiber, thereby enhancing the electrostatic attraction between the dye and fiber [12–16].

Microwave treatment is one environmental friendly less time consuming condition and the more energy saving phenomenon. Microwave radiation is presented as a substituted for conventional heating methods since it offers even, rapid and efficient heating by aiding all particles to heat up

simultaneously. In response to the growing demand for sustainable and efficient manufacturing paradigms, microwave-assisted dyeing has emerged as a revolutionary alternative technology. Microwave treatment improves the fabric's uptake ability and coloring characteristics. Microwave irradiation is part of the recent most simple, lower cost and valued technologies in textile dyeing [16,17]. The fundamental principle underpinning microwave heating is dielectric heating, whereby electromagnetic radiation, commonly at a frequency of 2.45 GHz, induces rapid molecular vibration and rotation of polar molecules, predominantly water, within the dye bath. This unique mechanism results in rapid, uniform, and volumetric heating throughout the entire dyeing system, a stark contrast to the slower, less uniform, and surface-to-core heat transfer characteristic of conventional heating methods. This internal generation of heat promises to dramatically curtail processing times, reduce energy consumption, and increase dye diffusion and fixation within the textile substrate. [18–45].

Recent scholarly investigations have increasingly underscored the transformative potential of microwave technology across diverse textile applications [18–45].

This study is designed to conduct a detailed comparative analysis of both conventional and microwave-assisted dyeing techniques for polyamide 6 fabric utilizing a model acid dye (Telon Blue M-2R). The research will systematically investigate the effects of key process parameters specifically temperature, dye concentration, dyeing time, and pH on the dyeing mechanism, ultimate dye uptake, and final color strength. The overarching goal is to furnish a robust scientific foundation that will facilitate the development of more efficient, economically viable dyeing protocols for polyamide textiles [44–65].

2. Materials and Methods

2.1. Materials

The substrate used for all dyeing experiments was a 100% polyamide 6 (PA6) fabric. The fabric was procured from Nurel Group (Turkey). Fabric contains different type polyamide yarn. %35 384T-70/24 Denier Polymaide FDY Semidull, %10 192T-40/13 Denier Poliamide FDY Semidull, %55 - 300 DN-70/24*4 Denier Texture Polyamide Semidull.

Polyamide 6 (PA6) is synthesized via the ring-opening polymerization of ϵ -caprolactam. The resulting polymer chain contains repeating amide groups (CONH), which constitute the majority of the polar sites. The polymer chains are terminated by a small number of carboxylic end groups (COOH) and amino end groups (NH). Since the number of strongly hydrophilic end groups is low relative to the less-hydrophilic amide groups, the fiber exhibits low swelling in aqueous media, which in turn makes dye penetration difficult [1–11].

The preliminary preparation of the fabrics was conducted at Nurel Tekstil. The greige fabrics were initially processed through a Binaco Happy Scour continuous washing machine using Bianco HS New detergent at 85 °C and a speed of 30 m/min. Subsequently, the fabrics were passed through a stenter at 195 °C and 30 m/min. to ensure dimensional stability. Chemical agents were employed in the dye bath to achieve a more uniform dyeing process. Specifically, a biodegradable detergent, Bianco HS New, which is compatible with the dye bath and effectively removes impurities from the fabric, was utilized in conjunction with a levelling agent.

Our dyed lace fabric contains four different polyamide yarns. It is more important for us to observe that all fibers are dyed uniformly and closely together, rather than focusing solely on the dye uptake of a single fiber. Our spectrophotometric readings, from which we obtained the K/S (Kind/S) values, were taken from three different points, and the average values were used. It was observed that the deviations were not significant.

Conventional dyeing experiments were conducted in a laboratory-scale, using Rapid Eco-Dyer Laboratory Machine.

The acid dye selected for this investigation was C.I. Acid Blue 324, commercially known as Telon Blue M-2R, supplied by DyStar (Germany). This dye possesses a molecular weight of 766.53 g/mol

and was used as received with a purification. The chemical structure of the dye is depicted in Figure 1 [12–16].

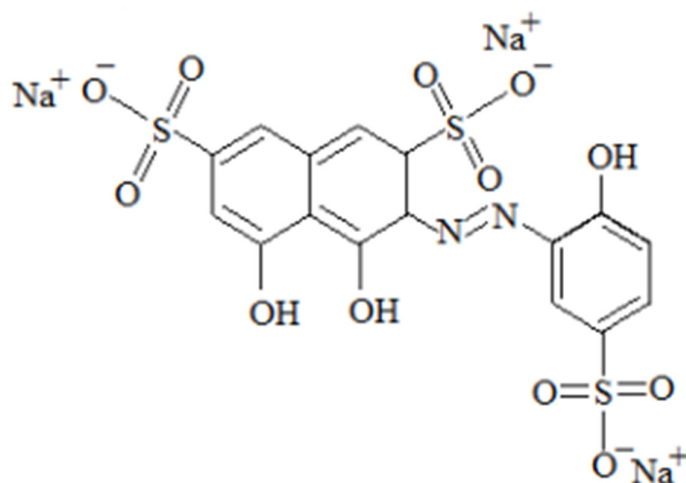


Figure 1. Chemical Structure of Telon Blue M-2R (C.I. Acid Blue 324).

For pH control and adjustment of the dyebaths, analytical grade acetic acid (glacial, 99.8%) was used to prepare appropriate buffer solutions.

2.2. Dyeing Procedures

2.2.1. Conventional Dyeing Methodology

Conventional dyeing experiments were conducted in a laboratory-scale. The dye bath was prepared with a liquor ratio of 1:50. The dyeing process was initiated at a starting temperature of 30 °C. The temperature was then uniformly raised to the target dyeing temperature (50, 60, 70, 80, or 95 °C) at a controlled rate of 1 °C/min. The dyeing was maintained at the final temperature for a duration of target reaction time (5-10-15-20-25-30 minutes) for comparative studies. Upon completion of the dyeing duration, the fabric samples were immediately removed, thoroughly rinsed with cold deionized water to remove any unfixed surface dye, and subsequently air-dried [44–65].

In addition, the effects of other reaction parameters such as pH (3, 3.5, 4, 4.5, 5, 6) and dye concentrations (0.1%, 0.25%, 0.5%, 0.75%, 1%, 1.5%) on dyeing were investigated at a different reaction times and conditions which are detailed in related sections [44–65].

2.2.2. Microwave-Assisted Dyeing Methodology

Dyeing experiments were conducted using a modified microwave oven (Milestone Start D Microwave Digestion System). Dyeing baths were prepared in microwave-transparent 100 ml capacity tubes to ensure uniform microwave energy absorption.

The dye bath was prepared using the same liquor ratio (1:50) and dye concentrations as in the conventional dyeing protocol [44–65]. The microwave power was systematically varied and set to 160 W. The dyeing duration was varied from 30 to 270 seconds (0.5 – 4.5 minutes), depending on the specific experimental conditions. Post-dyeing, the fabric samples were treated in the same manner as the conventionally dyed samples, involving a thorough rinsing and air-drying process [16–45].

Additional experiments were conducted to observe the effects of reaction time and reaction temperature at a different conditions which are detailed in related sections [16–45].

2.3. Analytical Procedures

2.3.2. Colorimetric Measurement

Dye uptake was determined by measuring the color strength in the fabric at predetermined time intervals using a Data Color SF 600 spectrophotometer at the maximum absorption wavelength of Telon Blue M2R ($\lambda_{\max} = 630$ nm). A calibration curve was established using known concentrations of the dye.

Color strength (K/S value) of the dyed fabric samples was measured using a reflectance spectrophotometer (Data Color 1000 spectrophotometer.) according to the Kubelka-Munk equation:

$$\frac{K}{S} = \frac{(1-R)^2}{2R} \quad (1)$$

where R is the reflectance value at the maximum absorption wavelength [44–65].

The percentage dye exhaustion (Dye Exhaustion is proportional with K/S) was calculated using the following equations:

$$\% \text{ Exhaustion} = \frac{(C_0 - C_t)}{C_0} \times 100 \quad (2)$$

$$K/S \propto \frac{(C_0 - C_t)}{C_0} \times 100 \quad (3)$$

$$\frac{K}{S} = \frac{(C_0 - C_t)}{C_0} \times A \quad (4)$$

where C_0 is the initial dye concentration and C_t is the dye concentration in the bath at time t [44–65].

The time-dependent calculation of dye concentration (C_t) in water was determined by using spectrophotometric measurements of the dye-water mixture and the proportionality of the K/S value to dye consumption. The difference between the initial concentration and the dye concentration remaining in the bath at time (t) gives the dye concentration absorbed by the fabric [44–65]. Additionally, a linear regression was performed between this value and the K/S value read by the spectrophotometer to confirm the relationship of K/S value with the concentration. This conversion coefficient (A) was determined to be approximately 15. This coefficient depends on the type of dye and the initial dye concentration.

3. Results and Discussions

3.1. Conventional Dyeing

3.1.1. Effect of PH

Figure 2 and Table 1 show the relationship between the initial pH of the dye bath and the resulting color strength (K/S) of the dyed material. The experiment was conducted under constant conditions of time (20 minutes) and temperature (80 °C), with a dye concentration of 1% in conventional media. The results, presented in Figure 2 and Table 1 clearly demonstrate a strong inverse correlation between the initial dye bath pH and the resulting K/S value.

The data in Figure 2 and Table 1 show that the highest color strength was achieved at the lowest initial pH of 3.0, while the lowest color strength was recorded at the highest initial pH of 6.0. This represents a significant decrease of approximately 47.5% in color strength as the initial pH is increased from 3.0 to 6.0.

The plot of K/S versus pH exhibits a distinct negative exponential relationship. As the pH increases, the K/S value decreases sharply, particularly in the highly acidic range pH 3.0 to 4.0, before the rate of decrease moderates at higher pH values (above 4.5).

Table 1. Effect of PH (Conventional Heating).

PH (in)	KS (Color Strength)
3	24,4815
3,5	21,0672
4	18,2372

4,5	15,9914
5,5	13,6445
6	12,8571

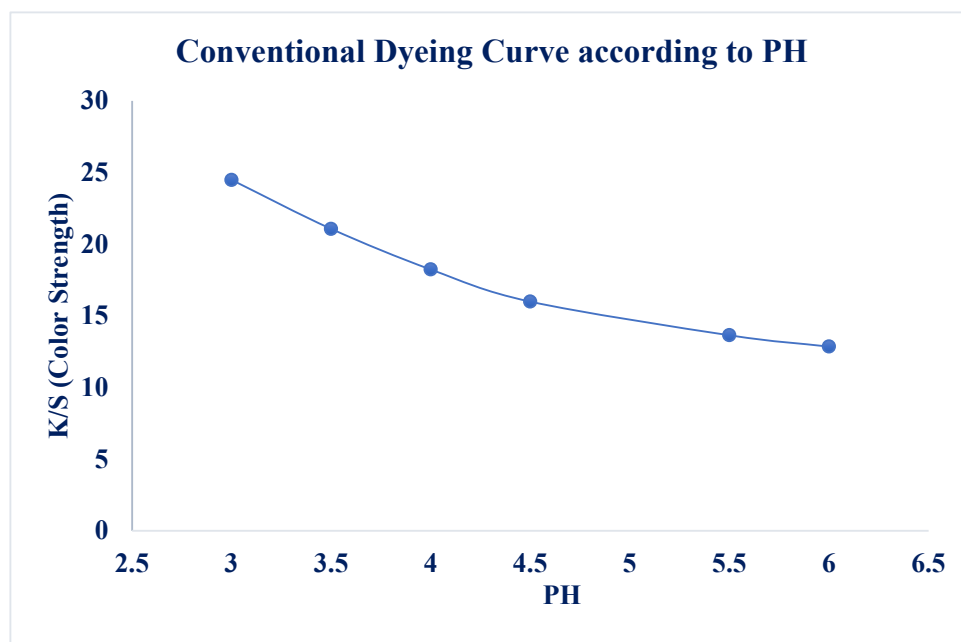


Figure 2. Effect of PH (Conventional Heating).

The data shows a progressive decrease in K/S as pH increases, with the steepest decline occurring between pH 3.0 and 4.0 (13.9% decrease per 0.5 pH unit). This indicates that the pH range 3.0–4.0 is critical for maximizing dye fixation on polyamide fibers. Polyamide fibers can be easily degraded if exposed to lower pH for a long time. At the same time, the exhaustion of dye molecules only triggers when kept at acidic pH [10].

3.1.2. Effect of Time and Temperature

The K/S value is a measure that indicates the color depth or dye uptake of a material. The Kubelka-Munk function is widely used in color science to quantify the color yield of a dye on a substrate, where a higher K/S value indicates greater color depth or strength. [44–65].

The analysis were conducted to understand the effects of the different dyeing times and the different temperatures at a pH 6-7 (without acid donor) and a dye concentration of 1%. The dye samples at 1% concentration were heated to target temperatures (50 °C, 60 °C, 70 °C, 80 °C, and 95 °C). Figures 3 and 4 show the change in K/S values and dye concentration over time (minutes) for five different temperatures. K/S values at 0, 5, 10, 15, 20, 25, and 30 minutes were measured for each temperature. Generally, K/S values show an increase over time at all temperatures. As the temperature increases, both the final level of K/S values and the rate of reaching saturation increase. Analysis of conventional dyeing curves and dyeing data in Figures 3 and 4 and Tables 2 and 3 clearly demonstrates that temperature and time play critical roles in K/S values and dyeing mechanism. At the highest temperature of 95 °C, the fastest dye uptake and the highest final K/S values were obtained.

Table 2. Effect of Time and Temperature on Color Strength (Conventional Heating).

K/S (Color Strength)	50 °C	60 °C	70 °C	80 °C	95 °C
0	0	0	0	0	0

5	2,151	3,745	6,980	9,000	11,820
10	3,671	5,764	9,527	11,270	13,228
15	4,802	7,026	10,846	12,276	13,750
20	5,675	7,889	11,653	12,867	14,063
25	6,371	8,518	12,208	13,235	14,247
30	6,938	8,995	12,629	13,520	14,371

Table 3. Effect of Time and Temperature on Concentration (Conventional Heating).

Concentration (g./100 ml)	50 °C	60 °C	70 °C	80 °C	95 °C
0	0,01000	0,01000	0,01000	0,01000	0,01000
5	0,00824	0,00706	0,00535	0,00400	0,00212
10	0,00700	0,00548	0,00365	0,00249	0,00118
15	0,00608	0,00449	0,00277	0,00182	0,00083
20	0,00537	0,00381	0,00223	0,00142	0,00062
25	0,00480	0,00332	0,00186	0,00118	0,00050
30	0,00434	0,00294	0,00158	0,00099	0,00042

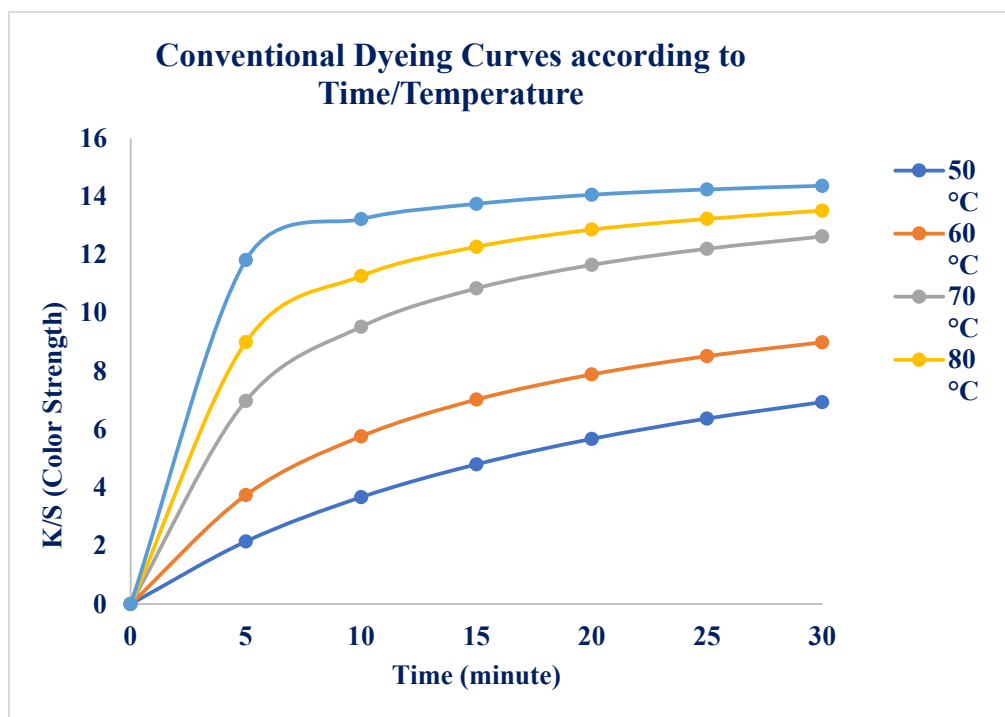


Figure 3. Effect of Time and Temperature on Color Strength (Conventional Heating).

The rate of dye exhaustion is profoundly influenced by temperature. As the temperature increases from 50 °C to 95 °C, the initial rate of dye uptake increases significantly. More importantly, the time required to reach equilibrium is drastically reduced. For instance, the 95 °C curve shows a near-complete exhaustion (minimal change in concentration) within the first 10–15 minutes, whereas the 50 °C curve continues to show a measurable, albeit slow, decrease in concentration even after 30 minutes (Figure 4 and Table 3).

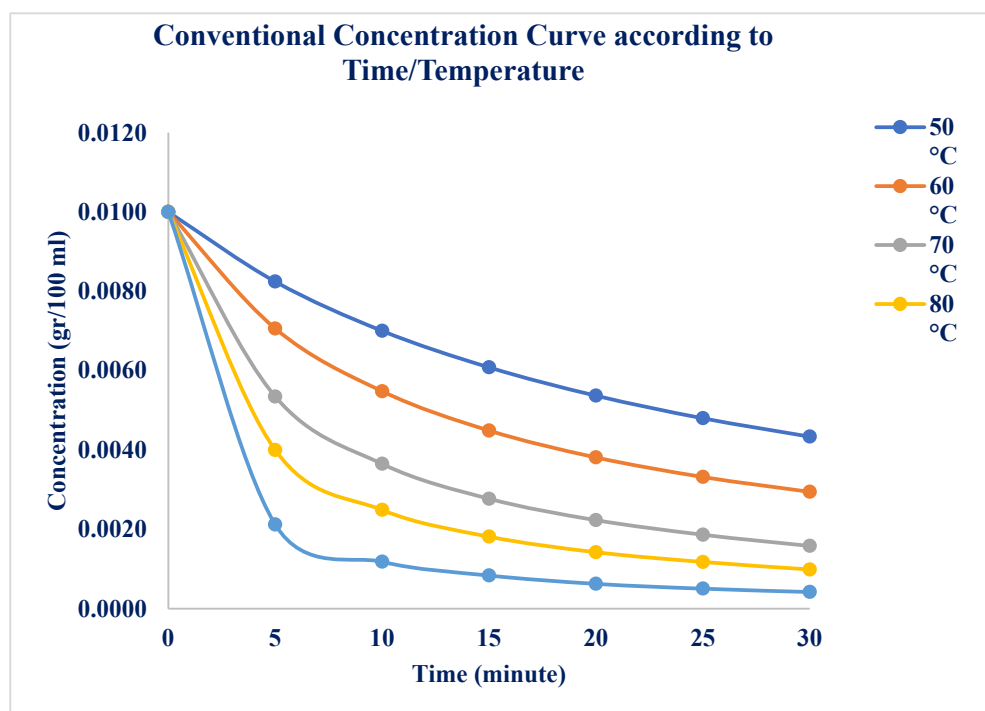


Figure 4. Effect of Time and Temperature on Dye Concentration (Conventional Heating).

3.1.3. Effect of Dye Concentration According to Different Temperatures

The dyeing process was initiated at a starting temperature of 30 °C to examine the effects of dye concentration on the reaction. The temperature was then uniformly raised to the target dyeing temperature (50, 60, 70, 80, 90 or 95 °C) at a controlled rate of 1 °C/min. Experiments were proceeded in the pH 6-7 (without acid donor) and a reaction time of 10 minutes to investigate the effects of different dye concentrations and temperature. Figures 5 and 6 and Table 4 illustrates the relationship between color strength, dye concentration, and dyeing temperature for a conventional dyeing process.

Table 4. Effect of Dye Concentration and Temperature (Conventional Heating).

Dye Concentration	Temperature					
	50 °C	60 °C	70 °C	80 °C	90 °C	95 °C
0,10%	0,4150	0,7507	0,8659	0,9112	1,7994	1,9654
0,25%	2,3466	2,8823	3,5761	4,8436	5,1342	5,4248
0,50%	2,6333	3,5349	4,3872	6,5147	6,9551	7,1561
0,75%	2,9199	4,1874	5,1982	8,1848	8,7760	8,8873
1,00%	3,2066	4,8399	6,0092	9,5722	11,0113	11,2309
1,50%	3,7799	6,1449	7,6311	12,3470	15,4817	15,9181

For any given dye concentration from Figure 5 and Table 4, an increase in temperature from 50 °C to 95 °C results in a substantial increase in the K/S value. These data shows that the dyeing process has a critical temperature zone where the mechanism of dyeing are dramatically accelerated.

The K/S value under these conditions is approximately 3.5 times greater than the value achieved at the same concentration but at 50 °C. This underscores the synergistic effect where a high dye concentration and high thermal energy (temperature) work in concert to maximize dye adsorption and fixation.

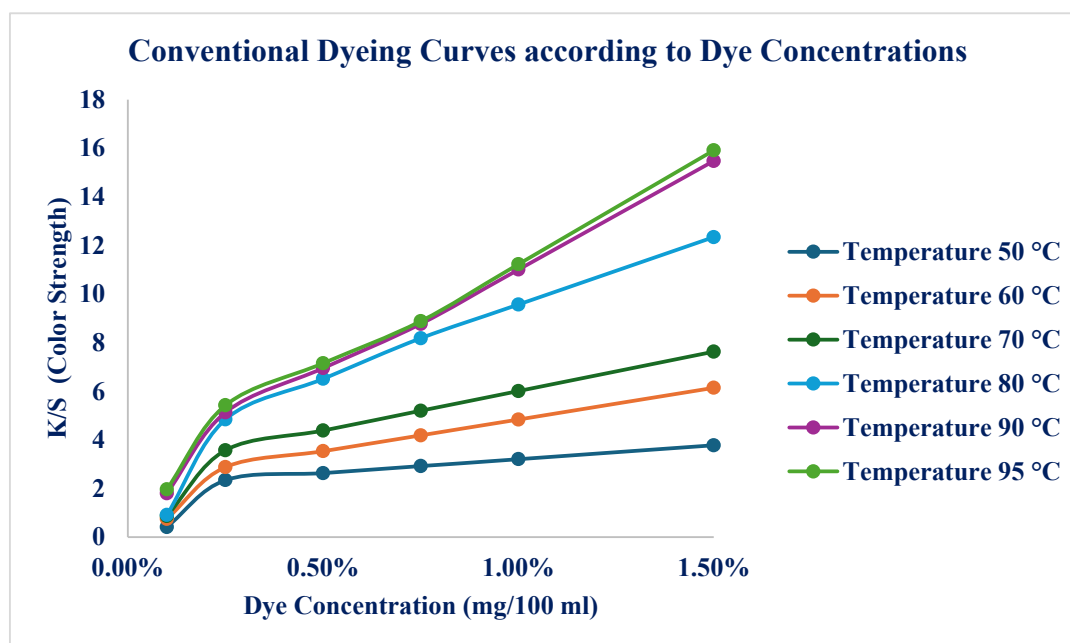


Figure 5. Effect of Dye Concentration at Different Temperature (Conventional Heating).

The Conventional Dyeing Curve presented in Figure 6 illustrates the relationship between temperature and color strength (expressed as K/S values) for varying dye concentrations ranging from 0.1% to 1,5%.

At all temperatures, higher dye concentrations result in higher K/S values, confirming that **color strength is concentration-dependent**. However, the relationship is **non-linear**, especially at elevated temperatures:

- At lower concentrations (0.1%), K/S values remain relatively low even at high temperatures, indicating limited availability of dye molecules.
- At higher concentrations (0.75% and 1,5%), K/S increases sharply up to 80–90 °C, after which the rate of increase diminishes. This behavior suggests site saturation within the fiber, where additional dye molecules contribute less effectively to color strength.

Notably, the 1,5% dye concentration exhibits the highest K/S values across all temperatures, reaching a maximum of approximately 15,91 at 95 °C, confirming superior dye loading under these conditions.

As observed, K/S values increase with rising temperature across all dye concentrations, indicating enhanced dye uptake and fixation at elevated temperatures.

For all dye concentrations, an overall increase in K/S is observed as the temperature increases from 50 to 95 °C. This trend can be attributed to several temperature-dependent phenomena:

Increased molecular mobility of dye molecules, which enhances diffusion from the dye bath into the fiber structure. Fiber swelling at elevated temperatures, leading to greater accessibility of internal dye-binding sites. The most pronounced increase in K/S occurs between 70 and 90 °C, particularly for dye concentrations of 0.5%, 0.75%, 1% , % 1.5, suggesting that this temperature range represents a critical transition where dye diffusion becomes significantly more efficient. Beyond 90 °C, the increase in K/S becomes marginal, indicating an approach to dye saturation or equilibrium uptake.

3.2. Microwave Dyeing

3.2.1. Effect of PH

Table 5 and Figure 7 shows the relationship between the initial pH of the dye bath and the resulting color strength (K/S) of the dyed material in microwave media. The experiment was

conducted under constant conditions of time (4 minutes) and temperature (80 °C), with a dye concentration of 1% in microwave media. The primary objective is to identify the optimal pH range for maximizing color yield in microwave media.

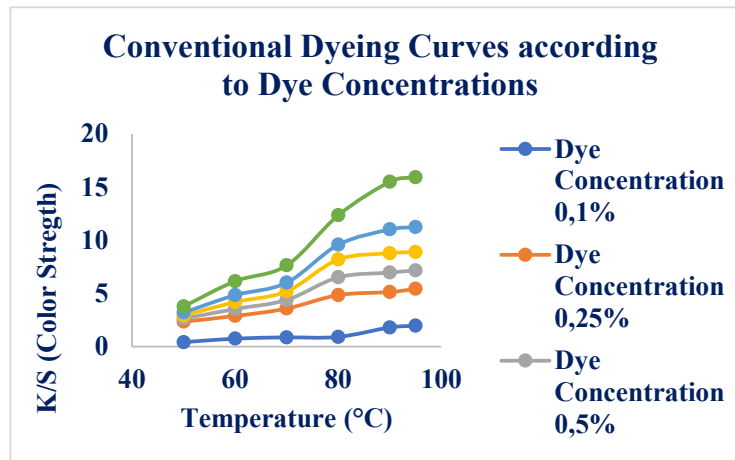


Figure 6. Effect of Temperature at Different Concentrations (Conventional Heating).

Table 5. Effect of PH (Microwave Heating).

PH	KS
3	25,0513
3,5	20,1982
4	18,2071
4,5	16,1967
5,75	13,3032
6,5	12,6054

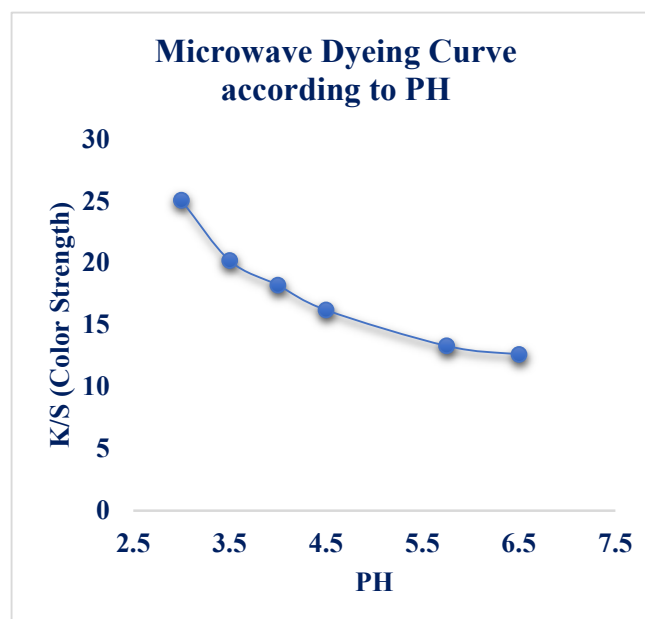


Figure 7. Effect of PH (Microwave Heating).

The results from Figure 7 and Table 5 demonstrate a strong inverse correlation between the initial pH of the dye bath and the color strength. The highest K/S value was achieved at the most acidic condition tested pH 3.0 as in conventional media.

The K/S value decreases sharply from a maximum of approximately 25.0 at pH 3.0 to 12.5 at pH 6.5. This reduction of nearly 50% in color strength highlights the paramount importance of pH control in the dyeing of polyamide fibers, particularly when using acid or metal-complex dyes [12–16].

The high K/S values achieved (up to 25.0) are indicative of a highly efficient dyeing process, which is likely enhanced by the microwave environment.

- **Accelerated Diffusion:** Microwave heating provides rapid, volumetric heating, which can significantly increase the molecular mobility of the dye and the segmental motion of the polymer chains. This effectively lowers the energy barrier for the internal diffusion of the dye into the fiber matrix, accelerating the overall dyeing rate and allowing for a higher equilibrium dye uptake in a shorter time [16–45].
- **Synergistic Effect:** The microwave energy acts synergistically with the optimal chemical conditions (pH: 3- 6). While the acidic condition provides the necessary thermodynamic driving force (electrostatic attraction), the microwave energy provides acceleration (enhanced diffusion), resulting in the superior color strength observed[16–45].

Both conventional and microwave-assisted dyeing show a clear, inverse relationship between pH and color strength. The K/S value is maximized at the lowest tested pH (pH 3.0) and decreases sharply as the dyebath becomes less acidic. The optimal pH for maximum dye uptake remains consistently at pH 3.0 for both conventional and microwave-assisted dyeing [10].

3.2.2. Effect of Time and Temperature

The analysis were conducted to understand the effects of the different dyeing times and the different temperatures at a pH 6-7 (without acid donor) and a dye concentration of 1%.

Figures 8 and 9 and Tables 6 and 7 show the effect of temperature (50– 95 °C) on the measured parameter over a 10 minute heating period. At all tested temperatures, the parameter increased continuously with time, indicating a temperature-dependent process. However, the rate of increase varied considerably with temperature.

Table 6. Effect of Time and Temperature on Color Strength (Microwave Heating).

K/S (Color Strength)	50 °C	60 °C	70 °C	80 °C	95 °C
0	0	0	0	0	0
1	1,399	3,085	2,892	8,308	11,530
2	2,559	4,330	5,134	9,710	12,418
3	3,521	5,280	6,870	10,637	12,968
4	4,319	6,077	8,216	11,347	13,374
5	4,981	6,778	9,259	11,931	13,697
6	5,530	7,411	10,068	12,431	13,967
7	5,985	7,991	10,694	12,869	14,199
8	6,363	8,530	11,179	13,262	14,403
9	6,676	9,036	11,555	13,618	14,586
10	6,936	9,514	11,847	13,944	14,751

Table 7. Effect of Time and Temperature on Concentration (Microwave Heating).

Concentration (g./100 ml)	50 °C	60 °C	70 °C	80 °C	95 °C
0	0,01000	0,01000	0,01000	0,01000	0,01000
1	0,00904	0,00787	0,00813	0,00481	0,00256
2	0,00824	0,00701	0,00669	0,00393	0,00199
3	0,00757	0,00636	0,00557	0,00335	0,00163
4	0,00702	0,00581	0,00470	0,00291	0,00137
5	0,00656	0,00533	0,00403	0,00254	0,00116
6	0,00619	0,00489	0,00350	0,00223	0,00099
7	0,00587	0,00449	0,00310	0,00196	0,00084
8	0,00561	0,00412	0,00279	0,00171	0,00071
9	0,00540	0,00377	0,00255	0,00149	0,00059
10	0,00522	0,00344	0,00236	0,00128	0,00048

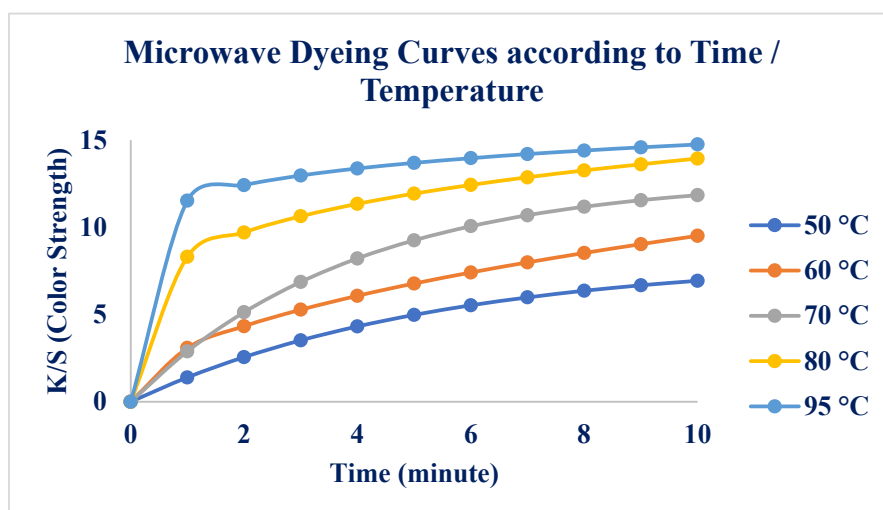


Figure 8. Effect of Time and Temperature on Color Strength (Microwave Heating).

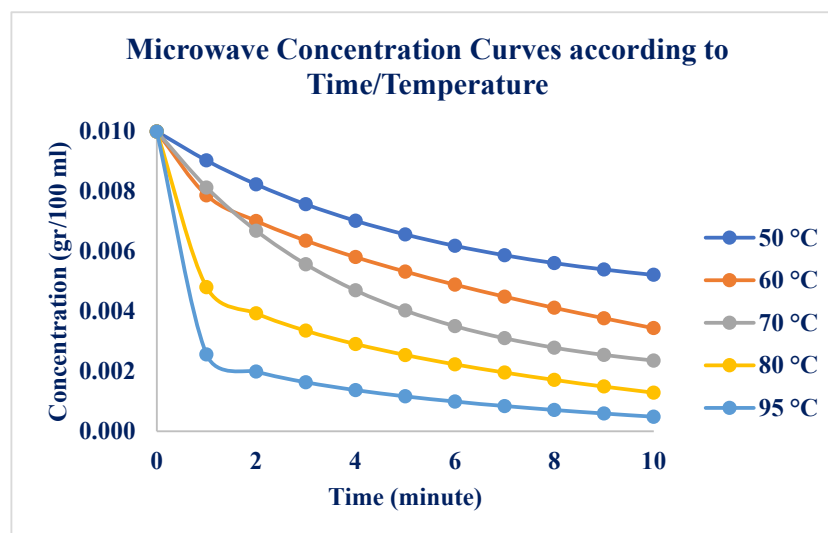


Figure 9. Effect of Time and Temperature on Dye Concentration (Microwave Heating).

Microwave-assisted dyeing is an advanced technique that utilizes electromagnetic radiation to rapidly heat the dye bath and the substrate, leading to faster diffusion and reduced processing times compared to conventional methods. The color strength, quantified by the Kubelka-Munk function (K/S), is a critical parameter for evaluating the efficiency of the dyeing process.

Temperature Dependence: For any given time point, the K/S value is directly proportional to the temperature. The 95 °C curve consistently yields the highest color strength, while the 50 °C curve yields the lowest.

The initial rate of dyeing (the slope of the curve at $t=0$) is significantly higher at elevated temperatures, particularly at 80 °C and 95 °C. The 95 °C curve exhibits a near-vertical rise in the first minute, achieving a K/S of 11.530, which is approximately 8.2 times the value achieved at 50 °C (K/S = 1.399) in the same period.

Equilibrium/Saturation: All curves exhibit a characteristic trend of rapid initial uptake followed by a gradual leveling off, suggesting that the dyeing process is approaching equilibrium exhaustion. The saturation point is reached fastest and at the highest K/S value for the 95 °C process.

Dye exhaustion, the percentage of dye transferred from the bath to the textile substrate, is a critical parameter in industrial dyeing, directly impacting color yield, process economics, and environmental sustainability. Monitoring the dye concentration in the bath over time is the standard method for determining the exhaustion rate. This analysis interprets the provided concentration data to quantify the effect of temperature on the rate and extent of dye uptake in a microwave-assisted system [44–65].

The data in Figure 9 and Table 7 clearly demonstrate the exponential relationship between temperature and dye exhaustion. The analysis of the dye bath concentration data confirms the superior efficiency of high-temperature microwave-assisted dyeing. The process at 95 °C achieves an exceptionally high dye exhaustion of 95.2% in just 10 minutes, which is indicative of a highly accelerated mass transfer process. This rapid and near-complete exhaustion is a direct result of the thermal energy provided by the microwave, which enhances the diffusion coefficient of the dye molecules and the swelling of the fiber structure. These findings underscore the potential of microwave technology for developing fast, high-yield, and environmentally conscious dyeing protocols.

The comparative analysis unequivocally demonstrates that microwave-assisted dyeing is superior to the conventional method. The microwave process significantly accelerates the rate of dye uptake, leading to substantially higher dye exhaustion in a fraction of the time required by the conventional method. This efficiency is particularly pronounced at 95 °C, where the microwave method achieves near-complete exhaustion 95.2% in just 10 minutes. The enhanced performance is attributed to the rapid, volumetric heating characteristic of microwave energy, which facilitates faster dye diffusion and fixation. These findings support the adoption of microwave technology as a more time-efficient and environmentally favorable alternative for industrial dyeing applications.

3.2.3. Effect of Dye Concentration According to Different Times

The analysis were conducted to understand the effects of the different dyeing times and the different concentrations at a pH 6-7 (without acid donor) and average temperature of 80 °C.

Table 8 and Figures 10 and 11 illustrate the relationship between dye concentration (% mg/100 ml) and color strength (K/S) for samples treated under microwave irradiation at different dyeing times (0–4.5 minutes).

Table 8. Effect of Dye Concentration and Reaction Times (Microwave Heating).

Dye Concentration (mg/100 ml) %	0 minut e	0,5 minut e	1,5 minut e	2 minut e	2,5 minut e	3 minut e	3,5 minut e	4 minut e	4,5 minut e
0,10%	0,0000	0,1578	0,1757	0,1936	0,4658	0,4733	0,4810	0,8172	1,0040

0,25%	0,0000	0,2241	0,4348	0,7972	1,1874	1,3161	1,7015	2,1245	2,7051
0,50%	0,0000	0,3771	0,7977	1,1424	1,8702	2,2534	2,7197	3,4885	3,7910
0,75%	0,0000	0,4855	1,1910	1,6459	2,2296	2,9205	3,7077	4,5910	5,5706
1,00%	0,0000	0,6010	1,1376	1,7582	2,4080	3,0728	3,9831	5,4080	6,1228
1,50%	0,0000	0,8315	1,7471	1,9827	2,7649	3,3774	4,5340	7,0420	7,2272

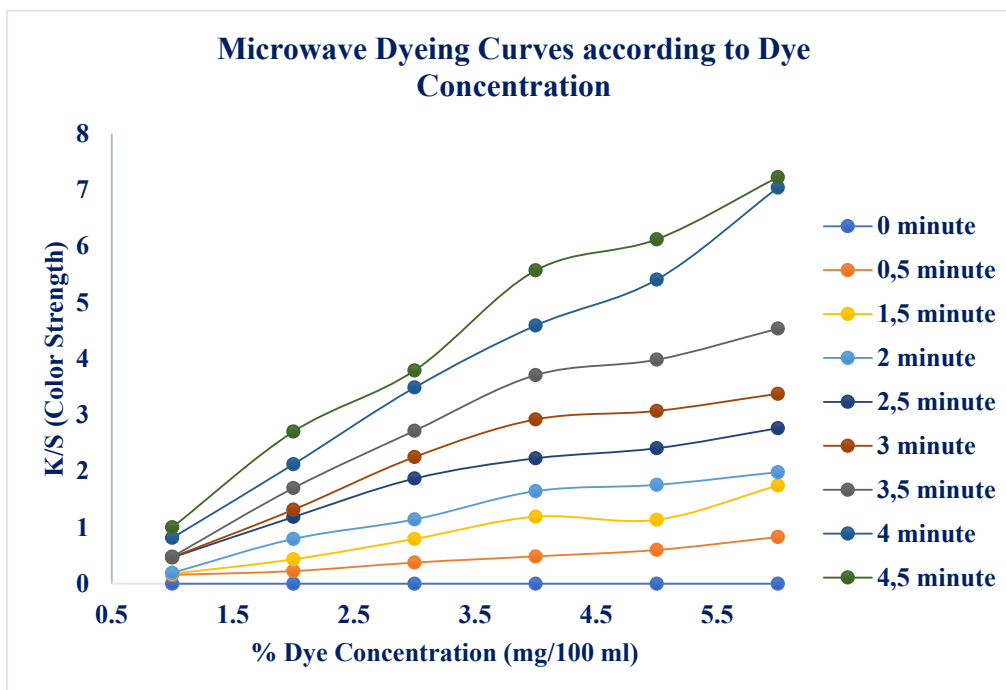


Figure 10. Effect of Dye Concentration at Different Reaction Times (Microwave Heating).

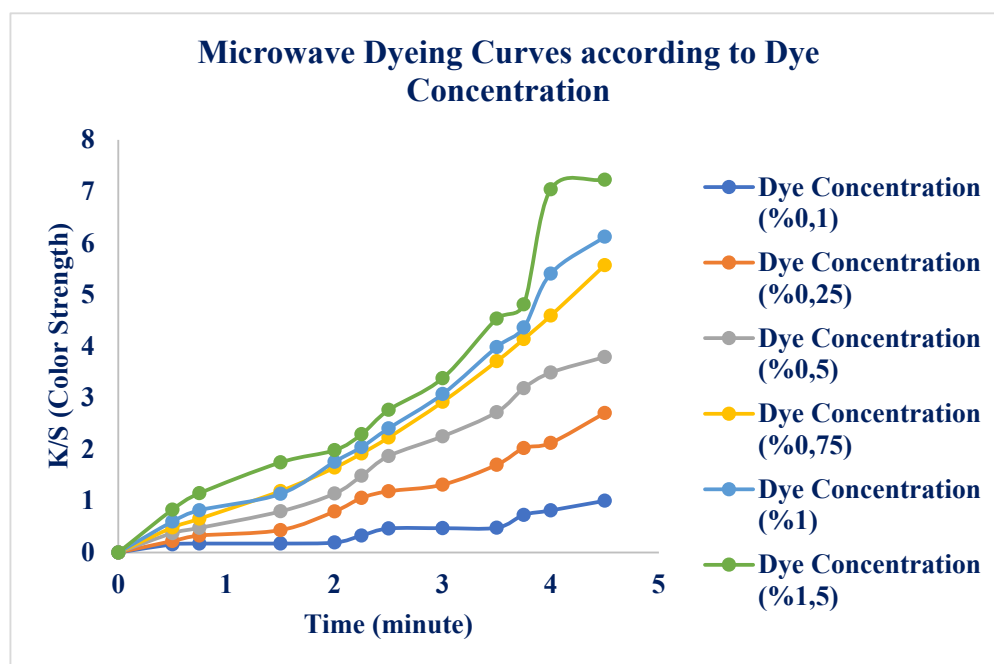


Figure 11. Effect of Reaction Time at Different Concentrations (Microwave Heating).

Overall, the results demonstrate that both dye concentration and microwave dyeing time have a significant positive effect on color strength. For all microwave exposure times, the K/S values increase with increasing dye concentration. This trend indicates that higher dye availability in the dye bath leads to greater dye uptake by the material, resulting in enhanced color strength. However, the increase is non-linear, suggesting a gradual approach toward saturation at higher concentrations.

At a fixed dye concentration, increasing the microwave treatment time markedly increases the K/S values. Short dyeing times (0–1.5 minutes) result in relatively low color strength, while longer times (3–4.5 minutes) produce substantially higher K/S values. This behavior can be attributed to the enhanced molecular mobility and diffusion of dye molecules under microwave heating, which promotes more efficient dye–fiber interactions.

The highest color strength is observed at the combined condition of high dye concentration and prolonged microwave exposure (4–4.5 minutes). This indicates a synergistic effect, where microwave energy accelerates dye penetration and fixation, particularly at higher dye concentrations.

The data suggest that microwave-assisted dyeing is an effective method for achieving high color strength in relatively short processing times. Optimizing microwave exposure time can reduce energy consumption while maintaining or enhancing dyeing efficiency.

The results in Figures 10 and 11 and Table 8 clearly demonstrate that both dye concentration and microwave exposure time have a pronounced effect on dye uptake. For all dye concentrations studied (0.1–1.5%), the K/S values increase monotonically with dyeing time, indicating progressive adsorption and fixation of dye molecules onto the substrate. A rapid increase in K/S is observed at the early stages (0–2.5 min), followed by a more gradual rise at longer times.

At any given dyeing time, K/S values increase systematically with increasing dye concentration:

$$K/S_{1.5\%} > K/S_{1.00\%} > K/S_{0.75\%} > K/S_{0.5\%} > K/S_{0.25\%} > K/S_{0.1\%}$$

This trend confirms that higher initial dye concentrations provide a greater driving force for mass transfer, leading to enhanced dye uptake. The effect is particularly pronounced under microwave conditions, where volumetric heating promotes:

- Faster dye diffusion
- Improved fiber swelling
- Increased accessibility of internal binding sites

At higher concentrations ($\geq 0.75\%$), the K/S values increase sharply after 3 minutes, suggesting that microwave irradiation effectively overcomes diffusion limitations that are typically observed in conventional dyeing processes.

3.3. Fastness Properties

Color fastness tests were performed according to ISO standards for fabrics dyed with Telon Blue M2R at a 1% dyeing concentration using the conventional method (95 °C, 30 min) and microwave-assisted method (10 min). Washing fastness tests were performed according to ISO 105 C06 B1S method, acidic and alkaline perspiration fastness tests were performed according to ISO 105 E04 method and water fastness tests were made according to ISO 105 E01. Dry/Wet Rubbing Fastness tests were made according to ISO105X12. Fastness properties were evaluated according to ISO 105 A02 and ISO 105 A03 method with grey scale in light cabinet.

Table 9. Fastness Properties (1% Conventional and Microwave Methods).

Dyeing Method	Washing Fastness [ISO105C06 B1S]	Acidic Persp. [ISO 105 E04]	Alkaline Persp. [ISO 105 E04]	Water Fastness [ISO 105 E01]	Dry/Wet Rubbing Fastness [ISO105X12]
Conventional	3/4	4	3/4	4	4/5 - 4

Microwave	3/4	4	3/4	4	4/5 - 4
-----------	-----	---	-----	---	---------

Similar test results were observed in the washing, acidic and alkaline perspiration, water and rubbing fastnesses applied according to ISO standards to fabrics dyed by conventional and microwave methods.

3.4. Role of Microwave Irradiation

Compared to conventional thermal dyeing reported in the literature, the observed dye uptake occurs within remarkably short dyeing times (≤ 4.5 min). This enhancement can be attributed to the specific effects of microwave irradiation, including:

- Rapid and uniform heating of the dye bath and substrate
- Dipole rotation and ionic conduction effects
- Reduced thermal gradients within the fiber matrix

These factors collectively accelerate dye–fiber interactions and improve fixation efficiency. The experimental results demonstrate that microwave-assisted dyeing enables:

- Fast color development
- High color strength at short processing times
- Efficient utilization of higher dye concentrations

Such characteristics make microwave-assisted dyeing a promising approach for energy-efficient and time-saving textile coloration processes.

4. Conclusions

Comprehensive comparative study was conducted on the acid dyeing of PA-6 fabric, systematically evaluating the performance of conventional heating against the innovative microwave-assisted technique using C.I. Acid Blue 324. This investigated the mechanism of acid dyeing of water 6 (PA6) fabrics, providing a detailed comparison between microwave-assisted heating and conventional dyeing methodologies. The investigation analyzed the influence of key parameters pH, temperature, dyeing time, and dye concentration on the resulting color strength (K/S).

The study confirmed that the conventional dyeing process adheres to established principles, with the highest dye uptake achieved at the most acidic condition (pH 3.0) and the highest temperature tested (95 °C). However, the process is inherently time consuming, requiring a duration of 30 minutes to achieve maximum color yield, which is a significant factor in industrial throughput and energy consumption.

The findings clearly demonstrate that the microwave-assisted method provides a robust scientific basis for developing faster, more energy-efficient, and more sustainable dyeing protocols in the textile industry.

Key Findings are as below.

Effect of pH: In both dyeing methods, the optimum pH value for maximum dye uptake (K/S value) was determined to be 3.0. This confirms the critical importance of an acidic environment to maximize the ionic interaction between the protonated amino groups in the PA6 fiber and the dye molecules.

Conventional Dyeing: In the conventional method, dye uptake increased proportionally with time and temperature, with the highest K/S values obtained after 30 minutes of dyeing at 95 °C. This indicates that the rate-determining step of dye diffusion and fixation is dependent on thermal energy.

Microwave-Assisted Dyeing: The microwave-assisted dyeing method provided a remarkable acceleration in the dyeing time. Thanks to the dielectric heating mechanism (160 W), the time required for dye uptake was drastically reduced compared to the conventional method (seconds instead of minutes).

Acknowledgments: The authors would like to thank Nurel Tekstil, Bursa, Turkey, for kindly supplying the polyamide fabrics and allowing the supports.

References

1. Böcek, Nevin (2001), Investigation of Fiber and Temperature Interaction in Dyeing of Synthetic Fibers, [Master's thesis, Sakarya University]. YÖK National Thesis Center. <https://tez.yok.gov.tr/UlusalTezMerkezi/>
2. K. Haggag, M. M. El-Molla, K. A. Ahmed (2015), Dyeing of Nylon 66 Fabrics Using Disperse Dyes by Microwave Irradiation Technology, International Research Journal of Pure & Applied Chemistry, 8(2): 103-111, 2015, <https://doi.org/10.9734/IRJPAC/2015/17922>
3. Atav, R., Soysal S., Haji, Aminoddin (2024), Environmentally Friendly Coloration of Polyamide Fabrics with the Use of Natural Dyes: A Study Including Results of Industrial Scale Applications, Fibers and Polymers, Volume 25, pages 2223–2232, <https://doi.org/10.1007/s12221-024-00576-7>
4. Ghaheh F.S., Razbin M., Tehrani M., Vayghan, L.Z.A., Sadrjahani, M., Modeling and optimization of dyeing process of polyamide 6 and woolen fabrics with plum-tree leaves using artificial intelligence, Scientific Reports volume 14, Article number: 15067 (2024), DOI: 10.1038/s41598-024-64761-7
5. Lara, L.; Cabral, I.; Cunha, J. Ecological Approaches to Textile Dyeing: A Review. *Sustainability* **2022**, *14*, 8353. <https://doi.org/10.3390/su14148353>
6. Atav, R., Soysal, S., & Haji, A. (2024). Environmentally friendly coloration of polyamide fabrics with the use of natural dyes: A study including results of industrial scale applications. *Fibers and Polymers*, *25*, 2223–2232. <https://doi.org/10.1007/s12221-024-00576-7>
7. H. A. Ghazal, (2020). "Microwave irradiation as a new novel dyeing of polyamide 6 fabrics by reactive dyes," *Egypt. J. Chem.*, vol. 63, no.6, pp. 2125-2132, doi:10.21608/ejchem.2019.18513.2239.
8. Nikodijevic, M., Vuckovic, N., Dordevic, D., (2020). Possibilities of Dyeing of Polyamide Fabric with Substantive Dye, The Eurasia Proceedings of Science, Technology, Engineering & Mathematics (EPSTEM), Volume 11, Pages 131-135
9. Eren, S.; Özyurt, İ. Waterless Dyeing of Polyamide 6.6. *Polymers* **2024**, *16*, 1472. <https://doi.org/10.3390/polym16111472>
10. Irfan M., Gao, A, (2025), Nylon dyeing with reactive dyes by intermittent exposure to microwave irradiations to improve leveling, Pigment&Resin Technology, 54/5, 674-681, DOI:10.1108/PRT/-04-2024-0041
11. Shahmoradi Ghaheh, F.; Razbin, M.; Tehrani, M.; Zolfipour Aghdam Vayghan, L.; Sadrjahani, M. Modeling and optimization of dyeing process of polyamide 6 and woolen fabrics with plum-tree leaves using artificial intelligence. *Sci. Rep.* **2024**, *14*, 15067. <https://doi.org/10.1038/s41598-024-64761-7>
12. Özcan Y., Textile Fiber and Dyeing Technique, 1978
13. Trotman E.R., Dyeing and Chemical Technology of Textile Fibres, 1970
14. Reda, E.M.; Othman, H.A.; Ghazal, H.; Hassabo, A.G. Kinetic and isothermal study of dye absorption using pre-treated natural fabrics using polyamine compounds. *Sci. Rep.* **2025**, *15*, 3794. <https://doi.org/10.1038/s41598-025-86012-z>
15. Adeel, S.; Razzaq, A.; Kiran, S.; Ahmad, T.; Hassan, A.; Rehman, H. A Comparative Study on Sustainable Dyeing of Silk and Wool with Acid Red 138 Dye. *J. Nat. Fibers* **2022**, *19*, 8181–8190.
16. Zhang, R., Liu, J., Wang, J., Wang, J., & Meng, J. (2009). A novel process of dyeing wool with acid dyes under microwave irradiation. *Journal of Applied Polymer Science*, *113*(5), 2798–2803. <https://doi.org/10.1002/app.30242>

17. Dülek, Y.; Yıldırım, İ.; Sevinç, B.; Mert, E.; Yılmaz, B.; Kut, D. A Comparative Study on Microwave Assisted Dyeing Properties of Conventional and Recycled Polyester Fabrics. *Eurasia Proc. Sci. Technol. Eng. Math.* **2023**, *23*, 300–306. <https://doi.org/10.55549/epstem.1368272>
18. Khalil, E.; Sarkar, J.; Rahman, M.M.; Shamsuzzaman, M.; Das, D. Advanced Technology in Textile Dyeing. In *Advanced Technology in Textiles: Fibre to Apparel*; Rahman, M.M., Mashud, M., Rahman, M.M., Eds.; Springer: Singapore, 2023; pp. 97–138. https://doi.org/10.1007/978-981-99-2142-3_4
19. Amesimeku, J.; Fan, L.; Jakpa, W.; Wang, C., Dyeing properties of meta-aramid fabric dyed with basic dye using ultrasonic–microwave irradiation. *Journal of Cleaner Production*, 2021, *278*, 123987.
20. Fiandra, E. F.; Starck, M.; Findlay, E. K.; Binks, J.; Si, G.; Chilton, R.; Sivik, M. R.; Thompson, R. L.; Wilson, M. R.; Mahon, C. S. Polyesters incorporating biobased monomers for soil-release treatment of synthetic textile surfaces. *Green Chem.* 2025, *27*, 14290–14300.,DOI: 10.1039/D5GC04056F
21. Xue, Q.; Zhu, J.; Meng, W.; Zhang, K. Effect of MXene Nanosheet Dispersed Phases on the Fabrication of Polyamide Nanofiltration Membranes. *ACS Appl. Eng. Mater.* **2023**, *1*, 679–689. DOI: 10.1021/acsaenm.2c00205
22. Alegbe, E. O., & Uthman, T. O. (2024). A review of history, properties, classification, applications and challenges of natural and synthetic dyes. *Heliyon*, 10, e33646. <https://doi.org/10.1016/j.heliyon.2024.e33646>
23. Usluoğlu A., Teker M. (2024), Investigation of Dyeing Kinetics of Cotton Fiber with C.I. Reactive Yellow 138:1 Dyestuff in Microwave Environment- *Journal of the Institute of Science of Yüzüncü Yıl University - Vol.29 -pp.119 - ISSN : 1300-5413 - DOI : 10.53433/yyufbed.1330002*
24. Yiğit E.A., Teker M. (2011), Disperse Dyeability of Polypropylene Fibers via Microwave and Ultrasonic Energy - *Polymer and Polymer Composites - Vol.19 - pp.711 - ISSN : 1478-2391 - DOI : 10.1177/096739111101900812*
25. Haggag K., El-Molla M.M., Mahmoud, Z.M., Dyeing of Cotton Fabric using Reactive Dyes by Microwave Irradiation Technique, *Indian Journal of Fibre & Textile Research* Vol.9, December 2014, pp. 406-410. <https://doi.org/10.56042/ijftr.v39i4.43879>
26. Rahman, M. M., Ahmed, M., Jalil, M. A., & Mondal, M. I. H. (2008). The effect of microwave preheating on the dyeing of wool fabric with a reactive dye. *Journal of Applied Polymer Science*, 108(1), 314–318. <https://doi.org/10.1002/app.27082>
27. Kim, S. S., Leem, S. G., Ghim, H. D., Kim, J. H., & Lyoo, W. S. (2003). Microwave heat dyeing of polyester fabric. *Fibers and Polymers*, 4(4), 204–209. <https://doi.org/10.1007/BF02875361>
28. Kocak D., Akalin M., Merdan N., Yılmaz Sahinbaskan B, Effect of Microwave Energy on Disperse Dyeability of Polypropylene Fibres, *Marmara Journal of Pure and Applied Sciences* 2015, Special Issue-1: 27-31
29. Haggag, K., Hanna, H. L., Youssef, B. M., & El-Shimy, N. S. (1995). Dyeing polyester with microwave heating using disperse dyestuffs. *Journal of the Society of Dyers and Colourists*, 111(5), 170-173. <https://doi.org/10.1111/j.1478-4408.1995.tb01704.x>
30. Büyükkıncı Y. B., Karada R., Guzel, E.T., Organic cotton fabric dyed with dyer's oak and barberry dye by microwave irradiation and conventional methods, *Industria Textila*, Vol No, 72, 30-38, 2021, DOI: 10.35530/IT.072.01.1755
31. Gouda M., Haggag K. M., Boraie W. E, Aljaafari A., Al-Faiyz Y. , Synthesis and Characterization of Inorganic Pigment Nanoparticles for Textile Coloration Using Microwave Techniques, *AATCC Journal of Research* Volume 3, Issue 3, May 2016, Pages 1-8, <https://doi.org/10.14504/ajr.3.3.1>
32. Kale, M.J., Bhat, N.V., Effect of microwave pretreatment on the dyeing behaviour of polyester fabric, *Society of Dyers and Colourists, Color. Technol.*, 127, 365–371, DOI: 10.1111/j.1478-4408.2011.00332.x
33. Popescu V., Astanei D.G., Burlica R., Popescu A., Munteanu C., Ciolacu F., Ursache M., Ciobanu L., Cocean A. Sustainable and cleaner microwave-assisted dyeing process for obtaining eco-friendly and fluorescent acrylic knitted fabrics, *Journal of Cleaner Production* Volume 232, 20 September 2019, Pages 451-461 <https://doi.org/10.1016/j.jclepro.2019.05.281>
34. Keglevich G., The Application of Microwaves in the Esterification of P-Acids, *Current Microwave Chemistry*, 2022, 9, 62-64; <https://doi.org/10.2174/2213335609666220413102739>

35. Ghaffar A., Adeel S., Habib N., Jalal F., Ul-Haq A., Munir B., Ahmad A., Jahangeer M., Jamil Q., Effects of Microwave Radiation on Cotton Dyeing with Reactive Blue 21 Dye, *Pol. J. Environ. Stud.* Vol. 28, No. 3 (2019), 1687-1691, DOI: 10.15244/pjoes/84774
36. Al-Etaibi A.M., El-Asasery M.A, Microwave-Assisted Synthesis of Azo Disperse Dyes for Dyeing Polyester Fabrics: Our Contributions over the Past Decade, *Polymers* 2022, 14, 1703. <https://doi.org/10.3390/polym14091703>
37. Elshemy N.S., Haggag, K., New Trend in Textile Coloration Using Microwave Irradiation, *J. Text. Color. Polym. Sci.*, Vol. 16, No.1, pp 33-48(2019) DOI:10.21608/jtcps.2019.9928.1019
38. Öner, E., Büyükkakıncı, Y., & Sökmen, N. (2013). Microwave-assisted dyeing of poly(butylene terephthalate) fabrics with disperse dyes. *Coloration Technology*, 129(2), 125–130. <https://doi.org/10.1111/cote.12014>
39. Büyükkakıncı, Y., Sökmen, N. and Öner, E., (2005). Microwave assisted exhaust dyeing of polypropylene. In: Paper presented at the 4th Centrel European Conference, Liberec, Czech Republic, 7-9 September 2005.
40. Haggag K., Fixation of pad-dyeing on cotton using microwave heating. *Am Dyestuff Rep*1990; pp. 26-30
41. Lill J. R., *Microwave-Assisted Proteomics*, 2009
42. Hayes B. L., *Microwave Synthesis*, 2002
43. Can M. C., *Microwave Heating as a Tool for Sustainable Chemistry*, 2010
44. A. Miklavc, *Chem. Phys.Chem*, 2001, 552.
45. Binner J.G.P., Hassine N. A. and Cross T. E., *J. Mater. Sci.*, 1995, 30, 5389.56
46. Garbacia S., Desai B., O. Lavaster and C. O. Kappe, *J. Org. Chem.*, 2003, 68, 9136.
47. A. Stadler and C. O. Kappe, *J. Chem. Soc., Perkin Trans. 2*, 2000, 2, 1363.
48. A. Hoz, A. Diaz-Ortiz and A. Moreno, *Chem. Soc. Rev.*, 2005, 34, 164.
49. Mortimer M., Taylor, P., *Chemical Kinetics and Mechanism*, 2002
50. House J. E., *Principles of Chemical Kinetics*, 2007
51. Balluffi, R.B., Allen, S.M., Carter, W.C., *Kinetics of Materials*, 2005
52. Barrante, J.R., *Applied Mathematics for Physical Chemistry*, 1998
53. Yiğit Atabek, E. (2009). Investigation of Dyeability of Polypropylene Fiber [Doctoral thesis, Sakarya University]. YÖK National Thesis Center. <https://tez.yok.gov.tr/UlusalTezMerkezi/>
54. Doyuran A. (2010). Dyeing of Synthetic Fibers in Microwave Environment [Master's thesis, Sakarya University]. YÖK National Thesis Center. <https://tez.yok.gov.tr/UlusalTezMerkezi/>
55. Xiaolei Z., Jinwei M., Yanxiu W., Tianjie N., Deshuai S., Long F., Xiaodong Z., Investigation on dyeing mechanism of modified cotton fiber, *Royal Society of Chemistry*, Volume 12, Issue 49, 3 November 2022, Pages 31596-31607. <https://doi.org/10.1039/D2RA05668B>
56. Vassileva V., Zheleva Z., Valcheva E., The Kinetic Model of Dye Fixation on Cotton Fibers, *Journal of University of Chemical Technology and Metallurgy*, 43, 3, 2008, 323-326
57. Teker, M; Imamoglu, M; Bocek, N. (2009) - Adsorption of Some Textile Dyes on Activated Carbon Prepared From Rice Hulls - *Fresenius Environmental Bulletin* - Vol.18 - pp.709 - ISSN : 1018-4619 - English - Article - 2009 - WOS:000266898500009, DOI:10.5281/zenodo.10785501
58. Ujhelyiova A., Bolhova E., Oravkinova J., Tin R., Marcin A., Kinetics of dyeing process of blend polypropylene/polyester fibres with disperse dye, *Dyes and Pigments* 72 (2007) 212-216. <https://doi.org/10.1016/j.dyepig.2006.02.003>
59. Georgiadou, K.L.; Tsatsaroni, E.G.; Eleftheriadis, I.C.; Kehayoglou, A.H. Disperse dyeing of polyester fibers: Kinetic and equilibrium study. *J. Appl. Polym. Sci.* 2002, 85, 123–128. <https://doi.org/10.1002/app.10664>
60. Fattahi, F.S. Investigation on the Kinetic Feature of CI Acid Blue 106 Dyeing on Woolen Material. *Nanochem. Res.* 2024, 9, 280–290. <https://doi.org/10.22036/NCR.2024.04.04>
61. Roy MN, Hossain MT, Hasan MZ, Islam K, Rokonuzzaman M, Islam MA, Khandaker S, Bashar MM. Adsorption, Kinetics and Thermodynamics of Reactive Dyes on Chitosan Treated Cotton Fabric. *Textile & Leather Review.* 2023; 6:211-232. <https://doi.org/10.31881/TLR.2023.030>
62. Lis M.J., Bezerra F.M., Meng X., Qian H., Immich A.P.S, Kinetics of Dyeing in Continuous Circulation with Direct Dyes:Tencel Case; *World Journal of Textile Engineering and Technology*, 2019, 5, 97-104. <https://doi.org/10.31437/2415-5489.2019.05.10>

63. Elshemy N. S., Elshakankery M. H., Shahien S. M., Haggag, El-Sayed K. H., Kinetic Investigations on Dyeing of Different Polyester Fabrics Using Microwave Irradiation, Egypt. J. Chem. The 8th. Int. Conf. Text. Res. Div., Nat. Res. Centre, Cairo (2017) pp. 79 - 88 (2017). <https://doi.org/10.21608/ejchem.2017.1604.1131>
64. Ujhelyiova A., Bolhova, E., Oravkinova J., Tiño R. and Marcinčin A., Kinetics of dyeing process of blend polypropylene/polyester fibres with disperse dye, Dyes and Pigments, vol. 72(2), 2007, pp. 212-216. <https://doi.org/10.1016/j.dyepig.2005.08.026>
65. Alşan, H. G. (2019), Investigation of Dyeing Kinetics of Cotton Fiber with Disperse Dyestuff in Microwave Environment [Master's thesis, Sakarya University]. YÖK National Thesis Center. <https://tez.yok.gov.tr/UlusalTezMerkezi/>

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.